



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: South Tees Development Corporation, South Tees Development Works, (in Courtyard, C212 2002) Tel: 01717 367 410 Fax: 01717 367 411
Regional Office: South Tees Development Corporation, South Tees Development Works, (in Courtyard, C212 2002) Tel: 01717 367 410 Fax: 01717 367 411

LABORATORY SAMPLE DESCRIPTION SHEET

Exploratory Hole No.	Sample Depth (m) ID	Description	Laboratory Tests/Remarks
PRAIRIE_AUK_BH104	5.95 J3	Brown with grey veining slightly sandy slightly gravelly CLAY of high plasticity.	MC PI BRE
PRAIRIE_AUK_BH104	6.50 U8	High strength brown slightly sandy CLAY.	HSV
PRAIRIE_AUK_BH104	11.00 J13	Brown sandy CLAY of low plasticity.	MC PI BRE
PRAIRIE_AUK_BH104	15.50 C21	Brown slightly sandy gravelly CLAY of low plasticity.	MC PI
PRAIRIE_AUK_BH104	17.50 C23	Brown slightly sandy gravelly CLAY of low plasticity.	MC PI
PRAIRIE_AUK_BH106	5.50 U2	Medium strength brown slightly sandy slightly gravelly CLAY.	UUT BRE QED
PRAIRIE_AUK_BH106	6.95 J3	Brown slightly sandy slightly gravelly CLAY of intermediate plasticity.	MC PI
PRAIRIE_AUK_BH106	7.00 B6	Brown slightly sandy slightly gravelly CLAY.	PSD SED
PRAIRIE_AUK_BH106	8.50 U8	Very high strength brown slightly sandy slightly gravelly CLAY.	UUT
PRAIRIE_AUK_BH106	9.50 J10	Grey sandy slightly gravelly CLAY of low plasticity.	MC PI BRE
PRAIRIE_AUK_BH107	3.00 U2	Low strength fissured brown/grey silty CLAY of intermediate plasticity.	MC PI Density UUT
PRAIRIE_AUK_BH107	3.45 J3	Brown CLAY with occasional sand pockets.	BRE
PRAIRIE_AUK_BH107	4.00 B5	Brown CLAY.	CP2 CBR
PRAIRIE_AUK_BH107	5.00 U7	Medium strength laminated brown silty CLAY.	UUT
PRAIRIE_AUK_BH107	7.50 J12	Red brown slightly sandy CLAY of low plasticity.	MC PI BRE
PRAIRIE_AUK_BH107	9.00 J16	Red brown CLAY with bands of white gypsum.	BRE
PRAIRIE_AUK_BH108	2.50 U2	High strength fissured brown CLAY of intermediate plasticity with occasional silt dustings.	MC PI HSV IS for UUT
PRAIRIE_AUK_BH108	2.95 J3	Brown CLAY of high plasticity.	MC PI
PRAIRIE_AUK_BH108	3.50 B5	Brown slightly sandy CLAY.	PSD SED PD
PRAIRIE_AUK_BH108	4.50 U7	Medium strength brown slightly sandy slightly gravelly CLAY becoming high strength with depth.	MC HSV
PRAIRIE_AUK_BH108	5.00 J9	Brown slightly sandy CLAY of low plasticity.	MC PI

Contract Title :- Prairie Site Ground Investigation Works	Client :- South Tees Development Corporation
---	--

	Signed :- 	Name :-	Page 2 of 11
	Date of issue :- 02/11/2020	Certificate No. :- SDW251/7	AEG Contract No. :- 4251


ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Brook Hill Industrial Estate, Kingsley Hill, Kingsley, South Shields, Tyne and Wear, S26 6JG. Tel: 0191 581 4700 Fax: 0191 581 4711
 Registered Office: 10000, Brookside Industrial Estate, South Shields, Tyne and Wear, S26 6JG. Tel: 0191 581 4700 Fax: 0191 581 4711

LABORATORY SAMPLE DESCRIPTION SHEET

Exploratory Hole No.	Sample Depth (m) ID	Description	Laboratory Tests/Remarks
PRAIRIE_AUK_BH108	6.50 J12	Brown sandy gravelly CLAY of low plasticity.	MC PI
PRAIRIE_AUK_BH108	7.00 B14	Brown slightly sandy slightly gravelly CLAY	PSD SED BRE
PRAIRIE_AUK_BH108	8.00 J15	Brown sandy CLAY of low plasticity.	MC PI BRE
PRAIRIE_AUK_BH108	8.50 J16	Red brown slightly gravelly SAND. Gravel includes gypsum.	MC PI(HP)
PRAIRIE_AUK_BH108	9.00 J18	Red brown clayey SAND including gypsum.	BRE
PRAIRIE_AUK_BH109	0.50 B4	Brown slightly sandy slightly gravelly CLAY of intermediate plasticity. (Sample has a hydrocarbon odour).	MC PI CBR
PRAIRIE_AUK_BH109	1.20 J16	Medium strength brown silty slightly sandy CLAY becoming high strength with depth. (Sample has a hydrocarbon odour).	MC HSV
PRAIRIE_AUK_BH109	1.65 J7	Brown slightly sandy CLAY of intermediate plasticity. (Sample has a strong hydrocarbon odour).	MC PI
PRAIRIE_AUK_BH109	2.00 B10	Brown slightly sandy slightly gravelly CLAY. (Sample has a strong hydrocarbon odour).	PSD SED CP2 CBR
PRAIRIE_AUK_BH109	3.00 U13	Medium strength brown slightly sandy CLAY.	UUT
PRAIRIE_AUK_BH109	3.45 J14	Brown slightly sandy CLAY of intermediate plasticity.	MC PI US for Density
PRAIRIE_AUK_BH109	5.00 U19	Medium strength brown CLAY becoming high strength with depth.	HSV
PRAIRIE_AUK_BH109	6.00 J22	Blue black MUDSTONE.	MC PI(IS for LL)
PRAIRIE_AUK_BH110	3.00 U2	Low strength laminated brown silty CLAY of intermediate plasticity with occasional sand pockets.	MC PI UUT
PRAIRIE_AUK_BH110	4.00 B5	Brown slightly sandy slightly gravelly CLAY.	PSD SED
PRAIRIE_AUK_BH110	5.00 U6	Medium strength brown silty CLAY of intermediate plasticity.	MC PI UUT
PRAIRIE_AUK_BH110	6.50 B10	Brown slightly sandy slightly gravelly CLAY.	CP2 CBR
PRAIRIE_AUK_BH110	8.00 U12	Medium strength brown CLAY of low plasticity.	MC PI UUT
PRAIRIE_AUK_BH110	9.50 J15	Red brown slightly sandy CLAY of low plasticity.	MC PI
PRAIRIE_AUK_BH110	9.50 B16	Brown slightly sandy slightly gravelly CLAY.	PSD SED
PRAIRIE_AUK_BH110	11.00 U18	Extremely high strength brown slightly sandy slightly gravelly CLAY.	UUT

Contract Title - Prairie Site Ground Investigation Works	Client - South Tees Development Corporation
--	---

	Signed - <i>msene</i>	Name -	Page 3 of 11
	Date of issue - 03/11/2020	Certificate No - SDI4251/3	AEG Contract No - 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 107/108 Great West Road, Uxbridge, Middlesex, U.K. Tel: 0181 887 4744 Fax: 0181 887 4745
Regional Office: Unit 10, Southdown Industrial Centre, Southdown Road, Basingstoke, Hampshire, U.K. Tel: 01753 66222 Fax: 01753 66223

LABORATORY SAMPLE DESCRIPTION SHEET

Exploratory Hole No.	Sample Depth (m) ID	Description	Laboratory Tests/Remarks
PRAIRIE_AUK_BH110	11.45 J19	Orange brown sandy slightly gravelly CLAY	BRE
PRAIRIE_AUK_BH110	13.50 J23	Brown slightly sandy slightly gravelly CLAY of low plasticity	MC PI
PRAIRIE_AUK_BH110	15.00 J27	Red brown MUDSTONE with white crystalline inclusions (possible gypsum)	MC BRE US for PI
PRAIRIE_AUK_TP101	0.50 J3	MADE GROUND (Brown slightly sandy gravel including brick fragments)	MC BRE Calorific Value
PRAIRIE_AUK_TP101	0.90 B4	MADE GROUND (Dark brown/black clayey/silty very sandy gravel including slag and brick fragments)	PSD CP2 CBR
PRAIRIE_AUK_TP101	2.50 J10	Grey mottled slightly sandy CLAY of high plasticity	MC PI
PRAIRIE_AUK_TP101	3.00 B11	Brown slightly sandy slightly gravelly CLAY	CBR
PRAIRIE_AUK_TP101	4.40 J14	Brown slightly organic slightly sandy slightly gravelly SILT of very high plasticity	MC PI BRE
PRAIRIE_AUK_TP102	1.50 J6	Brown sandy CLAY of low plasticity	MC PI
PRAIRIE_AUK_TP102	3.00 B6	Brown slightly sandy slightly gravelly CLAY	PSD SED CBR
PRAIRIE_AUK_TP103	0.80 B2	MADE GROUND (Dark grey sandy gravel with a high cobble content. Gravel includes slag, ash, concrete and clinker)	PSD
PRAIRIE_AUK_TP104	2.00 J8	Frable brown slightly sandy CLAY of intermediate plasticity	MC PI BRE
PRAIRIE_AUK_TP105	1.80 J4	Fissured brown slightly sandy slightly gravelly CLAY of high plasticity	MC PI
PRAIRIE_AUK_TP105	2.00 B5	Brown slightly sandy slightly gravelly CLAY	PSD SED CP2 CBR
PRAIRIE_AUK_TP106	1.00 B2	MADE GROUND (Dark grey clayey sandy gravel including ash, slag, ceramic and brick fragments)	PSD
PRAIRIE_AUK_TP106	2.50 J6	Brown slightly sandy CLAY of high plasticity	MC PI
PRAIRIE_AUK_TP106	3.50 J8	Brown slightly sandy CLAY of intermediate plasticity	MC PI
PRAIRIE_AUK_TP107	0.50 J3	Brown sandy slightly gravelly CLAY of intermediate plasticity with sand dustings	MC PI BRE
PRAIRIE_AUK_TP107	1.00 B4	Brown slightly sandy slightly gravelly CLAY	PSD SED CP2 CBR
PRAIRIE_AUK_TP107	2.30 J6	Brown slightly sandy CLAY of high plasticity	MC PI
PRAIRIE_AUK_TP108	0.80 B4	MADE GROUND (Grey slightly clayey sandy gravel with a high cobble content. Gravel includes metal, concrete and slag fragments)	PSD US for CP2

Contract Title :- Prairie Site Ground Investigation Works	Client :- South Tees Development Corporation
---	--

	Signed :- <i>msero</i>	Name :-	Page 4 of 11	
	Date of issue :- 03/11/2020	Certificate No. :- SD/4251/4	AEG Contract No. :- 4251	


ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 1000-10000 of Industrial Estate, Panchsheel, Chandigarh, India. Phone: 91-98151-8811 / 98151-8812 / 98151-8813
Regional Office: 10000 of Industrial Estate, Panchsheel, Chandigarh, India. Phone: 91-98151-8811 / 98151-8812 / 98151-8813

LABORATORY SAMPLE DESCRIPTION SHEET

Exploratory Hole No.	Sample Depth (m)	ID	Description	Laboratory Tests/Remarks
PRAIRIE_AUK_TP108	1.90	B7	MADE GROUND (Brown sandy gravel with a high cobble content. Gravel includes slag, ash, clinker and brick fragments)	PSD
PRAIRIE_AUK_TP110	1.60	B2	MADE GROUND (Brown clayey/silty very sandy gravel with a medium cobble content. Gravel includes slag and clinker)	PSD US for CP2 & CBR
PRAIRIE_AUK_TP110	2.50	J6	Brown slightly sandy CLAY of high plasticity	MC PI
PRAIRIE_AUK_TP110	3.00	B8	Brown slightly sandy slightly gravelly CLAY	PSD SED CP2 CBR
PRAIRIE_AUK_TP111	1.60	B5	MADE GROUND (Brown clayey sandy gravel with a medium cobble content. Gravel includes slag, metal and brick fragments)	PSD SED US for CP2 & CBR
PRAIRIE_AUK_TP111	2.00	J6	Brown CLAY of intermediate plasticity	MC PI
PRAIRIE_AUK_TP112	1.00	J3	MADE GROUND (Dark grey sandy gravel including slag and brick fragments)	BRE Calorific Value
PRAIRIE_AUK_TP112	1.70	B5	MADE GROUND (Dark grey clayey/silty very sandy gravel including plastic, slag and ceramic fragments)	PSD CP2 CBR
PRAIRIE_AUK_TP112	2.70	J9	Brown slightly sandy CLAY of high plasticity	MC PI
PRAIRIE_AUK_TP112	3.00	J10	Brown slightly sandy CLAY/SILT of intermediate plasticity	MC PI
PRAIRIE_AUK_TP112	3.20	B11	Brown silty slightly sandy CLAY	PSD SED CP2
PRAIRIE_AUK_TP113	1.60	B6	White/grey sandy GRAVEL	PSD US for CP2
PRAIRIE_AUK_TP113	2.50	J7	Brown slightly sandy CLAY of intermediate plasticity	MC PI
PRAIRIE_AUK_TP113	2.80	B8	Brown with grey mottling slightly sandy slightly gravelly CLAY	PSD SED CP2
PRAIRIE_AUK_TP114	0.40	B4	MADE GROUND (Brown clayey very sandy gravel including plastic, brick and metal fragments)	PSD US for CP2
PRAIRIE_AUK_TP115	1.40	J4	MADE GROUND (Grey slightly sandy gravel including slag fragments)	MC BRE Calorific Value
PRAIRIE_AUK_TP115	1.70	B5	MADE GROUND (Dark grey slightly clayey very sandy gravel)	PSD
PRAIRIE_AUK_TP115	1.60	J5	MADE GROUND (Brown slightly sandy slightly gravelly silt of intermediate plasticity. Gravel includes ceramic fragments)	MC PI BRE ORG
PRAIRIE_AUK_TP115	2.00	J7	Brown slightly sandy CLAY of high plasticity	MC PI
PRAIRIE_AUK_TP115	2.50	B8	Brown slightly sandy CLAY	CP2 CBR
PRAIRIE_AUK_TP116	3.00	J9	Reddish brown slightly sandy slightly gravelly CLAY of intermediate plasticity	MC PI

Contract Title :- Prairie Site Ground Investigation Works	Client :- South Tees Development Corporation
---	--

	Signed :- <i>msene</i>	Name :-	Page 5 of 11
	Date of issue :- 03/11/2020	Certificate No :- SD4251/5	AEG Contract No :- 4251

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 107-110 Kings Hill Industrial Estate, Park Road, Thurston, SO4 6BQ, UK. Tel: 01493 807478 Fax: 01493 807479
 Registered Office: 107-110 Kings Hill Industrial Estate, Park Road, Thurston, SO4 6BQ, UK. Tel: 01493 807478 Fax: 01493 807479

LABORATORY SAMPLE DESCRIPTION SHEET

Exploratory Hole No.	Sample Depth (m)	ID	Description	Laboratory Tests/Remarks
PRAIRIE_AUK_TP124	1.50	B4	MADE GROUND (Dark grey clayey very gravelly sand. Gravel includes ash, slag and brick fragments).	PSD CP2
PRAIRIE_AUK_TP124	2.00	J6	Brown with grey mottling slightly sandy CLAY of high plasticity	MC PI
PRAIRIE_AUK_TP126	1.80	B4	MADE GROUND (Grey cobbles of slag and brick)	PSD
PRAIRIE_AUK_TP131	1.00	J3	MADE GROUND (Brown slightly sandy gravel including brick fragments)	MC
PRAIRIE_AUK_TP131	2.60	J7	Brown slightly gravelly CLAY of high plasticity.	MC PI
PRAIRIE_AUK_TP131	3.60	J9	Fissured brown slightly silty CLAY of intermediate plasticity	MC PI
PRAIRIE_AUK_TP131	3.80	B10	Brown slightly sandy CLAY.	CP2 CBR
PRAIRIE_AUK_TP132	0.60	J2	MADE GROUND (Brown slightly sandy gravel including slag and brick fragments)	Calorific Value
PRAIRIE_AUK_TP132	2.00	B6	MADE GROUND (Grey sandy gravel with a medium cobble content. Gravel includes concrete, slag and glass fragments)	PSD US for CP2 & CP4
PRAIRIE_AUK_TP134	0.60	B2	MADE GROUND (Dark grey clayey very sandy gravel with a medium cobble content. Gravel includes slag, ash and brick fragments)	PSD
PRAIRIE_AUK_TP134	1.50	J4	Brown CLAY/SILT of intermediate plasticity with occasional silt pockets	MC PI
PRAIRIE_AUK_TP135	1.00	B3	MADE GROUND (Grey slightly clayey very sandy gravel including slag, concrete and brick fragments)	PSD
PRAIRIE_AUK_TP135	2.00	J7	Brown CLAY of intermediate plasticity.	MC PI
PRAIRIE_AUK_TP135	2.70	J9	Brown slightly silty CLAY of high plasticity	MC PI
PRAIRIE_AUK_TP136	1.00	J4	Red brown slightly sandy slightly gravelly SILT of intermediate plasticity.	MC PI
PRAIRIE_AUK_TP137	0.60	J3	MADE GROUND (Grey slightly sandy gravel including slag fragments)	MC
PRAIRIE_AUK_TP137	1.00	B4	MADE GROUND (Brown clayey sandy gravel including ash, clinker, slag and metal fragments)	PSD US for CP2
PRAIRIE_AUK_TP137	2.00	B7	Brown sandy CLAY.	CP2 CBR
PRAIRIE_AUK_TP137	2.60	J8	Brown slightly sandy CLAY of intermediate plasticity.	MC PI
PRAIRIE_AUK_TP138	1.00	B2	MADE GROUND (Brown slightly clayey very sandy gravel with a high cobble content. Gravel includes ceramic, ash and brick fragments)	PSD
PRAIRIE_AUK_TP139B0.20		B2	MADE GROUND (Dark grey clayey very sandy gravel including ash, slag and brick fragments)	PSD

Contract Title :- **Prairie Site Ground Investigation Works**

Client :- **South Tees Development Corporation**

Signed :- *m bene*
 Name :-
 Date of Issue :- 03/11/2020

Certificate No :- SDI4251/7

Page 7 of 11
 REG Contract No. :- 4251




ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 2nd Floor, 18 Southwell Road, Farnborough, Hampshire, UK. G11 1AA. Tel: 01329 519339 Fax: 01329 519340
Regional Office: Luton, Bedfordshire, UK. LU1 3JH. Tel: 01753 721999 Fax: 01753 721998

LABORATORY SAMPLE DESCRIPTION SHEET

Exploratory Hole No.	Sample Depth (m)	ID	Description	Laboratory Tests/Remarks
PRAIRIE_AUK_TP156A1.10	1.10	J5	Brown sandy CLAY of low plasticity	MC PI
PRAIRIE_AUK_TP162	0.70	J1	MADE GROUND (Brown sandy gravel with occasional clay pockets)	BRE Calorific Value
PRAIRIE_AUK_TP162	0.90	B2	MADE GROUND (Brown clayey very sandy gravel including glass, slag and brick fragments)	PSD
PRAIRIE_AUK_TP162	2.50	B6	Brown slightly sandy CLAY of high plasticity	MC PI PSD SED CP2 CBR
PRAIRIE_AUK_TP162	3.10	J7	Fissured brown silty CLAY of high plasticity	MC PI BRE
PRAIRIE_AUK_TP163	0.50	J1	MADE GROUND (Dark brown slightly sandy gravel with occasional clay pockets. Gravel includes brick fragments)	MC US for PI
PRAIRIE_AUK_TP163	0.80	B2	MADE GROUND (Brown clayey very sandy gravel including ash and clinker)	PSD CP2 CBR
PRAIRIE_AUK_TP163	1.60	J4	Grey brown slightly sandy CLAY of intermediate plasticity	MC PI BRE
PRAIRIE_AUK_TP163	1.70	B5	Brown slightly sandy CLAY	CP2 CBR
PRAIRIE_AUK_TP165	1.50	J4	MADE GROUND (Brown slightly sandy gravel including brick fragments)	BRE
PRAIRIE_AUK_TP165	1.80	B5	MADE GROUND (Dark brown slightly clayey/silty sandy gravel and cobbles including brick, slag and concrete fragments)	PSD US for CP4 & CBR
PRAIRIE_AUK_TP165	2.50	J6	MADE GROUND (Brown slightly sandy gravel including brick fragments)	Calorific Value
PRAIRIE_AUK_TP165	2.80	B7	MADE GROUND (Dark grey brown sandy gravel with occasional clay pockets and a medium cobble content. Gravel includes ash, slag and brick fragments)	PSD
PRAIRIE_AUK_TP167	1.80	B4	MADE GROUND (Dark grey slightly clayey/silty sandy gravel with a medium cobble content. Gravel includes slag, brick and concrete fragments)	PSD
PRAIRIE_AUK_TP168	1.40	J6	Fissured brown slightly sandy CLAY	MC
PRAIRIE_AUK_TP168	1.60	B7	Brown slightly sandy CLAY	PSD SED CP2 CBR
PRAIRIE_AUK_TP169	0.80	E2	MADE GROUND (Brown clayey very sandy gravel including ash, slag and brick fragments)	PSD US for CP4
PRAIRIE_AUK_TP172	0.60	B2	MADE GROUND (Dark grey brown cobbles of brick and slag fragments)	PSD US for CP2 & CBR
PRAIRIE_AUK_TP173	0.60	J1	MADE GROUND (Brown slightly sandy gravel including brick fragments)	MC BRE
PRAIRIE_AUK_TP173	0.80	B2	MADE GROUND (Brown very sandy gravel with clay pockets)	PSD SED CP2 CBR
PRAIRIE_AUK_TP174	1.20	J4	Brown slightly sandy CLAY of low to intermediate plasticity with occasional sand pockets	MC PI

Contract Title :- Prairie Site Ground Investigation Works	Client :- South Tees Development Corporation
---	--

	Signed :- <i>msone</i>	Name :-	Page 9 of 11	
	Date of Issue :- 02/11/2020	Certificate No :- SDI4251/9	AEG Contract No :- 4251	

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21, Watly, 1st Industrial Estate, Watly, St. Thomas's Road, St. Dunstons, D.C. 20th, Tel: 0141 574744 Fax: 0141 584744
Regional Office: Unit 10, Riverside Commercial, Essex, Loughton, Essex, Saffron Walden, Essex, Tel: 01773 731000 Fax: 01773 731000

LABORATORY SAMPLE DESCRIPTION SHEET

Exploratory Hole No.	Sample Depth (m)	ID	Description	Laboratory Tests/Remarks
PRAIRIE_AUK_TP175	0.60	B2	MADE GROUND (Grey brown clayey sandy cobbles of brick, slag and concrete fragments).	PSD US for CBR
PRAIRIE_AUK_TP175	1.40	J4	Grey slightly sandy CLAY of intermediate plasticity.	MC PI
PRAIRIE_AUK_TP176	0.50	B2	MADE GROUND (Brown clayey sandy gravel including ash and clinker fragments).	PSD
PRAIRIE_AUK_TP176	1.50	J4	Brown slightly organic slightly sandy CLAY.	MC BRE
PRAIRIE_AUK_TP176	2.00	B5	Brown slightly sandy CLAY.	PSD SED CP2 CBR
PRAIRIE_AUK_TP177	0.50	J4	MADE GROUND (Brown slightly sandy clay of high plasticity).	MC PI
PRAIRIE_AUK_TP177	1.80	B7	MADE GROUND (Brown cobbles with much gravel).	PSD US for CP2 & CBR
PRAIRIE_AUK_TP178	0.40	J1	MADE GROUND (Dark brown slightly sandy gravel including brick fragments).	MC BRE Calorific Value
PRAIRIE_AUK_TP178	0.60	B2	MADE GROUND (Brown clayey very sandy gravel including ash, clinker and slag fragments).	PSD CP2 CBR
PRAIRIE_AUK_TP178	1.60	B5	Brown with grey mottling slightly sandy slightly gravelly CLAY of very high plasticity.	MC PI BRE CP2
PRAIRIE_AUK_TP179	0.20	J1	MADE GROUND (Dark brown sandy gravel including brick fragments).	BRE Calorific Value
PRAIRIE_AUK_TP179	0.40	B2	MADE GROUND (Dark grey clayey/silty very gravelly sand with a medium cobble content. Gravel includes ash, clinker, slag and brick fragments).	PSD CP2
PRAIRIE_AUK_TP179	1.70	J5	Brown with grey veining slightly sandy CLAY of high plasticity.	MC PI
PRAIRIE_AUK_TP179	1.80	B6	Brown CLAY.	IS for CBR
PRAIRIE_AUK_TP181	0.50	B2	MADE GROUND (Brown very sandy gravel with occasional clay pockets. Gravel includes ash and clinker fragments).	PSD CBR US for CP2
PRAIRIE_AUK_TP181	1.10	B4	MADE GROUND (Brown cobbles of brick and slag fragments).	PSD
PRAIRIE_AUK_TP181	1.60	J5	Grey slightly silty sandy CLAY of intermediate plasticity.	MC PI
PRAIRIE_AUK_TP181	2.00	B6	Brown with grey veining slightly sandy CLAY.	CBR
PRAIRIE_AUK_TP182	0.30	J1	MADE GROUND (Dark brown sandy gravel including brick fragments).	Calorific Value
PRAIRIE_AUK_TP182	0.60	B2	MADE GROUND (Dark grey clayey very sandy gravel including slag fragments).	PSD CP2 CBR
PRAIRIE_AUK_TP182	1.30	J4	Fissured brown slightly sandy slightly gravelly CLAY of intermediate plasticity.	MC PI

Contract Title :- Prairie Site Ground Investigation Works	Client :- South Tees Development Corporation
---	--

	Signed :- <i>msoro</i>	Name :-	Page 10 of 11
	Date of issue :- 08/11/2020	Certificate No :- SQ4251/10	AEG Contract No :- 4251

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 202/203/204/205/206/207/208/209/210/211/212/213/214/215/216/217/218/219/220/221/222/223/224/225/226/227/228/229/230/231/232/233/234/235/236/237/238/239/240/241/242/243/244/245/246/247/248/249/250/251/252/253/254/255/256/257/258/259/260/261/262/263/264/265/266/267/268/269/270/271/272/273/274/275/276/277/278/279/280/281/282/283/284/285/286/287/288/289/290/291/292/293/294/295/296/297/298/299/300/301/302/303/304/305/306/307/308/309/310/311/312/313/314/315/316/317/318/319/320/321/322/323/324/325/326/327/328/329/330/331/332/333/334/335/336/337/338/339/340/341/342/343/344/345/346/347/348/349/350/351/352/353/354/355/356/357/358/359/360/361/362/363/364/365/366/367/368/369/370/371/372/373/374/375/376/377/378/379/380/381/382/383/384/385/386/387/388/389/390/391/392/393/394/395/396/397/398/399/400/401/402/403/404/405/406/407/408/409/410/411/412/413/414/415/416/417/418/419/420/421/422/423/424/425/426/427/428/429/430/431/432/433/434/435/436/437/438/439/440/441/442/443/444/445/446/447/448/449/450/451/452/453/454/455/456/457/458/459/460/461/462/463/464/465/466/467/468/469/470/471/472/473/474/475/476/477/478/479/480/481/482/483/484/485/486/487/488/489/490/491/492/493/494/495/496/497/498/499/500/501/502/503/504/505/506/507/508/509/510/511/512/513/514/515/516/517/518/519/520/521/522/523/524/525/526/527/528/529/530/531/532/533/534/535/536/537/538/539/540/541/542/543/544/545/546/547/548/549/550/551/552/553/554/555/556/557/558/559/560/561/562/563/564/565/566/567/568/569/570/571/572/573/574/575/576/577/578/579/580/581/582/583/584/585/586/587/588/589/590/591/592/593/594/595/596/597/598/599/600/601/602/603/604/605/606/607/608/609/610/611/612/613/614/615/616/617/618/619/620/621/622/623/624/625/626/627/628/629/630/631/632/633/634/635/636/637/638/639/640/641/642/643/644/645/646/647/648/649/650/651/652/653/654/655/656/657/658/659/660/661/662/663/664/665/666/667/668/669/670/671/672/673/674/675/676/677/678/679/680/681/682/683/684/685/686/687/688/689/690/691/692/693/694/695/696/697/698/699/700/701/702/703/704/705/706/707/708/709/710/711/712/713/714/715/716/717/718/719/720/721/722/723/724/725/726/727/728/729/730/731/732/733/734/735/736/737/738/739/740/741/742/743/744/745/746/747/748/749/750/751/752/753/754/755/756/757/758/759/760/761/762/763/764/765/766/767/768/769/770/771/772/773/774/775/776/777/778/779/780/781/782/783/784/785/786/787/788/789/790/791/792/793/794/795/796/797/798/799/800/801/802/803/804/805/806/807/808/809/810/811/812/813/814/815/816/817/818/819/820/821/822/823/824/825/826/827/828/829/830/831/832/833/834/835/836/837/838/839/840/841/842/843/844/845/846/847/848/849/850/851/852/853/854/855/856/857/858/859/860/861/862/863/864/865/866/867/868/869/870/871/872/873/874/875/876/877/878/879/880/881/882/883/884/885/886/887/888/889/890/891/892/893/894/895/896/897/898/899/900/901/902/903/904/905/906/907/908/909/910/911/912/913/914/915/916/917/918/919/920/921/922/923/924/925/926/927/928/929/930/931/932/933/934/935/936/937/938/939/940/941/942/943/944/945/946/947/948/949/950/951/952/953/954/955/956/957/958/959/960/961/962/963/964/965/966/967/968/969/970/971/972/973/974/975/976/977/978/979/980/981/982/983/984/985/986/987/988/989/990/991/992/993/994/995/996/997/998/999/1000

LABORATORY SAMPLE DESCRIPTION SHEET

Exploratory Hole No.	Sample Depth (m)	ID	Description	Laboratory Tests/Remarks
PRAIRIE_AUK_TP182	1.60	B5	Brown with grey veining slightly sandy CLAY (Sample has a strong hydro-carbon odour)	CBR
PRAIRIE_AUK_TP183	0.80	B2	MADE GROUND (Grey cobbles of concrete, slag and brick fragments)	PSD
PRAIRIE_AUK_TP185	3.50	B2	MADE GROUND (Brown slightly sandy slightly gravelly clay. Gravel includes brick and metal fragments)	PSD SED
PRAIRIE_AUK_TP186	0.40	J1	MADE GROUND (Dark brown sandy gravel including brick fragments)	MC BRE Calorific Value
PRAIRIE_AUK_TP188	0.60	B2	MADE GROUND (Dark brown clayey/silty sandy gravel including ash and clinker fragments)	PSD U5 for CP2 & CBR
PRAIRIE_AUK_TP189	0.30	J1	MADE GROUND (Brown slightly sandy gravel)	Calorific Value
PRAIRIE_AUK_TP189	0.50	B2	MADE GROUND (Dark brown clayey/silty very sandy gravel including slag and brick fragments)	PSD CBR
PRAIRIE_AUK_TP189	1.40	J3	Brown slightly sandy CLAY of high plasticity	MC FI BRE
PRAIRIE_AUK_TP189	1.50	B4	Grey brown mottled slightly sandy slightly gravelly CLAY	PSD SED CP2
PRAIRIE_AUK_TP189	2.70	J5	Red brown slightly sandy CLAY of intermediate plasticity	MC FI
PRAIRIE_AUK_TP189	2.90	B6	Brown with grey veining slightly sandy slightly gravelly CLAY	PSD SED CP2

Contract Title: **Prairie Site Ground Investigation Works**

Client: **South Tees Development Corporation**



Signed: *MSone*

Name: _____

Page 11 of 11

Date of issue: **03/11/2020**

Certificate No: **SD/4251/11**

AEG Contract No: **4251**



Moisture Content/Plasticity Index and Moisture Content



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 112 St. Marks Road, London, E8 3AP, UK. Tel: 020 850 5000 Fax: 020 850 5001
Regional Office: 1, Mill Lane, South Shields, Co. Durham, NE33 2JG, UK. Tel: 01773 751200 Fax: 01773 751201

MOISTURE CONTENT CERTIFICATE

BS 1377 - Part 2 - Clause 3.2

Exploratory Hole No.	Sample Depth (m)	Sample ID	Specific Depth (m)	Moisture Content (%)	Date Tested	Remarks
PRAIRIE_AUK_BH101	18.00	J33	18.00	16.6	17/06/2020	
PRAIRIE_AUK_BH108	4.50	U7	4.50	23.7	10/07/2020	
PRAIRIE_AUK_BH109	1.20	U6	1.20	21.8	10/07/2020	
PRAIRIE_AUK_BH110	15.00	J27	15.00	25.1	10/07/2020	
PRAIRIE_AUK_TP101	0.60	J3	0.60	14.4	28/09/2020	
PRAIRIE_AUK_TP115	1.40	J4	1.40	8.3	06/10/2020	
PRAIRIE_AUK_TP117	1.50	J4	1.50	11.8	06/10/2020	
PRAIRIE_AUK_TP118	0.50	J1	0.50	14.3	12/10/2020	
PRAIRIE_AUK_TP119	0.50	J1	0.50	7	19/10/2020	
PRAIRIE_AUK_TP124	1.00	J3	1.00	15.9	28/09/2020	
PRAIRIE_AUK_TP131	1.00	J3	1.00	12.2	29/09/2020	
PRAIRIE_AUK_TP137	0.60	J3	0.60	18	12/10/2020	
PRAIRIE_AUK_TP146C	1.00	J4	1.00	24.4	29/09/2020	
PRAIRIE_AUK_TP161	0.50	J1	0.50	14.6	30/09/2020	
PRAIRIE_AUK_TP168	1.40	J6	1.40	32.8	29/09/2020	
PRAIRIE_AUK_TP171	0.60	J1	0.60	20.9	29/09/2020	
PRAIRIE_AUK_TP176	1.50	J4	1.50	36.2	29/09/2020	
PRAIRIE_AUK_TP179	0.40	J1	0.40	27.7	29/09/2020	
PRAIRIE_AUK_TP182	1.30	J4	1.30	21.8	29/09/2020	
PRAIRIE_AUK_TP189	0.40	J1	0.40	16.1	29/09/2020	

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works	Client :- South Tees Development Corporation
---	--

	Signed :- <i>msore</i>	Name :-	Page 1 of 1
	Date of Issue :- 02/11/2020	Certificate No :- MC/4251/1	REG Contract No :- 4251




ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 10th Floor, 1st National Centre, Park Road, Halesowen, Walsley, Leamington, Warwick, CV32 9DF. Tel: 0191 5074700 Fax: 0111 5074710
Regional Office: 10th Floor, 1st National Centre, Park Road, Halesowen, Walsley, Leamington, Warwick, CV32 9DF. Tel: 01773 779 899 Fax: 0111 5074710

ATTERBERG LIMITS & NATURAL MOISTURE CONTENT

Test Method - BS 1377, Part 2, Clause 3.2, 4.1 to 4.4 & 5, 1990

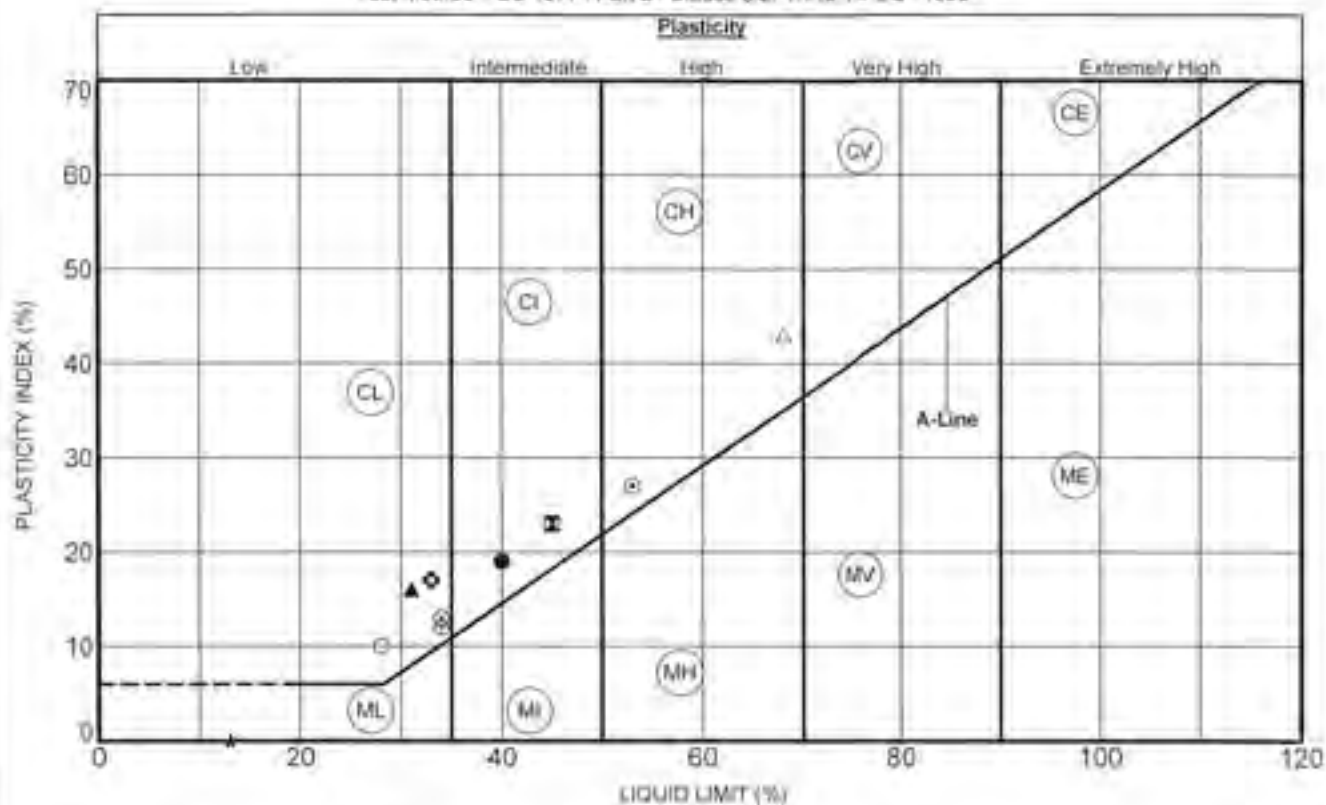

Exploratory Hole No.	Depth (m)	Sample Type/Ref.	Specific Depth (m)	LL	PL	PI	I _p	Preparation Method	<0.425mm (%)	m/c (%)	Date Tested
●PRAIRIE_AUK_BH1013.00	U2		3.25	40	21	19	0.20	Natural		24.8	17/06/2020
■PRAIRIE_AUK_BH1015.00	U7		5.17	45	22	23	0.51	Natural		33.7	17/06/2020
▲PRAIRIE_AUK_BH10111.00	U18		11.25	31	15	16	0.04	Natural		15.7	17/06/2020
▲PRAIRIE_AUK_BH10112.50	J21		12.50		13			Natural		12.0	17/06/2020
○PRAIRIE_AUK_BH1032.95	J3		2.95	53	26	27	0.01	Natural		26.2	06/10/2020
◆PRAIRIE_AUK_BH1038.50	J18		8.50	33	16	17	0.00	Natural		16.0	08/10/2020
○PRAIRIE_AUK_BH10313.00	J27		13.00	28	18	10	0.61	Natural		24.1	06/10/2020 #
○PRAIRIE_AUK_BH1045.95	J3		5.95	68	25	43	-0.03	Natural		23.7	19/10/2020
○PRAIRIE_AUK_BH10411.00	J13		11.00	34	21	13	-0.26	Natural		17.6	20/10/2020
○PRAIRIE_AUK_BH10415.50	C21		16.50	34	22	12	-1.09	Air Dried	49.0	8.9	12/10/2020

For description of sample please refer to the Laboratory Sample Description Sheet. # = Insufficient for 4 point PI
If sample is prepared in the natural state we are unable to determine % retained on the 0.425mm test sieve

Contract Title - **Prairie Site Ground Investigation Works**

Client - **South Tees Development Corporation**



Signed: *m.sore*

Name:-

Page 1 of 8

Date of Issue -
03/11/2020

Certificate No -
PA4251/1

AEG Contract No -
4251




1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 10, 11, 12, 13, 14, 15, 16, 17, 18, 19, 20, 21, 22, 23, 24, 25, 26, 27, 28, 29, 30, 31, 32, 33, 34, 35, 36, 37, 38, 39, 40, 41, 42, 43, 44, 45, 46, 47, 48, 49, 50, 51, 52, 53, 54, 55, 56, 57, 58, 59, 60, 61, 62, 63, 64, 65, 66, 67, 68, 69, 70, 71, 72, 73, 74, 75, 76, 77, 78, 79, 80, 81, 82, 83, 84, 85, 86, 87, 88, 89, 90, 91, 92, 93, 94, 95, 96, 97, 98, 99, 100, 101, 102, 103, 104, 105, 106, 107, 108, 109, 110, 111, 112, 113, 114, 115, 116, 117, 118, 119, 120, 121, 122, 123, 124, 125, 126, 127, 128, 129, 130, 131, 132, 133, 134, 135, 136, 137, 138, 139, 140, 141, 142, 143, 144, 145, 146, 147, 148, 149, 150, 151, 152, 153, 154, 155, 156, 157, 158, 159, 160, 161, 162, 163, 164, 165, 166, 167, 168, 169, 170, 171, 172, 173, 174, 175, 176, 177, 178, 179, 180, 181, 182, 183, 184, 185, 186, 187, 188, 189, 190, 191, 192, 193, 194, 195, 196, 197, 198, 199, 200, 201, 202, 203, 204, 205, 206, 207, 208, 209, 210, 211, 212, 213, 214, 215, 216, 217, 218, 219, 220, 221, 222, 223, 224, 225, 226, 227, 228, 229, 230, 231, 232, 233, 234, 235, 236, 237, 238, 239, 240, 241, 242, 243, 244, 245, 246, 247, 248, 249, 250, 251, 252, 253, 254, 255, 256, 257, 258, 259, 260, 261, 262, 263, 264, 265, 266, 267, 268, 269, 270, 271, 272, 273, 274, 275, 276, 277, 278, 279, 280, 281, 282, 283, 284, 285, 286, 287, 288, 289, 290, 291, 292, 293, 294, 295, 296, 297, 298, 299, 300, 301, 302, 303, 304, 305, 306, 307, 308, 309, 310, 311, 312, 313, 314, 315, 316, 317, 318, 319, 320, 321, 322, 323, 324, 325, 326, 327, 328, 329, 330, 331, 332, 333, 334, 335, 336, 337, 338, 339, 340, 341, 342, 343, 344, 345, 346, 347, 348, 349, 350, 351, 352, 353, 354, 355, 356, 357, 358, 359, 360, 361, 362, 363, 364, 365, 366, 367, 368, 369, 370, 371, 372, 373, 374, 375, 376, 377, 378, 379, 380, 381, 382, 383, 384, 385, 386, 387, 388, 389, 390, 391, 392, 393, 394, 395, 396, 397, 398, 399, 400, 401, 402, 403, 404, 405, 406, 407, 408, 409, 410, 411, 412, 413, 414, 415, 416, 417, 418, 419, 420, 421, 422, 423, 424, 425, 426, 427, 428, 429, 430, 431, 432, 433, 434, 435, 436, 437, 438, 439, 440, 441, 442, 443, 444, 445, 446, 447, 448, 449, 450, 451, 452, 453, 454, 455, 456, 457, 458, 459, 460, 461, 462, 463, 464, 465, 466, 467, 468, 469, 470, 471, 472, 473, 474, 475, 476, 477, 478, 479, 480, 481, 482, 483, 484, 485, 486, 487, 488, 489, 490, 491, 492, 493, 494, 495, 496, 497, 498, 499, 500, 501, 502, 503, 504, 505, 506, 507, 508, 509, 510, 511, 512, 513, 514, 515, 516, 517, 518, 519, 520, 521, 522, 523, 524, 525, 526, 527, 528, 529, 530, 531, 532, 533, 534, 535, 536, 537, 538, 539, 540, 541, 542, 543, 544, 545, 546, 547, 548, 549, 550, 551, 552, 553, 554, 555, 556, 557, 558, 559, 560, 561, 562, 563, 564, 565, 566, 567, 568, 569, 570, 571, 572, 573, 574, 575, 576, 577, 578, 579, 580, 581, 582, 583, 584, 585, 586, 587, 588, 589, 590, 591, 592, 593, 594, 595, 596, 597, 598, 599, 600, 601, 602, 603, 604, 605, 606, 607, 608, 609, 610, 611, 612, 613, 614, 615, 616, 617, 618, 619, 620, 621, 622, 623, 624, 625, 626, 627, 628, 629, 630, 631, 632, 633, 634, 635, 636, 637, 638, 639, 640, 641, 642, 643, 644, 645, 646, 647, 648, 649, 650, 651, 652, 653, 654, 655, 656, 657, 658, 659, 660, 661, 662, 663, 664, 665, 666, 667, 668, 669, 670, 671, 672, 673, 674, 675, 676, 677, 678, 679, 680, 681, 682, 683, 684, 685, 686, 687, 688, 689, 690, 691, 692, 693, 694, 695, 696, 697, 698, 699, 700, 701, 702, 703, 704, 705, 706, 707, 708, 709, 710, 711, 712, 713, 714, 715, 716, 717, 718, 719, 720, 721, 722, 723, 724, 725, 726, 727, 728, 729, 730, 731, 732, 733, 734, 735, 736, 737, 738, 739, 740, 741, 742, 743, 744, 745, 746, 747, 748, 749, 750, 751, 752, 753, 754, 755, 756, 757, 758, 759, 760, 761, 762, 763, 764, 765, 766, 767, 768, 769, 770, 771, 772, 773, 774, 775, 776, 777, 778, 779, 780, 781, 782, 783, 784, 785, 786, 787, 788, 789, 790, 791, 792, 793, 794, 795, 796, 797, 798, 799, 800, 801, 802, 803, 804, 805, 806, 807, 808, 809, 810, 811, 812, 813, 814, 815, 816, 817, 818, 819, 820, 821, 822, 823, 824, 825, 826, 827, 828, 829, 830, 831, 832, 833, 834, 835, 836, 837, 838, 839, 840, 841, 842, 843, 844, 845, 846, 847, 848, 849, 850, 851, 852, 853, 854, 855, 856, 857, 858, 859, 860, 861, 862, 863, 864, 865, 866, 867, 868, 869, 870, 871, 872, 873, 874, 875, 876, 877, 878, 879, 880, 881, 882, 883, 884, 885, 886, 887, 888, 889, 890, 891, 892, 893, 894, 895, 896, 897, 898, 899, 900, 901, 902, 903, 904, 905, 906, 907, 908, 909, 910, 911, 912, 913, 914, 915, 916, 917, 918, 919, 920, 921, 922, 923, 924, 925, 926, 927, 928, 929, 930, 931, 932, 933, 934, 935, 936, 937, 938, 939, 940, 941, 942, 943, 944, 945, 946, 947, 948, 949, 950, 951, 952, 953, 954, 955, 956, 957, 958, 959, 960, 961, 962, 963, 964, 965, 966, 967, 968, 969, 970, 971, 972, 973, 974, 975, 976, 977, 978, 979, 980, 981, 982, 983, 984, 985, 986, 987, 988, 989, 990, 991, 992, 993, 994, 995, 996, 997, 998, 999, 1000

ATTERBERG LIMITS & NATURAL MOISTURE CONTENT

Test Method :- BS 1377 : Part 2 : Clause 3.2.4.1 to 4.4 & 5 : 1990

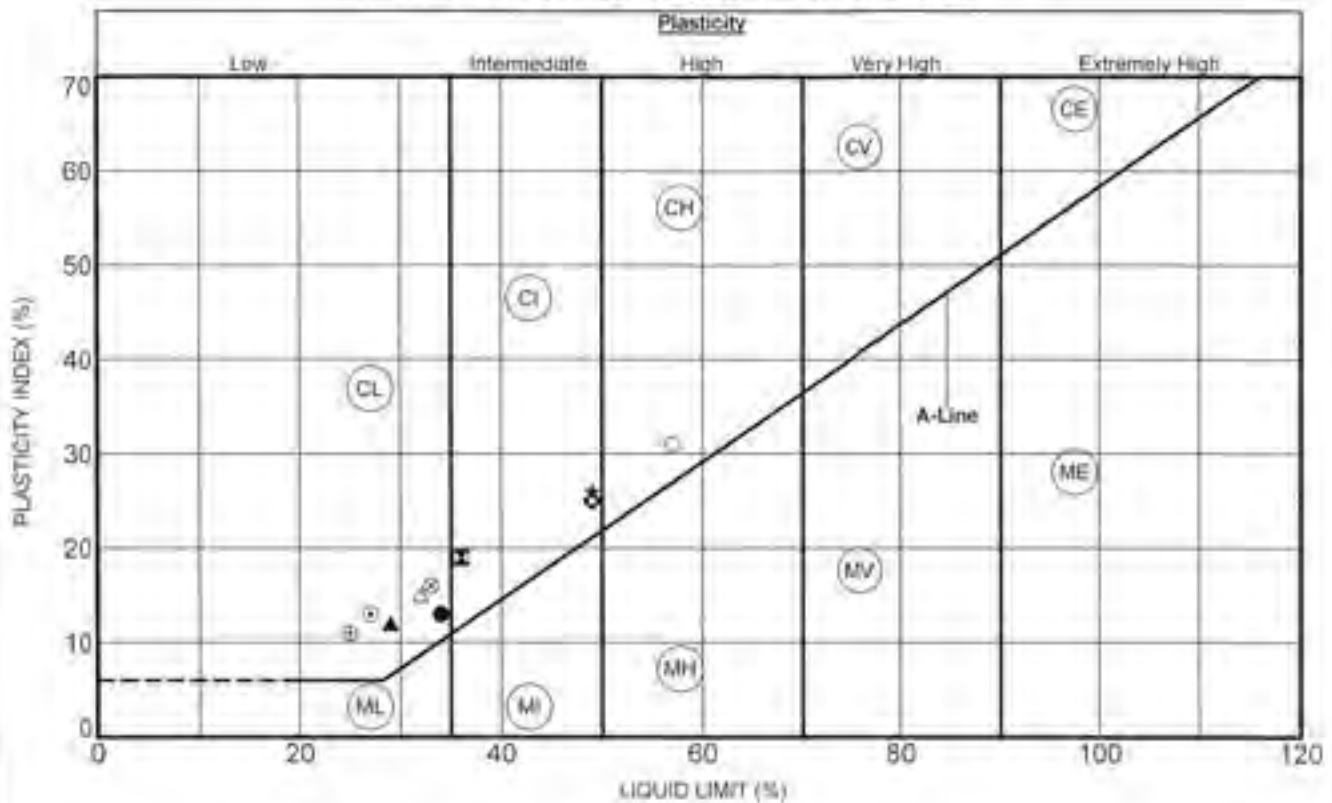

Exploratory Hole No.	Depth (m)	Sample Type/Ref.	Specific Depth (m)	LL	PL	PI	I	Preparation Method	$+0.425\text{mm}$ (%)	m/c (%)	Date Tested
● PRAIRIE_AUK_BH10417.50	5.00	C23	18.00	34	21	13	-1.07	Air Dried	36.0	7.1	12/10/2020
✕ PRAIRIE_AUK_BH1065.95	5.95	J3	5.95	36	17	19	-0.08	Natural		15.5	06/10/2020
▲ PRAIRIE_AUK_BH1069.50	9.50	J10	9.50	29	17	12	-0.10	Natural		15.8	06/10/2020
◆ PRAIRIE_AUK_BH1073.00	3.35	U2	3.35	49	23	26	0.55	Natural		37.3	10/07/2020
○ PRAIRIE_AUK_BH1077.50	7.50	J12	7.50	27	14	13	0.18	Natural		16.3	10/07/2020
○ PRAIRIE_AUK_BH1082.50	2.55	U2	2.55	49	24	25	0.07	Natural		25.8	10/07/2020
○ PRAIRIE_AUK_BH1082.95	2.95	J2	2.95	57	26	31	0.13	Natural		30.0	06/10/2020
○ PRAIRIE_AUK_BH1085.00	5.00	J9	5.00	32	17	15	-0.09	Natural		15.6	10/07/2020
○ PRAIRIE_AUK_BH1085.50	6.50	J12	6.50	33	17	16	-0.39	Air Dried	35.0	10.7	10/07/2020 #
○ PRAIRIE_AUK_BH1088.00	8.00	J15	8.00	25	14	11	-0.17	Natural		12.1	06/10/2020

For description of sample please refer to the Laboratory Sample Description Sheet. # = Insufficient for 4 point PI
If sample is prepared in the natural state we are unable to determine % retained on the 0.425mm test sieve

Contract Title :- Prairie Site Ground Investigation Works	Client :- South Tees Development Corporation
---	--


	Signed :- <i>mzone</i>	Name :-	Page 2 of 8	
	Date of issue :- 03/11/2020	Certificate No :- PL4251/2	AEG Contract No :- 4251	

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 1st Floor, 100, Victoria Road, South Tees, Sunderland, Tyne & Wear, S15 4JG. Tel: 0191 511 3000 Fax: 0191 511 3001
Regional Office: 1st Floor, 100, Victoria Road, South Tees, Sunderland, Tyne & Wear, S15 4JG. Tel: 0191 511 3000 Fax: 0191 511 3001

ATTERBERG LIMITS & NATURAL MOISTURE CONTENT

Test Method - BS 1377 - Part 2 - Clause 3.2, 4.1 to 4.4 & 5 - 1990

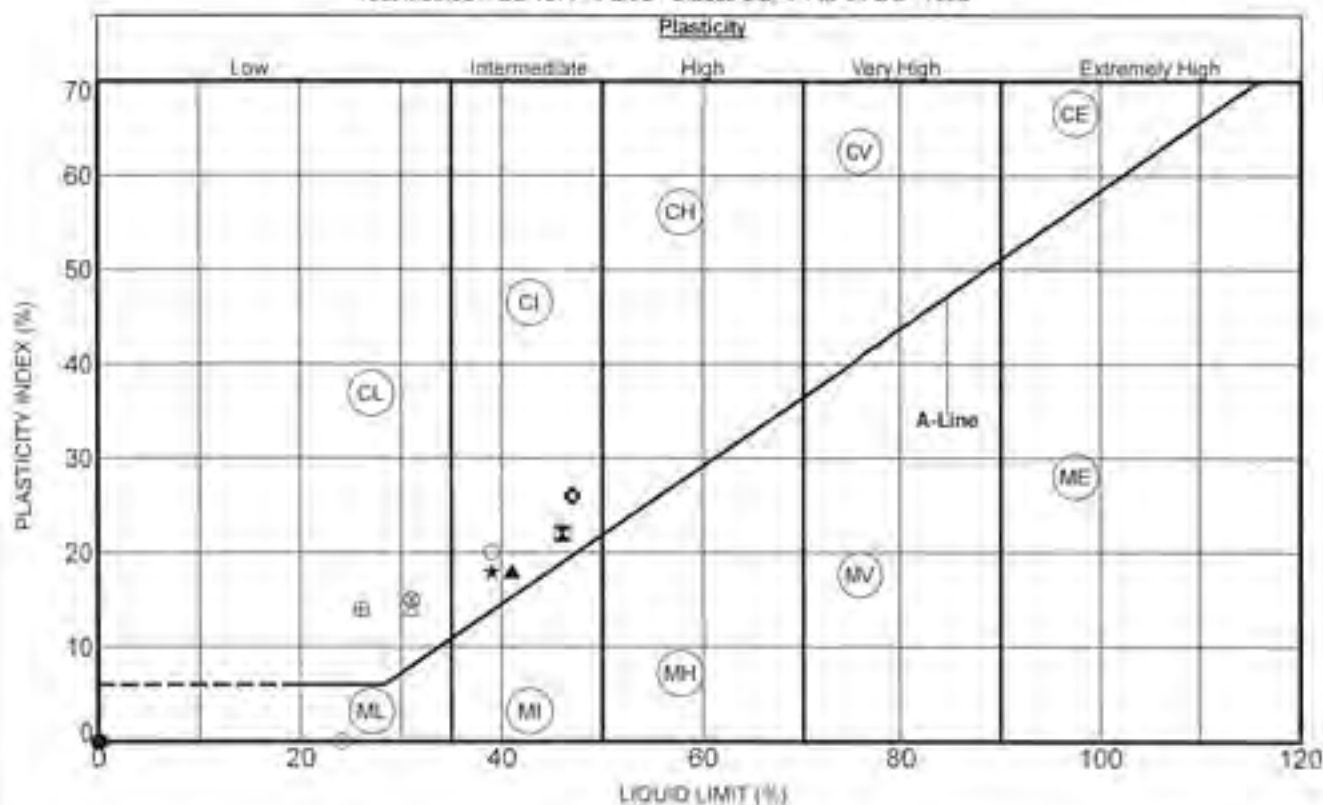

Exploratory Hole No.	Depth (m)	Sample Type/Ref.	Specific Depth (m)	LL	PL	PI	I_p	Preparation Method	<0.425mm (%)	wvc (%)	Date Tested
● PRAIRIE_AUK_BH1088.50	J16	B4	0.50	NP	NP	NP		Natural		15.3	10/07/2020
⊗ PRAIRIE_AUK_BH1090.50	J16	B4	0.50	46	24	22	0.00	Natural		23.9	13/07/2020
▲ PRAIRIE_AUK_BH1091.65	J7	B4	1.65	41	23	18	0.12	Natural		25.1	10/07/2020
★ PRAIRIE_AUK_BH1093.45	J14	B4	3.45	39	21	18	0.11	Natural		23.0	10/07/2020
⊙ PRAIRIE_AUK_BH1095.00	J22	B4	6.00	39	24			Air Dried	39.0	10.8	10/07/2020
⊙ PRAIRIE_AUK_BH1103.00	U2	B4	3.00	47	21	26	0.31	Natural		29.1	13/07/2020
○ PRAIRIE_AUK_BH1105.00	U6	B4	5.35	39	19	20	0.21	Natural		23.2	10/07/2020
△ PRAIRIE_AUK_BH1108.00	U12	B4	8.35	31	17	14	0.85	Natural		28.9	10/07/2020
▽ PRAIRIE_AUK_BH1109.50	J15	B4	9.50	31	16	15	-0.23	Natural		12.6	10/07/2020
⊖ PRAIRIE_AUK_BH11013.50	J23	B4	13.50	26	12	14	0.04	Natural		12.6	10/07/2020

For description of sample please refer to the Laboratory Sample Description Sheet # = Insufficient for 4 point PI
sample is prepared in the natural state we are unable to determine % retained on the 0.425mm test sieve

Contract Title - **Prairie Site Ground Investigation Works**

Client - **South Tees Development Corporation**



Signed: *msore*

Name: _____

Page 3 of 8

Date of issue - 03/11/2020

Certificate No. - P/4251/3

AEG Contract No. - 4251




1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 2nd Floor, Commercial Centre, Fallow Park, Thrumpton Road, South Tees, Darlington, Co. Durham, DL1 1BA. Tel: 01781 510000 Fax: 01781 510001
Regional Office: 100/101, South Tees Development Centre, South Tees, Darlington, Co. Durham, DL1 1BA. Tel: 01781 751000 Fax: 01781 751001

ATTERBERG LIMITS & NATURAL MOISTURE CONTENT

Test Method - BS 1377 : Part 2 : Clause 3.2.4.1 to 4.4 & 5 : 1990

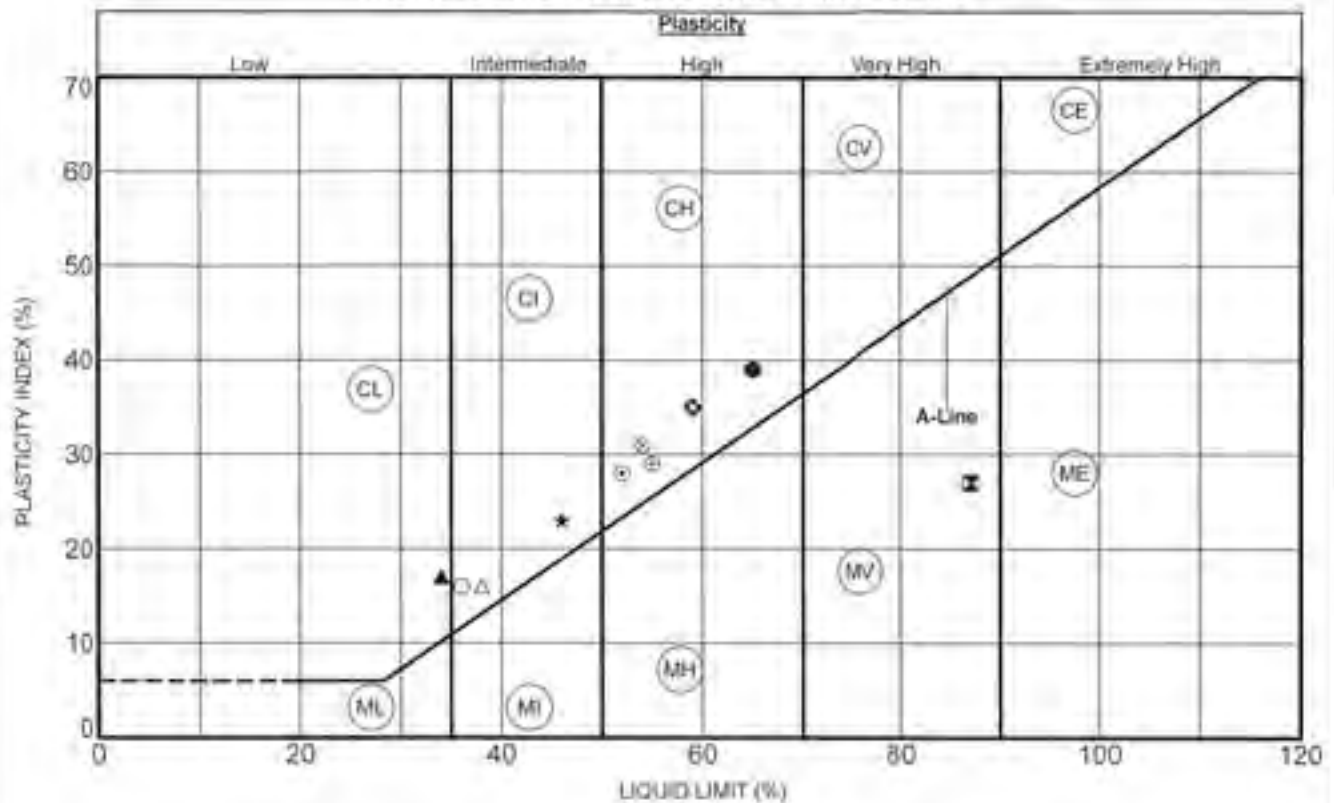

Exploratory Hole No.	Depth (m)	Sample Type/Ref.	Specific Depth (m)	LL	PL	PI	I _p	Preparation Method	<0.425mm (%)	w/c (%)	Date Tested
● PRAIRIE_AUK_TP1012.50	5.0	J10	2.50	65	26	39	-0.35	Natural		12.2	28/09/2020
⊠ PRAIRIE_AUK_TP1014.40	4.0	J14	4.40	87	60	27	1.07	Natural		89.0	28/09/2020 #
▲ PRAIRIE_AUK_TP1021.50	1.50	J6	1.50	34	17	17	0.05	Natural		17.8	06/10/2020 #
★ PRAIRIE_AUK_TP1042.00	2.00	J8	2.00	46	23	23	-0.08	Natural		21.2	28/09/2020 #
⊙ PRAIRIE_AUK_TP1051.80	1.80	J4	1.80	52	24	28	0.22	Natural		30.1	28/09/2020
◆ PRAIRIE_AUK_TP1062.50	2.50	J6	2.50	59	24	35	0.06	Natural		26.2	06/10/2020 #
○ PRAIRIE_AUK_TP1063.50	3.50	J8	3.50	36	20	16	-0.23	Natural		16.3	06/10/2020 #
△ PRAIRIE_AUK_TP1070.50	0.50	J3	0.50	38	22	16	-0.02	Natural		21.7	29/09/2020 #
⊗ PRAIRIE_AUK_TP1072.30	2.30	J6	2.30	54	23	31	0.13	Natural		27.1	29/09/2020
⊞ PRAIRIE_AUK_TP1102.50	2.50	J6	2.50	55	26	29	0.24	Natural		32.9	06/10/2020 #

For description of sample please refer to the Laboratory Sample Description Sheet # = Insufficient for 4 point Pi
If sample is prepared in the natural state we are unable to determine % retained on the 0.425mm test sieve

Contract Title - **Prairie Site Ground Investigation Works**

Client - **South Tees Development Corporation**



Signed - *msene*

Name -

Page 4 of 8

Date of Issue - 09/11/2020

Certificate No - FV4253/4

REG Contract No - 4251




1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: South Tees Development Corporation, Princes Road, Middlesbrough, Co. Durham, TS1 1PL. Tel: 01462 433444 Fax: 01462 433444
Regional Office: 100000, Boulevard, Middlesbrough, Co. Durham, TS1 1PL. Tel: 01462 433444 Fax: 01462 433444

ATTERBERG LIMITS & NATURAL MOISTURE CONTENT

Test Method - BS 1377 - Part 2 - Clause 3.2, 4.1 to 4.4 & 5 - 1990

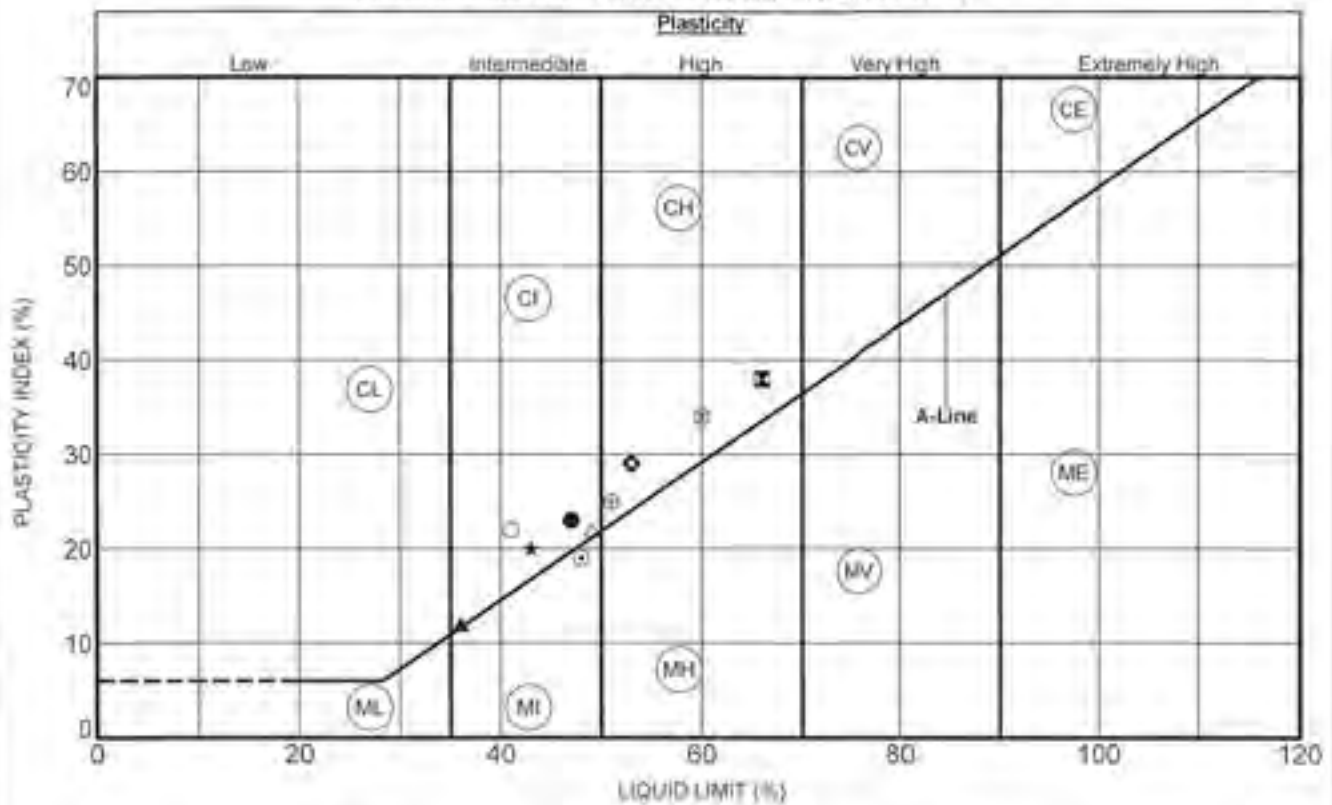

Exploratory Hole No.	Depth (m)	Sample Type/Ref.	Specific Depth (m)	LL	PL	PI	I _p	Preparation Method	<0.425mm (%)	w/c (%)	Date Tested	
● PRAIRIE_AUK_TP112.00	J6	J6	2.00	47	24	23	-0.10	Natural		21.8	06/10/2020	#
⊠ PRAIRIE_AUK_TP112.70	J9	J9	2.70	66	26	38	0.07	Natural		30.6	06/10/2020	
▲ PRAIRIE_AUK_TP112.00	J10	J10	3.00	36	24	12	0.32	Natural		27.8	06/10/2020	
★ PRAIRIE_AUK_TP112.50	J7	J7	2.50	43	23	20	0.20	Natural		26.9	28/09/2020	
○ PRAIRIE_AUK_TP116.60	J5	J5	1.60	48	29	19	-0.12	Natural		26.8	20/10/2020	
◊ PRAIRIE_AUK_TP116.2.00	J7	J7	2.00	53	24	29	0.03	Air Dried	99.0	24.9	20/10/2020	
○ PRAIRIE_AUK_TP116.3.00	J9	J9	3.00	41	19	22	-0.07	Natural		17.5	20/10/2020	
▽ PRAIRIE_AUK_TP118.1.50	J4	J4	1.50	49	27	22	0.16	Natural		30.6	12/10/2020	#
⊘ PRAIRIE_AUK_TP118.2.20	J6	J6	2.20	60	26	34	0.23	Natural		33.8	12/10/2020	#
⊚ PRAIRIE_AUK_TP119.2.50	J6	J6	2.50	51	26	25	0.12	Natural		29.1	06/10/2020	#

For description of sample please refer to the Laboratory Sample Description Sheet. # = Insufficient for 4 point PI
If sample is prepared in the natural state we are unable to determine % retained on the 0.425mm test sieve

Contract Title - **Prairie Site Ground Investigation Works**

Client - **South Tees Development Corporation**



Signed - *msere*

Name -

Page 5 of 8

Date of issue
05/11/2020

Certificate No -
PI/4251/5

AEG Contract No -
4251




1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 100, Westwood Road, Westwood, South Tees, Durham, DA1 1PP, England
 Regional Office: 100, Westwood Road, Westwood, Durham, DA1 1PP, England

ATTERBERG LIMITS & NATURAL MOISTURE CONTENT

Test Method - BS 1377, Part 2, Clause 3.2, 4.1 to 4.4 & 5, 1990

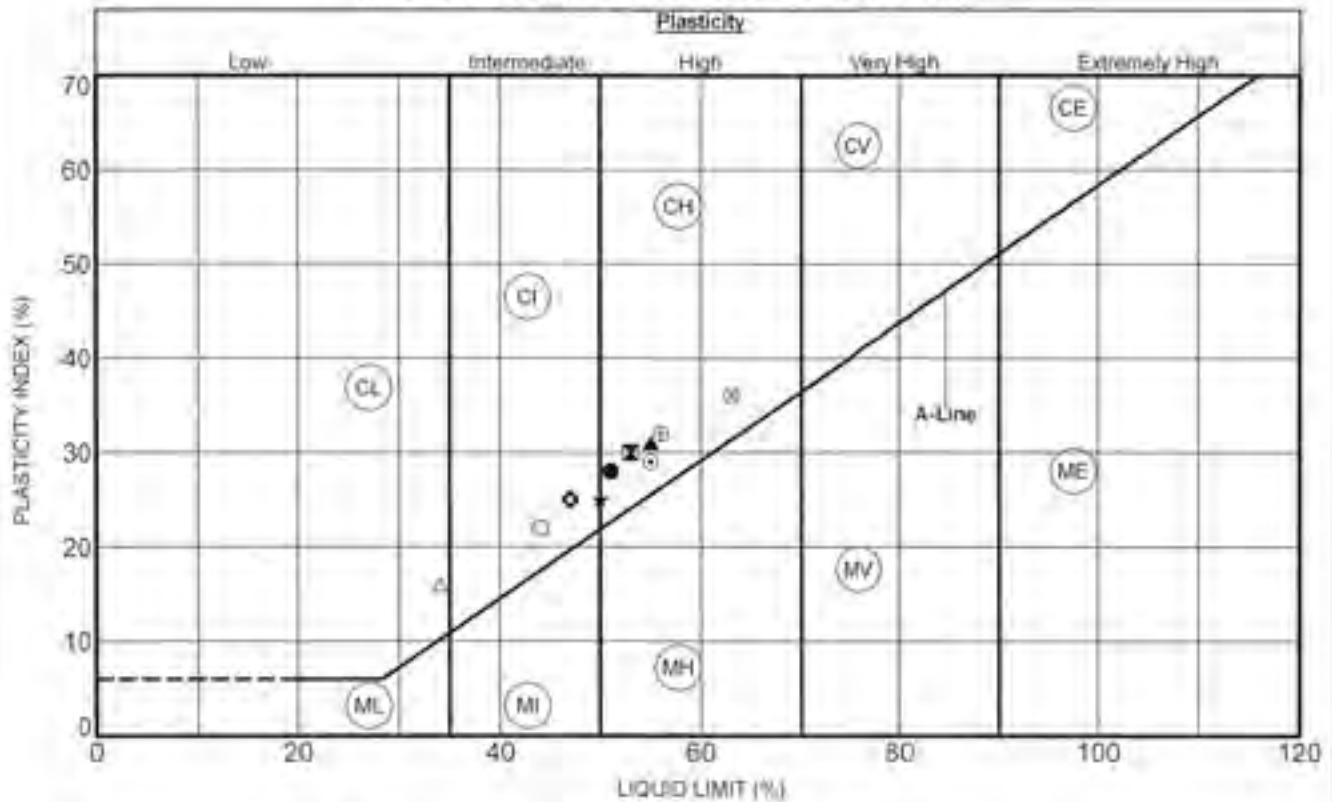

Exploratory Hole No.	Depth (m)	Sample Type/Ref.	Specific Depth (m)	LL	PL	PI	I _p	Preparation Method	<0.425mm (%)	w _c (%)	Date Tested
● PRAIRIE_AUK_TP145	1.90	J5	1.90	51	23	28	0.01	Natural		23.4	29/09/2020
⊠ PRAIRIE_AUK_TP145	2.90	J7	2.90	53	23	30	0.24	Natural		30.2	29/09/2020 #
▲ PRAIRIE_AUK_TP146	0.70	J7	1.70	55	24	31	0.09	Natural		28.8	29/09/2020 #
★ PRAIRIE_AUK_TP146	1.80	J4	1.80	50	25	25	0.20	Natural		29.9	06/10/2020 #
○ PRAIRIE_AUK_TP154	1.30	J4	1.30	55	26	29	0.04	Natural		27.2	06/10/2020
◊ PRAIRIE_AUK_TP154	2.30	J6	2.30	47	22	25	0.03	Natural		22.8	05/10/2020
∩ PRAIRIE_AUK_TP155	1.20	J4	1.20	44	22	22	-0.19	Natural		17.8	12/10/2020
△ PRAIRIE_AUK_TP156	1.10	J5	1.10	34	18	16	-0.01	Natural		17.8	06/10/2020 #
⊗ PRAIRIE_AUK_TP162	2.50	B6	2.50	63	27	36	0.19	Natural	96.0	33.7	29/09/2020
⊙ PRAIRIE_AUK_TP162	3.10	J7	3.10	56	24	32	0.28	Natural		33.0	29/09/2020

For description of sample please refer to the Laboratory Sample Description Sheet # = Insufficient for 4 point PI
 if sample is prepared in the natural state we are unable to determine % retained on the 0.425mm test sieve

Contract Title - Prairie Site Ground Investigation Works	Client - South Tees Development Corporation
---	--


	Signed - <i>msone</i>	Name -	Page 7 of 8	
	Date of Issue - 03/11/2020	Certificate No. - FV4251/T	REG Contract No. 4251	

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 24-25 Bickley Road, Bickley, London SE16 5JG. Tel: 020 87 4761 Fax: 020 87 4762
Regional Office: 104, St. James Street, London SW1 1SL. Tel: 020 7578 4444 Fax: 020 7578 4445

ATTERBERG LIMITS & NATURAL MOISTURE CONTENT

Test Method: - BS 1377: Part 2: Clause 3.2.4.1 to 4.4 & 5: 1990

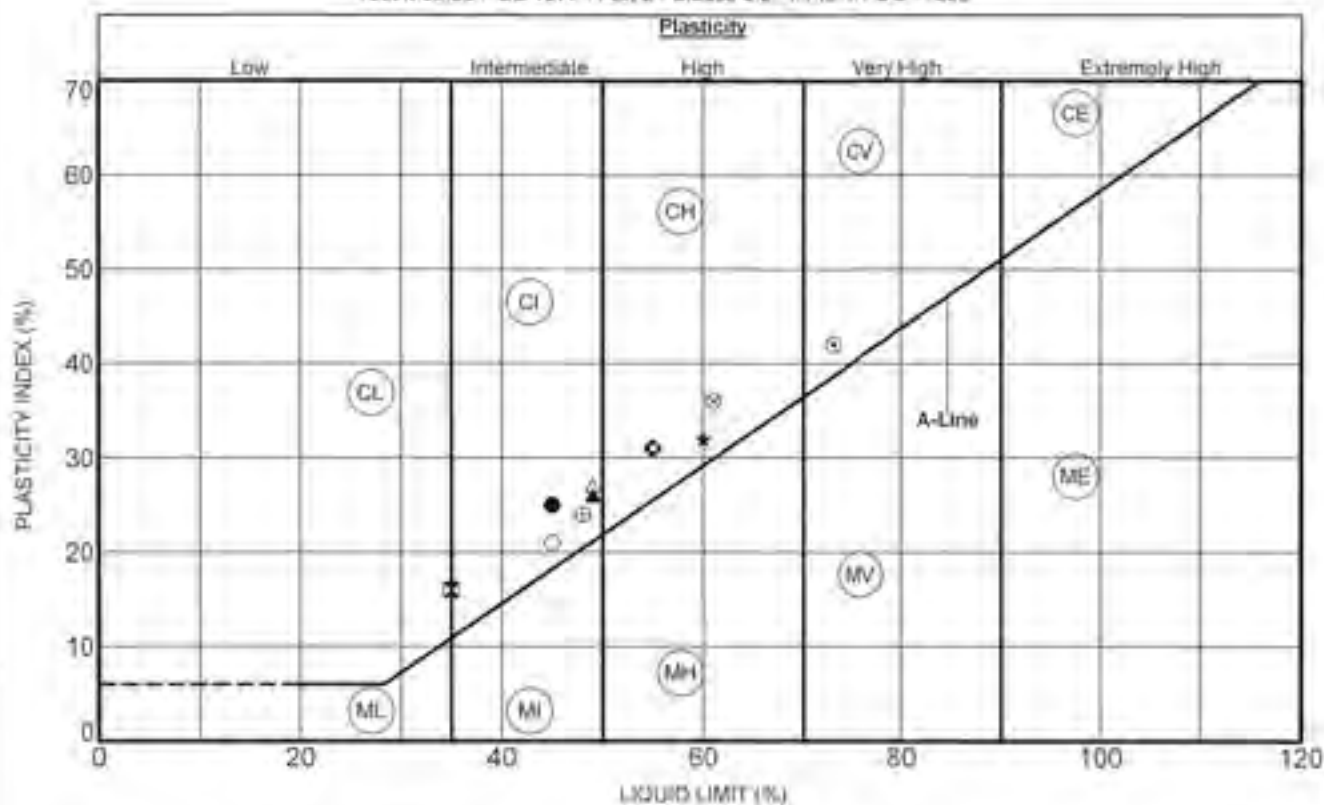

Exploratory Hole No.	Depth (m)	Sample Type/Ref	Specific Depth (m)	LL	PL	PI	I _p	Preparation Method	<0.425mm (%)	m/c (%)	Date Tested
● PRAIRIE_AUK_TP1831.60	J4	J4	1.60	45	20	25	0.22	Natural		25.6	29/09/2020
⊠ PRAIRIE_AUK_TP1741.20	J4	J4	1.20	35	19	16	0.41	Natural		25.6	28/09/2020
▲ PRAIRIE_AUK_TP1751.40	J4	J4	1.40	49	23	26	0.08	Natural		25.1	29/09/2020
★ PRAIRIE_AUK_TP1770.90	J4	J4	0.90	60	28	32	0.20	Natural		34.5	28/09/2020
⊙ PRAIRIE_AUK_TP1781.60	B5	B5	1.60	73	31	42	0.43	Natural		49.1	30/09/2020
◆ PRAIRIE_AUK_TP1791.70	J5	J5	1.70	55	24	31	0.23	Natural		31.1	29/09/2020
○ PRAIRIE_AUK_TP1811.80	J5	J5	1.80	45	24	21	-0.04	Natural		23.1	29/09/2020
◊ PRAIRIE_AUK_TP1821.30	J4	J4	1.30	49	22	27	-0.01	Natural		21.8	29/09/2020
⊗ PRAIRIE_AUK_TP1891.40	J3	J3	1.40	61	25	36	0.08	Natural		27.9	29/09/2020
⊕ PRAIRIE_AUK_TP1882.70	J5	J5	2.70	48	24	24	0.16	Natural		27.9	29/09/2020

For description of sample please refer to the Laboratory Sample Description Sheet. # = insufficient for 4 point PI
If sample is prepared in the natural state we are unable to determine % retained on the 0.425mm test sieve

Contract Title: - **Prairie Site Ground Investigation Works**

Client: - **South Tees Development Corporation**



Signed: *msop*

Name: -

Page 8 of 8

Date of Issue: - 03/11/2020

Certificate No: - P/4251/8

AEG Contract No: - 4251



1367

Determination of Particle Density

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Colver Lane, Huddersfield, West Yorkshire, HD1 3JH. Tel: 01484 527 400 Fax: 01484 527 401
Regional Office: Unit 26, Bessard Close, Barnsley, South Yorkshire, S70 2SL. Tel: 01225 391 288 Fax: 01225 391 289

DETERMINATION OF PARTICLE DENSITY

BS1377 Part 2 : Clause 8.2 : 1990

Exploratory Hole No.	Depth (m)	Sample Type & No.	Specific Depth (m)	Particle Density (Mg/m ³)	Date Tested
PRAIRIE_AUK_BH101	3.00	U2	3.00	2.61	18/06/2020
PRAIRIE_AUK_BH101	11.00	U18	11.00	2.69	18/06/2020
PRAIRIE_AUK_BH108	3.50	B5	3.50	2.61	27/07/2020

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works	Client :- South Tees Development Corporation
---	--

	Signed :- <i>msene</i>	Name :-	Page 1 of 1	
	Date of Issue :- 03/11/2020	Certificate No. :- PD/4251/1	AEG Contract No. :- 4251	

Particle Size Distribution Sieving and Sedimentation




ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 20, Business Development Centre, Farnham Road, Farnham, Surrey, GU14 7AB, UK. Tel: 01251 355 0200 Fax: 01251 352 4710
Regional Office: Unit 20, Business Development Centre, Farnham Road, Farnham, Surrey, GU14 7AB, UK. Tel: 01251 355 0200 Fax: 01251 352 4710

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

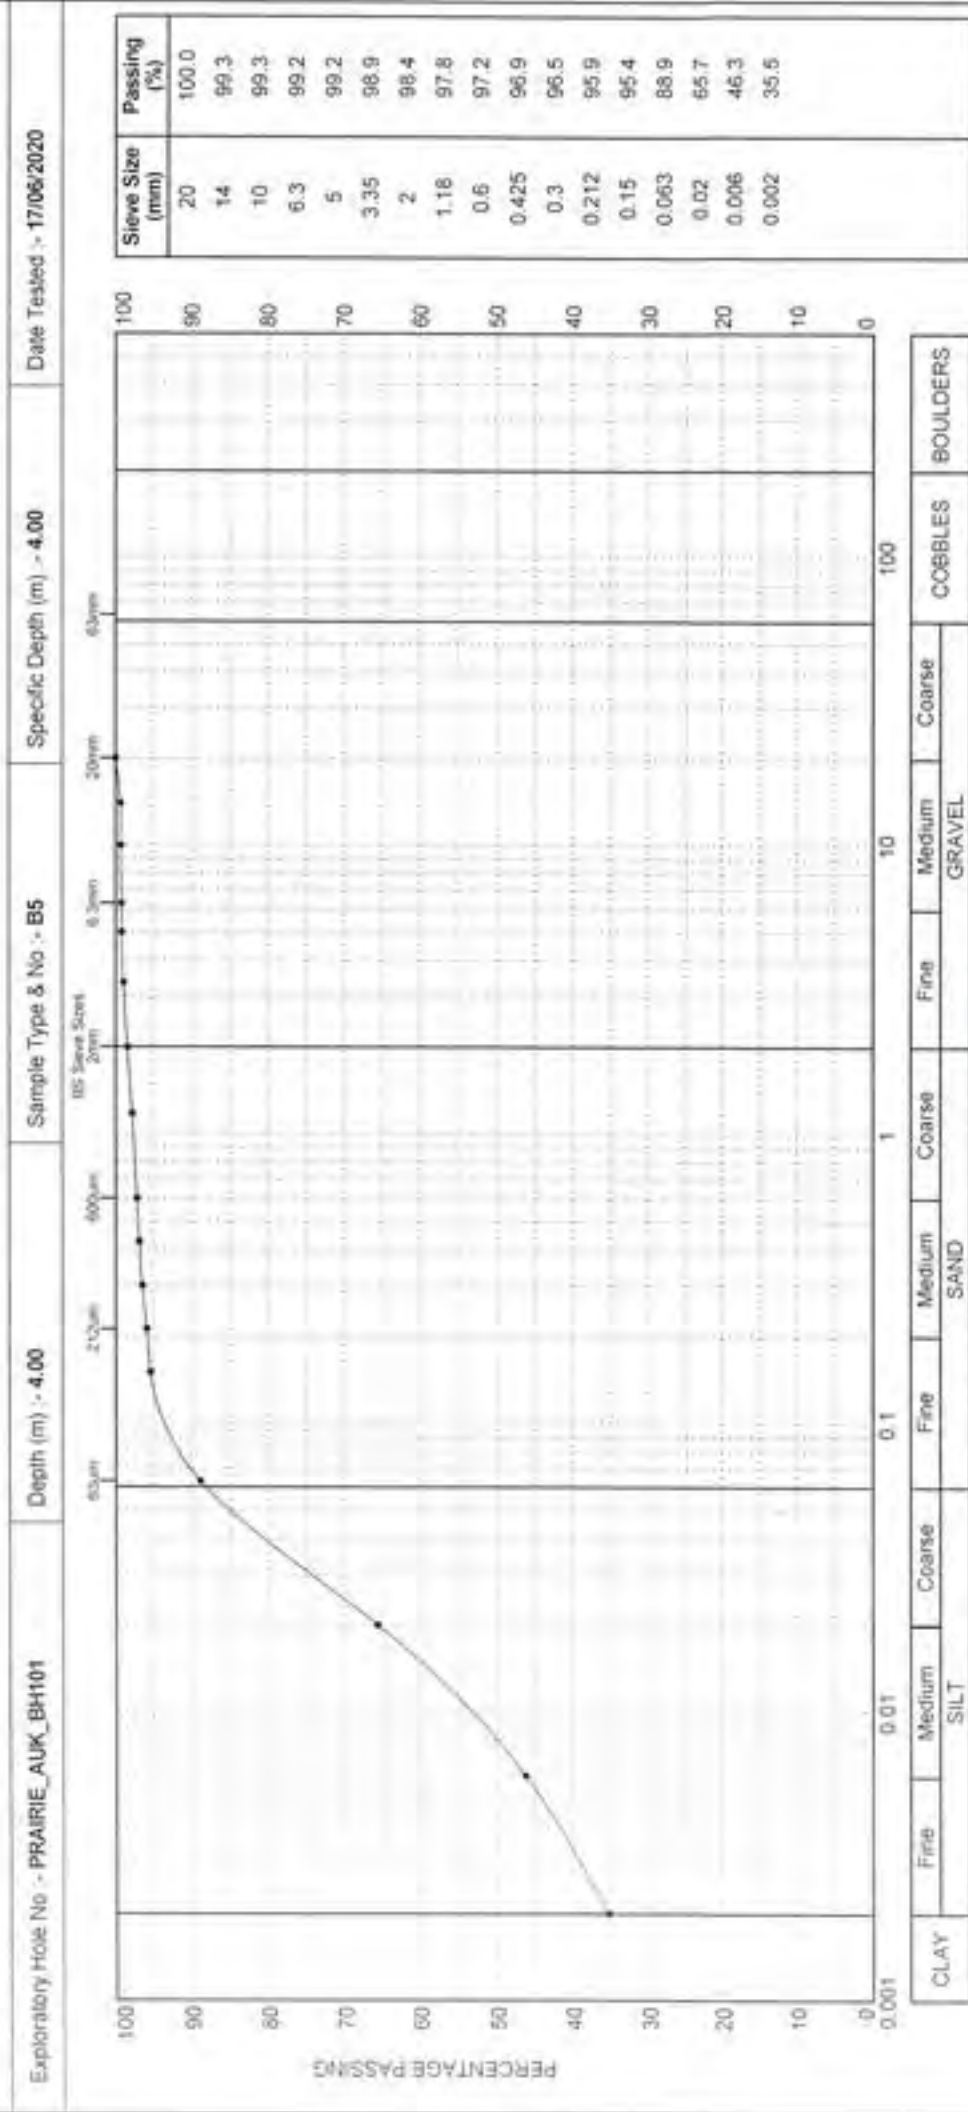

For description of sample please refer to the Laboratory Sample Description Sheet

	Date of issue > 29/06/2020	Certificate No > PSD/4251/PRAIRIE_AUK_BH101/B5/4.00	Signed > <i>M. Sore</i>	Name > M. Sore	Page 1 of 1
	Client > South Tees Development Corporation	Contract Title > Prairie Site Ground Investigation Works	AEG Contract No > 4251		




ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 25-26a Greenfield Lane, Prairies, Gateshead, Tyne and Wear, NE10 0JG, UK. Tel: 0191 445 388. Fax: 0191 445 382. E-mail: info@allied-geotech.co.uk
Regional Office: 207-210, Barnard Castle Road, Easingwold, North Yorkshire, YO21 3DE, UK. Tel: 01753 723 555. Fax: 01753 723 555.

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

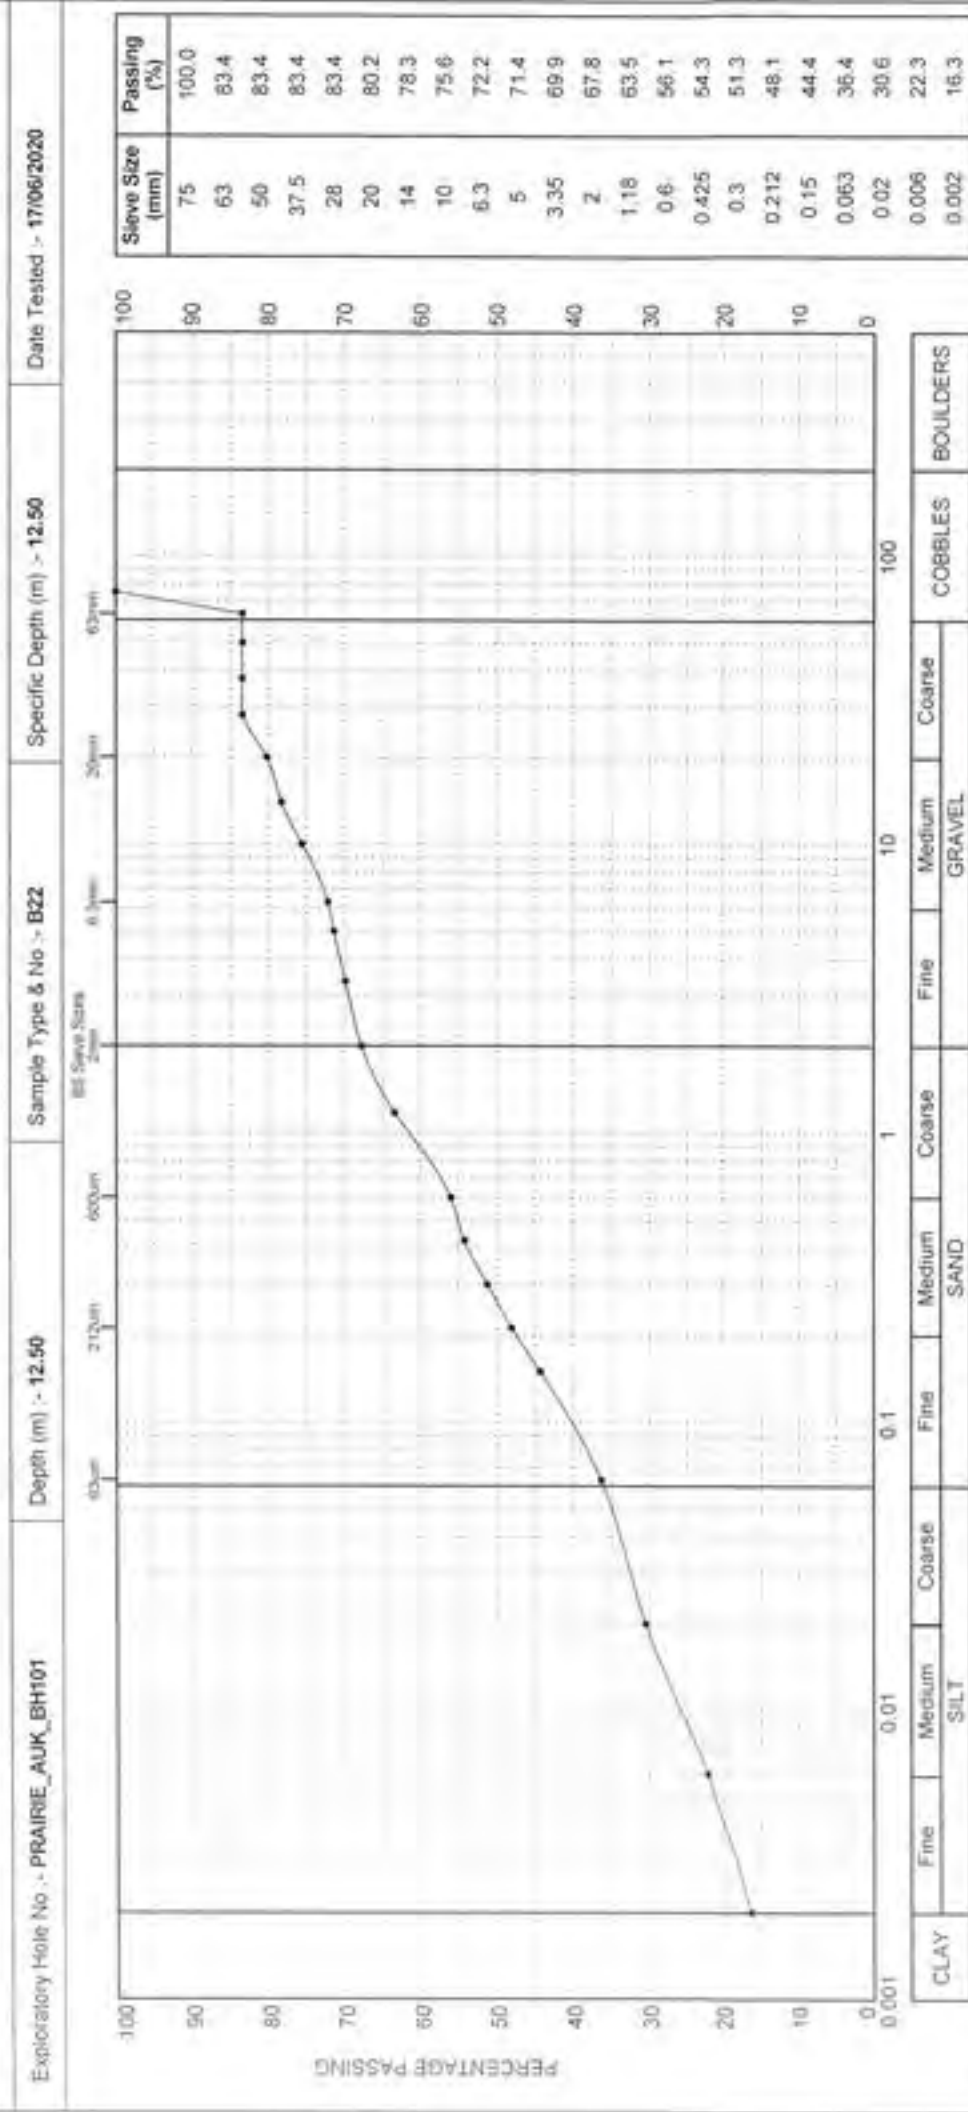

For description of sample please refer to the Laboratory Sample Description Sheet

	Date of issue :- 29/06/2020	Certificate No :- PSD/4251/PRAIRIE_AUK_BH101/B22/12.50	Signed :- <i>MSore</i>	Name :-
	Client :- South Tees Development Corporation	Contract Title :-	Prairie Site Ground Investigation Works	
Page 1 of 1		AEG Contract No :- 4251		



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990


Exploration Project No : PHARMAE_AUK_BH103

Depth (m) : 5.50

Sample Type & No : B12

Specific Depth (m) : 5.50

Date Tested : 15/10/2020

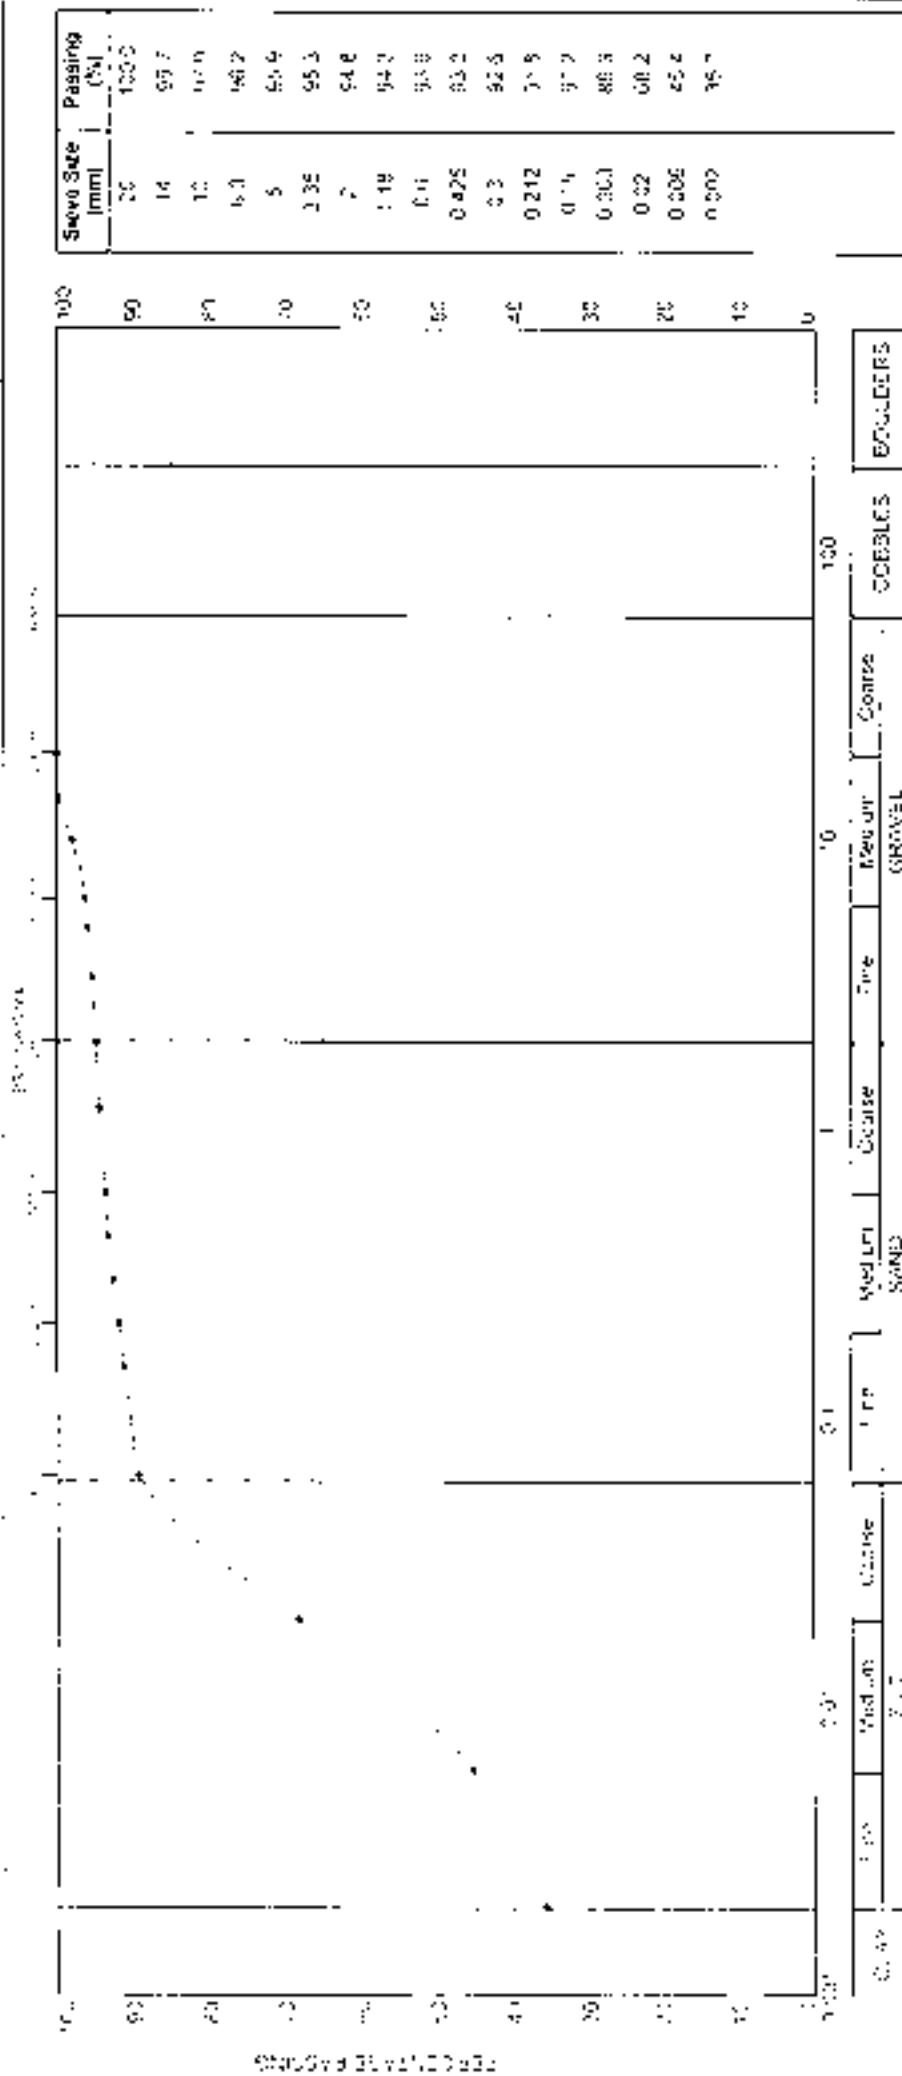

Date of issue : 21/10/2020

Contract No : MS04201P45143_AUK_BH103/2/15/16

Client : Pharmacia Auk

Page 1 of 1

Client

Soil Test (You are the Contractor)

Contract No

Print or Site (You are Investigator/Client)

AEG Contract No : 4251



1257

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 1st Fl, 100, Giff Street, Edinburgh, UK. Tel: 0131 425 4250 Fax: 0131 362 4714
Regional Office: 1st Fl, 20, Bannockburn Court, London SW14 2SE, UK. Tel: 01753 735 000 Fax: 01753 735 000

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

Exploratory Hole No - PRAIRIE_AUK_BH103	Depth (m) - 8.50	Sample Type & No - B19	Specific Depth (m) - 8.50	Date Tested - 15/10/2020
---	------------------	------------------------	---------------------------	--------------------------

PERCENTAGE PASSING

Sieve Size (mm)	Passing (%)
20	100.0
14	99.7
10	99.5
6.3	98.5
5	98.0
3.35	97.0
2	95.6
1.18	94.0
0.6	91.7
0.425	90.3
0.3	88.0
0.212	84.6
0.15	80.0
0.063	69.6
0.02	56.9
0.006	39.9
0.002	29.7

CLAY	Fine	Medium	Coarse	Fine	Medium	Coarse	Fine	Medium	Coarse	BOULDERS
	SILT			SAND			GRAVEL			

For description of sample please refer to the Laboratory Sample Description Sheet

Date of issue - 23/10/2020	Certificate No - PSD/4251/PRAIRIE_AUK_BH103/B19/8.50	Signed - <i>msore</i>	Name -
Client - South Tees Development Corporation	Contract Title -		Contract No - 4251
Client - South Tees Development Corporation		Contract Title - Prairie Site Ground Investigation Works	

Page 1 of 1


ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Baxby, 2nd Industrial Estate, Park Road, Doncaster, DN4 5DG - Tel: 01522 767400 Fax: 01522 767474
Regional Office: Unit 25, Baxby, 2nd Industrial Estate, Park Road, Doncaster, DN4 5DG - Tel: 01522 767400 Fax: 01522 767474

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 ; 1990

Exploratory Hole No. : PRAIRIE_AUK_BH108 Depth (m) : 3.50 Sample Type & No. : B5 Specific Depth (m) : 3.50 Date Tested : 10/07/2020

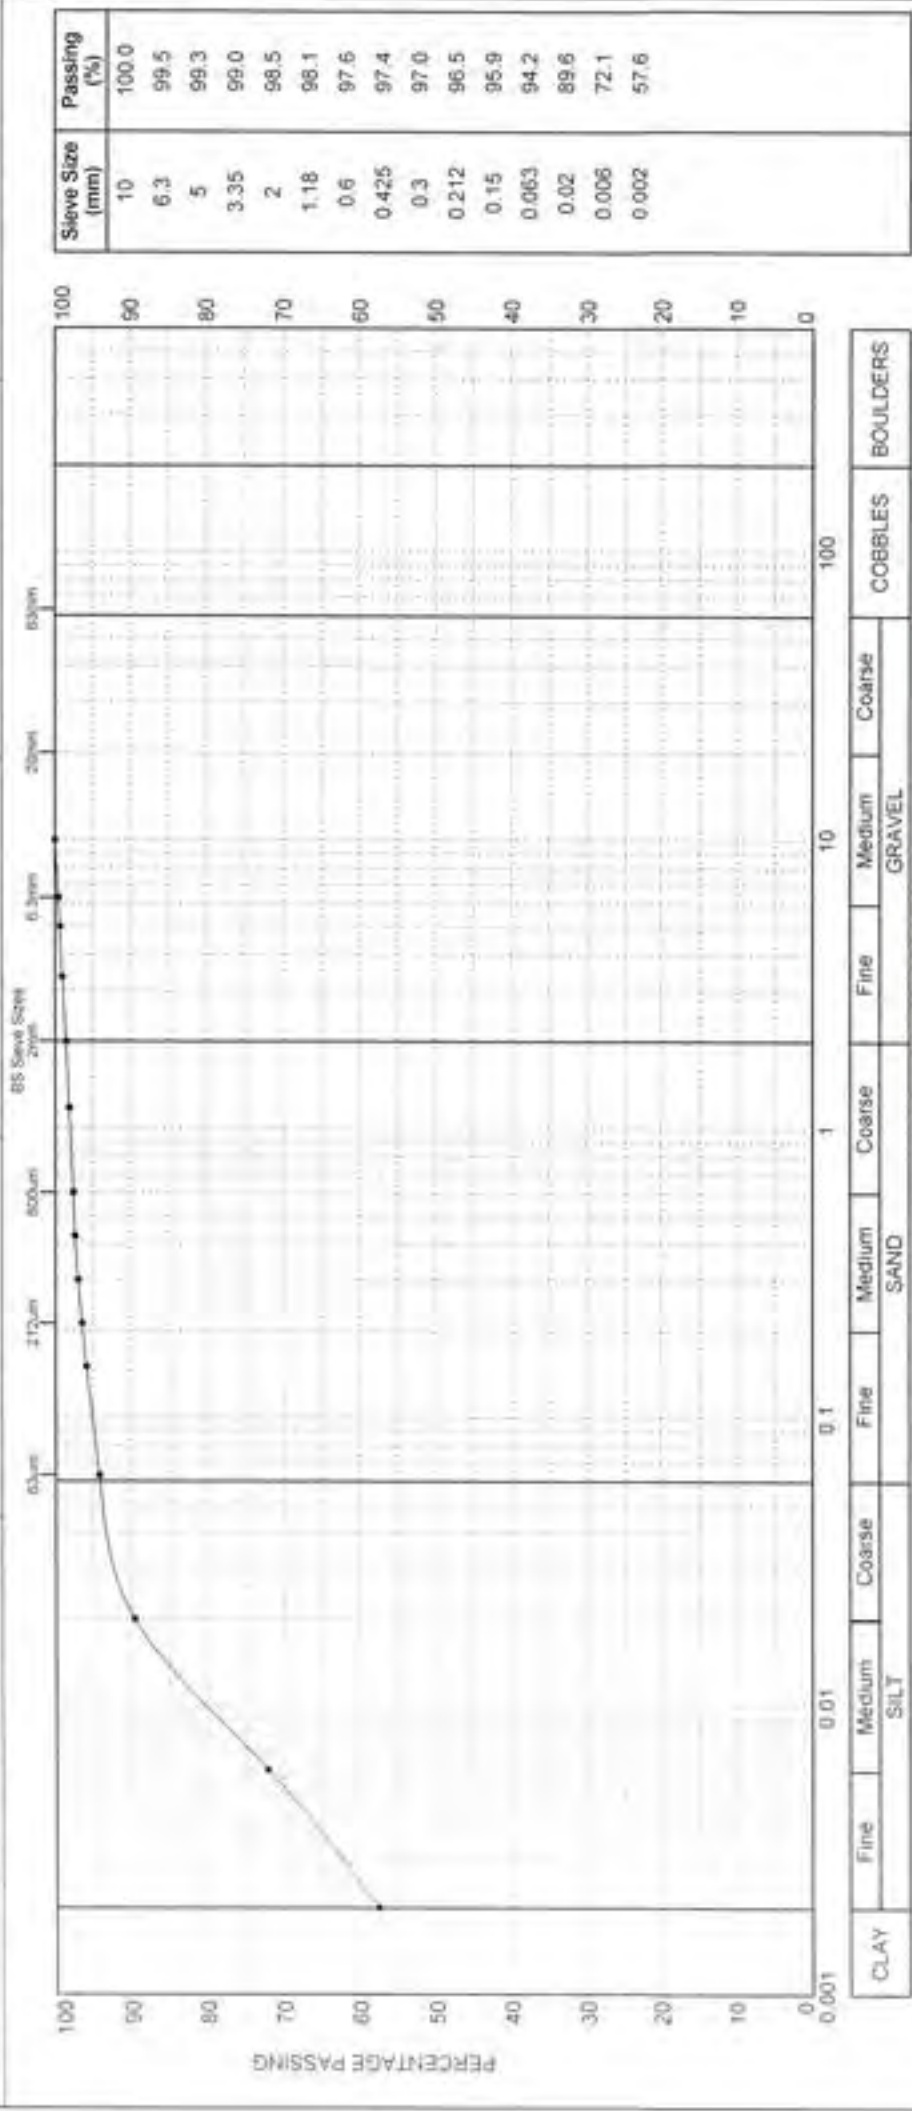

For description of sample please refer to the Laboratory Sample Description Sheet

Date of Issue : 30/07/2020	Certificate No. : PSD/4251/PRAIRIE_AUK_BH108/B5/3.50	Signed : <i>msore</i>	Name : M. BELKINIK	Page 1 of 1
Client : South Tees Development Corporation	Contract Title : Prairie Site Ground Investigation Works	AEG Contract No. : 4251		




1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Office: Unit 21, Riverside Development Centre, Farnham Road, Farnham, Surrey GU14 7AB, UK. Tel: +44 (0)1253 850000 Fax: +44 (0)1253 850001
 Registered Office: Unit 21, Riverside Development Centre, Farnham Road, Farnham, Surrey GU14 7AB, UK. Tel: +44 (0)1253 850000 Fax: +44 (0)1253 850001

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

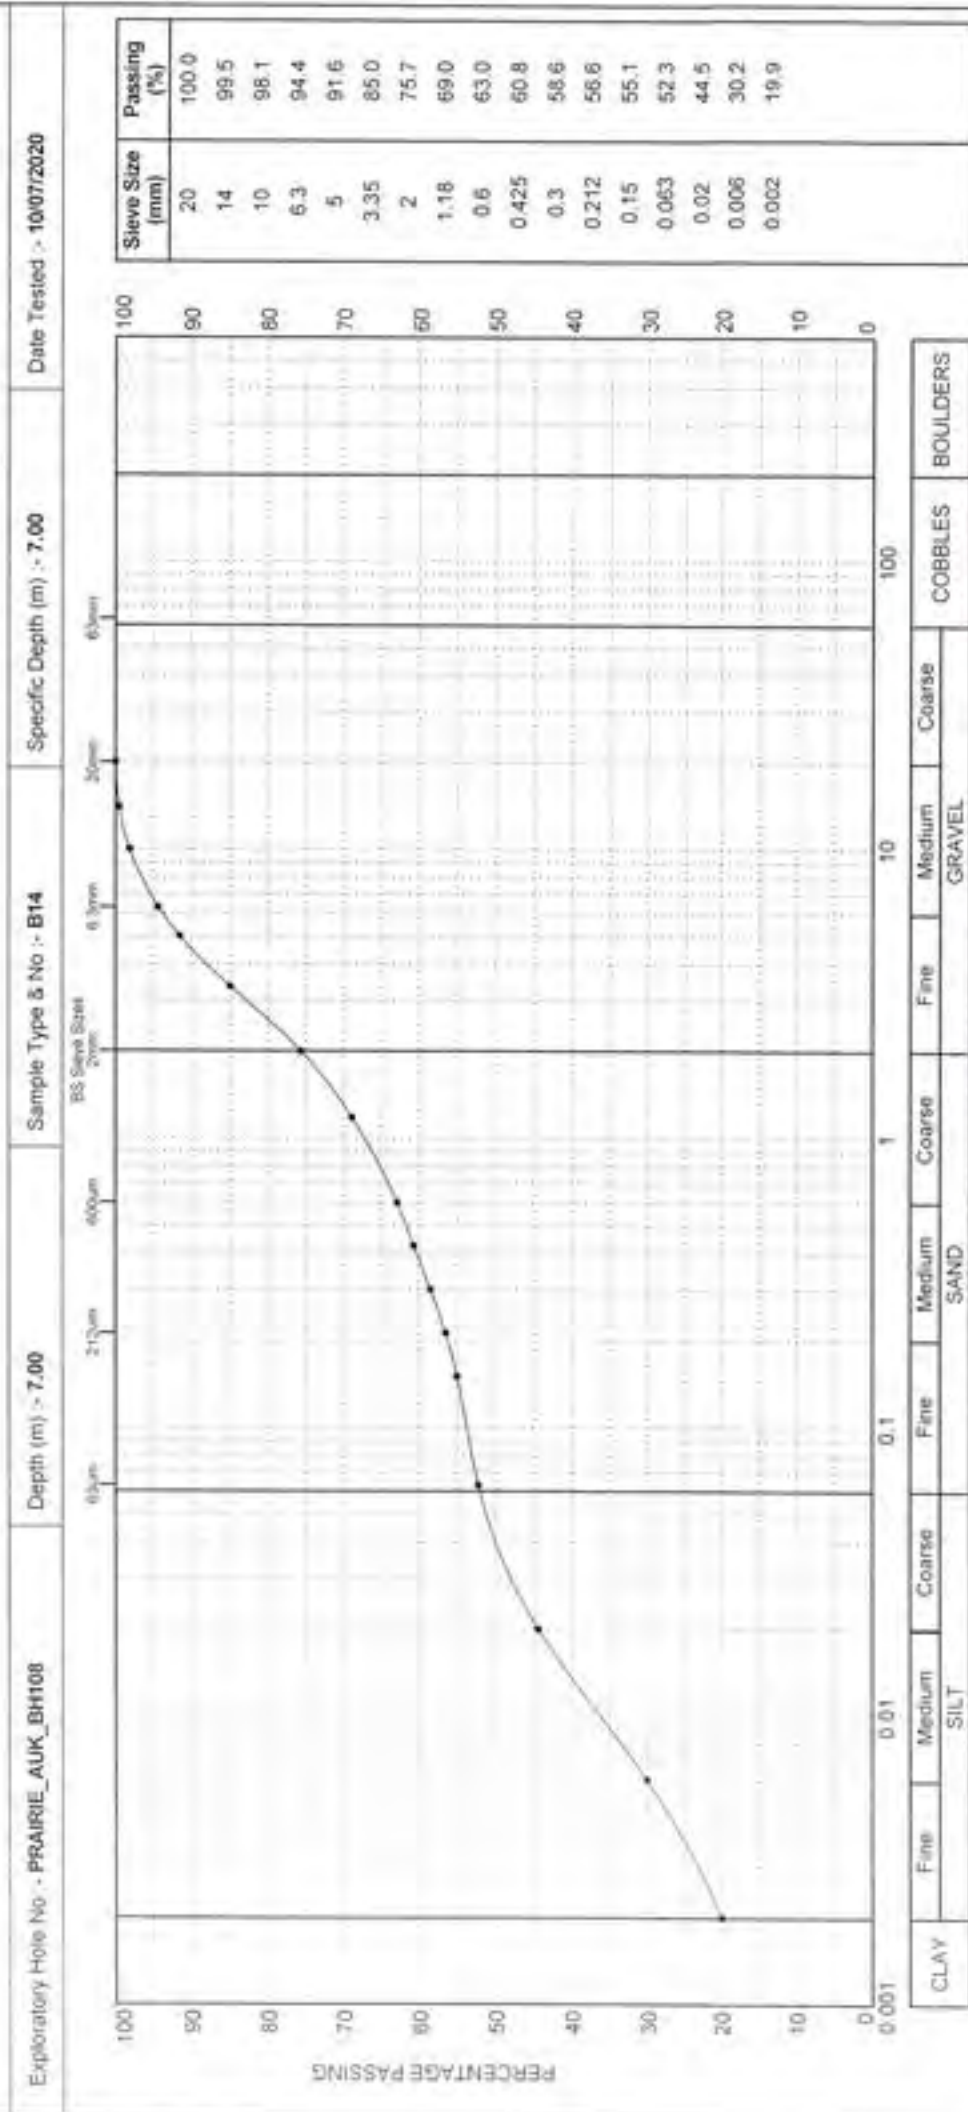

For description of sample please refer to the Laboratory Sample Description Sheet

Date of issue :- 30/07/2020	Certificate No :- PSD/4251/PRAIRIE_AUK_BH108/B14/7.00	Signed :- <i>M. Seno</i>	Name :- <i>DELTA</i>
Client :- South Tees Development Corporation	Contract Title :- Prairie Site Ground Investigation Works	AEG Contract No :- 4251	


Page 1 of 1

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 1st & 2nd Floors, 100, The Quadrant, Colchester, Essex, CO1 1JL. Tel: 0206 881111 Fax: 0206 881112
Regional Office: 10th Floor, 100, The Quadrant, Colchester, Essex, CO1 1JL. Tel: 0206 881111 Fax: 0206 881112

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

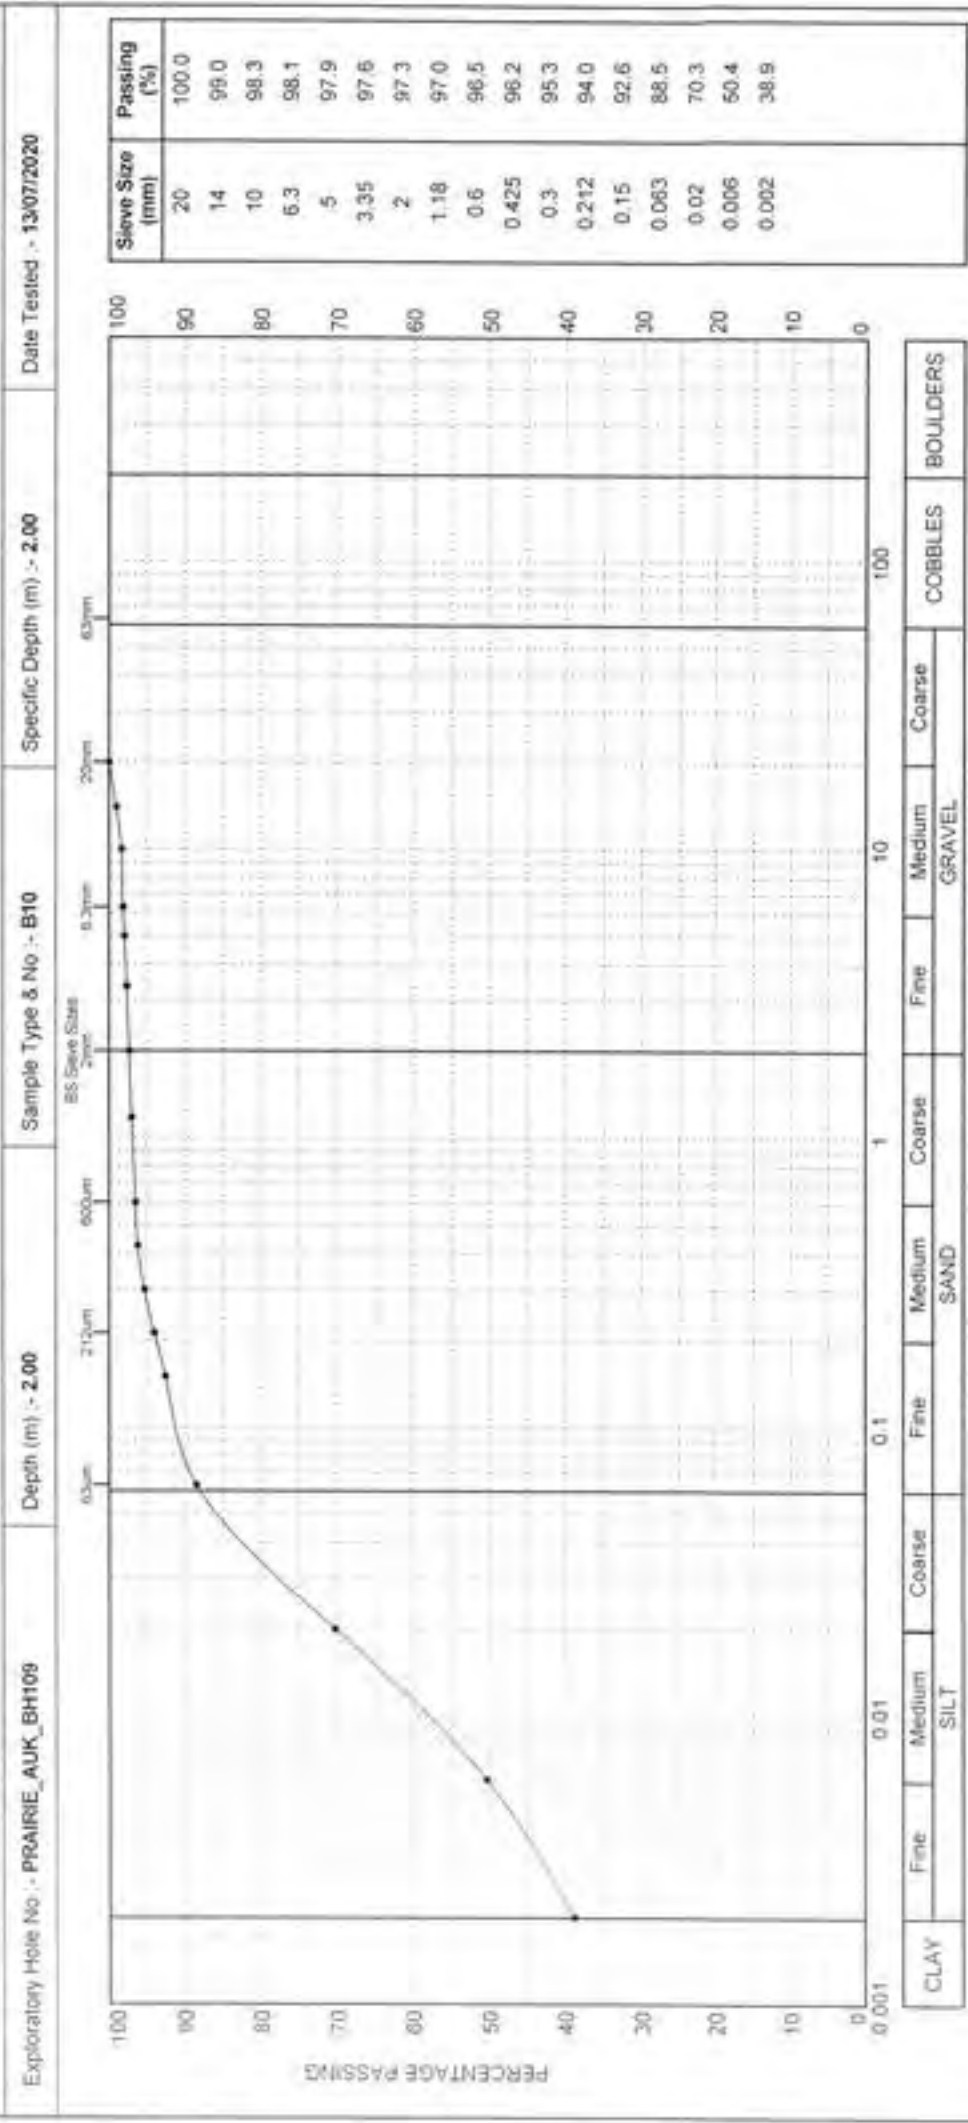

For description of sample please refer to the Laboratory Sample Description Sheet


	Date of issue :- 30/07/2020 Certificate No :- PSD/4251/PRAIRIE_AUK_BH109/B10/2.00	Name :- <i>MSone</i> Signed :- <i>MSone</i>	Page 1 of 1 AEG Contract No :- 4251
	Client :- South Tees Development Corporation	Contract Title :- Prairie Site Ground Investigation Works	

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 11, The Old Industrial Estate, Park Road, Chesham, Bucks, HP80 2SD, UK. Tel: 01494 363 420 Fax: 01494 363 470
Regional Office: Unit 21, Enterprise Development Centre, Epsom Road, Borehampton, BS11 3SE, UK. Tel: 01753 350 300 Fax: 01753 350 399

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

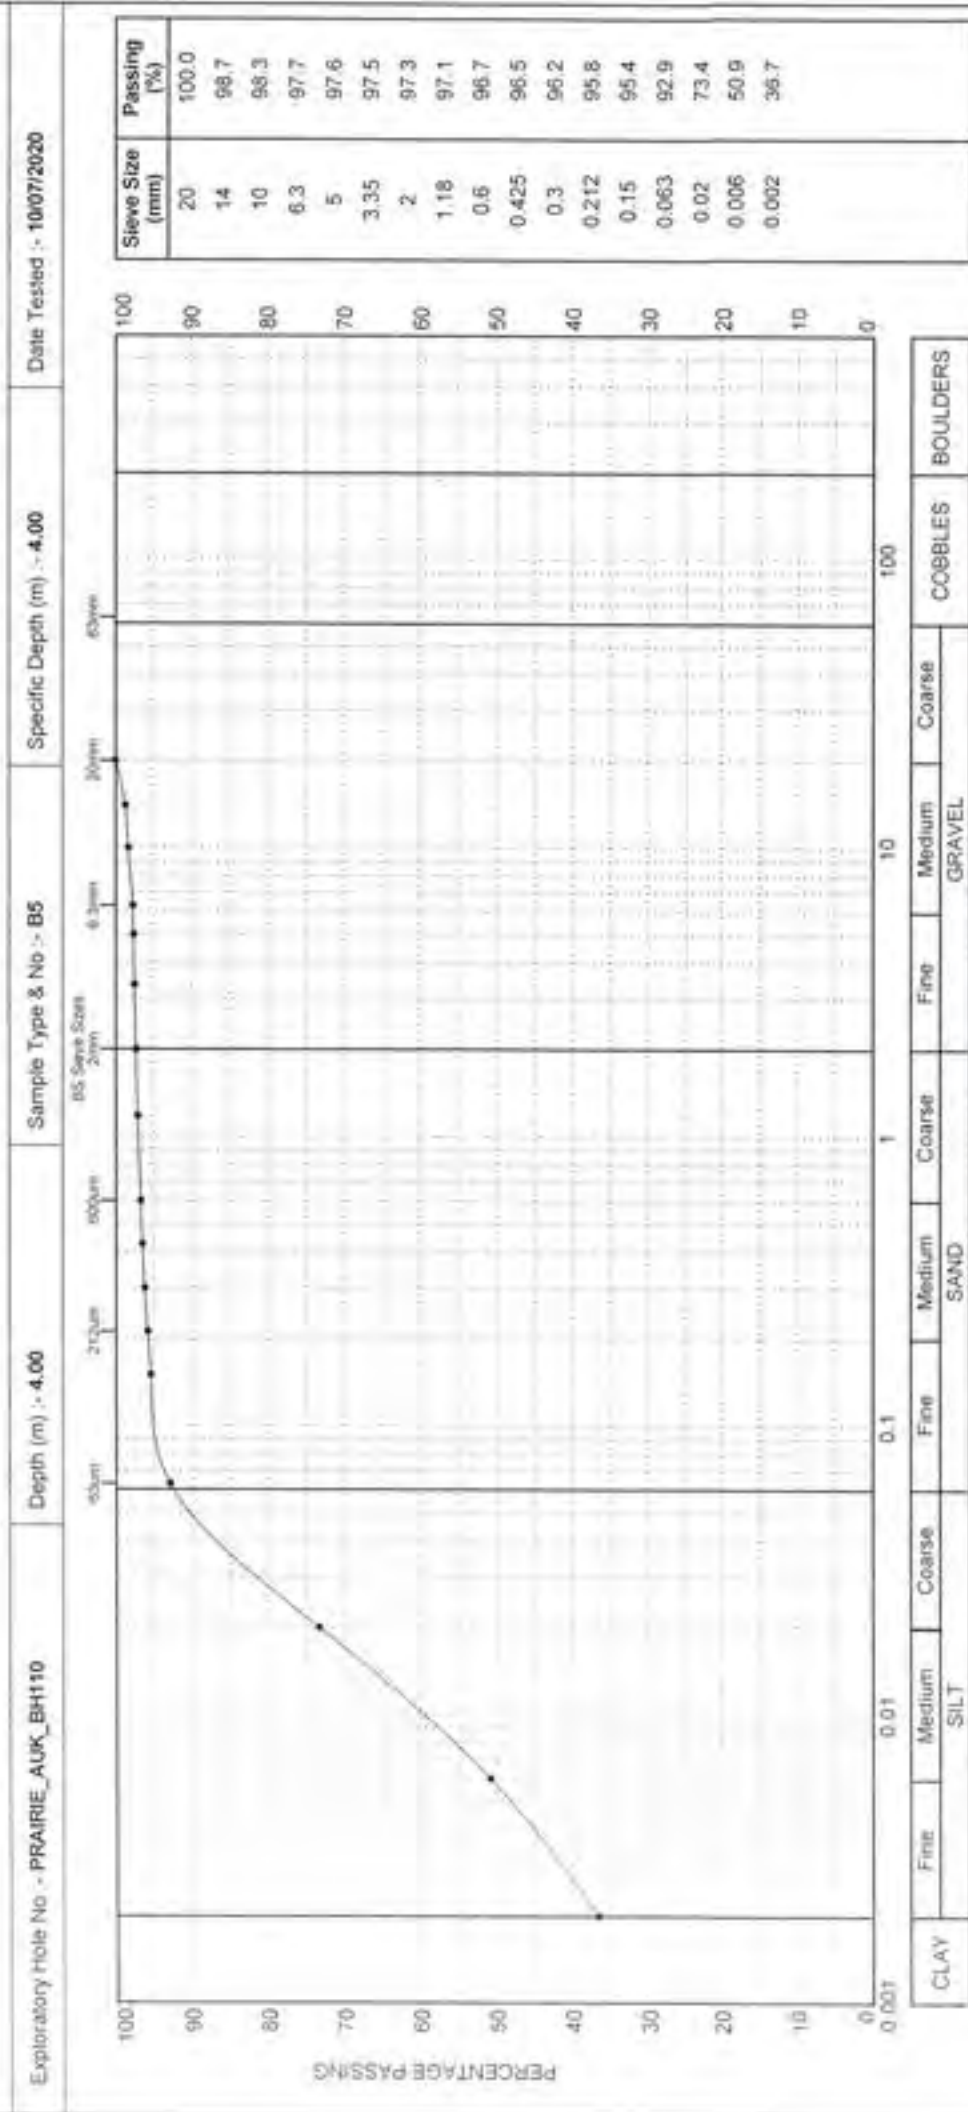

For description of sample please refer to the Laboratory Sample Description Sheet

AS	Date of issue :- 30/07/2020	Certificate No. :- PSD/4251/PRAIRIE_AUK_BH110/B5/4.00	Signed :- <i>msone</i>	Name :- M SELKIRK
Client :- South Tees Development Corporation	Contract Title :-	Praise Site Ground Investigation Works		
				Page 1 of 1
				AEG Contract No. :- 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Ebbw Vale Industrial Estate, Ebbw Vale, South Wales, NP23 5YU
 Regional Office: Unit 23, Blaenau Ffestiniog Industrial Estate, Blaenau Ffestiniog, Gwynedd, LL23 7JY
 Tel: 01497 821111 Fax: 01497 821112 Email: sales@allied-geotech.co.uk

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

(Test deviated from standard due to insufficient sample mass)


Exploratory Hole No - PRAIRIE_AUK_TP101

Depth (m) - 0.90


Sample Type & No - B4

Specific Depth (m) - 0.90

Date Tested - 08/10/2020

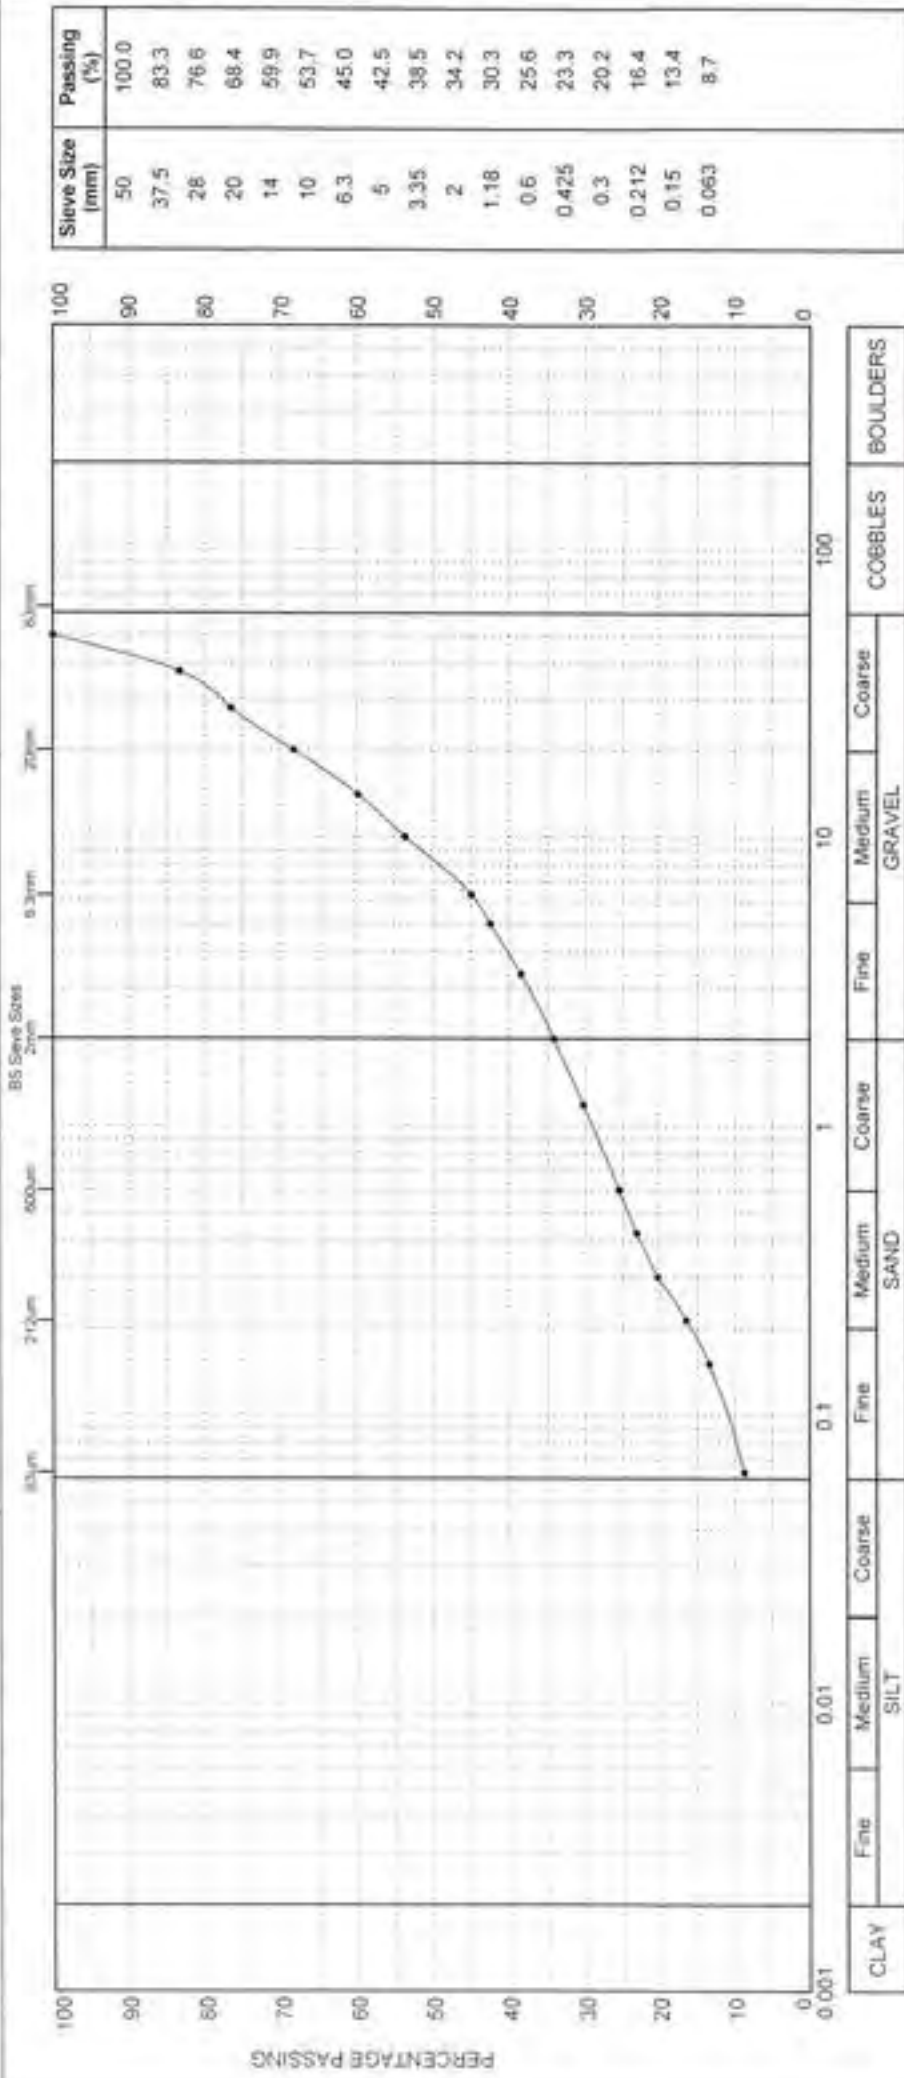

For description of sample please refer to the Laboratory Sample Description Sheet

	Date of issue - 20/10/2020	Certificate No - PSD/4251/PRAIRIE_AUK_TP101/B4/0.90	Name - M. SELKIRK	Page 1 of 1
	Client - South Tees Development Corporation	Signed - <i>msop</i>	Contract Title - Prairie Site Ground Investigation Works	AEG Contract No - 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 - Part 2 - Clause 9.2 & 9.4 1990


Project Name: PRAIRIE_AUK_TP102

Depth (m): 2.00

Sample Type: % - BS

Specific Depth (m): 2.00

Date Tested: 19/10/2020

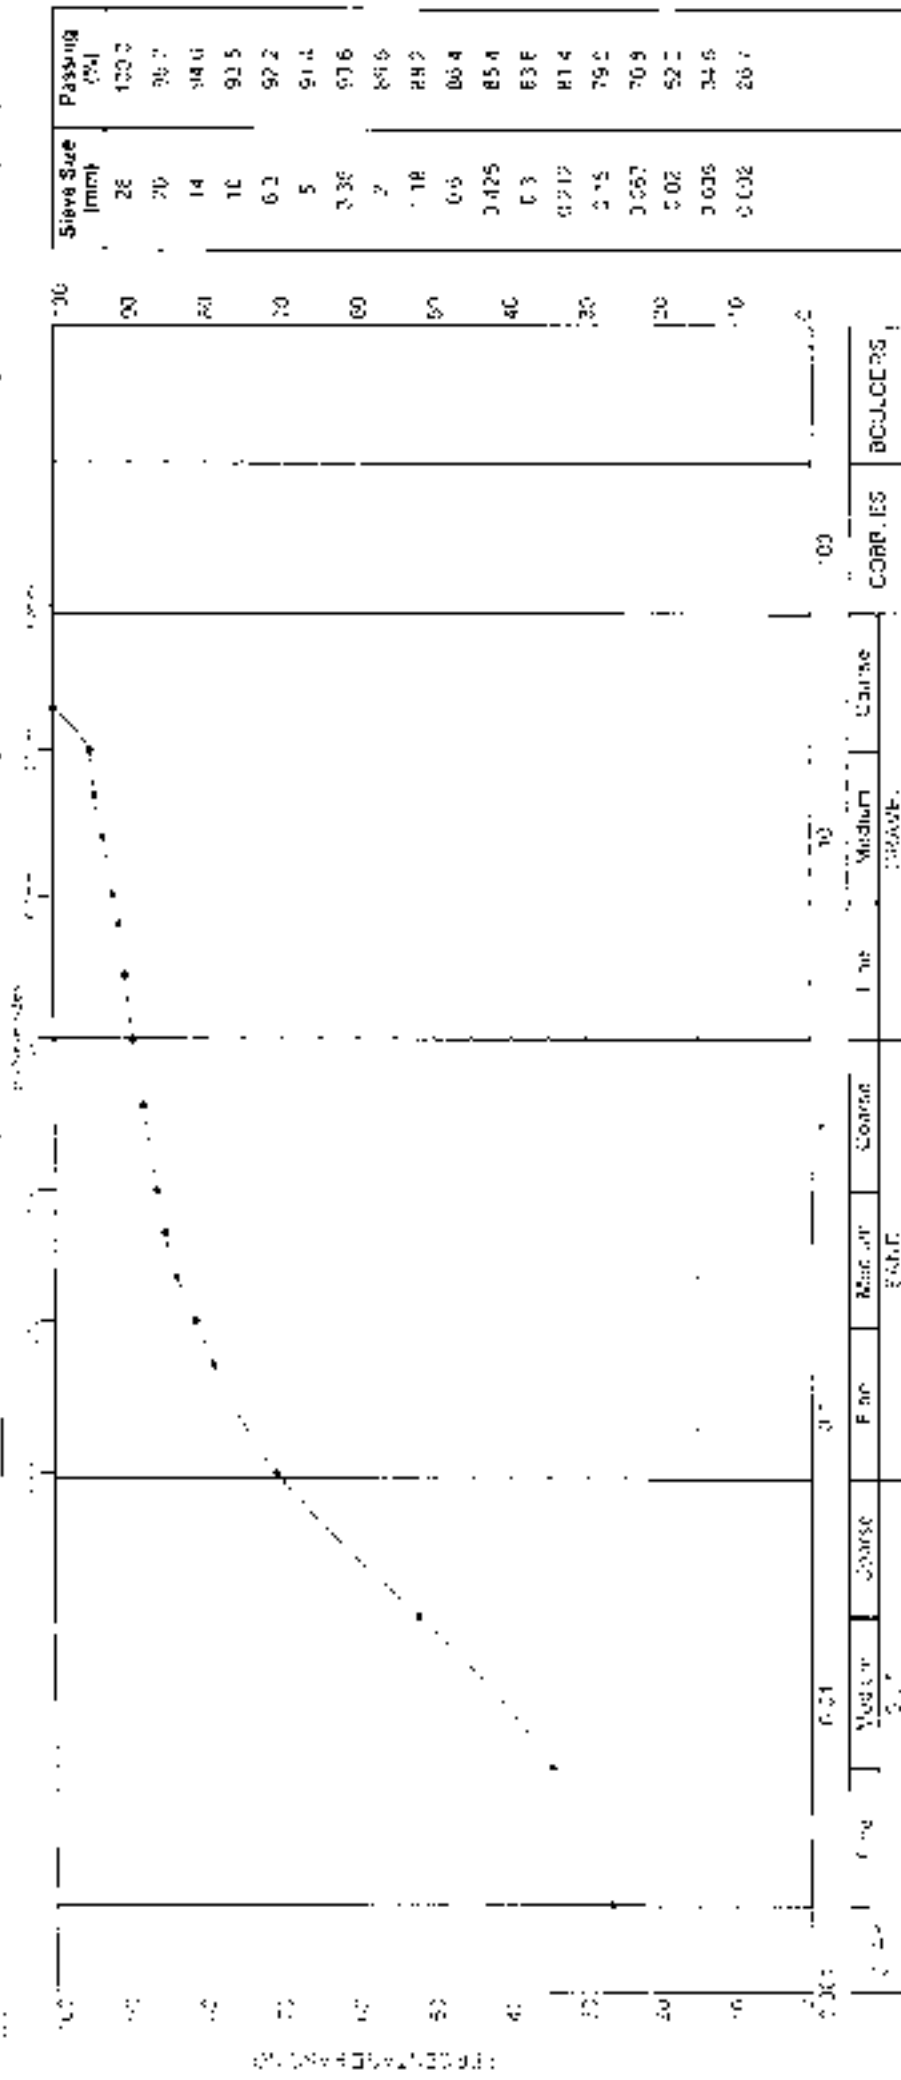

Page 1 of 1
REG Contract No: 4251

Name: *MSA*
Site: *MSA*

Contract No: *MSA*
Please See Client Investigation Works

Contract No: *MSA*
Please See Client Investigation Works

Contract No: *MSA*
Please See Client Investigation Works

Contract No: *MSA*
Please See Client Investigation Works

Contract No: *MSA*
Please See Client Investigation Works

Contract No: *MSA*
Please See Client Investigation Works

Contract No: *MSA*
Please See Client Investigation Works

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

651077 - Part 2 : Clause 9.2 & 9.4 - 1996


Exploration No: PRAIRIE_AUK_TPT05

Depth (m): 2.00

Sample Type & No: B5

Specimen Depth (m): 2.00


Date Tested: 30/05/2020

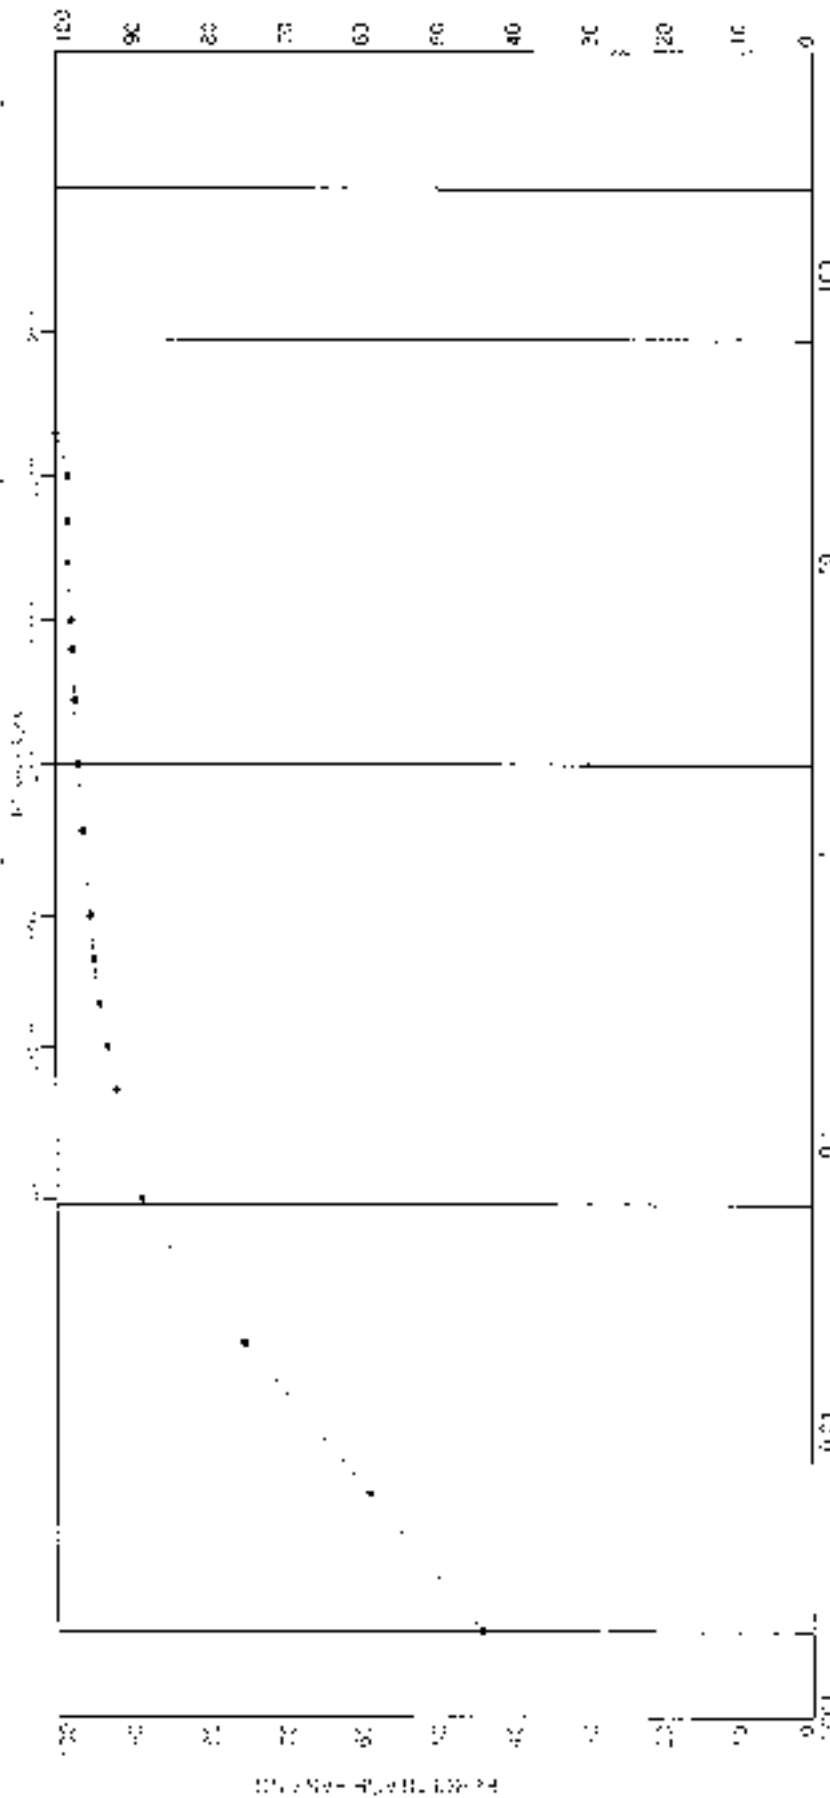

Sieve Size (mm)	Passing (%)
25	100.0
20	98.4
14	96.4
10	94.4
6.3	94.0
5	93.6
3.35	93.5
2	93.1
1.18	90.4
0.6	85.0
0.425	85.0
0.3	84.2
0.212	83.0
0.15	82.1
0.075	80.8
0.075	75.5
0.075	69.0
0.075	44.2

Coarse	0.075	0.15	0.3	0.6	1.18	2.0	4.75	7.5	15	30	60	100
Very Fine	0.075	0.15	0.3	0.6	1.18	2.0	4.75	7.5	15	30	60	100
Fine	0.075	0.15	0.3	0.6	1.18	2.0	4.75	7.5	15	30	60	100
Medium	0.075	0.15	0.3	0.6	1.18	2.0	4.75	7.5	15	30	60	100
Coarse	0.075	0.15	0.3	0.6	1.18	2.0	4.75	7.5	15	30	60	100
Very Coarse	0.075	0.15	0.3	0.6	1.18	2.0	4.75	7.5	15	30	60	100
COBBLES	0.075	0.15	0.3	0.6	1.18	2.0	4.75	7.5	15	30	60	100
BOULDERS	0.075	0.15	0.3	0.6	1.18	2.0	4.75	7.5	15	30	60	100

The results of this test are provided as best as possible, based on the information provided.



Contract No: 42511
Contract Title: PRAIRIE_AUK_TPT05
Client Name: Earth Tech Environmental Corporation
Contract No.: AEG Contract No. 42511
Page 1 of 1



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 22, The Industrial Estate, Mill Hill, Chesham, Bucks, UK. Tel: 01494 603400 Fax: 01494 362474
 Regional Offices: Unit 25, Barnwood Development Park, Church Road, Gloucestershire, GL1 5SB. Tel: 01172 233339 Fax: 01172 756566

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

Exploratory Hole No :- PRAIRIE_AUK_TP107	Depth (m) :- 1.00	Sample Type & No :- B4	Specific Depth (m) :- 1.00	Date Tested :- 30/09/2020																																										
<table border="1" style="width: 100%; border-collapse: collapse;"> <thead> <tr> <th>Sieve Size (mm)</th> <th>Passing (%)</th> </tr> </thead> <tbody> <tr><td>50</td><td>100.0</td></tr> <tr><td>37.5</td><td>96.3</td></tr> <tr><td>28</td><td>94.8</td></tr> <tr><td>20</td><td>94.8</td></tr> <tr><td>14</td><td>93.9</td></tr> <tr><td>10</td><td>91.9</td></tr> <tr><td>6.3</td><td>89.2</td></tr> <tr><td>5</td><td>87.8</td></tr> <tr><td>3.35</td><td>86.1</td></tr> <tr><td>2</td><td>84.4</td></tr> <tr><td>1.18</td><td>82.9</td></tr> <tr><td>0.6</td><td>81.2</td></tr> <tr><td>0.425</td><td>80.3</td></tr> <tr><td>0.3</td><td>78.9</td></tr> <tr><td>0.212</td><td>77.1</td></tr> <tr><td>0.15</td><td>75.0</td></tr> <tr><td>0.063</td><td>62.5</td></tr> <tr><td>0.02</td><td>51.6</td></tr> <tr><td>0.006</td><td>38.6</td></tr> <tr><td>0.002</td><td>28.3</td></tr> </tbody> </table>					Sieve Size (mm)	Passing (%)	50	100.0	37.5	96.3	28	94.8	20	94.8	14	93.9	10	91.9	6.3	89.2	5	87.8	3.35	86.1	2	84.4	1.18	82.9	0.6	81.2	0.425	80.3	0.3	78.9	0.212	77.1	0.15	75.0	0.063	62.5	0.02	51.6	0.006	38.6	0.002	28.3
Sieve Size (mm)	Passing (%)																																													
50	100.0																																													
37.5	96.3																																													
28	94.8																																													
20	94.8																																													
14	93.9																																													
10	91.9																																													
6.3	89.2																																													
5	87.8																																													
3.35	86.1																																													
2	84.4																																													
1.18	82.9																																													
0.6	81.2																																													
0.425	80.3																																													
0.3	78.9																																													
0.212	77.1																																													
0.15	75.0																																													
0.063	62.5																																													
0.02	51.6																																													
0.006	38.6																																													
0.002	28.3																																													
For description of sample please refer to the Laboratory Sample Description Sheet																																														
Date of issue :- 20/10/2020	Certificate No :- PSD/4251/PRAIRIE_AUK_TP107/B4/1.00	Signed :- <i>MSR</i>	Name :- <i>SELKING</i>	Page 1 of 1																																										
Client :- South Tees Development Corporation	Contract Title :-		AEG Contract No :- 4251																																											

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

RS1377 : Part 2 : Clause 9.2 & 9.4 : 1990
(Test dividing from standard due to insufficient sample mass)


Test Identity File No: **FRAIR E_AUK_TP103**

Exp. No.: **0.90**

Sample Type & No.: **B4**

Specific Depth (m): **0.90**

Date Tested: **30/09/2020**

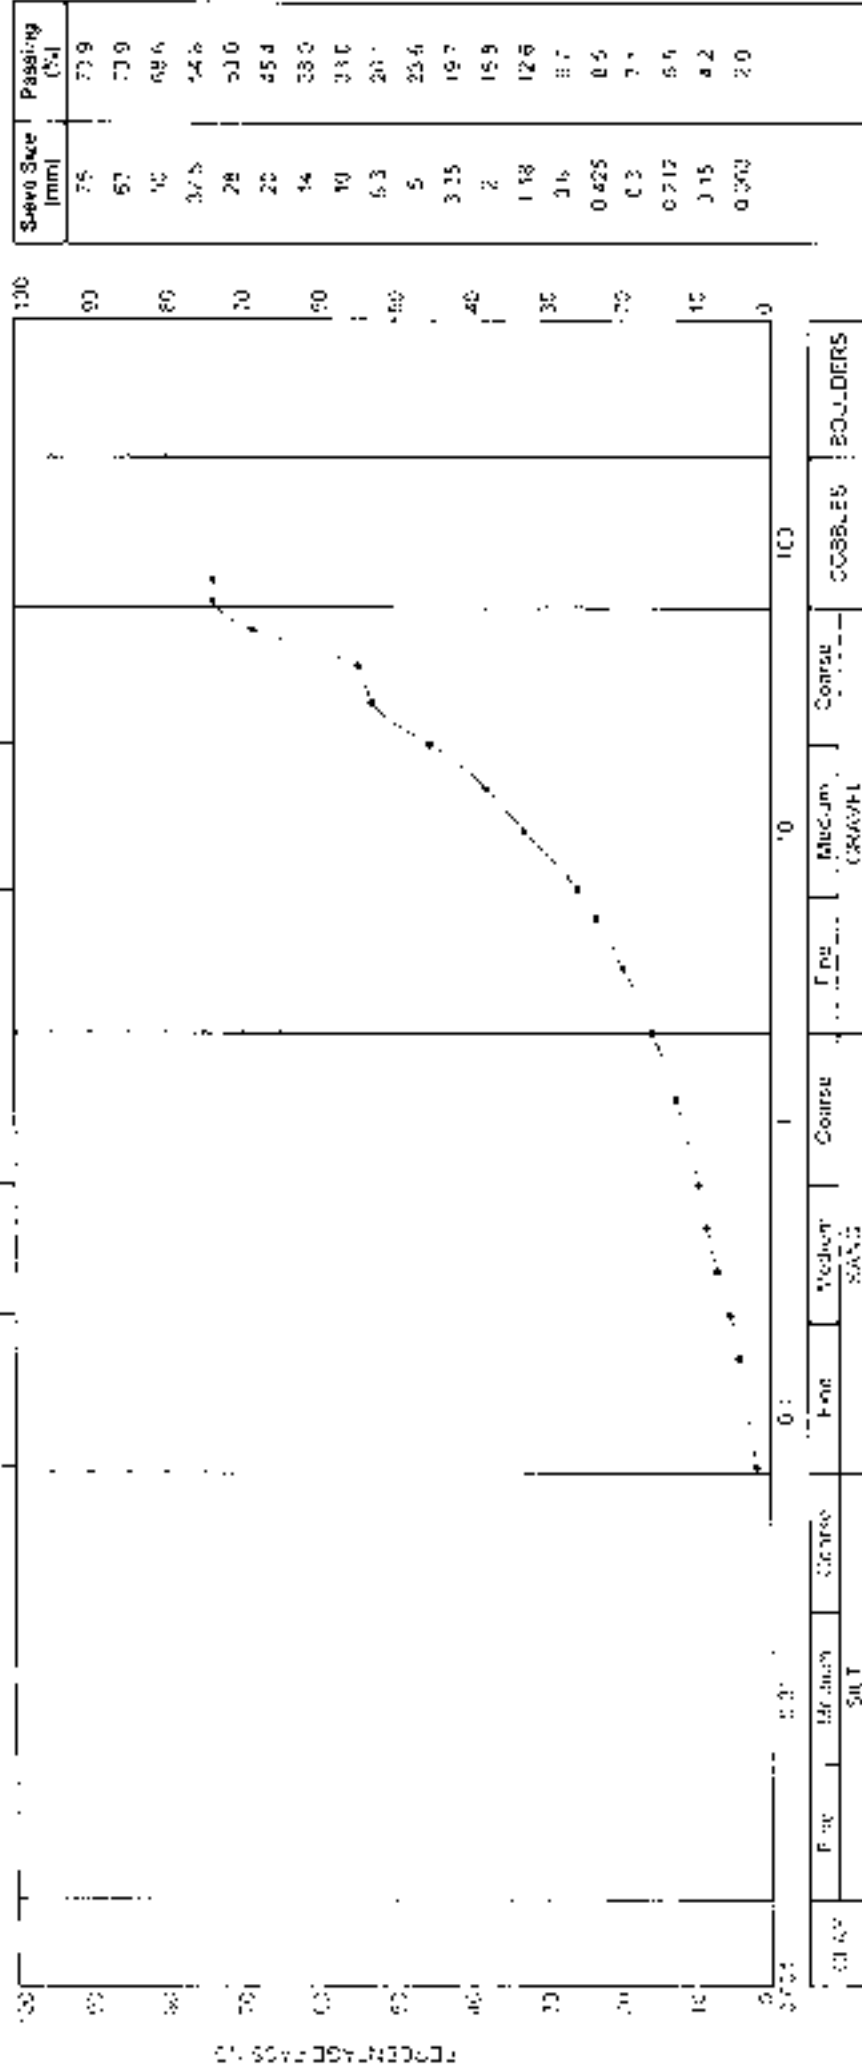

Page 1 of 1
AS Contract No: 4251

Project Name: **FRANKLIN ROAD**

Contract Title: **FRANKLIN ROAD**

Client: **FRANKLIN ROAD**

Site: **FRANKLIN ROAD**

Date of Issue: **30/09/2020**

Certificate No: **9504251**



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clauses 9.2 & 9.4 : 1990

(Test deviated from standard due to insufficient sample mass)


Exploratory Test No: PRAIRIE_AUK_TP108

Depth (m): 1.90

Sample Type & No: BT


Specific Depth (m): 1.90

Curve Tested: 8009/2020

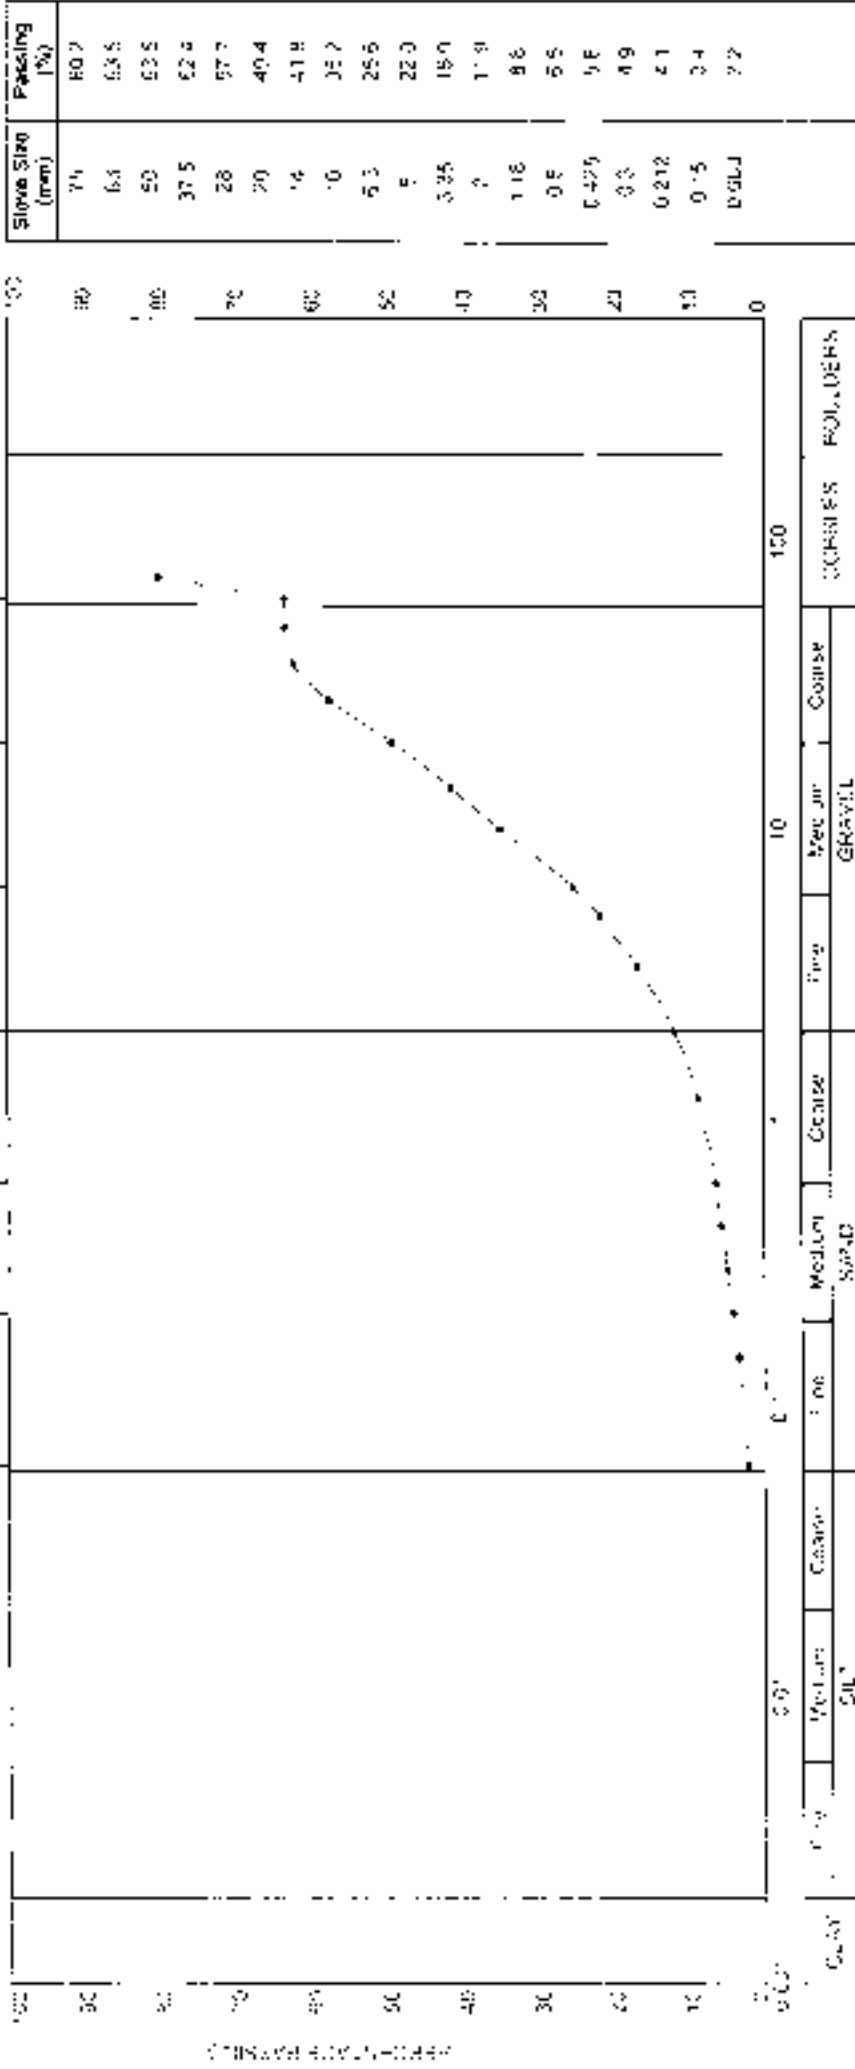


Coarse	Fine	Coarse	Fine	Medium	Coarse	Fine	Medium	Coarse	Fine	Coarse	Coarse	FULL DEFS
				SAND								GRAVEL

For a complete report please refer to the full report or your test order sheet



Soil Test Development Company



1967

Date of Issue: 20/12/2020

Prepared by: PSE-425 - PRAIRIE_AUK_TP108 8009 2020

Checked by: [Signature]

Depth (m): 1.90

Sample Type & No: BT

Specific Depth (m): 1.90

Curve Tested: 8009/2020

Page 1 of 1

ALC Contract No: 4251

Home Site Ground Investigation Works

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS 1377 - Part 2: Clause 9.2 & 9.4: 1990

(Test deviated from standard due to insufficient sample mass)


Project No: 140 PRAIRIE AUK_TP110

Design: 1.00


Sample Type: B to - B2

Seeds Depth: 1.00

Date Tested: 16/01/2020

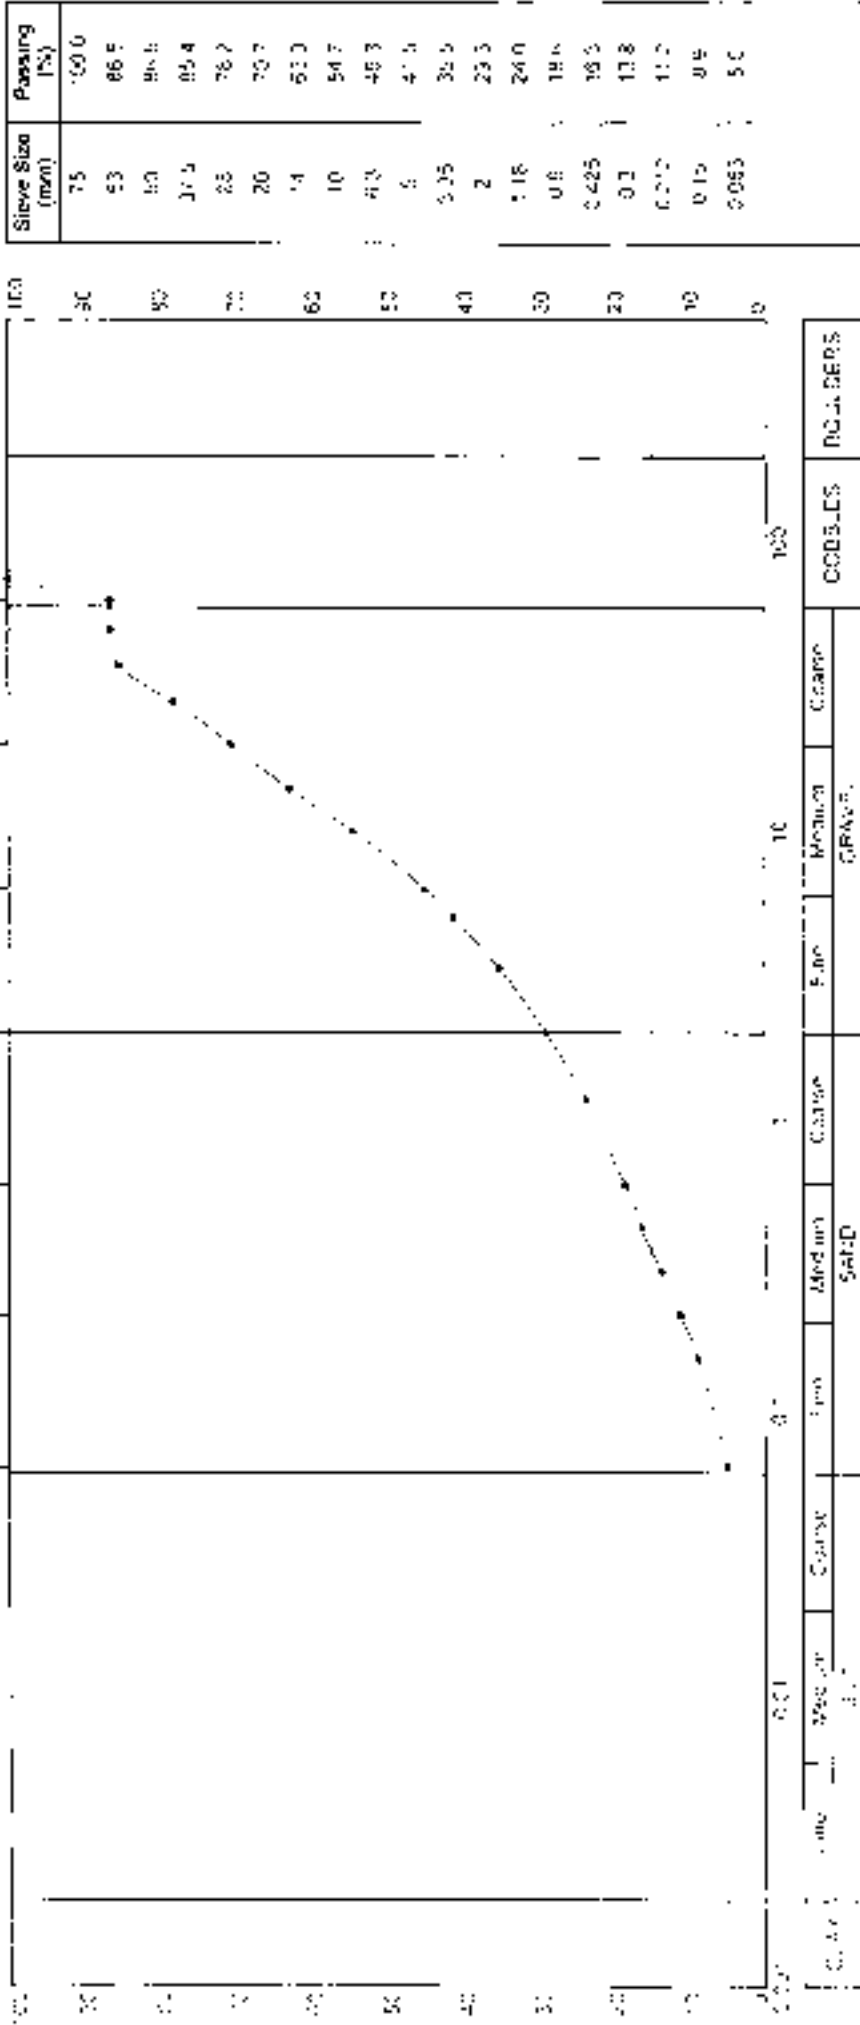

Coarse	Medium	Fine	Very Fine	Clay	Plastic
0.0	0.0	0.0	0.0	0.0	0.0



Tested by: [Signature]
Checked by: [Signature]
Date: 16/01/2020

Project: PRAIRIE AUK_TP110
Sample: B to - B2
Seeds Depth: 1.00

Date Tested: 16/01/2020

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2.8.3.4 : 1990


Location: PROAIRIE_AUK_TP110

Depth: 3.00

Sample Type & No: D8

Specific Depth: 3.00

Date Tested: 16/10/2020

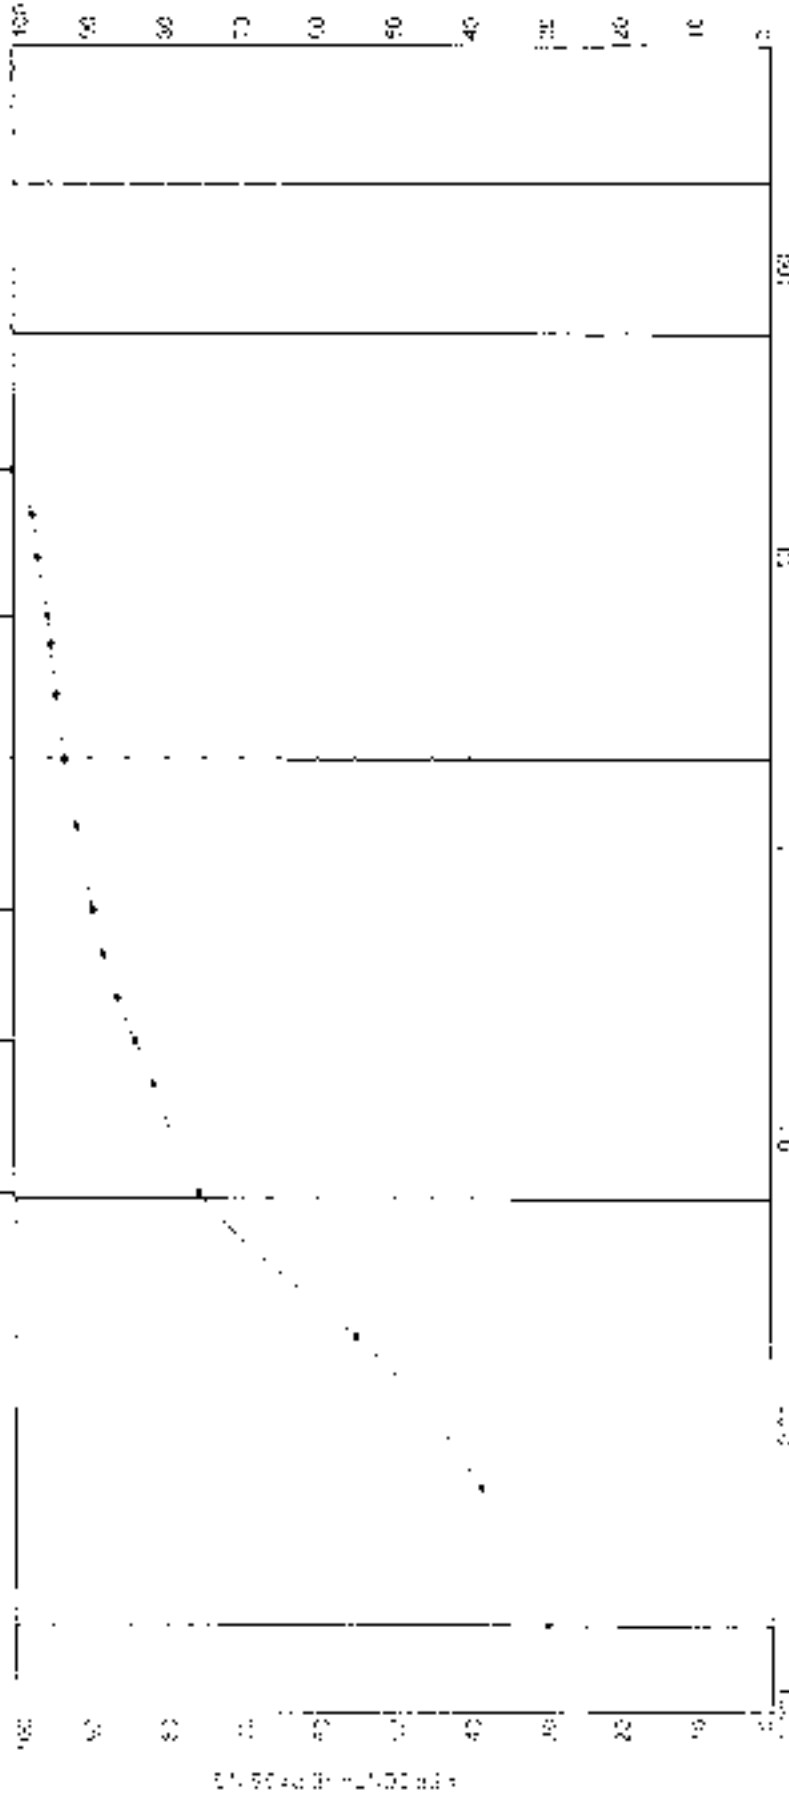

Course	Free	Medium	Coarse	COARSE	FINES
0.075	0.0	0.0	0.0	0.0	0.0
0.150	0.0	0.0	0.0	0.0	0.0
0.300	0.0	0.0	0.0	0.0	0.0
0.425	91.7	91.7	91.7	91.7	91.7
0.600	91.7	91.7	91.7	91.7	91.7
0.750	91.7	91.7	91.7	91.7	91.7
1.000	91.7	91.7	91.7	91.7	91.7
1.500	91.7	91.7	91.7	91.7	91.7
2.000	91.7	91.7	91.7	91.7	91.7
2.500	91.7	91.7	91.7	91.7	91.7
3.000	91.7	91.7	91.7	91.7	91.7
3.750	91.7	91.7	91.7	91.7	91.7
4.750	91.7	91.7	91.7	91.7	91.7
6.000	91.7	91.7	91.7	91.7	91.7
7.500	91.7	91.7	91.7	91.7	91.7
9.500	91.7	91.7	91.7	91.7	91.7
12.000	91.7	91.7	91.7	91.7	91.7
15.000	91.7	91.7	91.7	91.7	91.7
19.000	91.7	91.7	91.7	91.7	91.7
25.000	91.7	91.7	91.7	91.7	91.7
31.500	91.7	91.7	91.7	91.7	91.7
40.000	91.7	91.7	91.7	91.7	91.7
50.000	91.7	91.7	91.7	91.7	91.7
63.000	91.7	91.7	91.7	91.7	91.7
78.000	91.7	91.7	91.7	91.7	91.7
100.000	91.7	91.7	91.7	91.7	91.7

Method: 3000 (BS1377 Part 2)

Date of test: 16/10/2020
 Certificate No: NSD 4791 TR4 R - 2020 - 01111888 3.021
 Client: South West Water Corporation
 Contract No: 4251

Page 1 of 1
 SEG Contract No: 4251

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

RS1377 Part 2 Clause 9.2 & 9.4 : 1990

(Test deviated from standard due to insufficient sample mass)


Job Reference No: PRAIRIE_AUK_TP111

Depth (m): 1.60

Sample Type & No: BS

Specific Gravity: 1.00

Date Tested: 10/10/2020

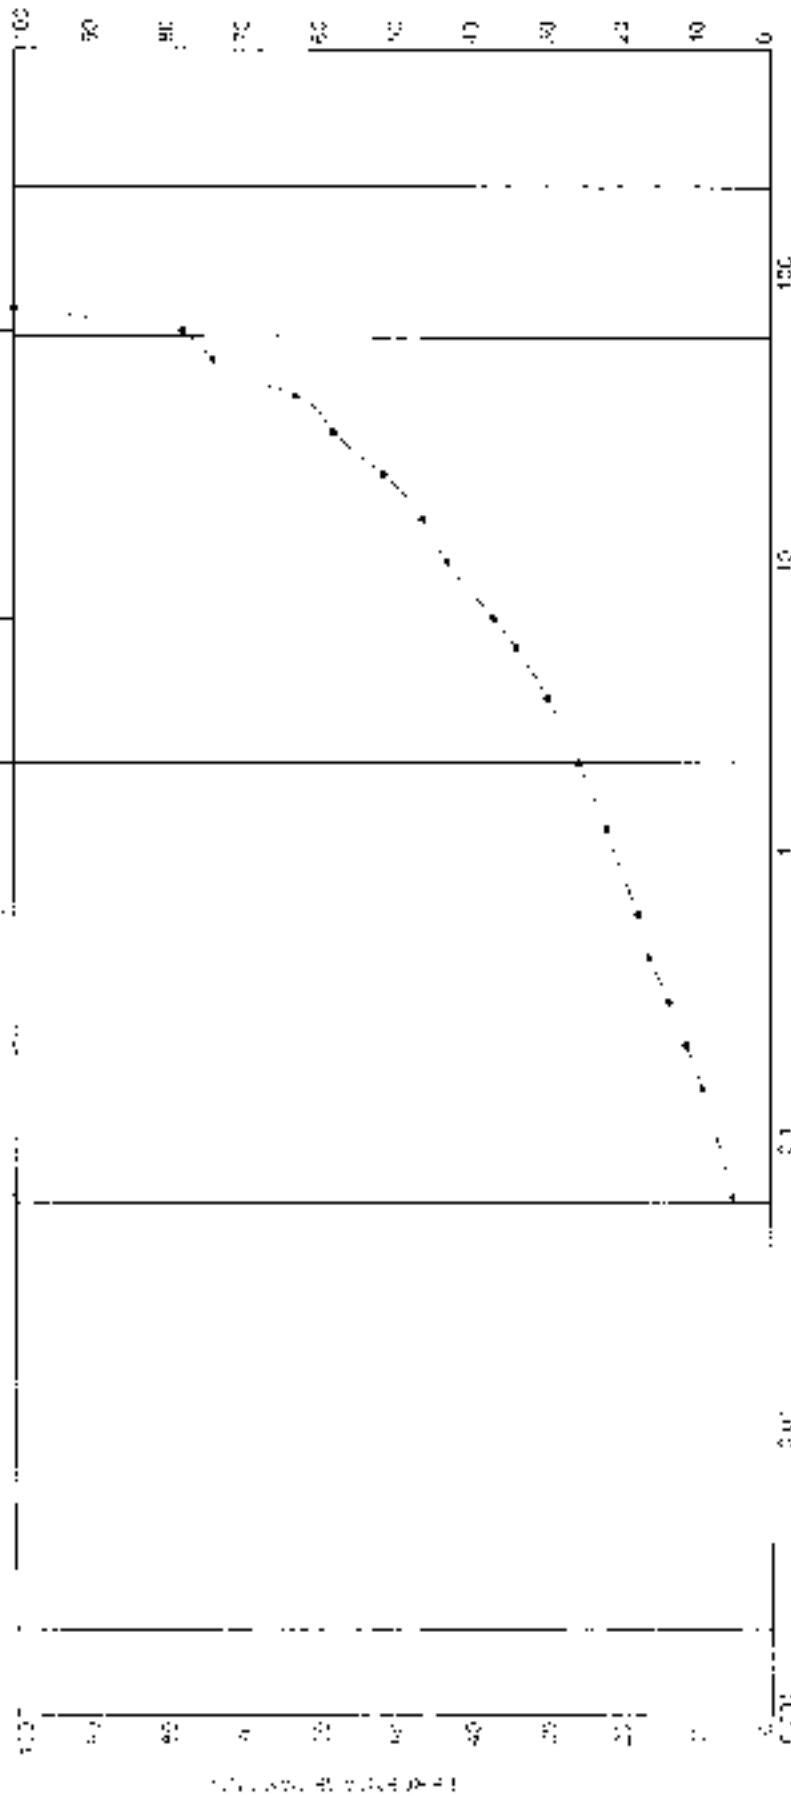

Class	Fine	Medium	Coarse	Very Fine	Very Coarse	Gravel	Boulders
SAND	0.075	0.425	2.0	4.75	9.5	47.5	95
GRAVEL	75	150	300	600	1200	2400	4800

The mass of soil retained on any sieve shall be determined by weighing the soil to the nearest 0.1g.

Date: 23/10/2020

Quantity: 100g

Client: PRAIRIE_AUK_TP111

Name: [Signature]

Page 1 of 1

Scale: Tests Conducted

Signed: [Signature]

Project: Prairie Site Ground Investigation - 2019

Page 1 of 1

Client:

Contract No:

Project: Prairie Site Ground Investigation - 2019

Page 1 of 1



1967

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377, Part 2, Clauses 9.2 & 9.4 : 1990
(Test deviated from standard due to insufficient sample mass)


Sample No: **PIRANIE AUK_TP112**

Depth: **1.70**

Sample Type: **So - BS**

Specific Gravity: **1.70**

Date Tested: **19/10/2020**

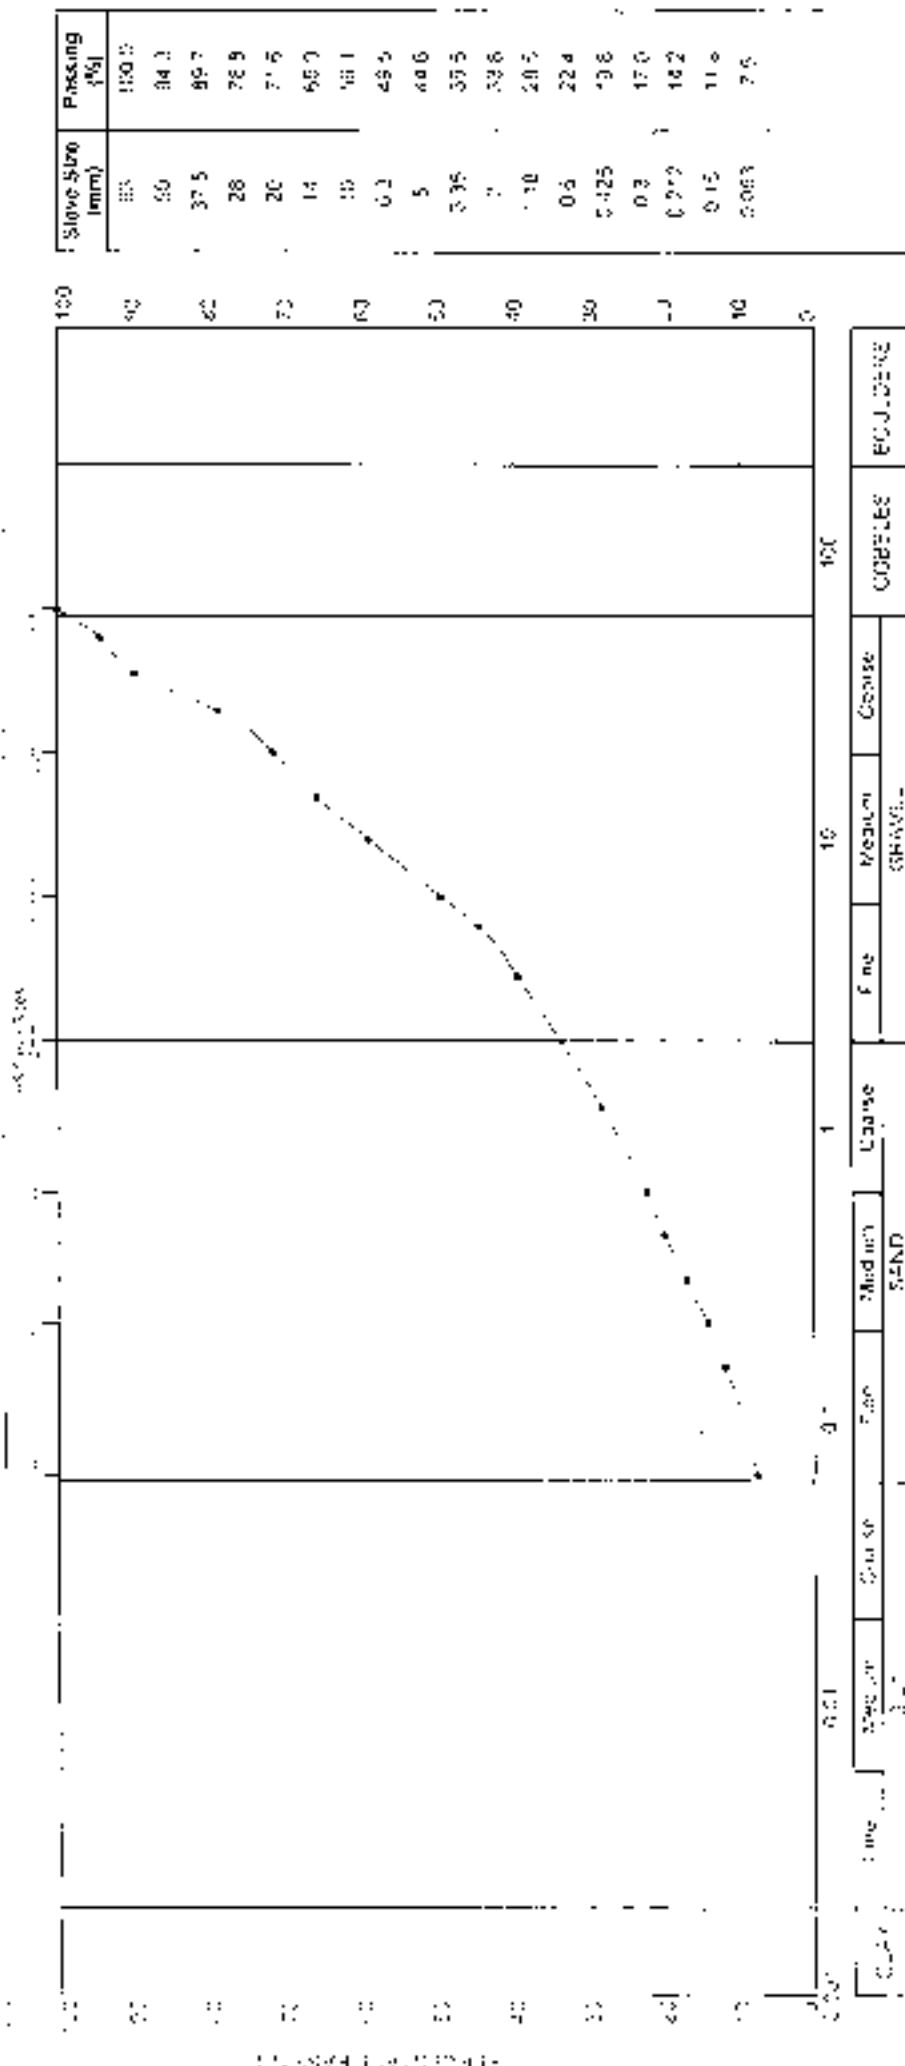

Coarse	Very Coarse	Coarse	Medium	Fine	Medium	Coarse	Coarse	Coarse	Coarse

By reference to the test procedure used, about 10% of the sample is lost.

Client: **PIRANIE AUK_TP112**
 Date: **19/10/2020**
 Report No: **AGG-2020-001**

Contract No: **AGG-2020-001**
 Project: **PIRANIE AUK_TP112**

Signature: **M. S. M. M. M.**
 Name: **M. S. M. M. M.**

Page 1 of 1
 AGG Contract No: **4251**



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377: Part 2 - Clause 9.2.8.3.4 © 1990


Client: **PRAIRIE_AUK_TP112**

Depth: **3.20**

Sample type & no: **B11**

Soil Depth: **3.20**

Date Tested: **16/10/2020**

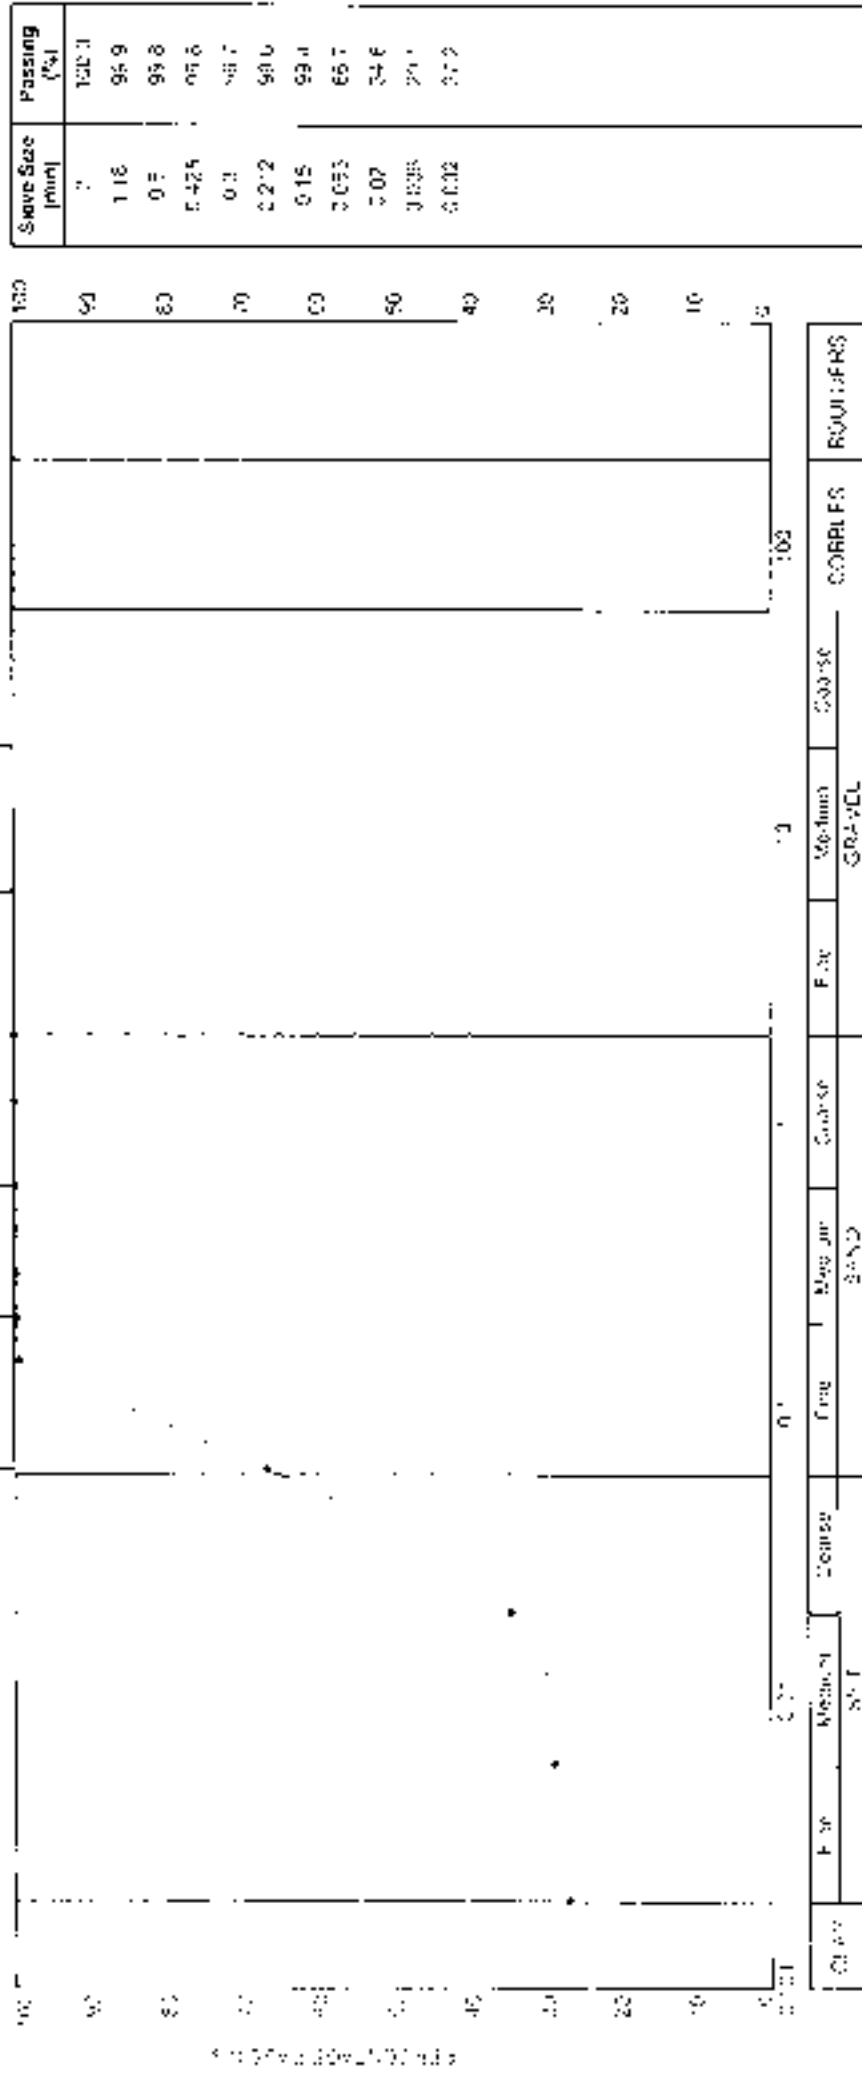

Course	Sub-course	Free	Mass per	Gravim	Free	Moisture	Gravim	Gravim	Gravim
0.075	0.15	0.3	0.6	1.18	2.5	5.0	10.0	20.0	40.0


Date of Issue: 20/10/2020

Calculators No: MS10428

Project No: PR10428

Soil Name: MS10428

Page 1 of 1



Soil Name: MS10428

Project No: PR10428

Soil Name: MS10428

Page 1 of 1



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

US1377 : Part 2 : Clause 9.2 & 9.4 : 1990
(Test deviated from standard due to insufficient sample mass)


File Path: \\c:\p\p\p\PEMARIE_AUK_TP113

Depth (m) : 1.80

Sample Type & No : B6

Specific Depth (m) : 1.80

Date Tested : 30/09/2020

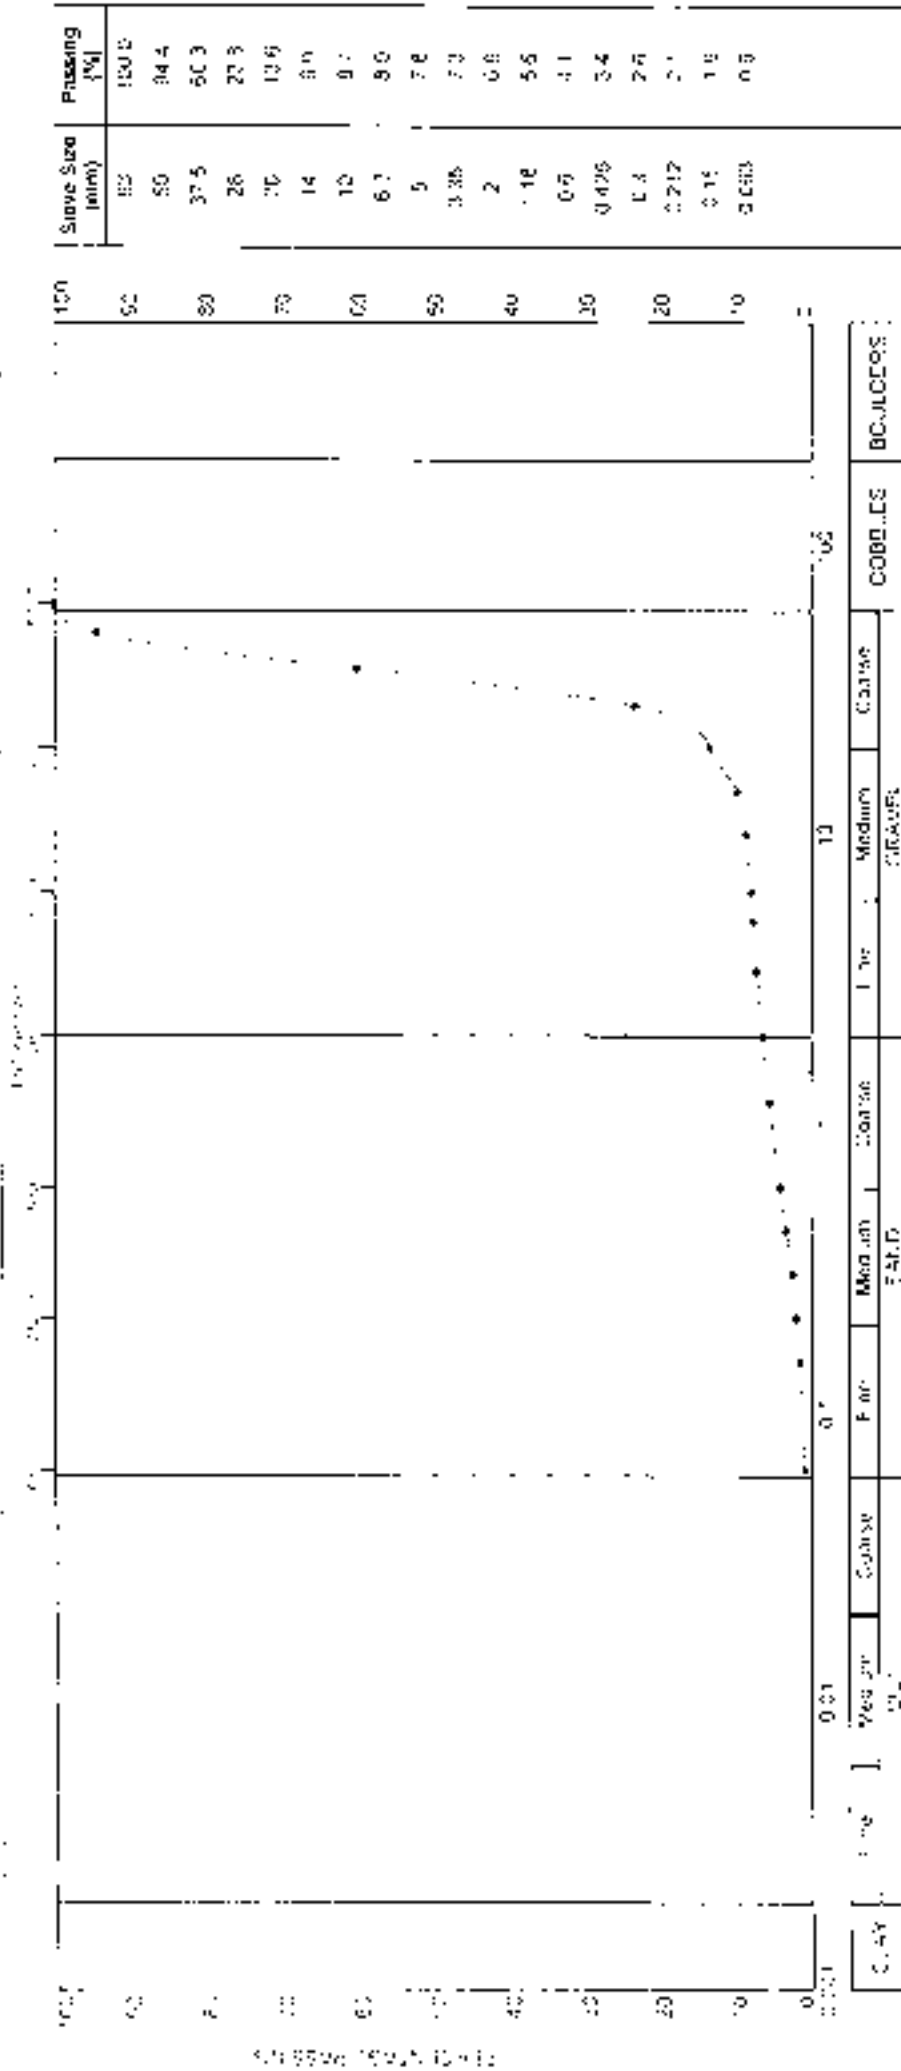

Class	Yes or No	Coarse	Medium	Coarse	Medium	Coarse	COBBLES	BCULICES

Location: Change Extension on Primary Camp - 1st floor 504

Date of Issue: 30/09/2020
 Client: PEG Contract No. 4251
 Site: The Site Ground Investigation Works



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

651377 - Part 2 : Clause 9.2 & 9.4 : 1990


Client: Prairie Auk TP113

Depth: 2.80

Sample Type: So - BB

Specific Depth (m): 2.80

Date Tested: 09/04/2020

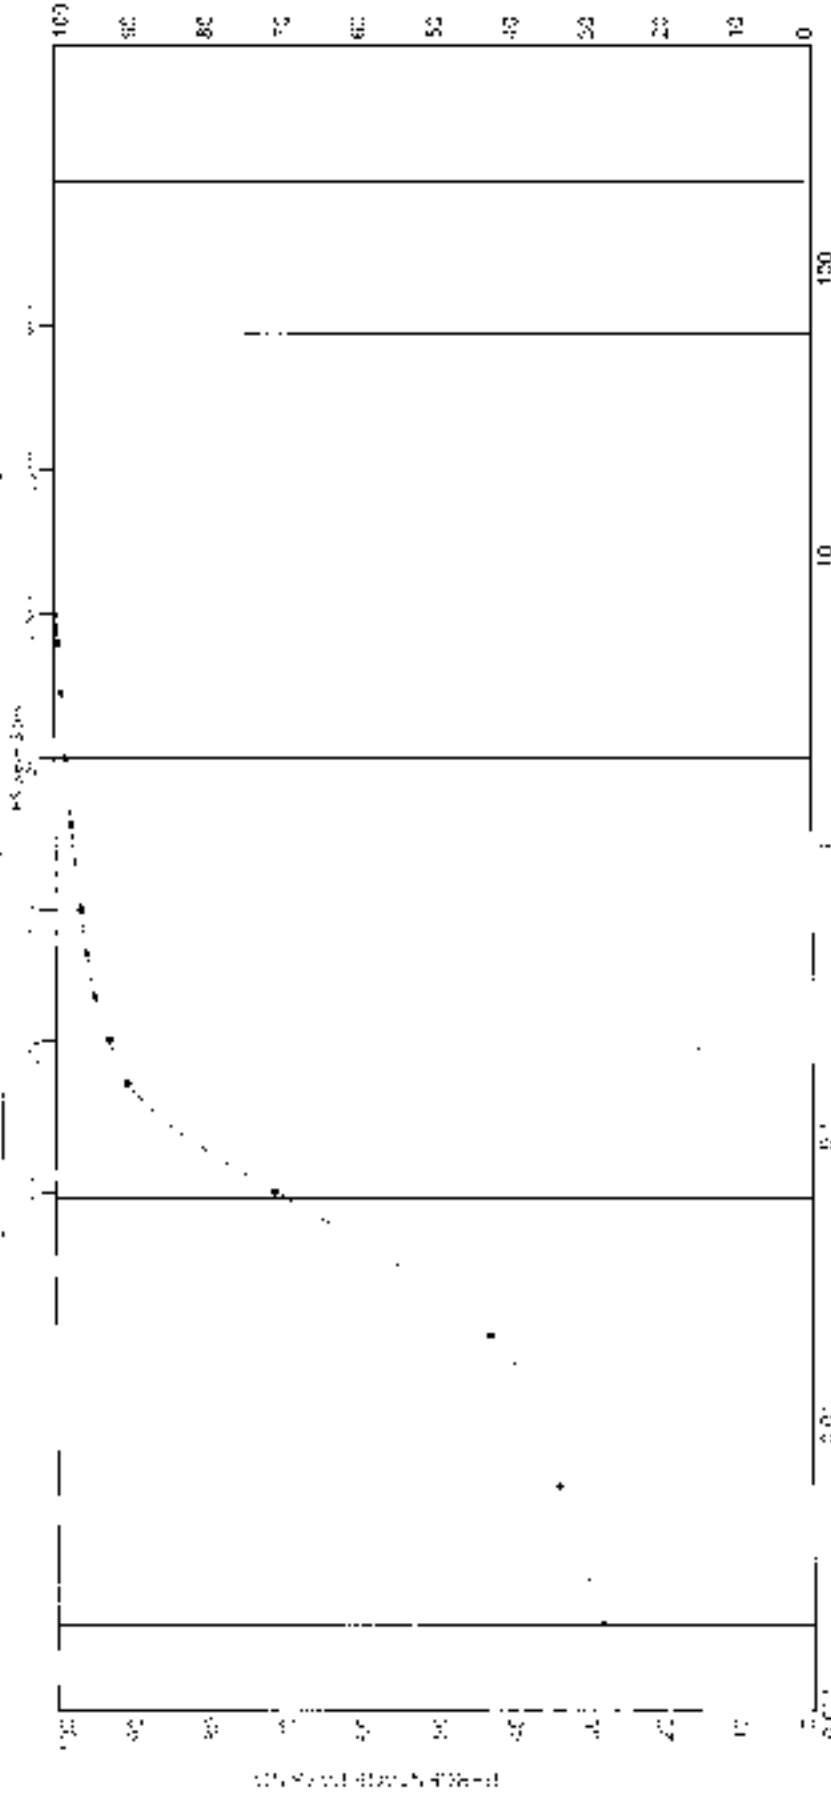

Sieve Size (mm)	Passing (%)
75	100.0
60	99.5
45	99.5
30	99.5
15	99.5
7.5	99.5
4.75	78.0
2.5	70.0
1.5	65.0
0.85	60.0
0.6	55.0
0.425	50.0
0.25	45.0
0.15	40.0
0.075	35.0

Clay	Fine	Med	Coarse	Gravel	Course	Coarse	Medium	Coarse	Gravel	Medium	Coarse	Gravel	Coarse	Gravel	Coarse	Gravel	Coarse	Gravel	

For details of test methods refer to the laboratory's current test methods sheet

Order of Issue: 0040 2020

Issue Date: 09/04/2020

Project: PRAIRIE_AUK_TP113 - 2.80 - So (m)

Name:

Mason

Client: South East Development Corporation

Project: Phase 3 - Ground Investigation Works

AEG Control No: 4251

Page: 1 of 1



1387


ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 2nd Flr, 25, South of Moor Road, Easingwold, Yorks YO21 2JG, UK. Tel: 01833 622200 Fax: 01833 362476
Regional Office: 107-10, Eborac Road, Easingwold, Yorks YO21 2JG, UK. Tel: 01753 730300 Fax: 01753 730300

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

(Test deviated from standard due to insufficient sample mass)

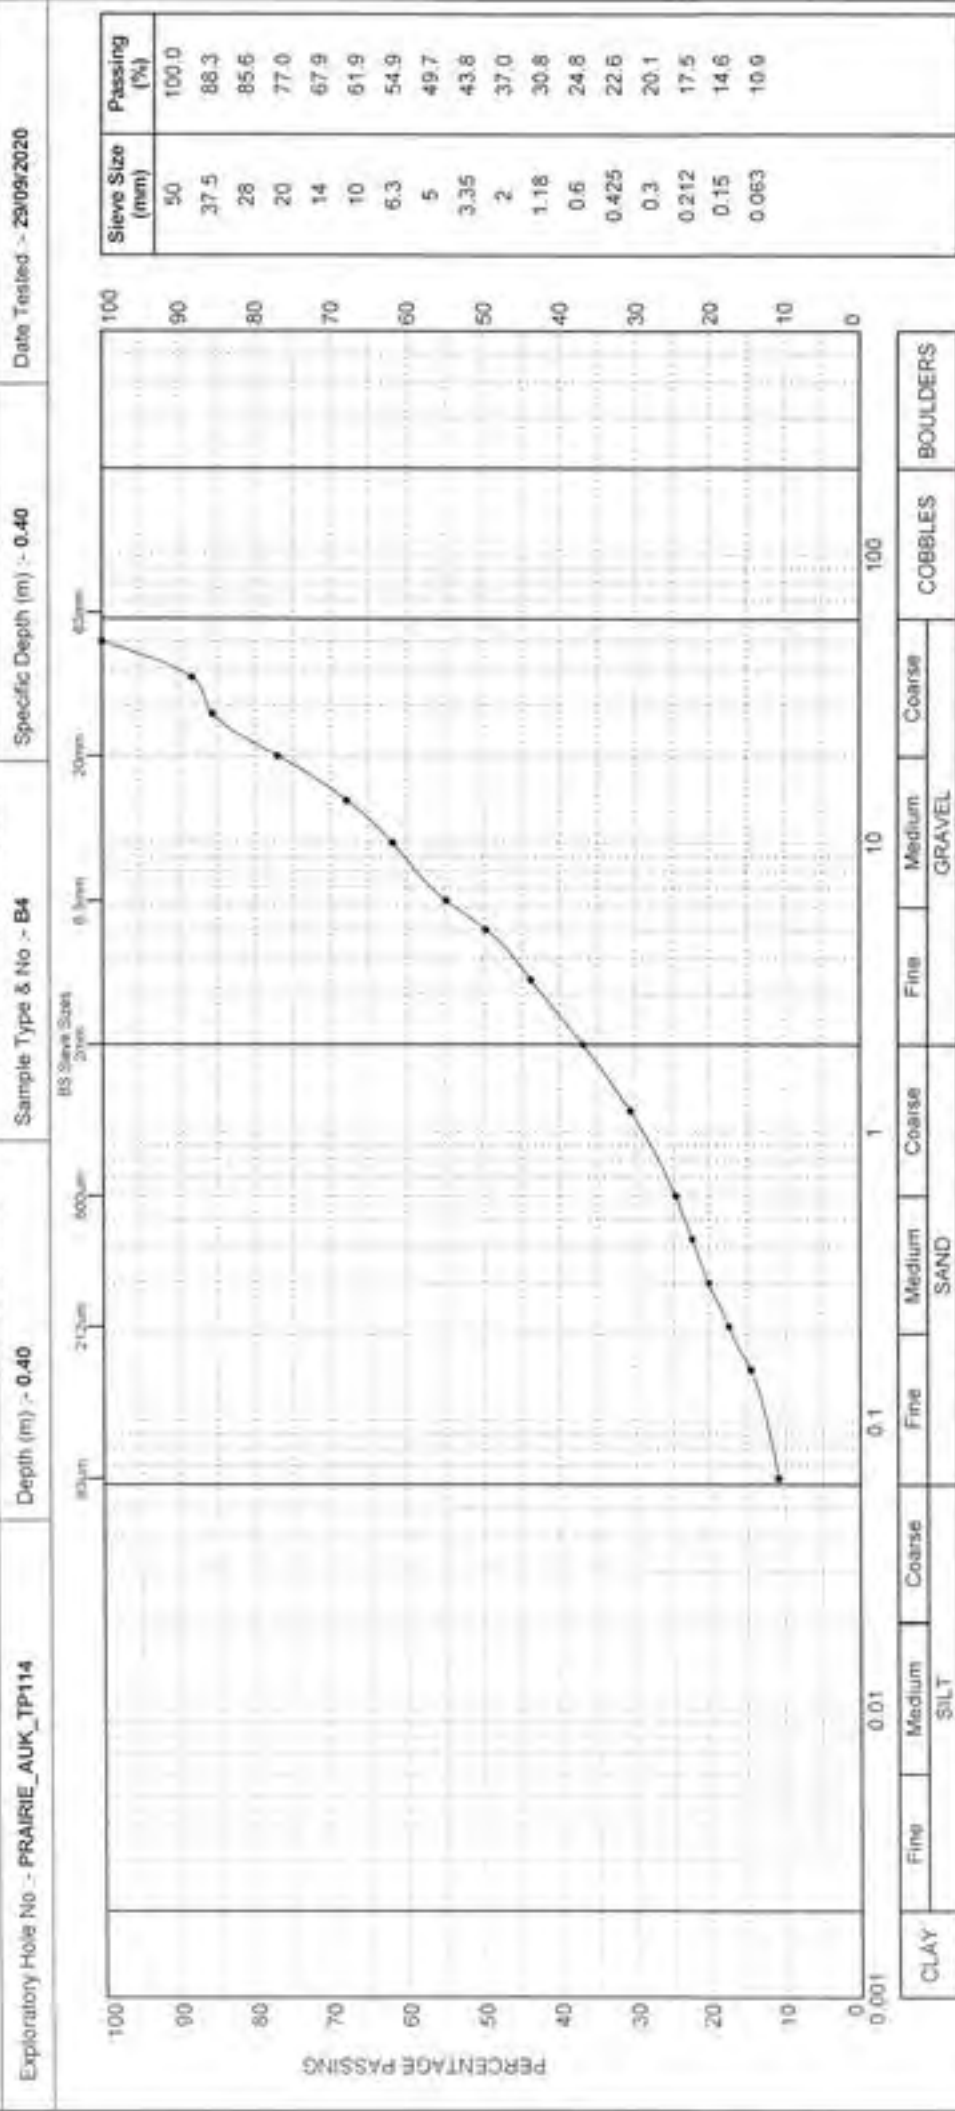

For description of sample please refer to the Laboratory Sample Description Sheet

Date of issue - 20/10/2020	Certificate No - PSD/4251/PRAIRIE_AUK_TP114/B4/0.40	Signed - <i>msone</i>	Name - SELKIRK
Client - South Tees Development Corporation	Contract Title - Prairie Site Ground Investigation Works		
Page 1 of 1		AEG Contract No - 4251	



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 110-111, Old Church Lane, South Park, Scarborough, North Yorkshire, YO15 1JG. Tel: 01303 827400 Fax: 01303 827470
Regional Offices: 1st Floor, 25, Rotherham Road, Rotherham, South Yorkshire, S60 1JG. Tel: 0114 272330 Fax: 0114 272339

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

Exploratory Hole No - PRAIRIE_AUK_TP115	Depth (m) - 1.70	Sample Type & No - B5	Specific Depth (m) - 1.70	Date Tested - 14/10/2020																																						
<table border="1" style="width:100%; border-collapse: collapse;"> <thead> <tr> <th>Sieve Size (mm)</th> <th>Passing (%)</th> </tr> </thead> <tbody> <tr><td>63</td><td>100.0</td></tr> <tr><td>50</td><td>94.3</td></tr> <tr><td>37.5</td><td>94.3</td></tr> <tr><td>28</td><td>93.0</td></tr> <tr><td>20</td><td>87.4</td></tr> <tr><td>14</td><td>78.1</td></tr> <tr><td>10</td><td>59.5</td></tr> <tr><td>6.3</td><td>43.9</td></tr> <tr><td>5</td><td>38.6</td></tr> <tr><td>3.35</td><td>31.9</td></tr> <tr><td>2</td><td>26.0</td></tr> <tr><td>1.18</td><td>21.2</td></tr> <tr><td>0.6</td><td>15.9</td></tr> <tr><td>0.425</td><td>13.8</td></tr> <tr><td>0.3</td><td>11.4</td></tr> <tr><td>0.212</td><td>9.3</td></tr> <tr><td>0.15</td><td>7.6</td></tr> <tr><td>0.075</td><td>4.7</td></tr> </tbody> </table>					Sieve Size (mm)	Passing (%)	63	100.0	50	94.3	37.5	94.3	28	93.0	20	87.4	14	78.1	10	59.5	6.3	43.9	5	38.6	3.35	31.9	2	26.0	1.18	21.2	0.6	15.9	0.425	13.8	0.3	11.4	0.212	9.3	0.15	7.6	0.075	4.7
Sieve Size (mm)	Passing (%)																																									
63	100.0																																									
50	94.3																																									
37.5	94.3																																									
28	93.0																																									
20	87.4																																									
14	78.1																																									
10	59.5																																									
6.3	43.9																																									
5	38.6																																									
3.35	31.9																																									
2	26.0																																									
1.18	21.2																																									
0.6	15.9																																									
0.425	13.8																																									
0.3	11.4																																									
0.212	9.3																																									
0.15	7.6																																									
0.075	4.7																																									
<p>For description of sample please refer to the Laboratory Sample Description Sheet</p>																																										
Date of issue -> 23/10/2020	Certificate No -> PSD/4251/PRAIRIE_AUK_TP115/B5/1.70	Signed -> <i>msore</i>	Name -> <i>msore</i>	Page 1 of 1																																						
Client -> South Tees Development Corporation		Contract Title -> Prairie Site Ground Investigation Works																																								
		AEG Contract No -> 4251																																								



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

OS1377 - Part 2 - Clause 9.2 & 9.4 : 1998
(Test deviated from standard due to insufficient sample mass)


Estimator: MORTON - PRA RIE, AUK, TP117

Density: 2.65

Sample Type: S_u - B9

Spec. for: Drayman - 3.20

Date Tested: 16/10/2020

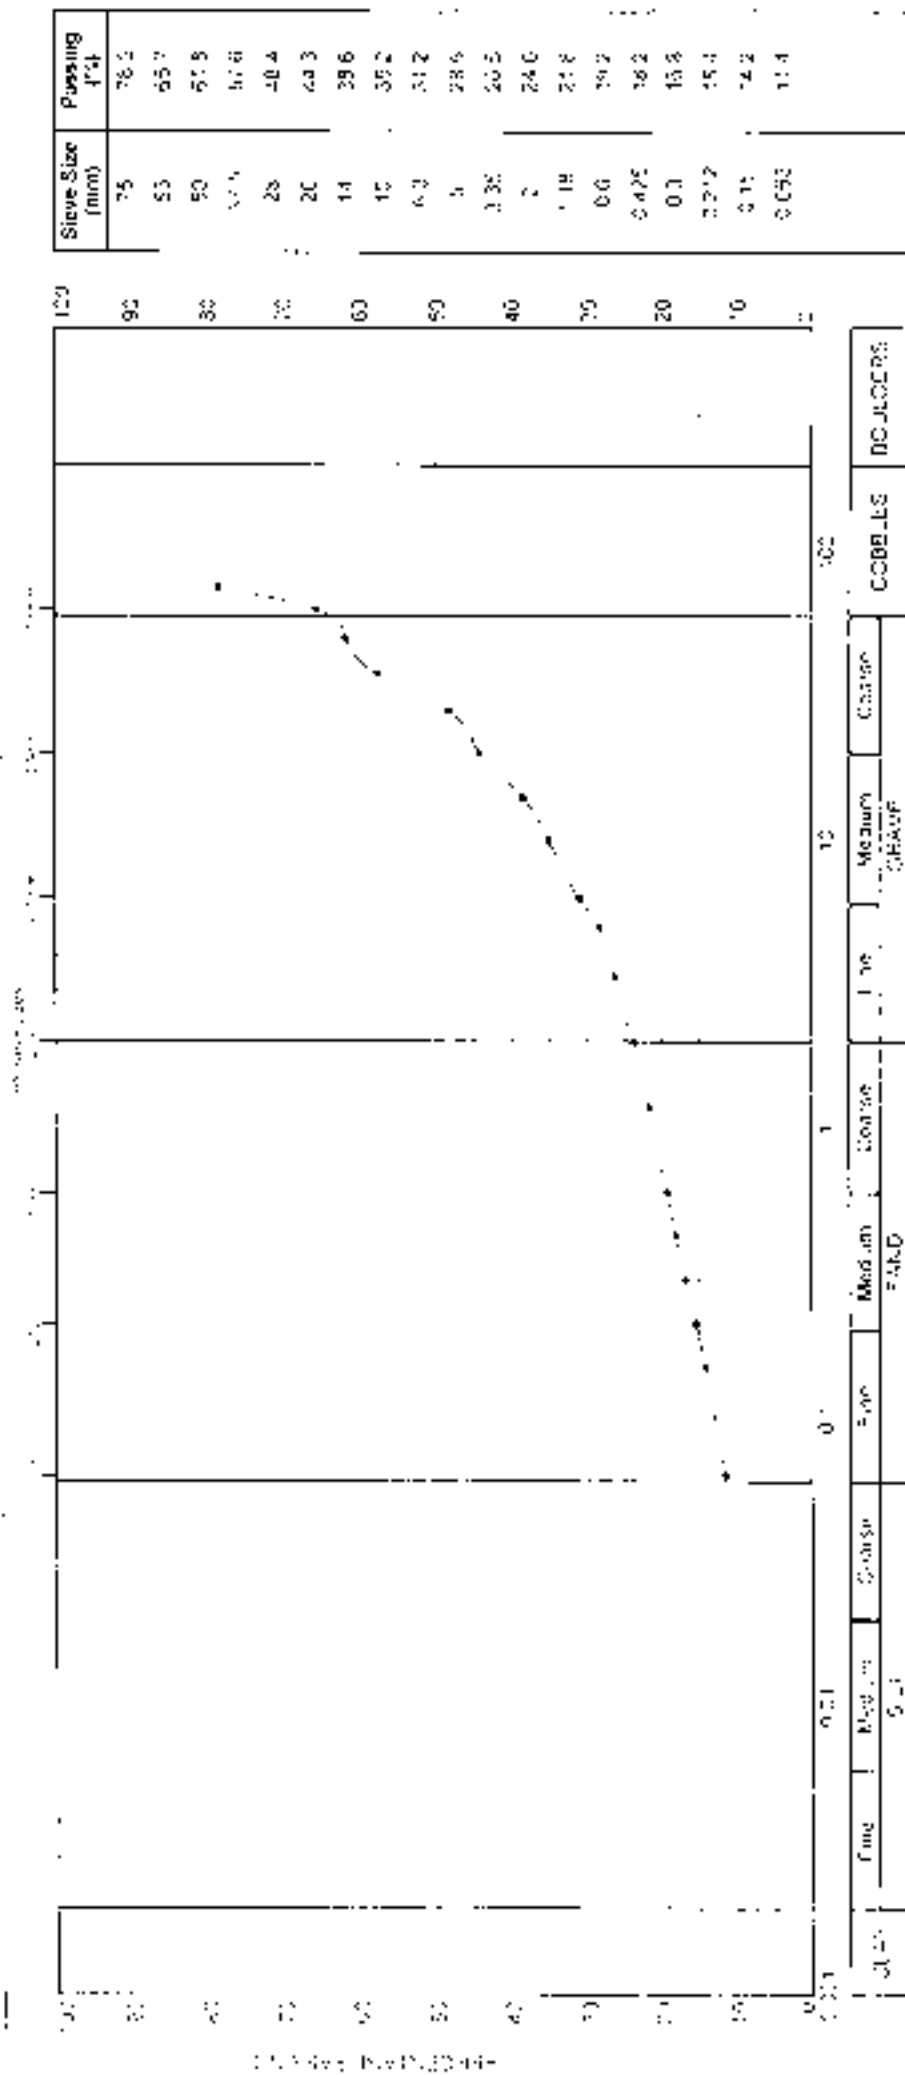


Client: PSC 225 - FORD RIVER, AUK, TP117 B9320 - 5.3m

Contract No: 4251

Project Name: Ford River Stream Control

Page 1 of 1

At C: Harrison Rd - 4251



Name: Morten

Contract No: 4251

Project Name: Ford River Stream Control

Page 1 of 1

At C: Harrison Rd - 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

GS1077 - Part 2 - Clause 9.2 & 9.4 - 1996

(Test deviated from standard due to insufficient sample mass)


Project No: PRAIRIE_AUX_TP118

Depth: 1.00

Sample Type & No: S2

Soils & Deposition: 100

Date Tested: 19/10/2020

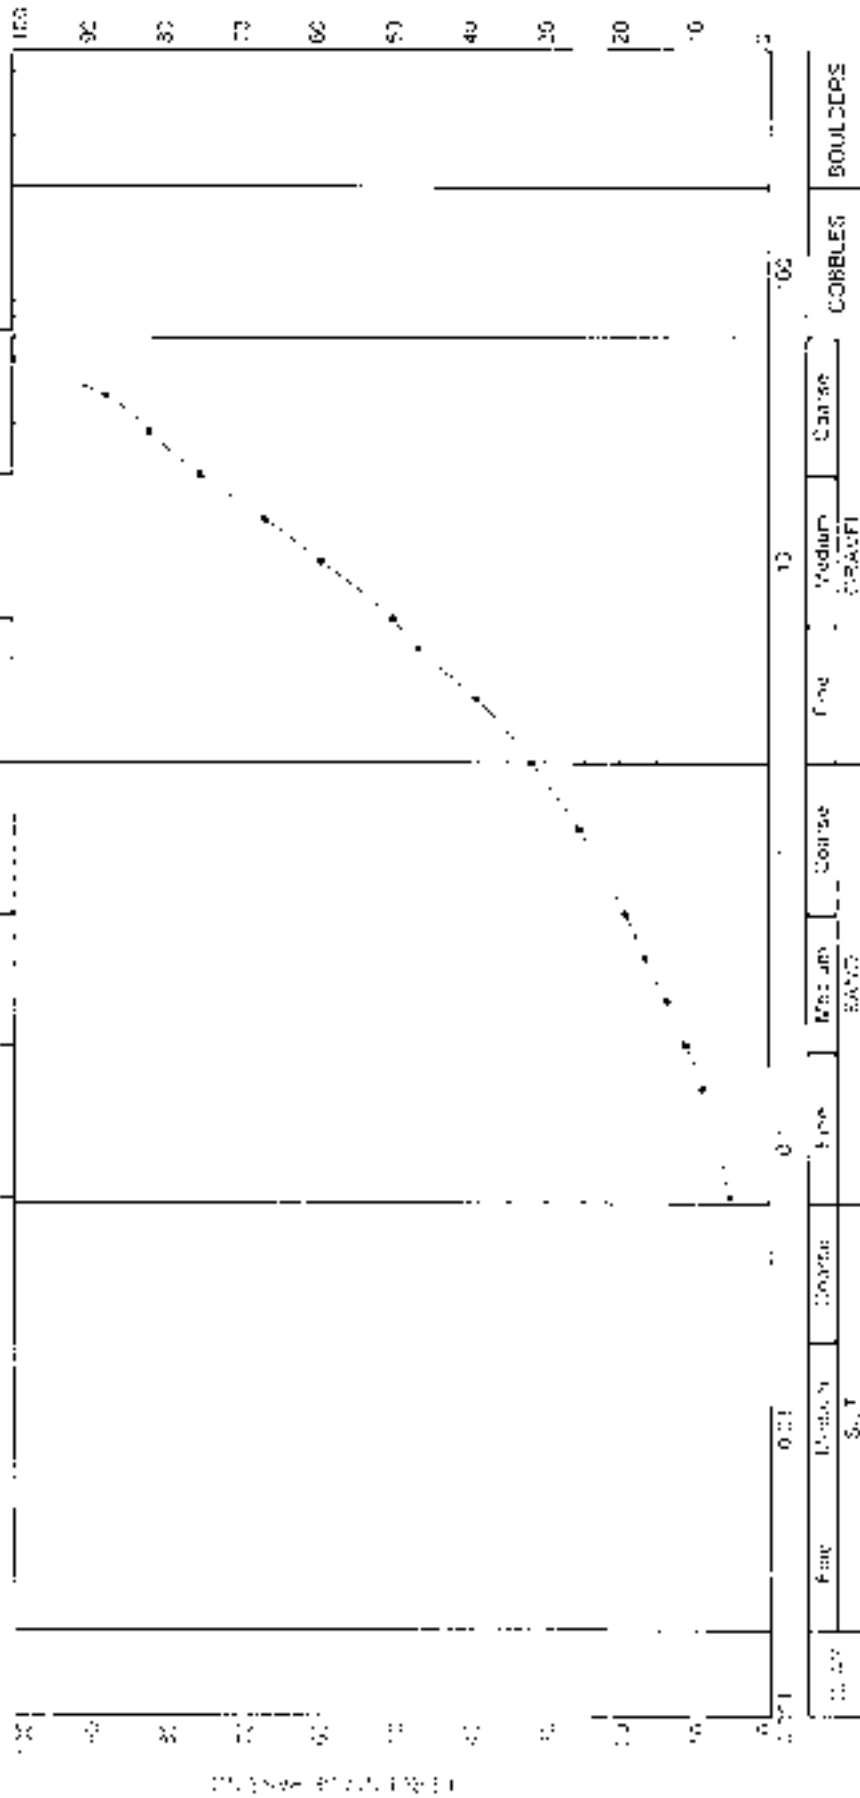

Soil	Sub	Very Fine	Fine	Medium	Coarse	Very Coarse	Coarse	Very Coarse	Very Coarse



Date of Issue: 21/10/2020
 Prepared by: PSD (PSD) 23 Aug 2019 08:00
 Checked by: [Signature]
 Approved by: [Signature]
 Name: [Blank]
 Project No: 4251
 Project Name: Prairie Creek Investigation Works
 Page 1 of 1
 1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 Part 2 - Clause 9.2.3.3 - 1990

(Test deviated from standard due to insufficient sample mass)


Report Reference: **PRAIRIE_AUK_TPI19**

Depth: **1.00**

Sample Type & No: **D2**

Specific Description: **1.00**

Date Tested: **19/10/2020**

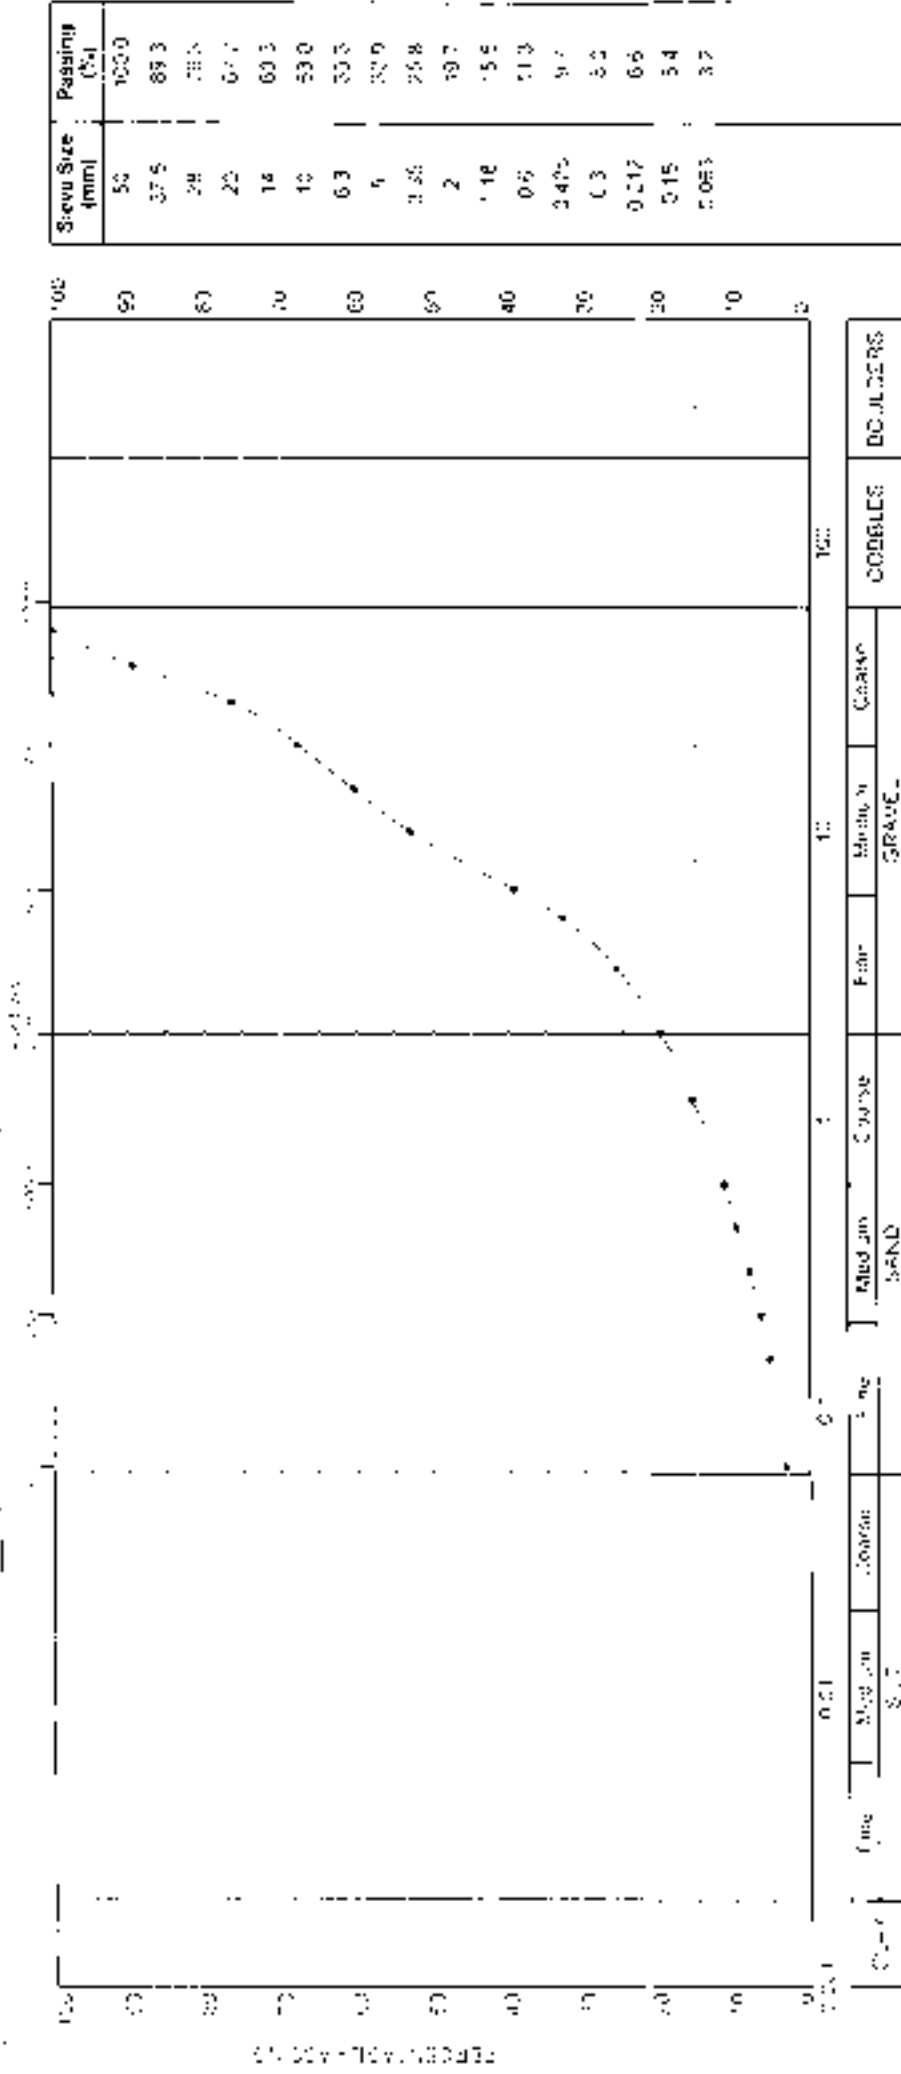

Coarse	Fine	Medium	Coarse	Medium	Fine	Medium	Coarse	COBBLES	BOULDERS
SAND			GRAVEL			GRAVEL			

1000 75 20 15 10 7.5 6.3 5 3.75 2 1.18 0.75 0.425 0.3 0.212 0.15 0.075

Client: **01052020**


Client Reference: **PRD-4251-000195-00**

Client Test Description: **Client Ref: 01052020**

Drawn by: **MSW**

Checked by: **MSW**

Scale: **1:1**



Page 1 of 1

ALS Contact No: **4251**

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

ES1077 : Part 2 : Clause 9.2 & 9.4 : 1996
 (Test deviated from standard due to insufficient sample mass)


Sample No: PRAIRIE AUK_TP119

Depth (m) : 2.00

Sample Type & No: B5

Specific Depth (m) : 2.00

Culc Tested : 19/10/2020

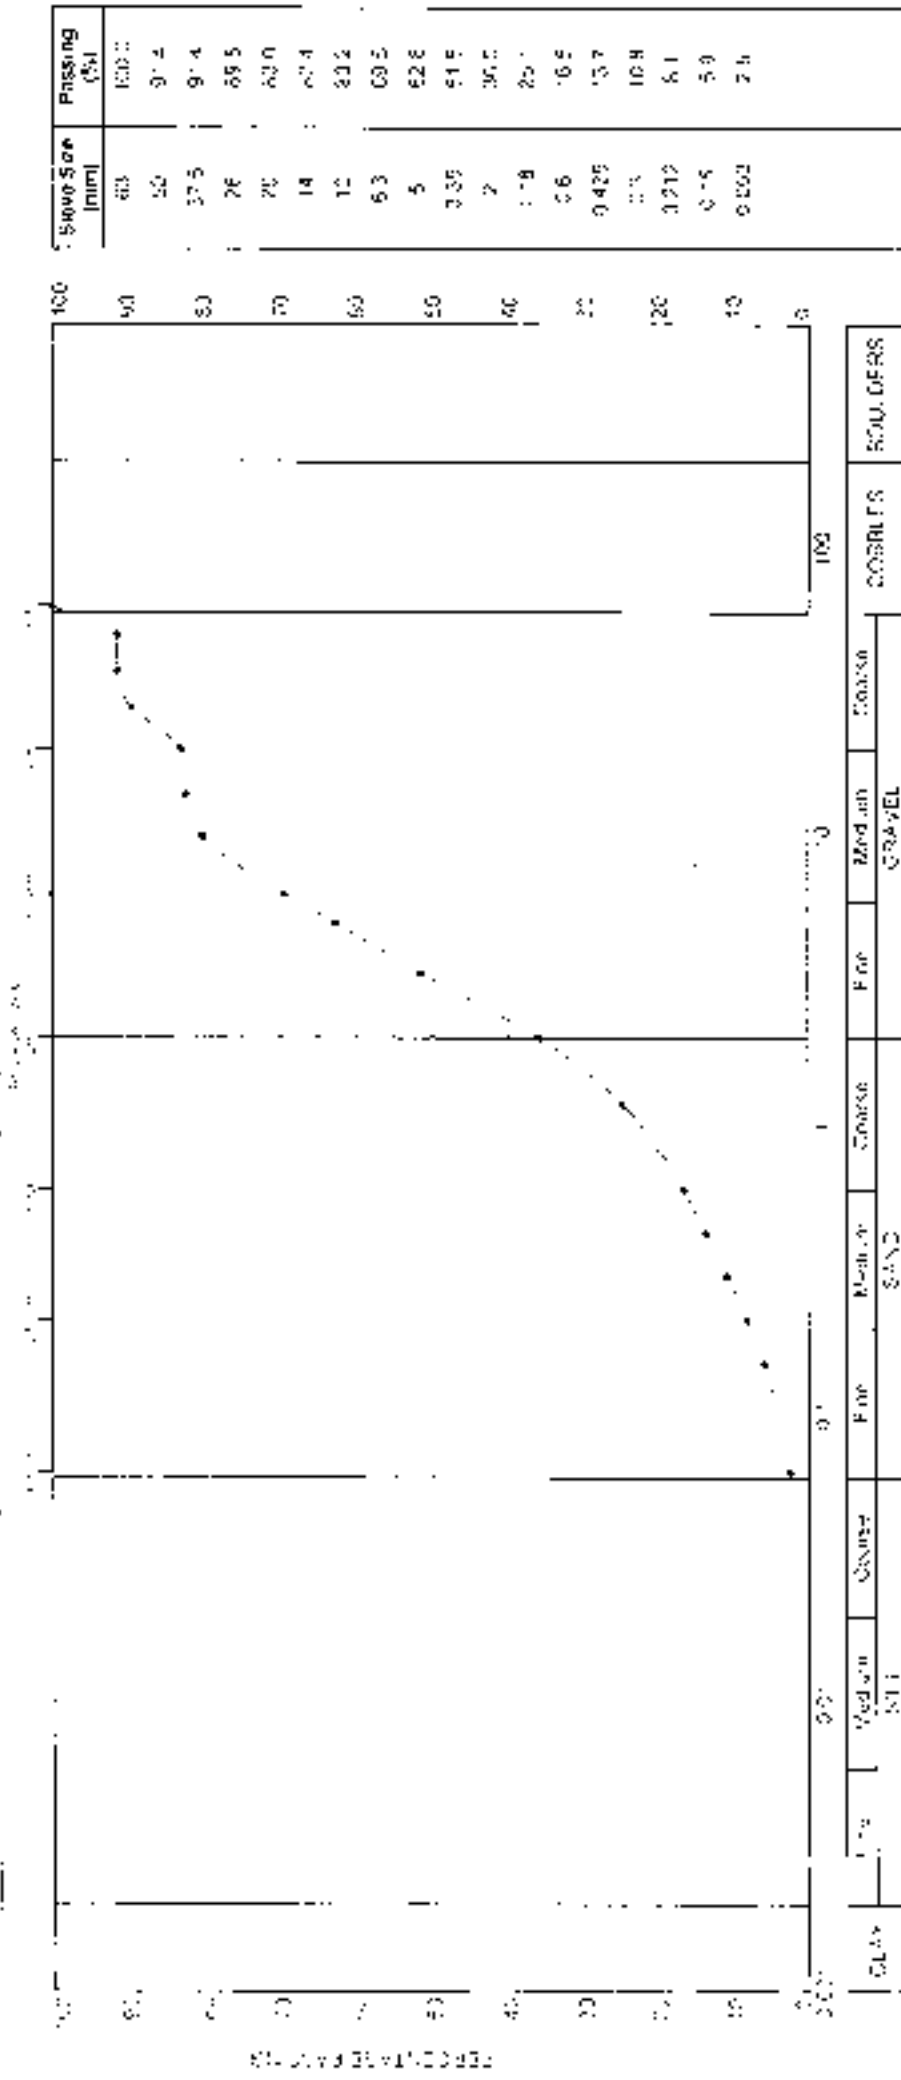

CLAY	Fine	Medium	Coarse	Fine	Medium	Coarse	COBBLES	SCALDERS
		SILT	SAND		GRAVEL			

Note: All values are based on the wet weight of the laboratory sample unless stated otherwise.




Date of Issue: 19/10/20

Credit No: AEG 4251

Prepared by: AEG 4251

Signed: *M. Misra*

Name: *Misra*



Page 1 of 1

AEG Contract No: 4251

Soil Test Complement Computer

Consultant

Field Site Ground Investigation Works

1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

DS1977 - Part 2 - Clause 9.2 & 9.4 1990


Project Name: PRAIRIE_AUK_TP120A

Location: 0.80

Sample Type & Size: B2

Specific Depth: 0.80

Date Tested: 15/12/2020

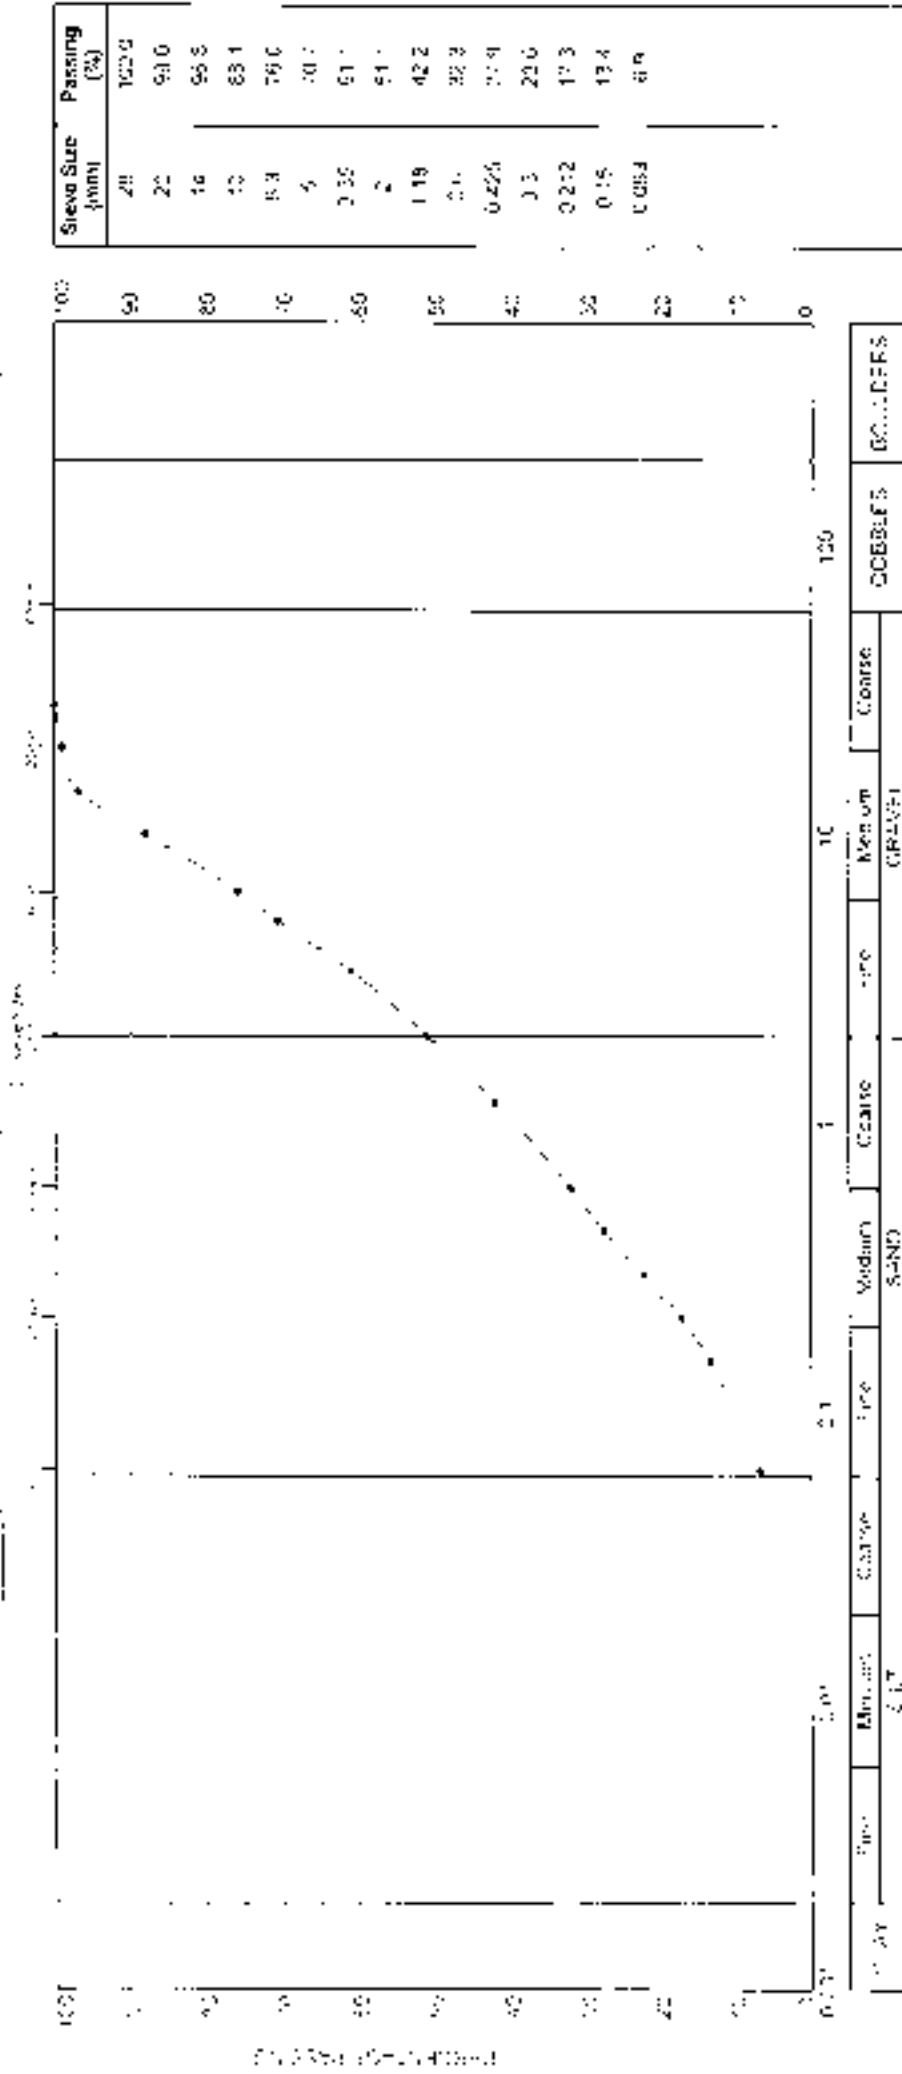

Project No: 20101020
 Date: 15/12/2020
 Site: PRAIRIE_AUK_TP120A B2-0.80
 Location: 0.80

Client: MSA
 Contact: MSA
 Project: PRAIRIE_AUK_TP120A B2-0.80



Page 1 of 1
 475
 1057

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

RS1377 Part 2 - Clause 9.2 & 9.4 - 1990


Exploratory File No. PHALRIE_AUK_TP124

Depth (m) 0.80

Sample Type & No. B2

Specific Depth (m) 0.80

Date tested - 01/10/2020

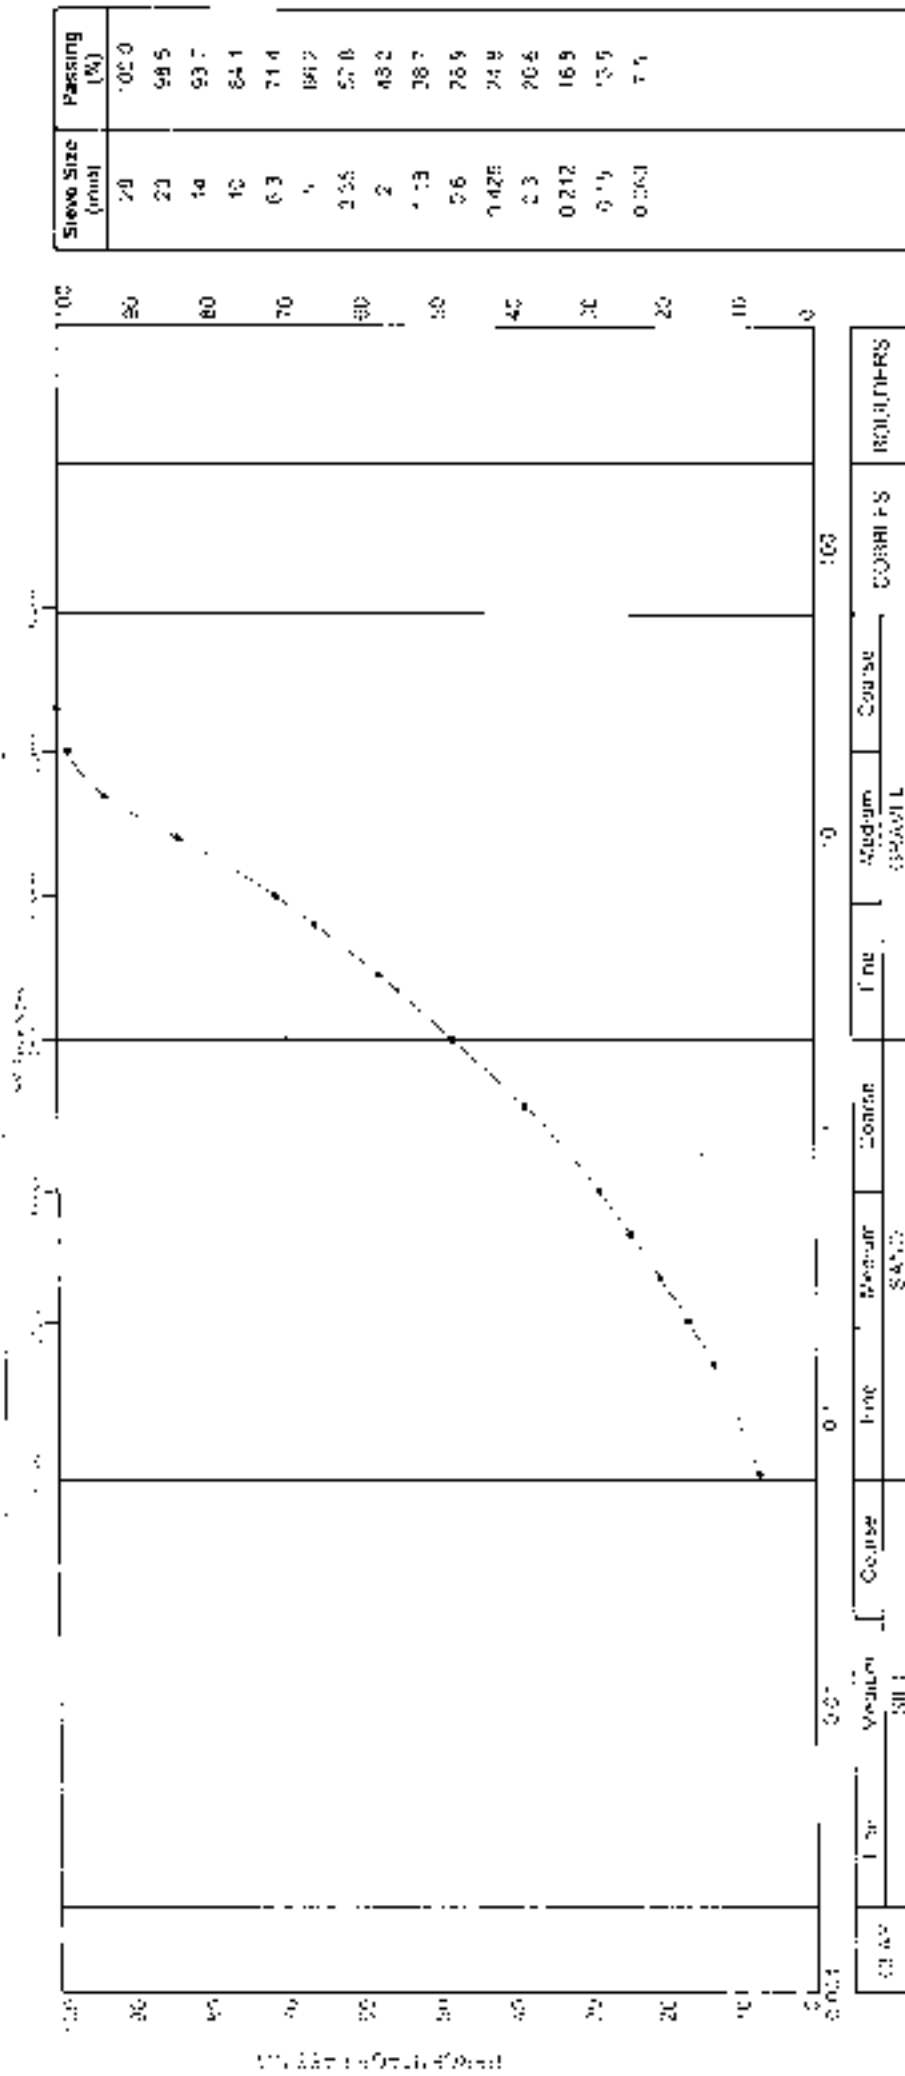

Class	Medium	300	Course	COBH 15	NO. OF TESTS
Fin	Medium	300	Course	COBH 15	
Medium	300	Course	COBH 15		
Coarse	300	Course	COBH 15		
Very Coarse	300	Course	COBH 15		
Extremely Coarse	300	Course	COBH 15		

For details of the test procedure refer to the Laboratory Manual Test procedures

Date of issue: 23/10/2020
 Certificate No: PHO 4751 PR0 010 AUK_TP124 B2 0.80

MSO

Name:



Page 1 of 1
 AEG Contract No: 4751



Company: South Coast Geotechnics Corporation

Contract Title: P124 - Soil Ground Investigation Works

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 - Part 2 - Clause 9.2 & 9.4 - 1990
 (Test deviated from standard due to insufficient sample mass)



Client Ref: **PROARIE_AUK_TP123**

Diaper No: **0.50**

Sample Type & No: **BZ**

Specific Depth (m): **0.50**

Date Tested: **28/09/2020**

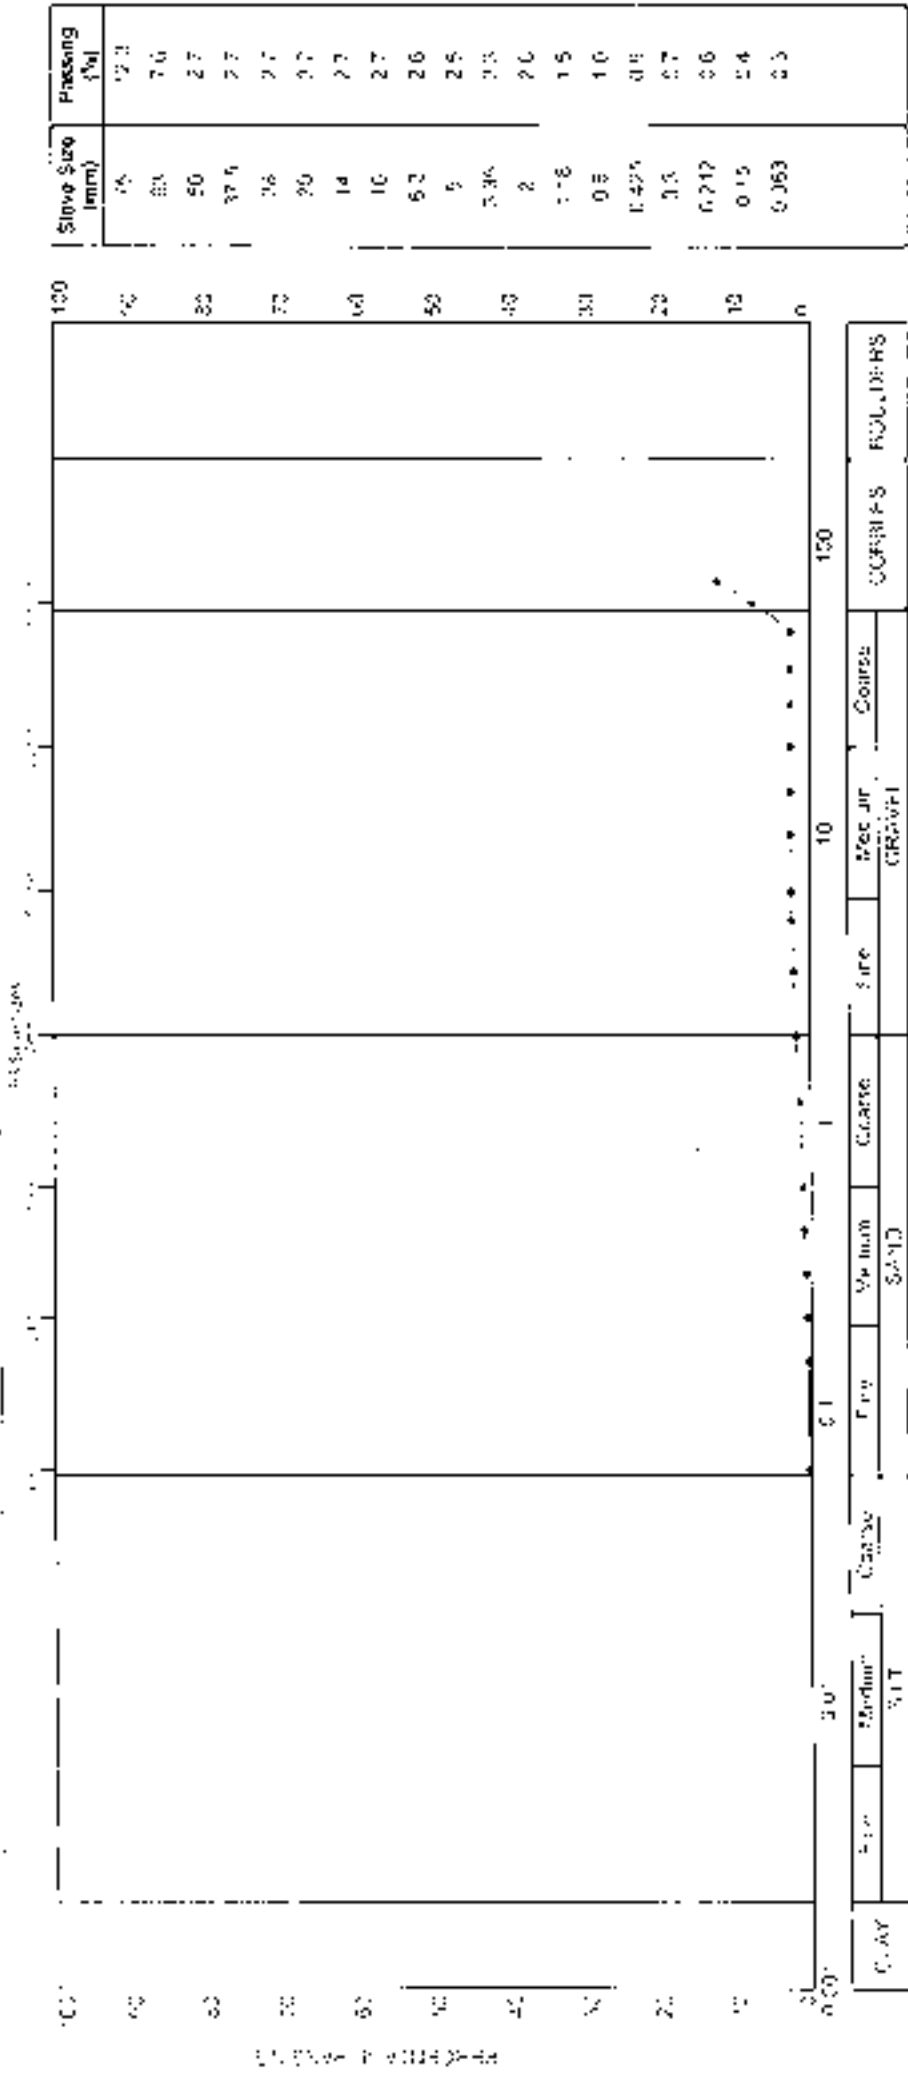

Page: of 1
 AEG Contract No: 4251

Project Name: **msaw**
 Figure 2.14 Gravel Investigation Marks

Scale: 1:10
 Date: 28/09/2020

Client: **PROARIE_AUK_TP123**
 Project: **msaw**




ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

(AS1377 - Part 2 - Clause 9.2 & 9.4 - 1998)

Property Name: **PRAIRIE_AUK_TP124** Depth: **1.50** Sample Type: **So - B4** Spec. Depth: **1.50** Date Tested: **28/09/2020**

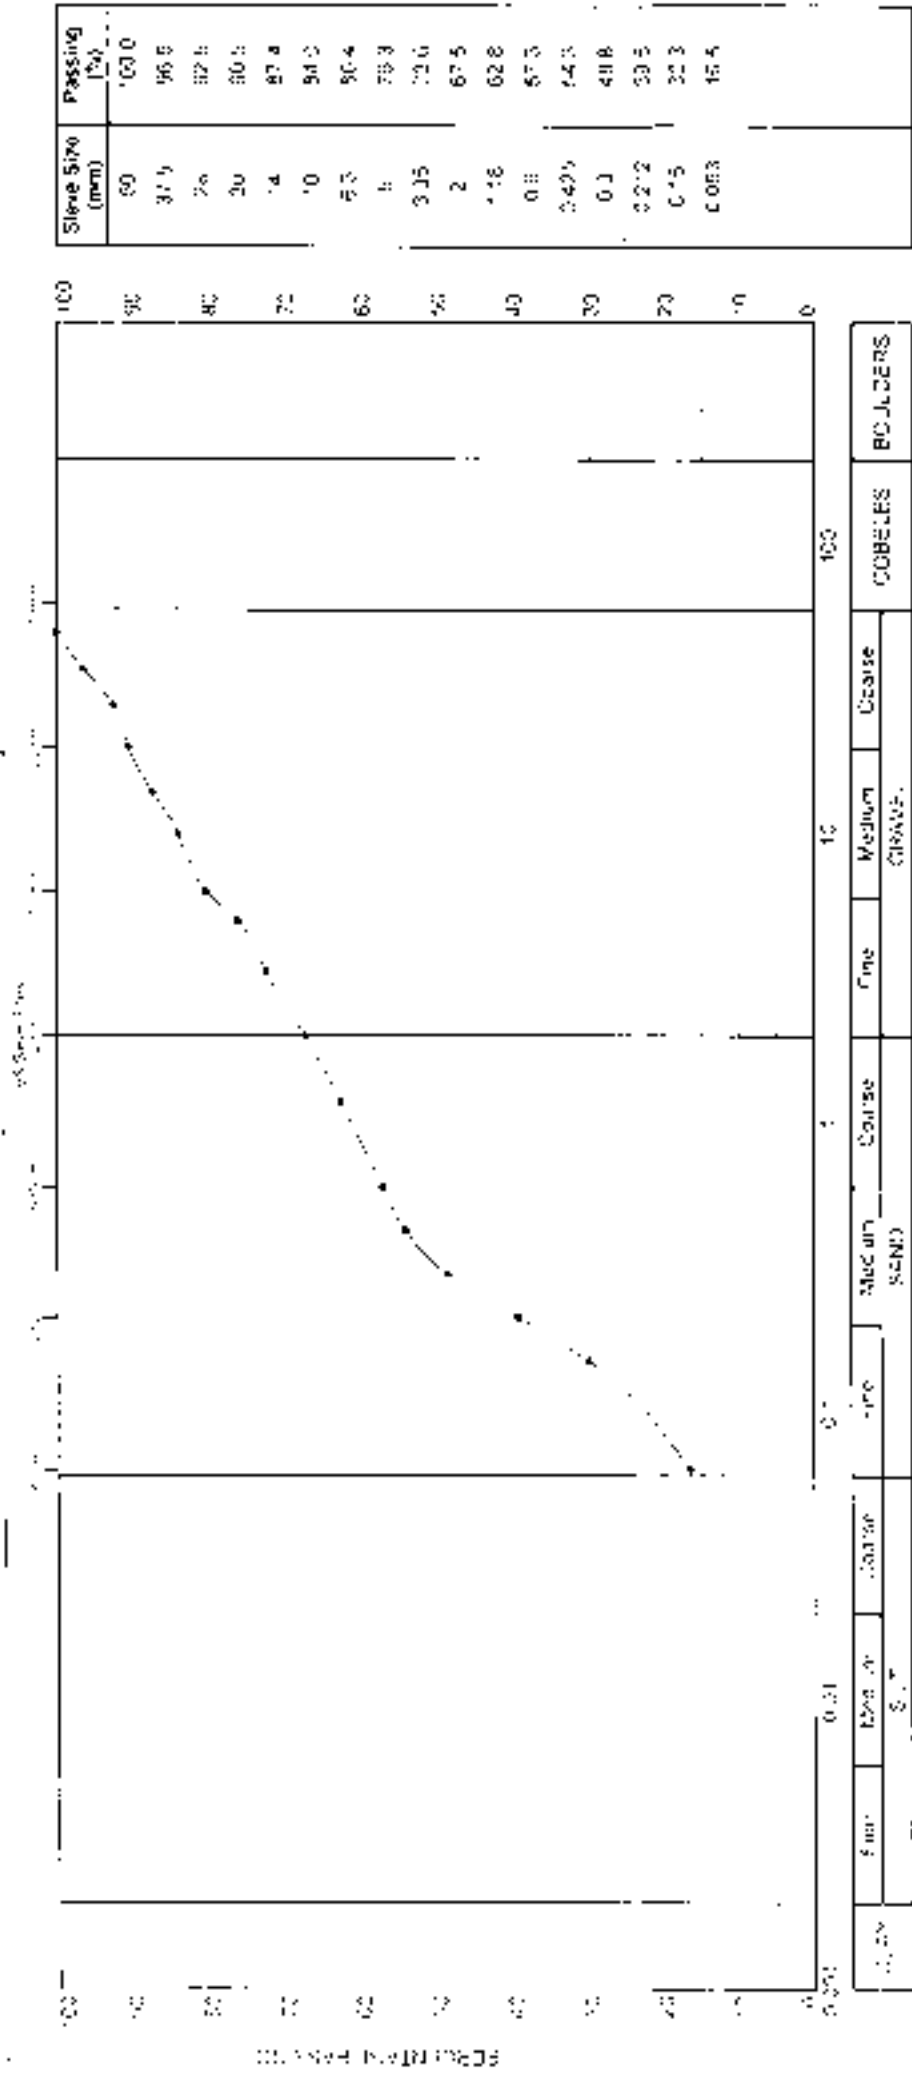


Very Fine	Fine	Medium	Coarse	COBBLES
0.075 - 0.425	0.425 - 2.0	2.0 - 7.5	7.5 - 20.0	> 20.0
FINE SAND				COBBLES
MEDIUM SAND				COBBLES
COARSE SAND				COBBLES

Certificate No: _____
 Job No: _____
 Client: _____
 Project: _____

Site: _____
 Sample Description: _____
 Date: _____
 Test No: _____



Page 1 of 1
 AEG Contact No - 4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990
(Test deviated from standard due to insufficient sample mass)


Location: PRAIRIE_AUK_FP120

Depth: 1.80

Sample Type & No: G4

Specific Description: 1.80

Date Tested: 16/01/2020

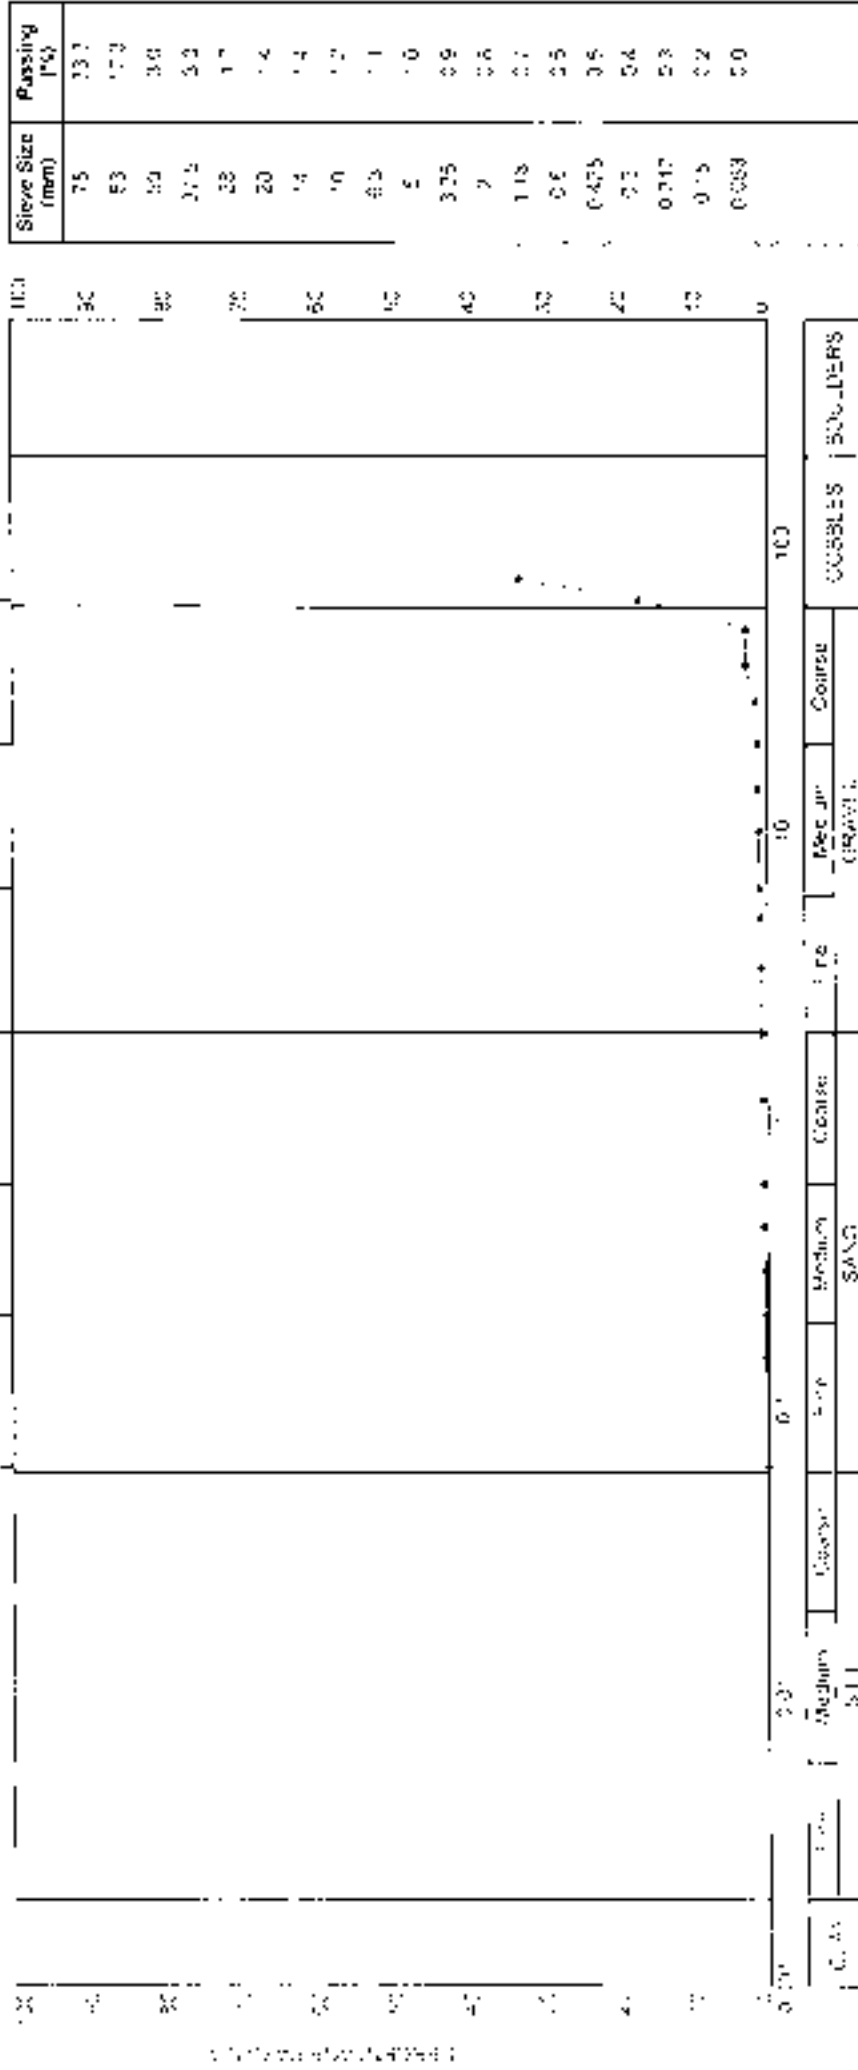

Course	Medium	Coarse	Per cent Gravels	Course	Cobbles	Scallers
SANG						
10						

For Test Results from the Geotechnical Laboratory, Contact us on 01867 500000



Date of Issue: 22/01/2020

Client Name: MASON'S CIVIL ENGINEERING

Project Name: PRAIRIE_AUK_FP120 - SANG

Name: Mason

Page 1 of 1

Client:

Site: PRAIRIE_AUK_FP120 - SANG

Contract No:

Figure 2 to Geotechnical Investigation Works

AEG Contract No: 4261




1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

DS4377 - Part 2 - Clause 8.2.8.9.4 : 1980
(Test deviated from standard due to insufficient sample mass)

Exp. No: PISAIRIE_AUX TP132 Depth: 2.00 Sample Type: D8 Specific Depth: 2.00 Date Tested: 30/09/2020

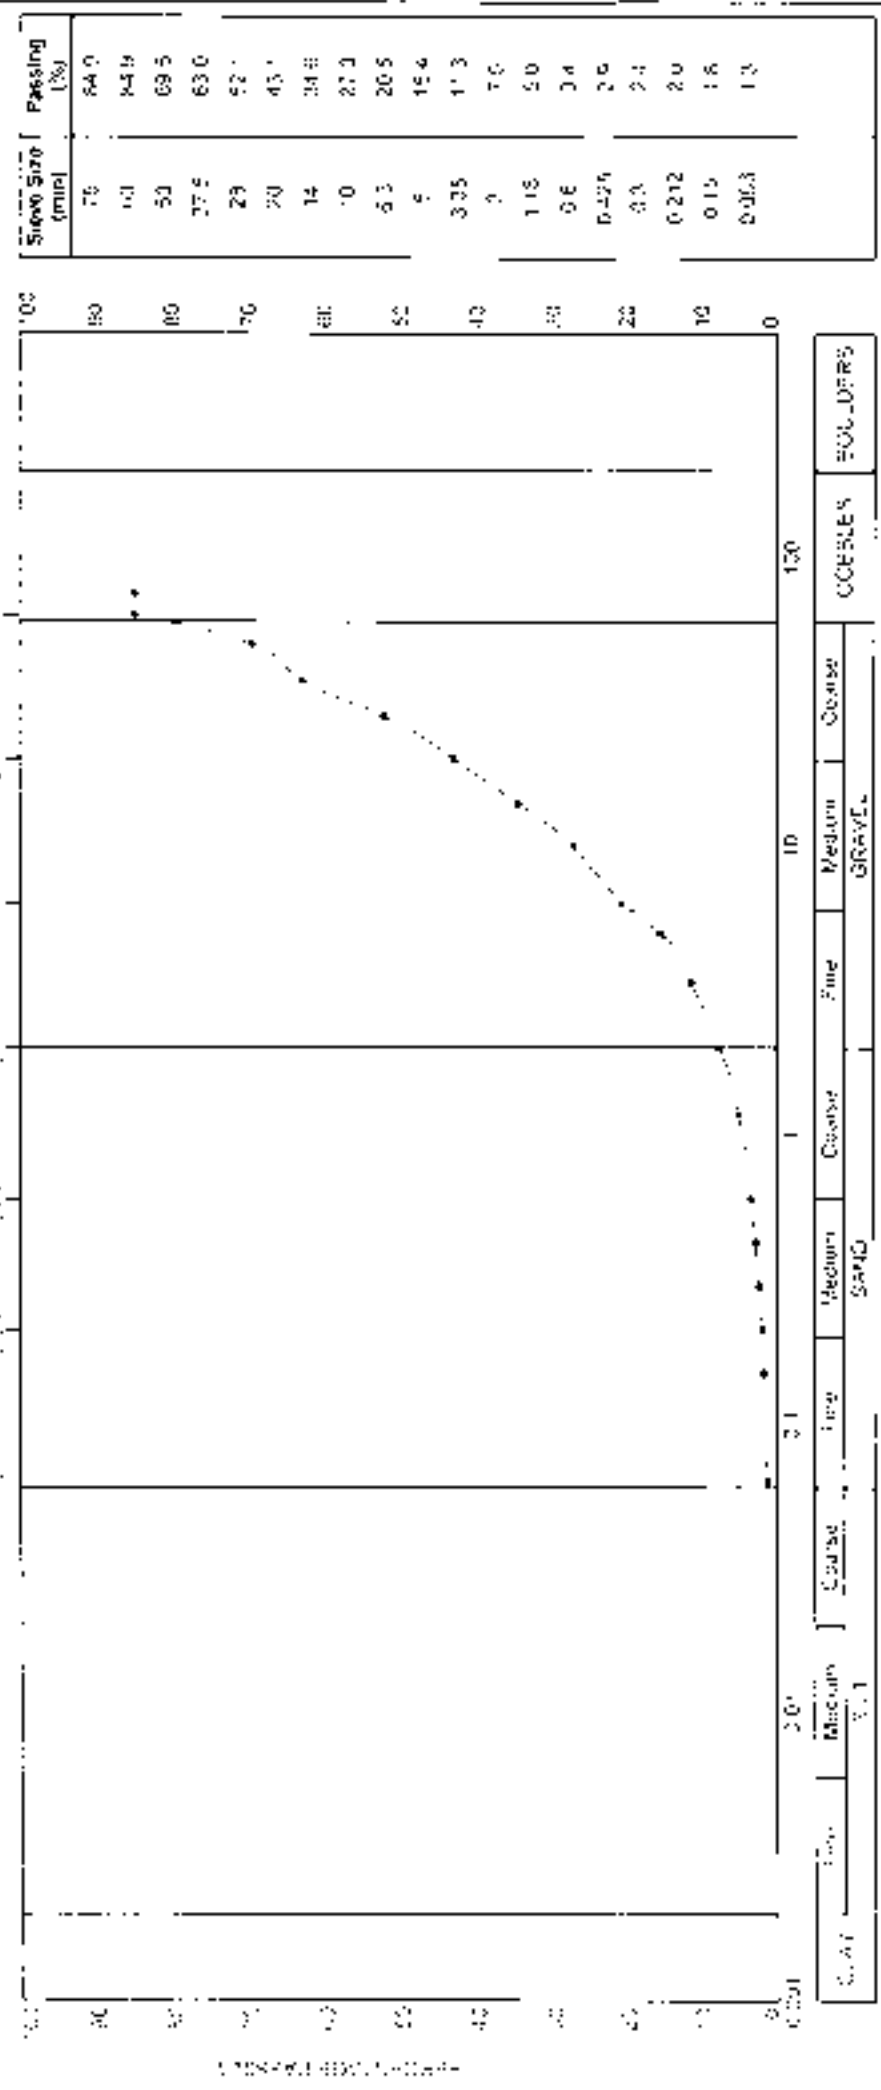

Date of Issue: 30/09/2020

Client: PISAIRIE_AUX_TP132

Site: PISAIRIE_AUX_TP132

Contract Title: *None*

Page 1 of 1

AEG Certified No: 4251

Prime Site Geologic Investigation Works

AEG

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS4377 : Part 2 : Clause 9.2 & 9.4 : 1990

(Test deviation from standard due to insufficient sample mass)


Sample No. : PRAIRIE_AUK_TP134

Depth : 0.80

Sample Type & No. : B2

Soils, Depth (m) : 0.80

Date Tested : 15/10/2020

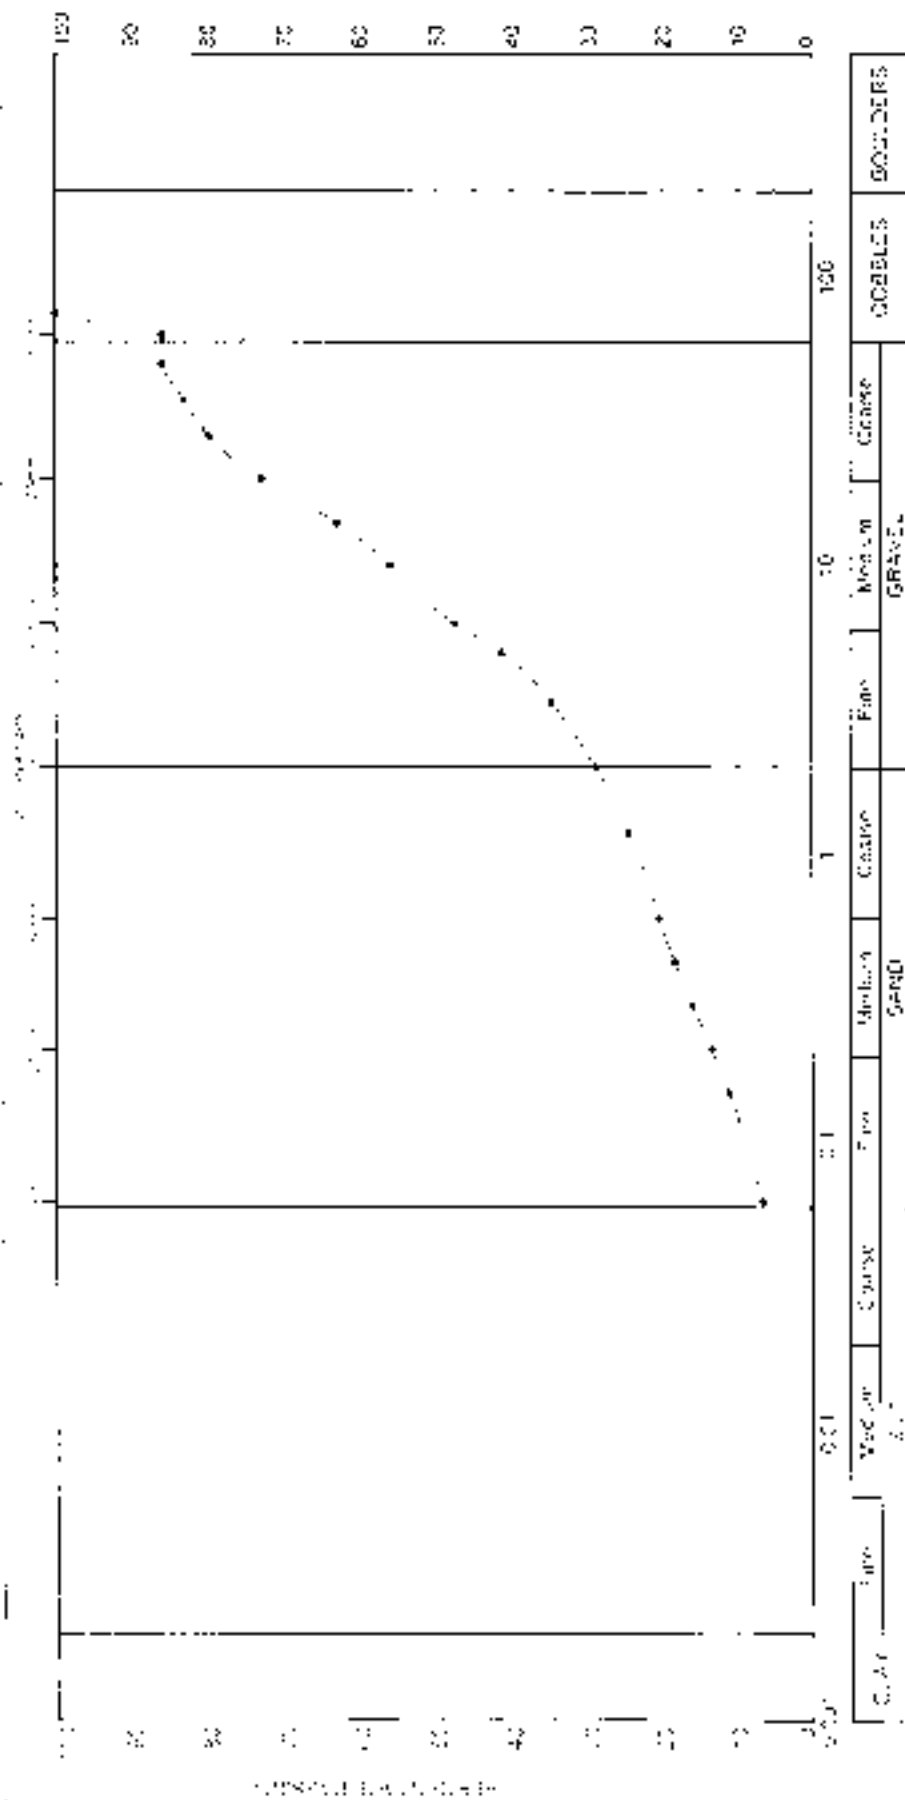

Grain Size	Coarse	Medium	Fine	Coarse	Medium	Coarse	COBBLES	BOULDERS
SAND			GRAVEL					

Tested by: [Signature] Date: 15/10/2020



Contract No. : 21-02520
 Project Name : PRAIRIE_AUK_TP134
 Location : Prairie Site Ground Investigation

[Signature] M. S. [Signature]

None

Page 1 of 1
 AEG Contract No. : 4751



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS 1377 : Part 2 - Clause B 2 & B 4 : 1990
(Test deviated from standard due to insufficient sample mass)


Project No: HIGHLIE_AUG_TP135

Client: 100

Sample Type & Qty: B3

Specific Description: 100

Date Tested: 10/10/2020

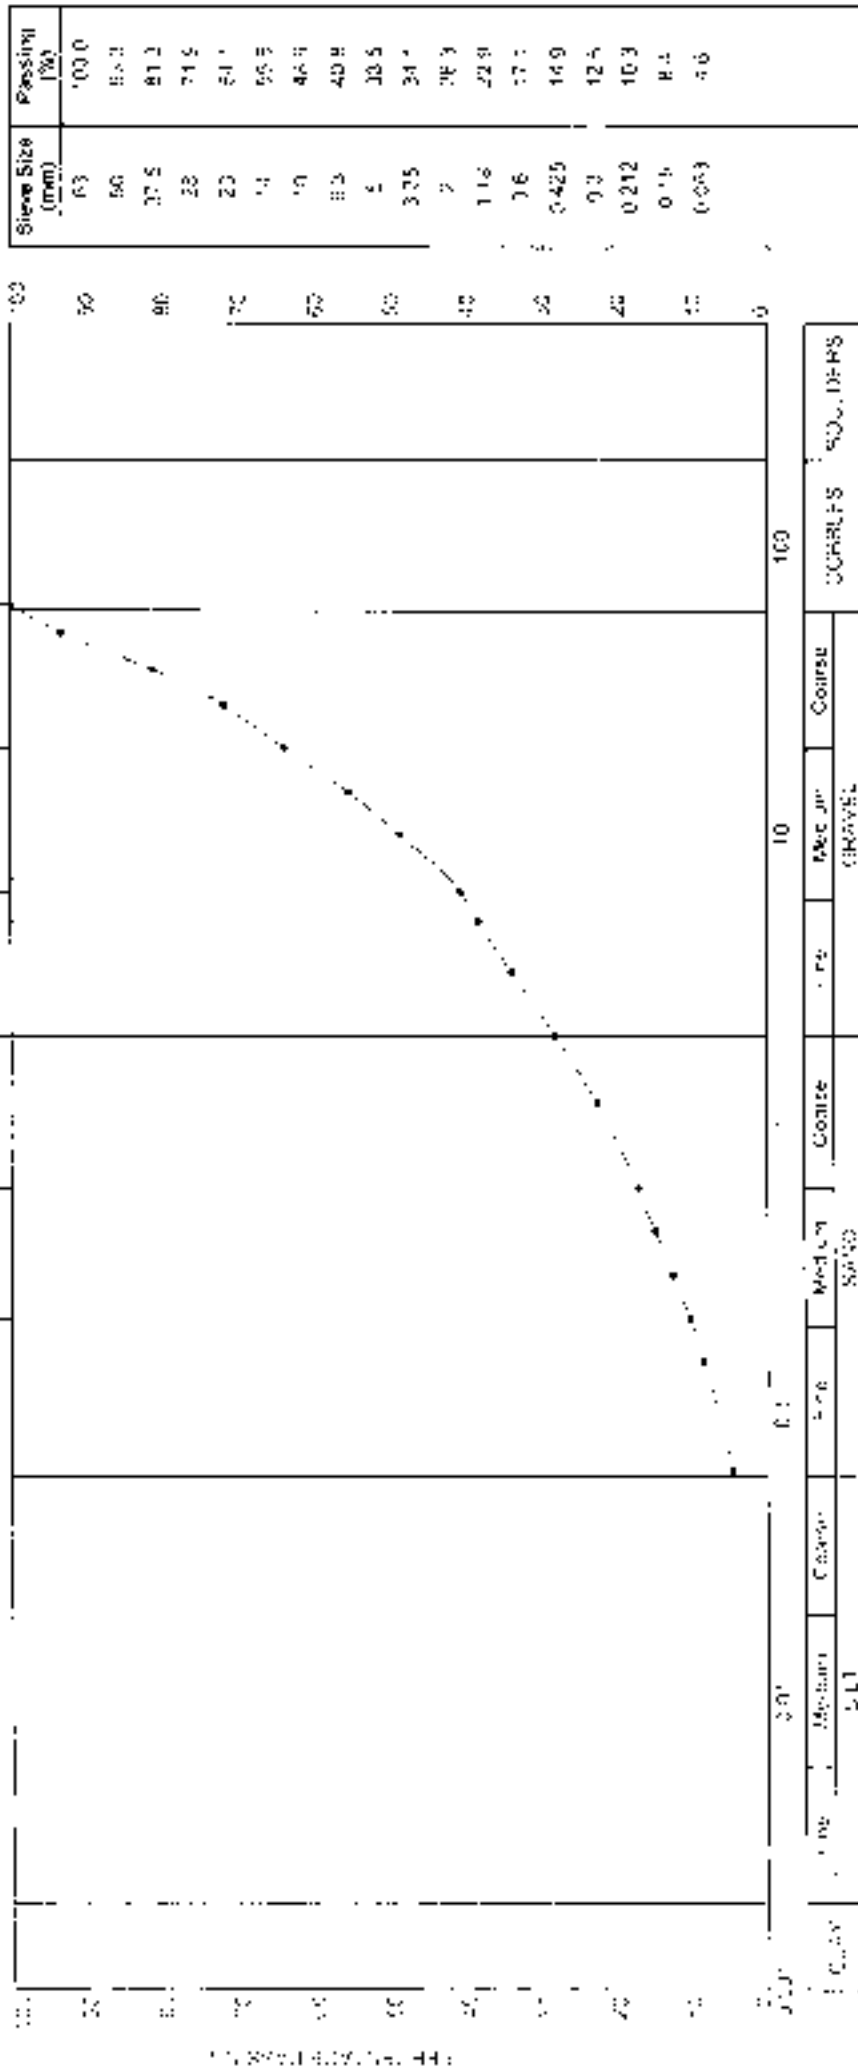

Zone	Coarse	Medium	Fine	Coarse	Course	SOULS	SOULS	SOULS
GRAVEL								

For more information on sample preparation and laboratory testing visit our website

Client: 100

Contract No: HIGHLIE_AUG_TP135

Contract Title:

Name:

msw

Soil Testing & Development Company

Home Office (England) Registration No: 4251

Page 1 of 1




ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2.9.4 : 1990
 (Test deviated from standard due to insufficient sample mass)

Project Name: PRAIRIE_AUR_1P137 Depth: 1.00 Sample Type & No: U4 Specific Gravity: 1.00 Date Tested: 19/10/2020

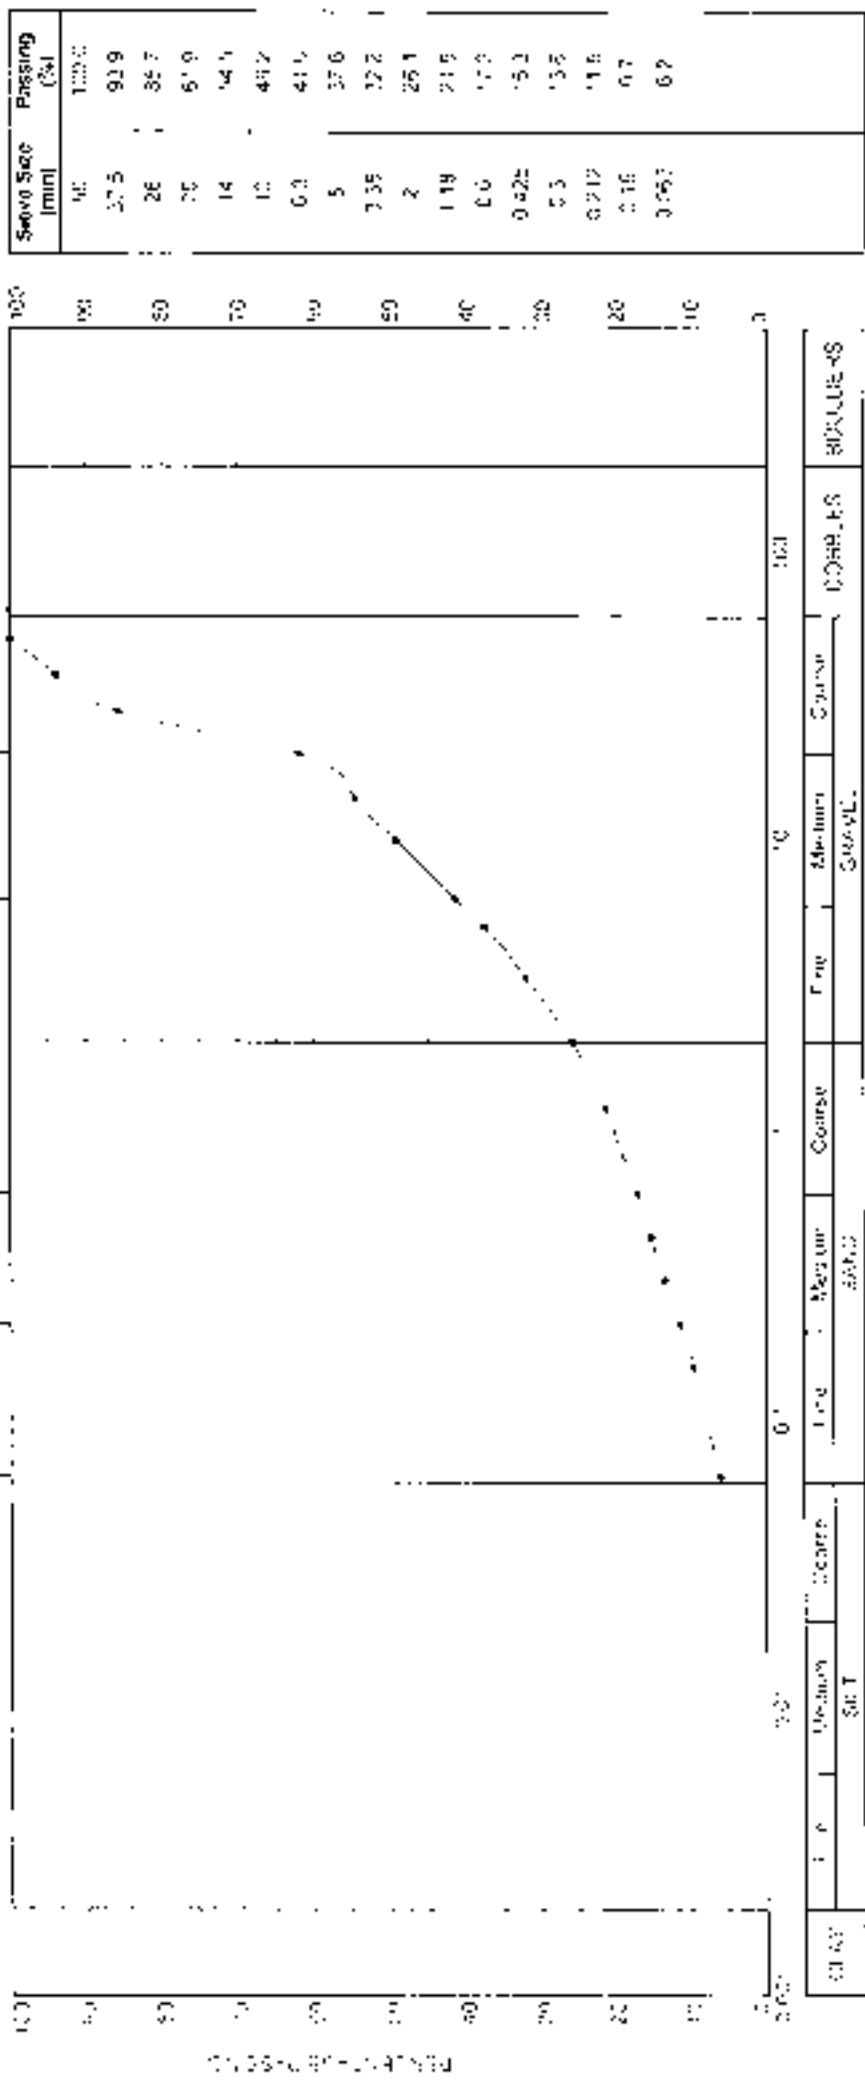

CLASS	TYPE	METHOD	COURSE	LINE	MEASURE	COURSE	FINE	MEDIUM	COURSE	COURSE	COARSE	VALUES
		SIT			200.0							

AEGS
 Date of Test: 19/10/2020
 Location: 2000 2000
 Geotechnical No.:
 Project No.: PRAIRIE_AUR_1P137
 Sample No.: U4
 Signed: *MSR*
 Company: Allied Exploration & Geotechnics Limited
 Address: 2000 2000

Date of Report: 19/10/2020
 Author: MSR
 Checked: MSR
 For: Soil Ground Investigation Works
 Report No.: 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 - Part 2 - Clause 9.2 & 9.4, 1990
 (Test deviated from standard due to insufficient sample mass)


Project No: PFAIR F_AUK_TP138

Depth: 1.00

Sample Type & No.: B2

Special Depth: 1.00

Date Tested: 15/10/2020

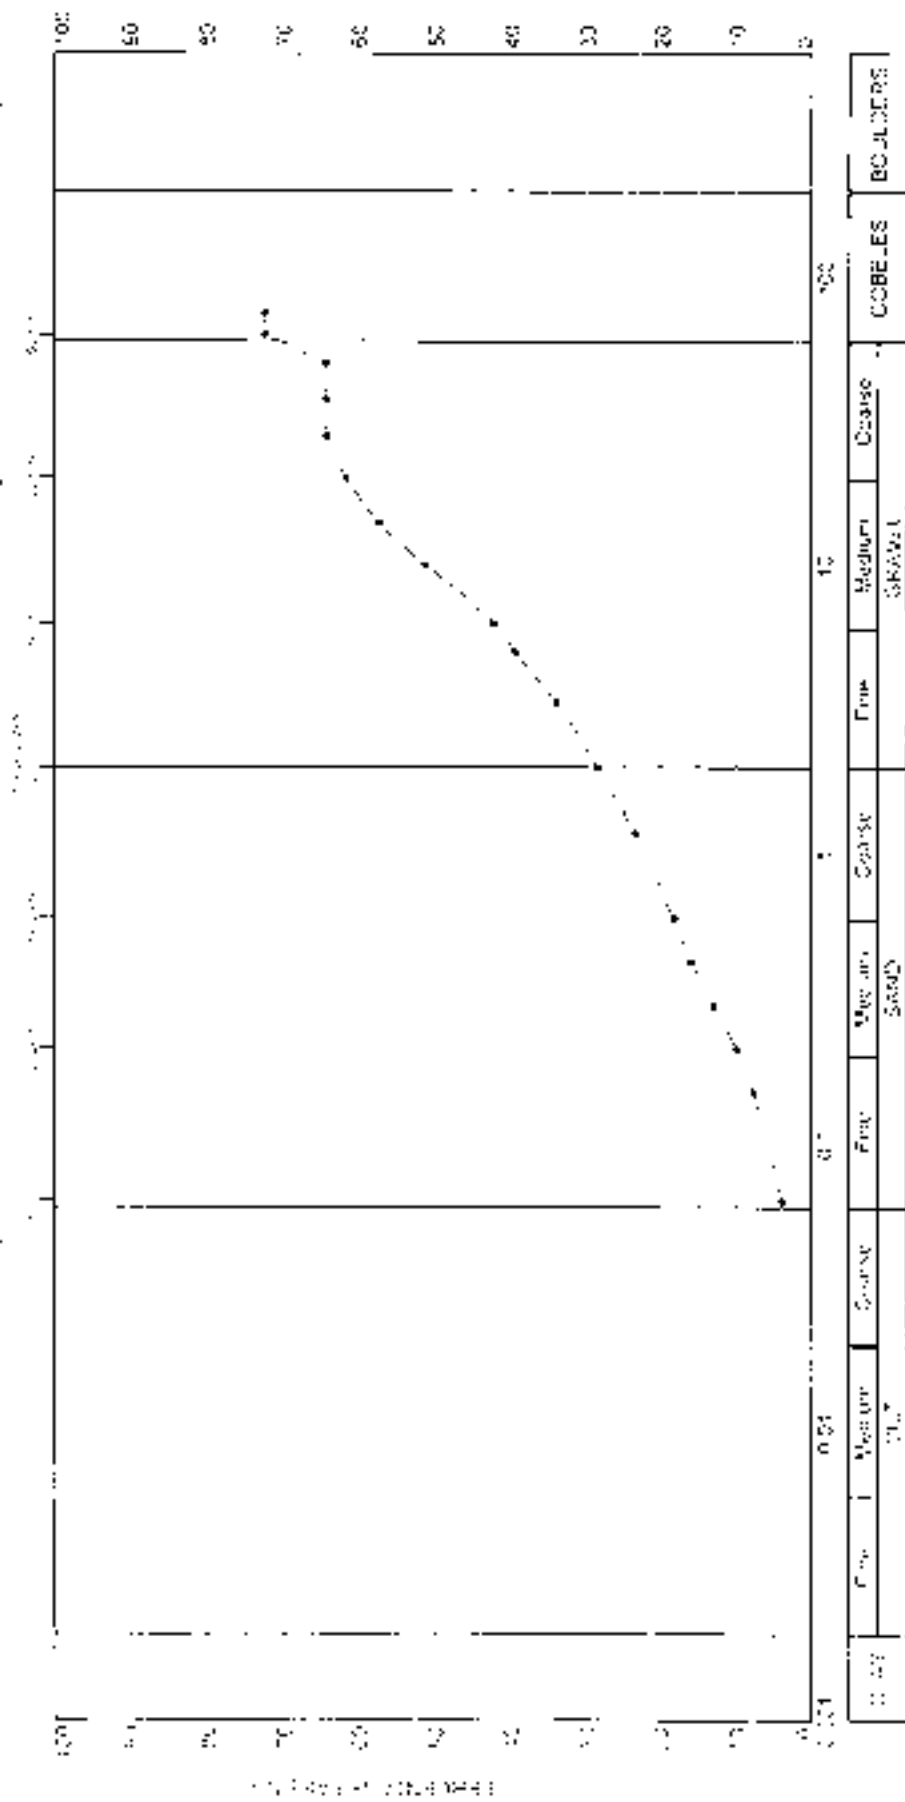

SAND			GRAVEL		
Coarse	Medium	Fine	Coarse	Medium	Coarse
0	0	0	0	0	0

For details of test procedure refer to BS1377-2:1990, clause 9.2.4.1

Client: **CH2M HILL**

Project: **FAIR F_AUK_TP138**

Location: **FAIR F_AUK_TP138**

Contract No.: **4251**

Date: **15/10/2020**

Page 1 of 1

1967

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Millfield Industrial Estate, Park Road, Doncaster, South Yorkshire, DN11 9JF, UK. Tel: 01172 324 4500 Fax: 01172 324 4711
Regional Office: Unit 25, Millfield Industrial Estate, Park Road, Doncaster, South Yorkshire, DN11 9JF, UK. Tel: 01172 324 4500 Fax: 01172 324 4711

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

(Test deviated from standard due to insufficient sample mass)

Exploratory Hole No :- PRAIRIE_AUK_TP139B	Depth (m) :- 0.20	Sample Type & No :- B2	Specific Depth (m) :- 0.20	Date Tested :- 14/10/2020																																						
<table border="1" style="width: 100%; border-collapse: collapse;"> <thead> <tr> <th>Sieve Size (mm)</th> <th>Passing (%)</th> </tr> </thead> <tbody> <tr><td>63</td><td>100.0</td></tr> <tr><td>50</td><td>94.9</td></tr> <tr><td>37.5</td><td>94.9</td></tr> <tr><td>25</td><td>88.5</td></tr> <tr><td>20</td><td>85.4</td></tr> <tr><td>14</td><td>81.6</td></tr> <tr><td>10</td><td>74.4</td></tr> <tr><td>6.3</td><td>64.8</td></tr> <tr><td>5</td><td>60.0</td></tr> <tr><td>3.35</td><td>53.0</td></tr> <tr><td>2</td><td>46.7</td></tr> <tr><td>1.18</td><td>40.9</td></tr> <tr><td>0.6</td><td>34.3</td></tr> <tr><td>0.425</td><td>31.1</td></tr> <tr><td>0.3</td><td>26.5</td></tr> <tr><td>0.212</td><td>20.7</td></tr> <tr><td>0.15</td><td>16.3</td></tr> <tr><td>0.063</td><td>9.6</td></tr> </tbody> </table>					Sieve Size (mm)	Passing (%)	63	100.0	50	94.9	37.5	94.9	25	88.5	20	85.4	14	81.6	10	74.4	6.3	64.8	5	60.0	3.35	53.0	2	46.7	1.18	40.9	0.6	34.3	0.425	31.1	0.3	26.5	0.212	20.7	0.15	16.3	0.063	9.6
Sieve Size (mm)	Passing (%)																																									
63	100.0																																									
50	94.9																																									
37.5	94.9																																									
25	88.5																																									
20	85.4																																									
14	81.6																																									
10	74.4																																									
6.3	64.8																																									
5	60.0																																									
3.35	53.0																																									
2	46.7																																									
1.18	40.9																																									
0.6	34.3																																									
0.425	31.1																																									
0.3	26.5																																									
0.212	20.7																																									
0.15	16.3																																									
0.063	9.6																																									
<p style="font-size: x-small;">For description of sample please refer to the Laboratory Sample Description Sheet</p> <table border="1" style="width: 100%; border-collapse: collapse;"> <tr> <td style="width: 12.5%;">CLAY</td> <td style="width: 12.5%;">Fine</td> <td style="width: 12.5%;">Medium</td> <td style="width: 12.5%;">Coarse</td> <td style="width: 12.5%;">SILT</td> <td style="width: 12.5%;">Fine</td> <td style="width: 12.5%;">Medium</td> <td style="width: 12.5%;">Coarse</td> <td style="width: 12.5%;">SAND</td> <td style="width: 12.5%;">Fine</td> <td style="width: 12.5%;">Medium</td> <td style="width: 12.5%;">Coarse</td> <td style="width: 12.5%;">GRAVEL</td> <td style="width: 12.5%;">Medium</td> <td style="width: 12.5%;">Coarse</td> <td style="width: 12.5%;">BOULDERS</td> </tr> </table>					CLAY	Fine	Medium	Coarse	SILT	Fine	Medium	Coarse	SAND	Fine	Medium	Coarse	GRAVEL	Medium	Coarse	BOULDERS																						
CLAY	Fine	Medium	Coarse	SILT	Fine	Medium	Coarse	SAND	Fine	Medium	Coarse	GRAVEL	Medium	Coarse	BOULDERS																											
Date of issue :- 23/10/2020		Certificate No :- PSD/4251/PRAIRIE_AUK_TP139B/020.20		Signed :- <i>M. SELKIRK</i>		Name :- <i>M. SELKIRK</i>		Page 1 of 1																																		
Client :- South Tees Development Corporation		Contract Title :-		Contract No :- 4251		AEG Contract No :- 4251																																				



Praine Site Ground Investigation Works

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 - Part 2 - Clause 9.2 & 9.4 : 1990


Job Name: PRAIRIE_AUR_TP146

Depth: 1.00

Sample Type & No: B3

Specific Depth: 1.00

Date Tested: 28/08/2020

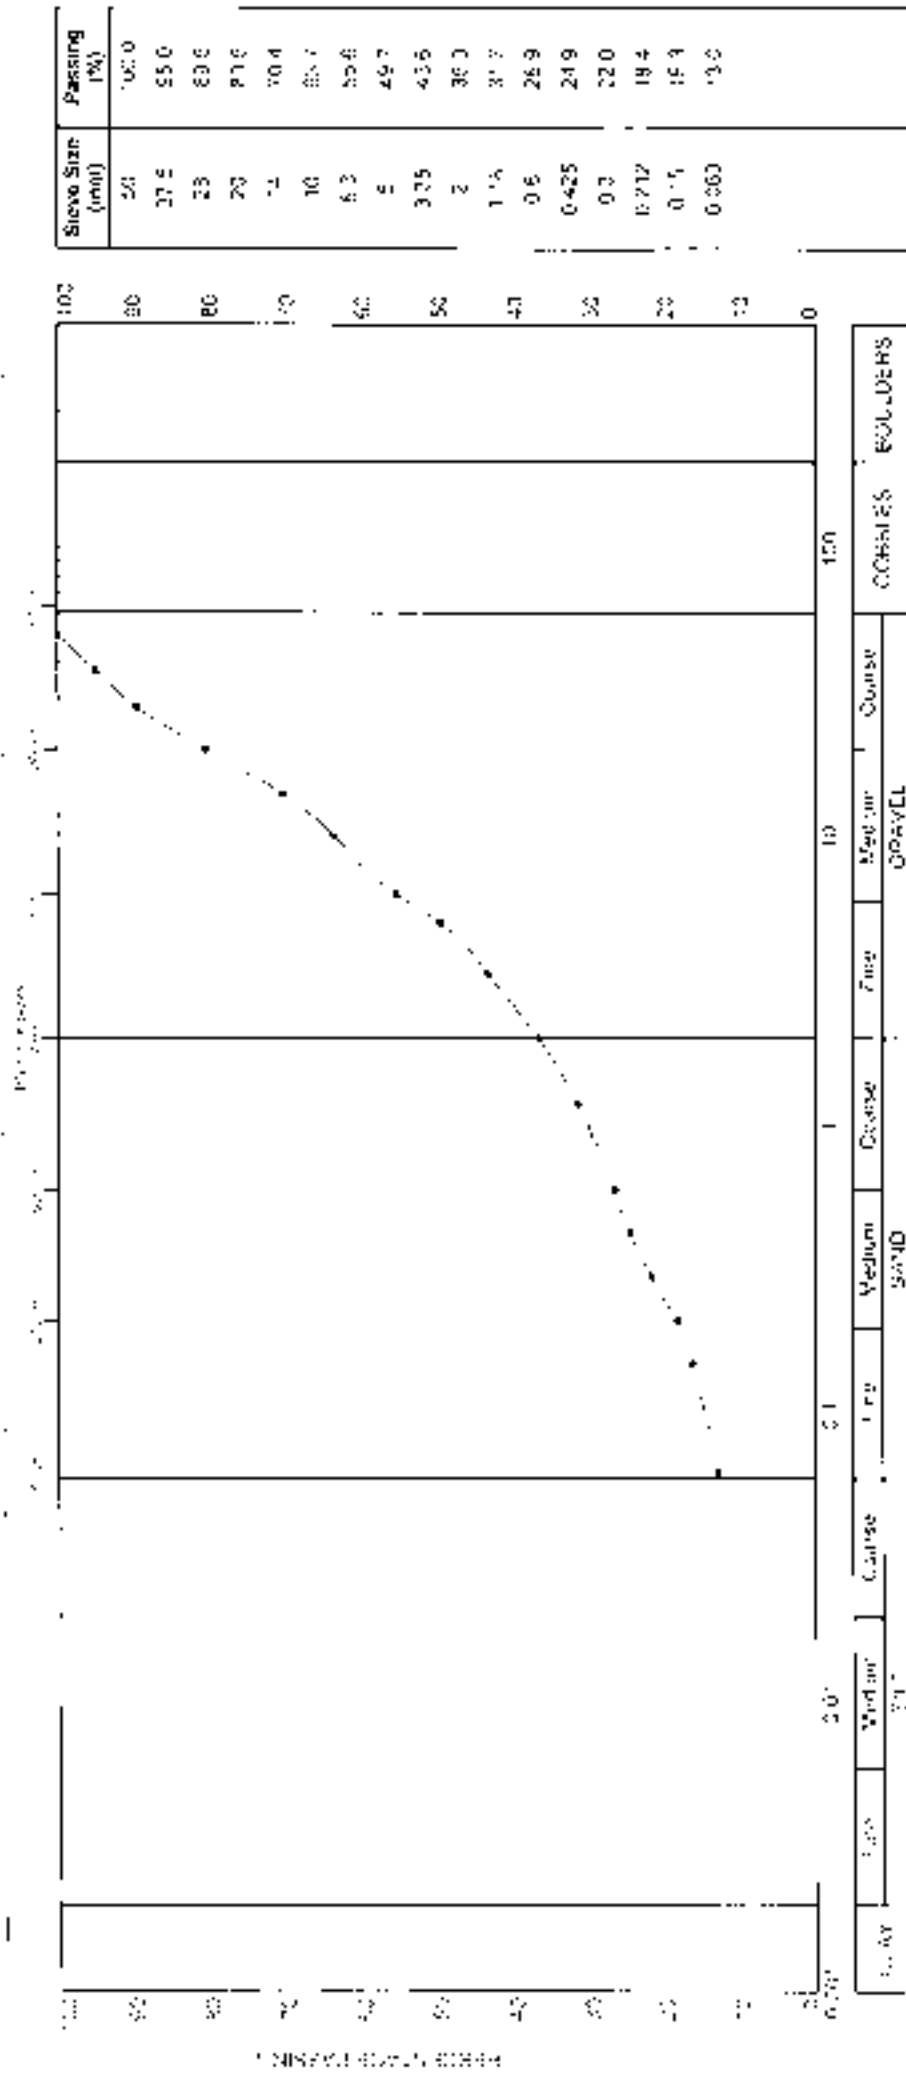

Date of Issue:

28/08/2020

Drawn by:

PR146/1/PR146_AUR_TP146 (0.075 to 1.00)

Name:

msae

Checked by:

South Tiers Development Corporation

Pratt Site Ground Investigation Works



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

RS1377 Part 2 Clauses 9.2 & 9.4 : 1990


Project No: HQAIRIF_AUK_TPI48C

Depth: 1.30

Sample Type & No.: BS

Specific Depth (m): 1.30

Date Tested: 02/10/2020

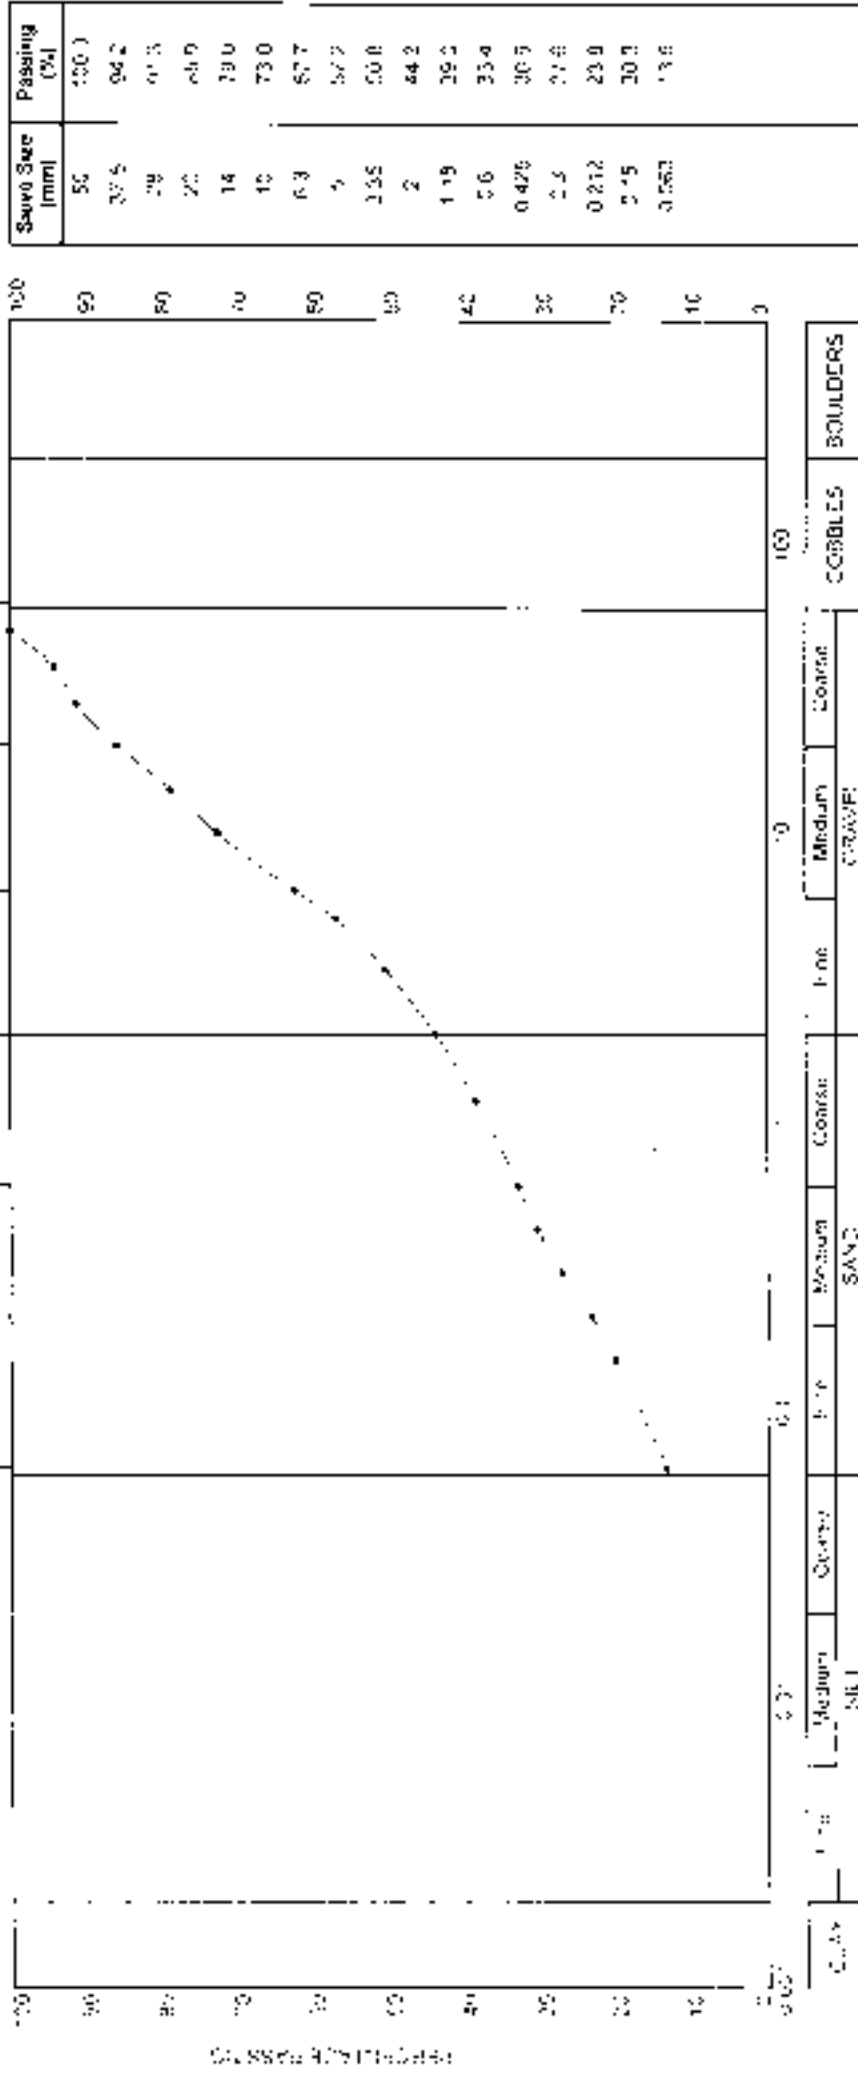

Condition of Sample: As received in the laboratory, Sample Disturbed: Yes

Date of Issue: 02/10/2020

Client No: RS1377 Part 2 Clauses 9.2 & 9.4 : 1990

Signed: *MSB*

Name: *MSB*

Page 1 of 1



Client: Staffs Transport Consultant

Contract Title:

Fig. 9.2.9 Ground Investigation Works

APC Contract No.: 4251

1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

DS 4377 - Part 2 - Clause B 2.8.9.4 : 1990
(Test deviated from standard due to insufficient sample mass)


Laboratory No: PRA RIE_AUK_TP148

Drill No: 1.00

Sample Type & No: B2

Soils Depth (m): 1.00

Date Tested: 19/10/2020

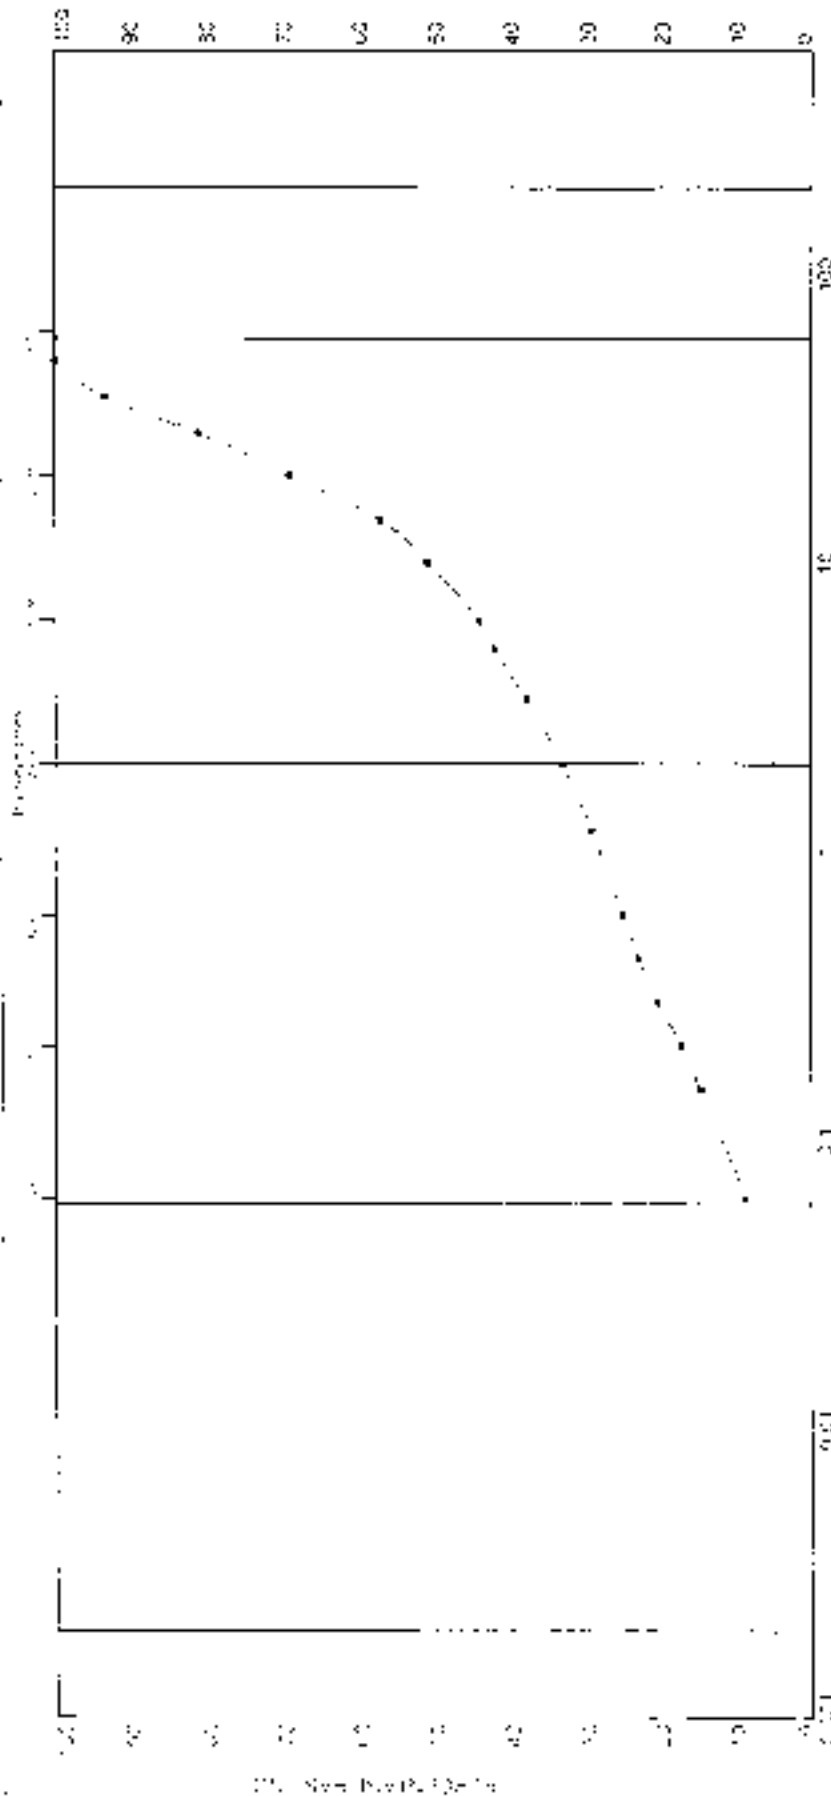

Coarse Sand	Medium Sand	Fine Sand	Coarse Silts
0.075 - 4.75	4.75 - 2.0	2.0 - 0.075	0.075 - 0.002

Sieve Size (mm)	Passing (%)
50	100.0
37.5	93.5
25	91.1
20	80.2
15	67.3
10	51.1
6.3	44.3
5	42.1
3.75	38.0
3	33.5
1.18	29.5
0.5	25.4
0.425	23.2
0.3	20.5
0.25	17.4
0.15	14.2
0.075	9.6

Soils prepared from wet sieving using large sieve size

Client No:

20/10/2020

Soils Test Certificate Description

PSC 425 (PRA) RIE_AUK_TP148 B2: 00

Signed:

Name:

Page 1 of 1



Contract No:

Prime Site Ground Investigation Works

Soils Certificate No: 425

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

RS1377 Part 2 Clause 9.2 & 9.4, 1990


Project No: PRAIRIE_AUK_TP949

Location: 2.20

Sample Type & No.: BS

Specific Description: 2.20

Test Reference: 16/10/2020

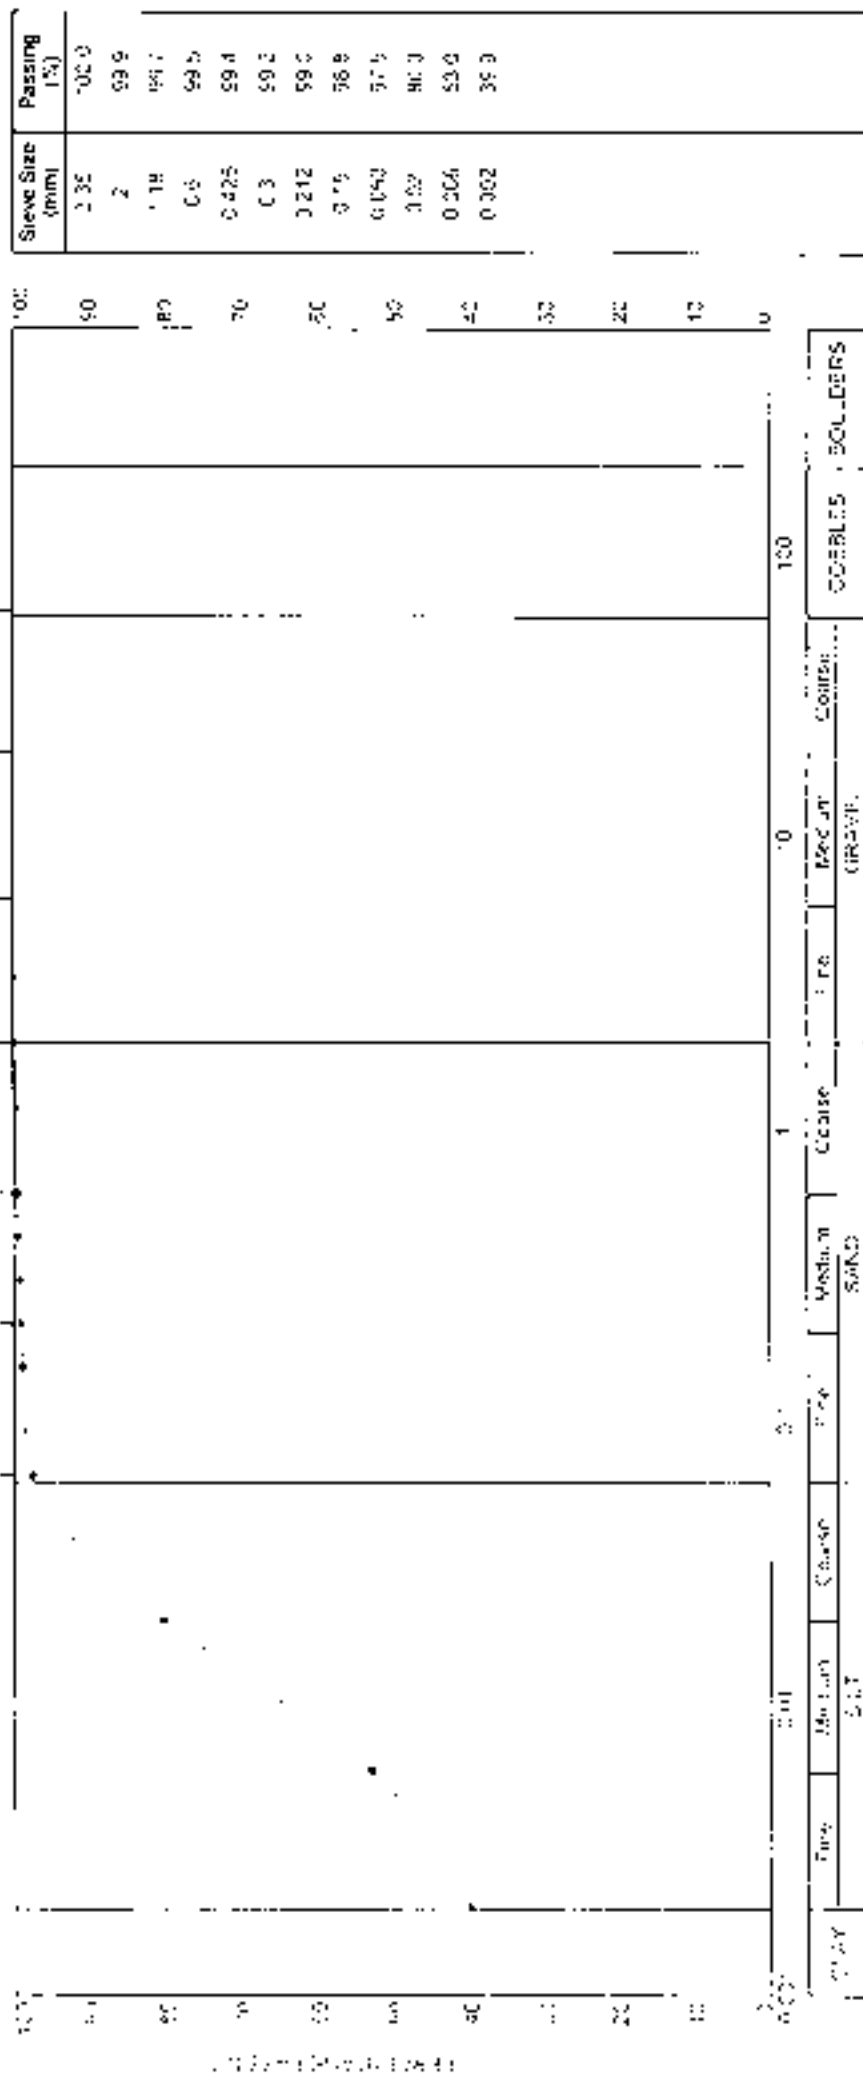

Client No: 19-300

Cell No: 300

Field No: 19-300

Sample No: 19-300

Sheet No: 1

Sample Name: MSONO

Frame:

Page 1 of 1



Soil Tests Development Group

Quality T.C.

Frame Sale Contract Investigation Works

AEG Contract No: 4291

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

051377 - Part 2 - Clause 9.2 & 9.4 - 1990
 (Test deviated from standard due to insufficient sample mass)


Client: **PRINIE AUK TP160**

Depth: **0.60**

Sample Type & No: **B2**

Soil Depth (m): **0.60**


Date Tested: **15/10/2023**

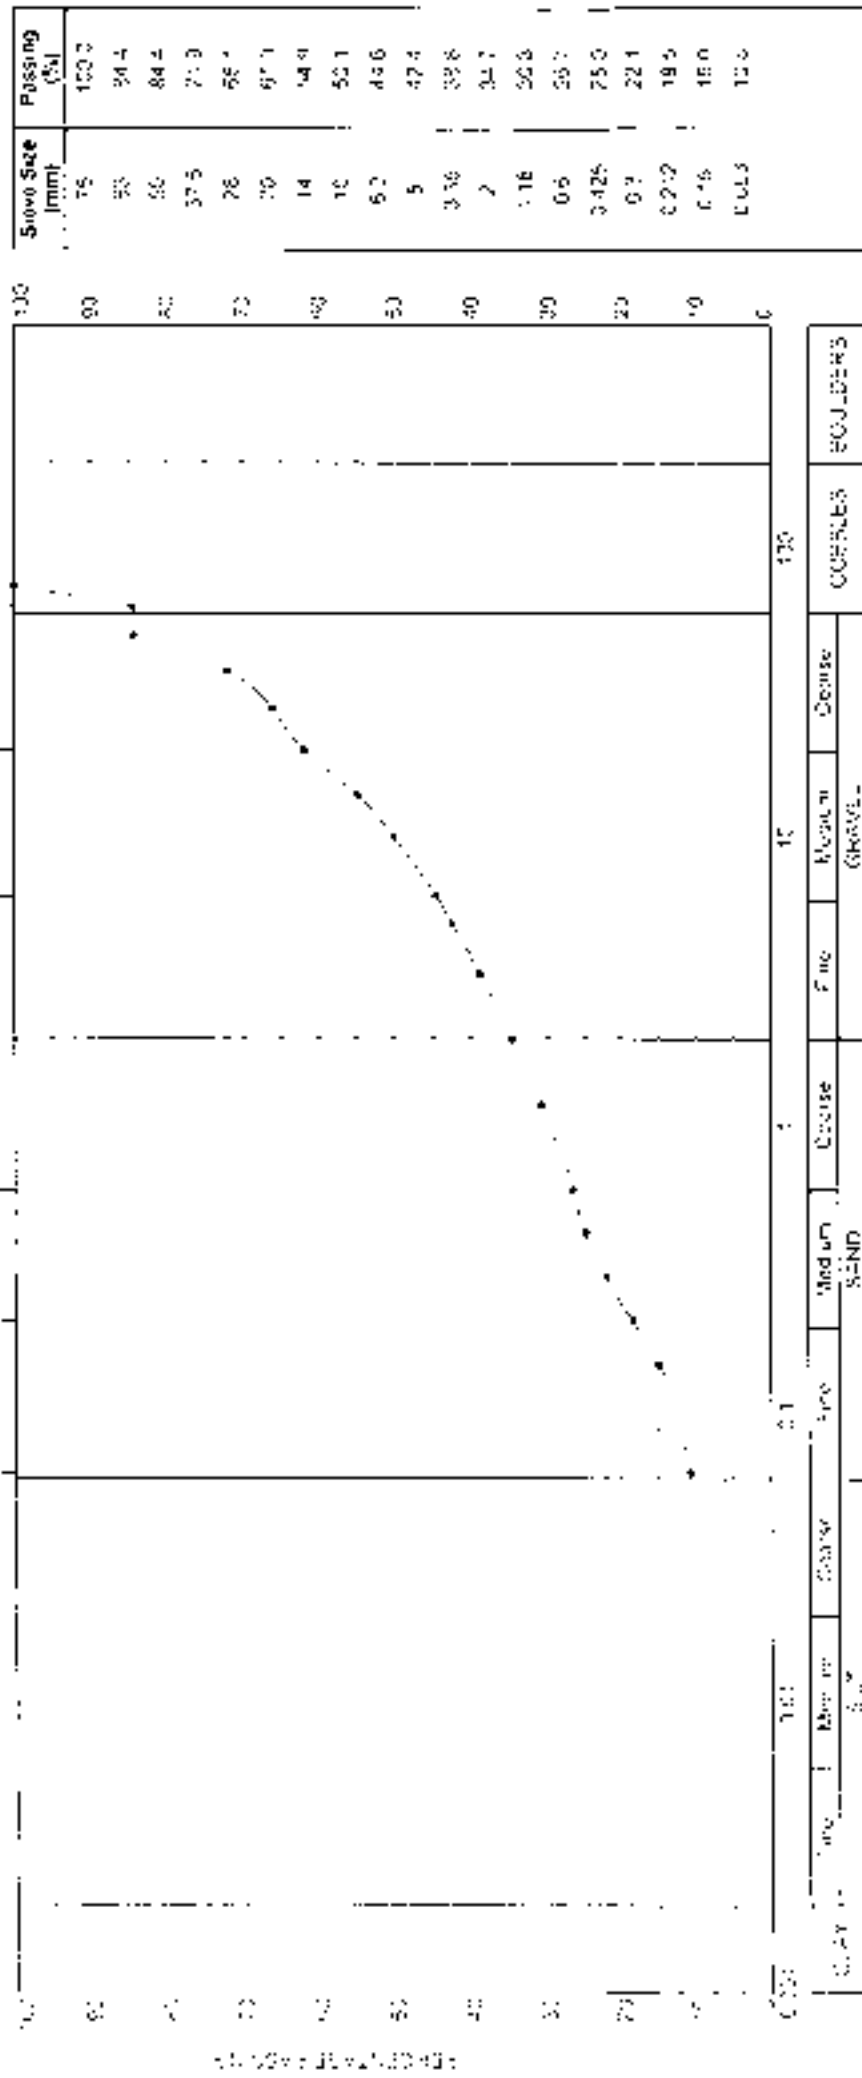

CLAY	FINE SAND	MEDIUM SAND	COARSE SAND	GRAVEL	CORNER	SOILS

Soil Classification: **SP-SM**

Drawn: **AS**
 Checked: **AS**
 Date: **15/10/2023**
 Scale: **1:1**
 Project: **PRINIE AUK TP160 B2-05C**
 Location: **None**
 Signed: **MS**
 Contract Title: **Contract Title**
 Client: **PRINIE AUK TP160**
 Scale: **1:1**



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

NS1077 - Part 2 - Clause 9.2.4.9.4 - 1990
 (Test deviated from standard due to insufficient sample mass)


Client Name: **PROAIRIE_AUR_TP155**

Depth (m): **0.50**

Sample Type & No.: **B2**


Specific Depth (m): **0.50**

Date Tested: **19/10/2020**

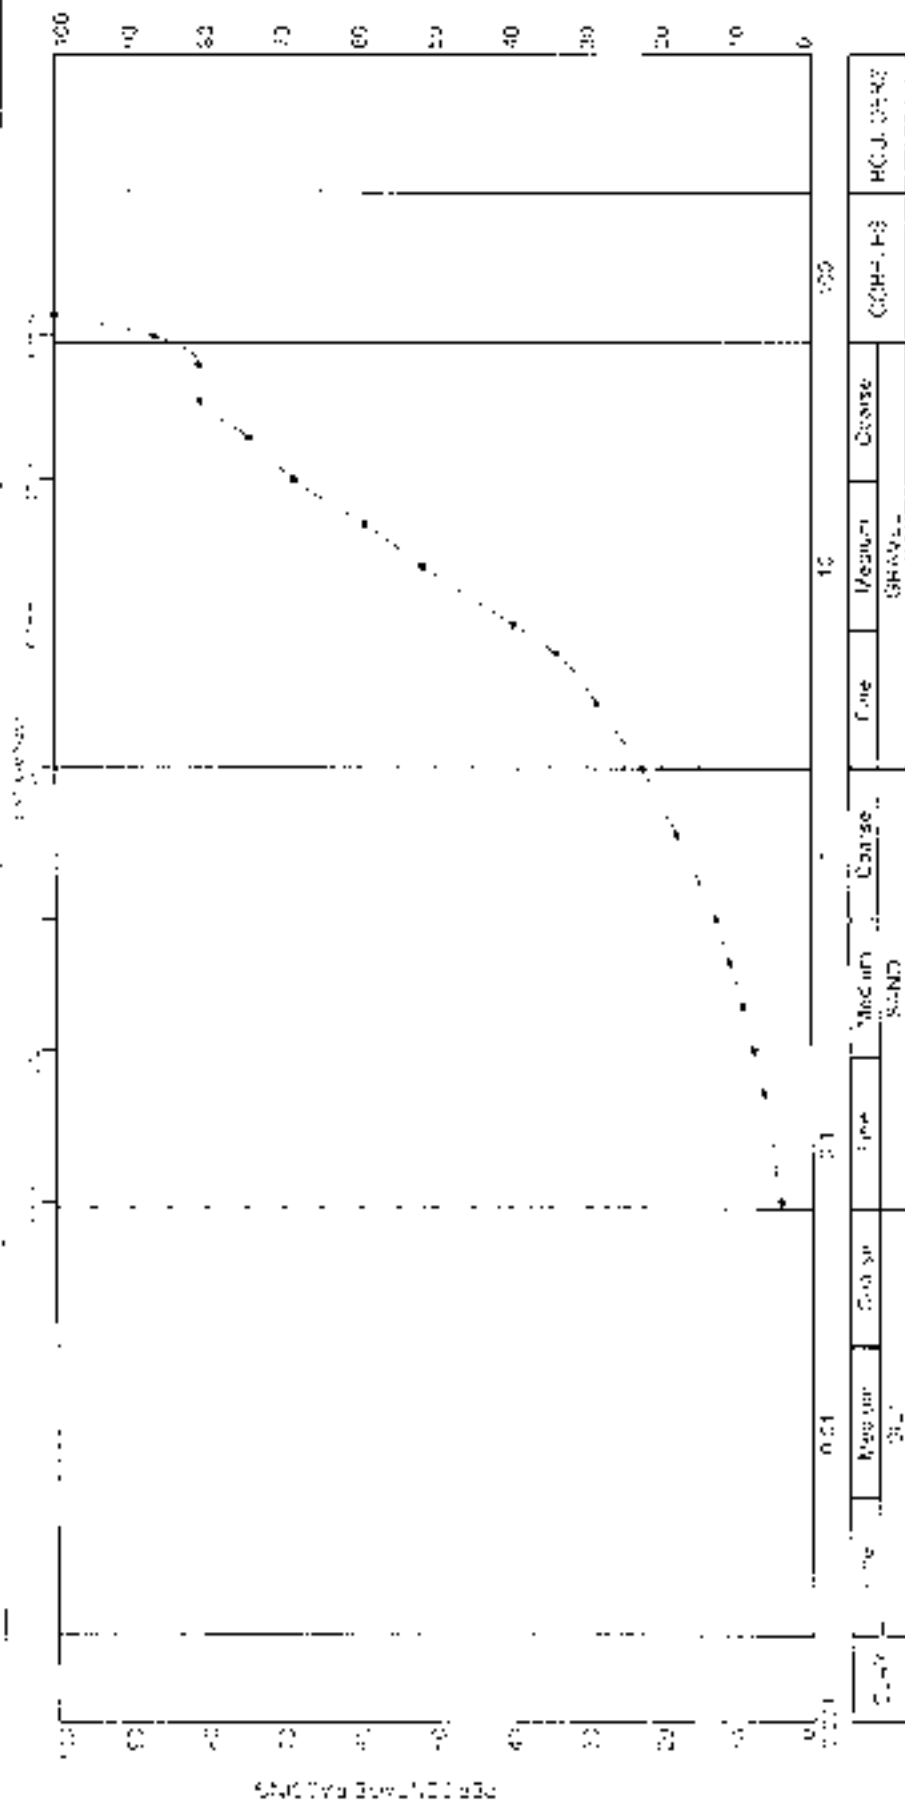

Coarse	Fine	Medium	Coarse	Coarse	Coarse	Coarse	Coarse

Percentage of sample passing through sieve at 0.075 mm is 100%



Date of Issue: **20/10/2020**
 Drawn: **South West Engineering Corporation**

Client Code No.: **PSD 4251-PROAIRIE_AUR_TP155-B2-0.50**
 Signed: **MSA**
 Checked By: **MSA**

Page 1 of 1
 AEGS Contract No: **4251**



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

DS1377 Part 2 Clause 9.2 & 9.4: 1990


Project No: **PHOENIX AUK TP155**

Depth: **1.60**

Sample Type: **3 No. BS**

Specific Depth: **1.60**

Date Test: **14/10/2020**

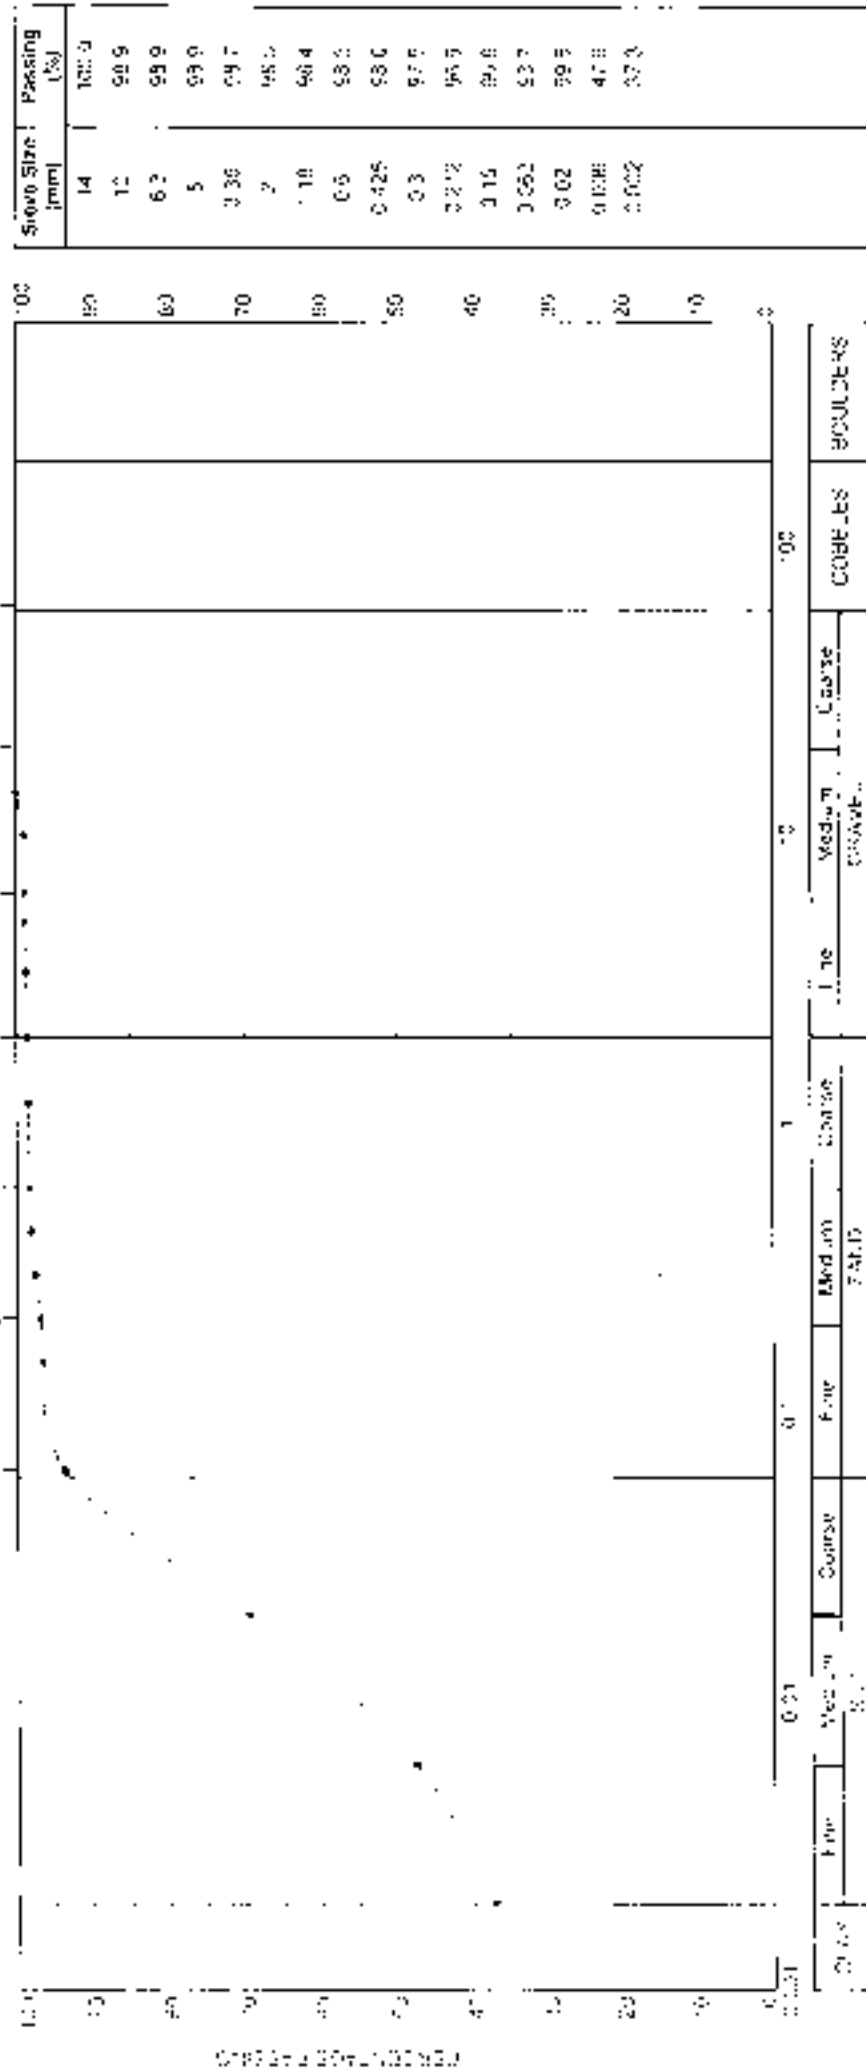

Date of Issue: **23/10/2020**

Client Code: **690400**

Client Name: **PHOENIX AUK TP155**

Client Address: **60**

Client Contact: **4252**



Client Name: **PHOENIX AUK TP155**

Client Address: **60**

Client Name: **MSR**

Client Name: **MSR**

Client Contact: **4252**

Client Name: **PHOENIX AUK TP155**

Client Address: **60**

Client Name: **MSR**

Client Name: **MSR**

Client Contact: **4252**

Client Name: **PHOENIX AUK TP155**

Client Address: **60**

Client Name: **MSR**

Client Name: **MSR**

Client Contact: **4252**

Client Name: **PHOENIX AUK TP155**

Client Address: **60**

Client Name: **MSR**

Client Name: **MSR**

Client Contact: **4252**

Client Name: **PHOENIX AUK TP155**

Client Address: **60**

Client Name: **MSR**

Client Name: **MSR**

Client Contact: **4252**

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

NS1377 Part 2 - Clause 9.2 R 9.4 : 1990
(Test deviated from standard due to insufficient sample mass)


Project Name: PHAHLIA_AUK_TPI36A

Depth: 0.70

Sample Type: S10 - B4

Specific Dependent: 0.70

Date Tested: 15/10/2020

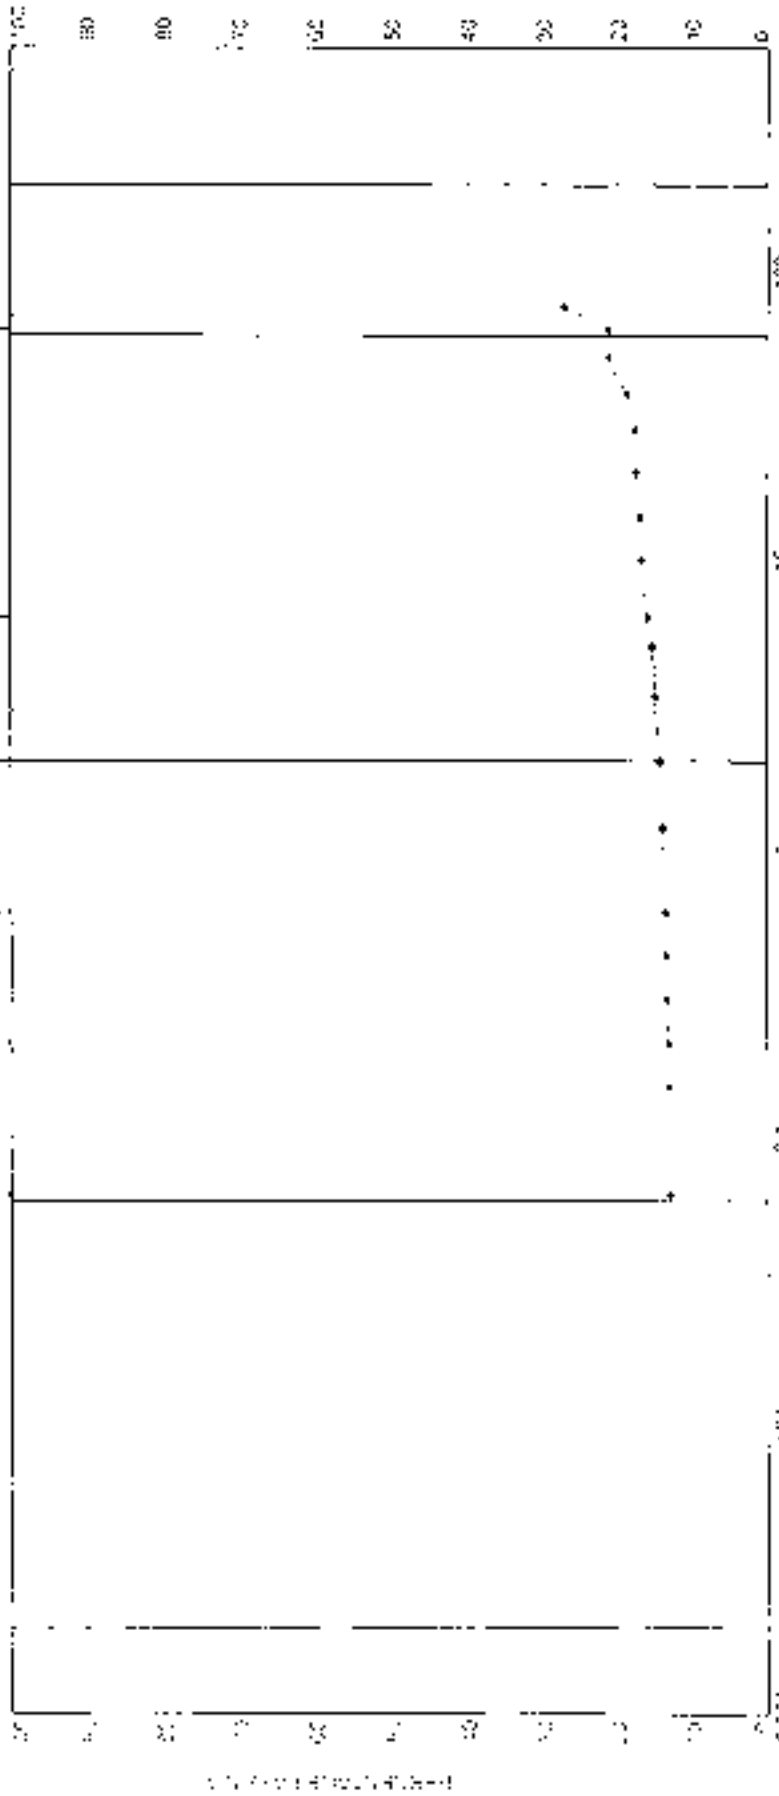

Coarse	Medium	Coarse	Medium	Coarse	Coarse	Coarse	Coarse
SAND		GRAVEL		COBBLES			



Client Name: PSD 425 - PHAHLIA_AUK_TPI36A B4.10 - Superficial
 Client Address: 1000-1000
 Client Contact: 0800 765 765

Analyst Name: *Mason*

Page: 1 of 1
 Report No: AEG-001-2020-04251




1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377, Part 2: Clause 9.2 & 9.4 1990
(Test deviated from standard due to insufficient sample mass)

Project File No: PRAIRIE_AUK_TP162 Sample No: 02 Specific Depth (m): 0.90 Date Tested: 30/09/2020

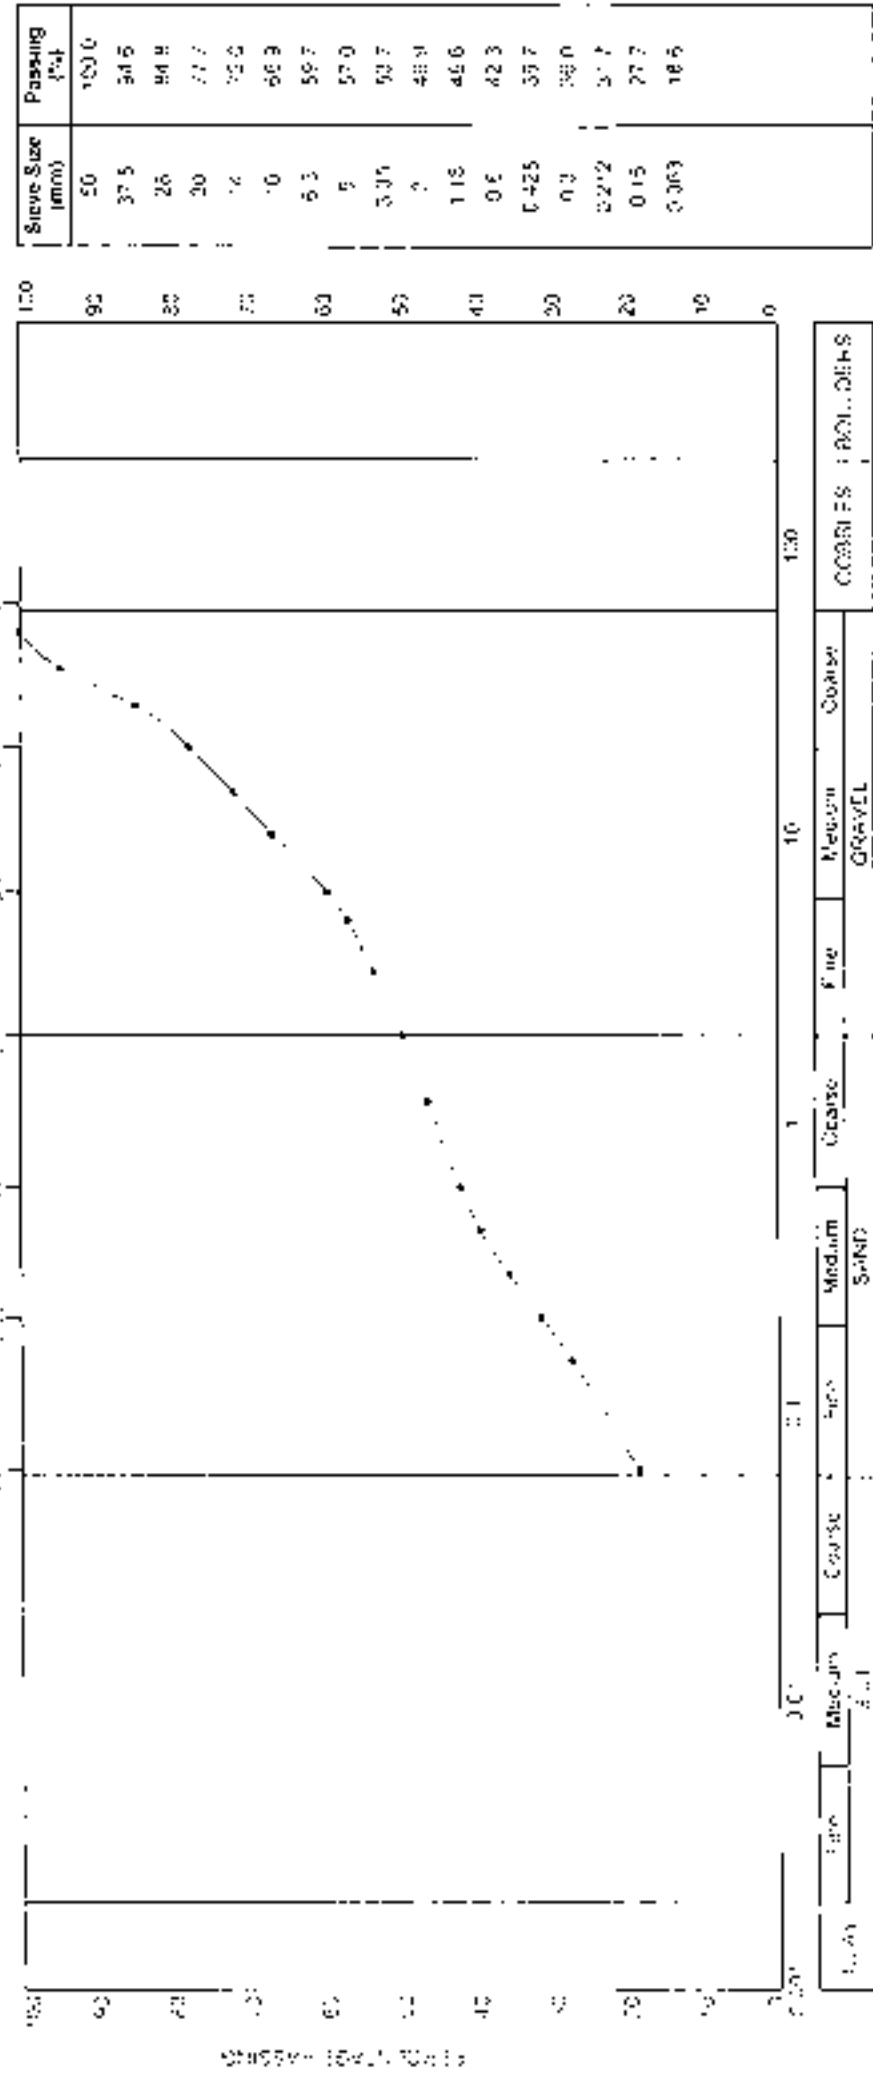

Drawn by: [Signature] Date: 20/10/2020 Control No: [Signature]

Checked by: [Signature] Date: [Signature] Control Title: [Signature]

South Tiers Quaternary Consultant Prairie Site Ground Investigation Works

Page 1 of 1

AEC Control No: 4251

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 - Part 2 - Clause 9.2 & 9.4 : 1990


Location: No. 1 PRAIRIE, AUK, TP162

Depth: 2.50

Sample Type & No.: BS

Specific Depth (m): 2.50

Date tested: 20/09/2020

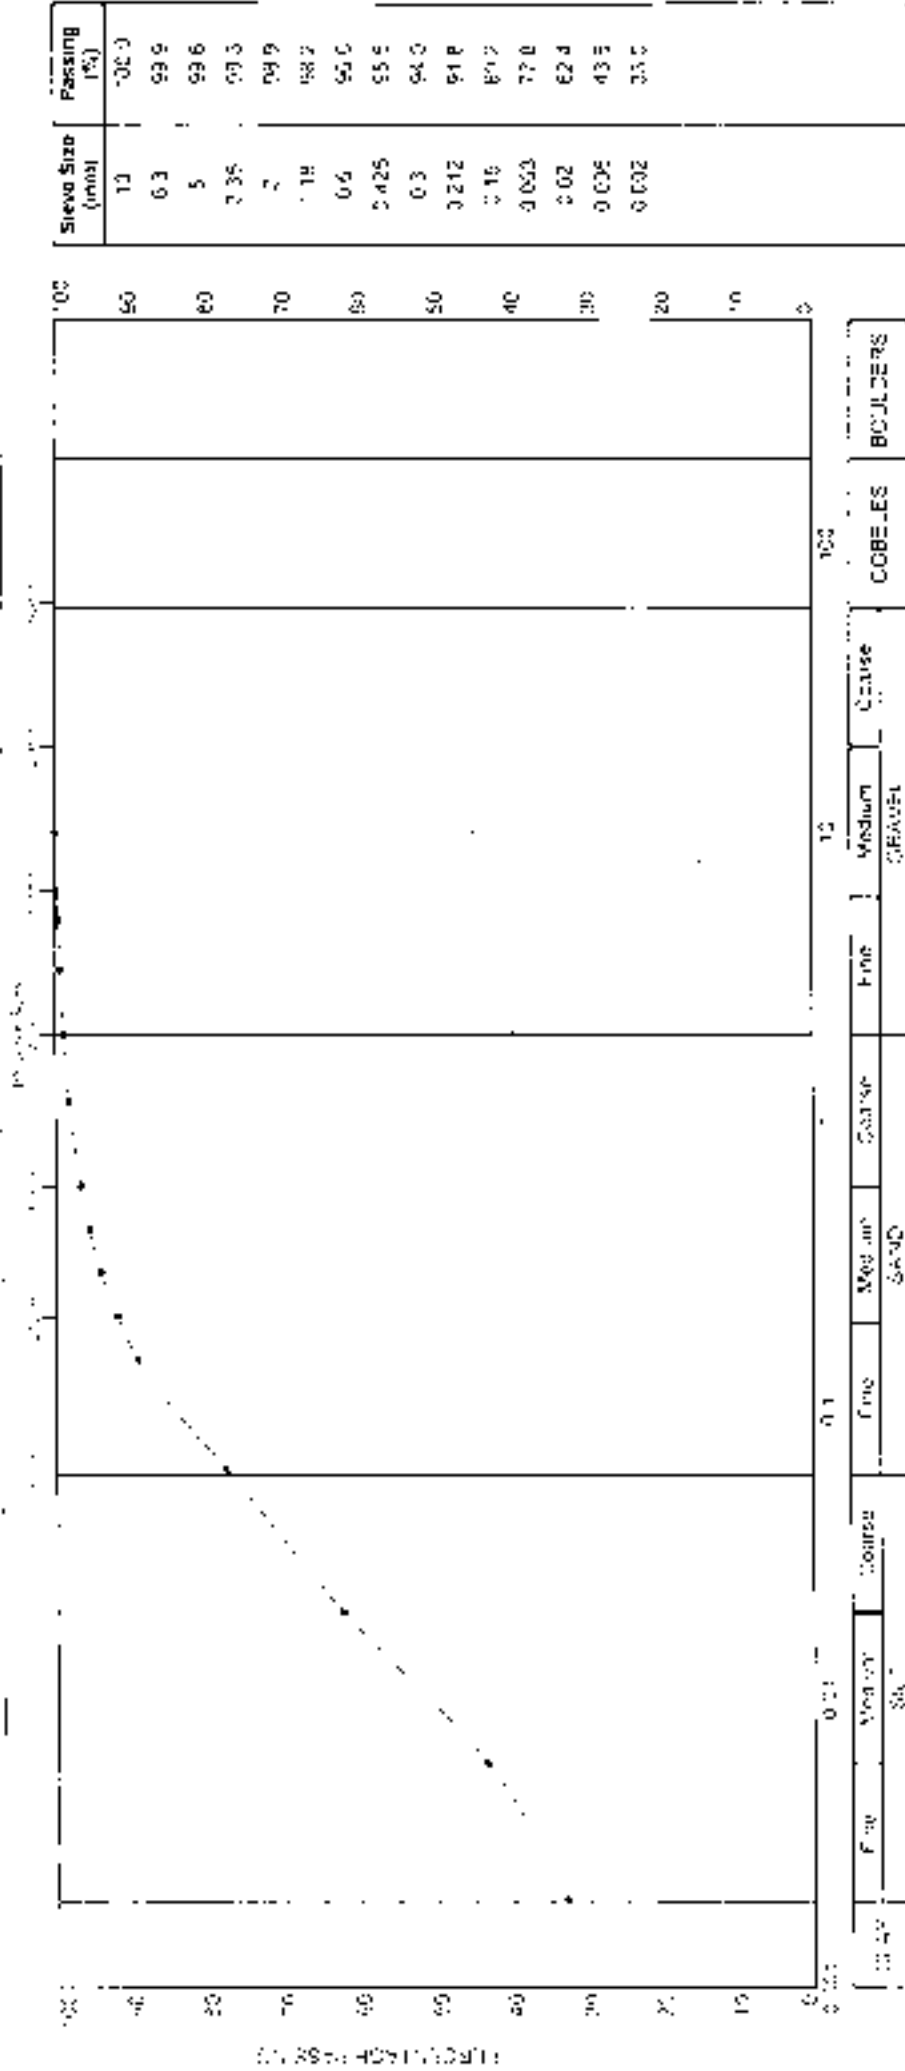

Comments: This test result is preliminary and subject to audit.



Date of Issue: 20/09/2020
 Certificate No.: PSD-125-1-PR-16-AUK-TP162-BS-2-50-5-grain
 Client: South West Coast Cement Co. (P) Ltd
 Contactable: [Redacted]
 Name: MSONE
 Page 1 of 1
 AEG Contract No: 4201
 Full Name Group: Westpac Work

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 Part 2 - Clause 9.2 B.9.4 1990


Project Name: PRAIRIE_AUK_IP103

Depth: 0.80

Sample Type & No: B2

Specific Depth (m): 0.80

Date Tested: 05/10/2020

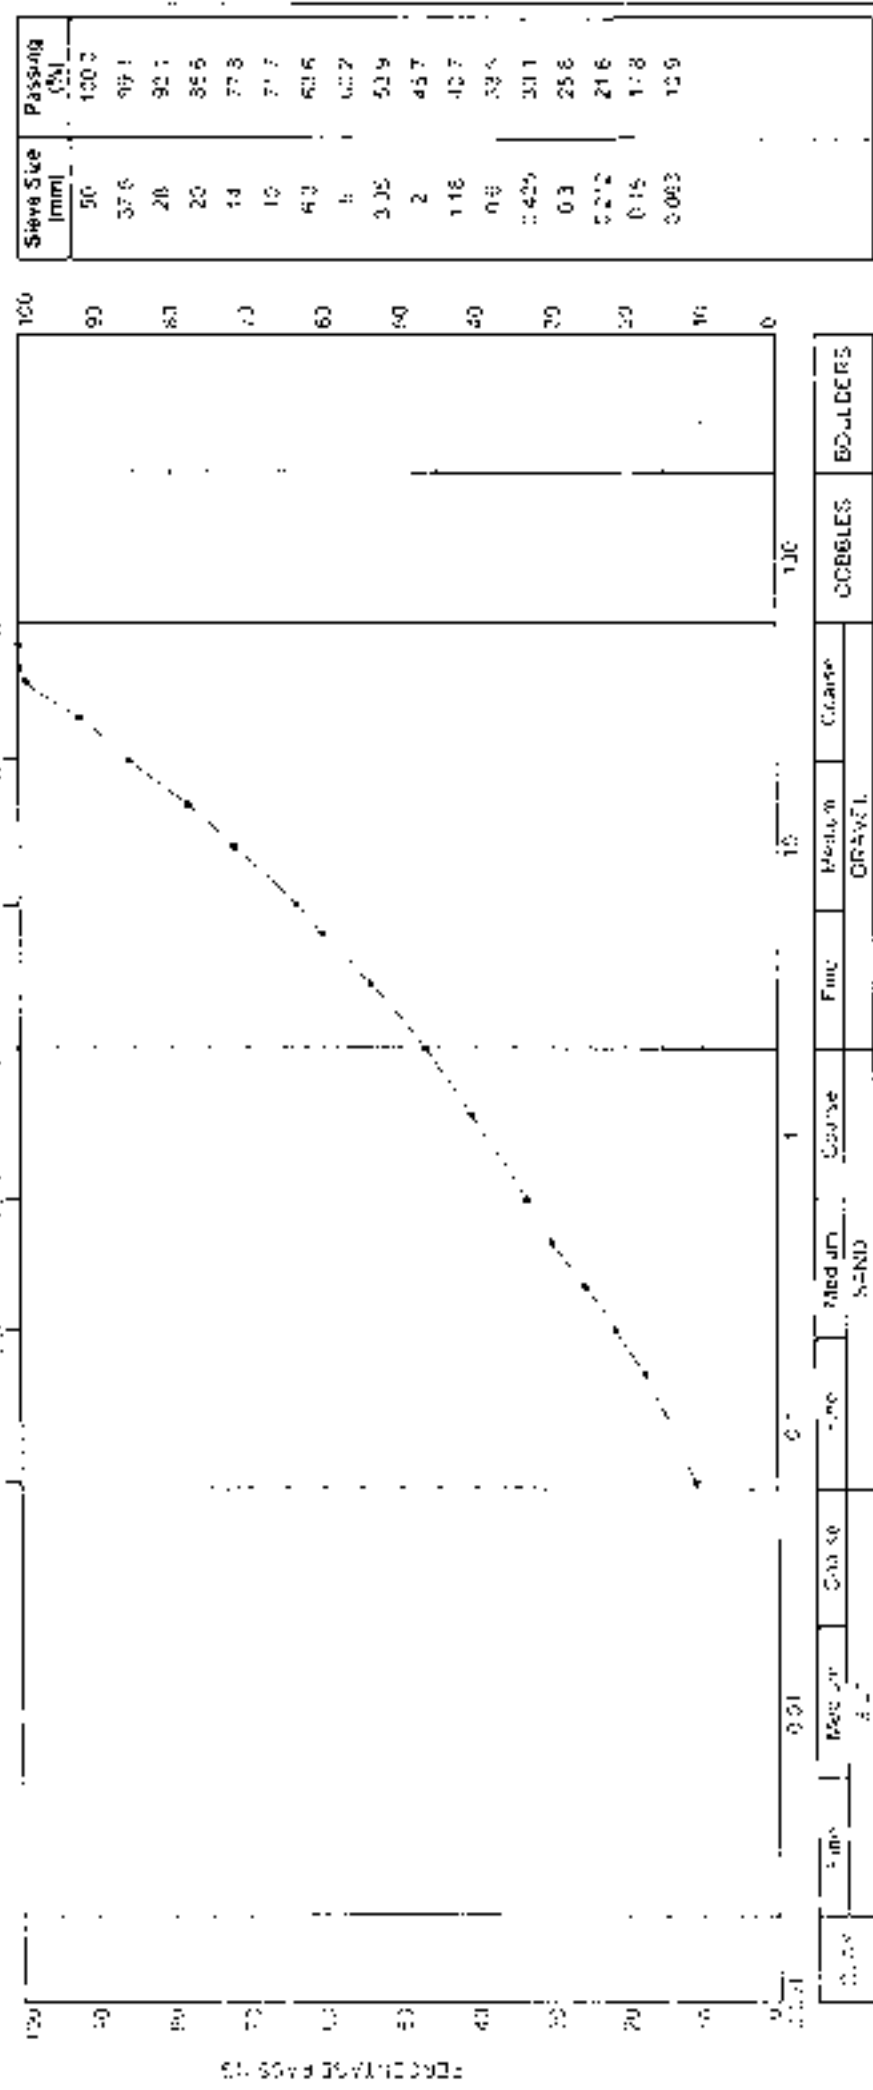

This report is valid only for the laboratory Sample Description Sheet

Date of Issue: 20/10/2020
 Client: Geotechnical Department, Canterbury University
 Project Name: PRAIRIE_AUK_IP103
 Specific Depth (m): 0.80
 Sample Type & No: B2
 Contact Title: *msore*

Page 1 of 1
 AEG Central File: 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED


Head Office: 15, Northwood Road, Northwood, Greater London, NW20 7JG, UK. Tel: 0191 353 4330 Fax: 0191 367 4716
Regional Offices: 1st Fl, 21, St. Andrew's Street, London, EC4A 3DF, UK. Tel: 01753 336 330 Fax: 01753 738 909

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

(Test deviated from standard due to insufficient sample mass)

Explanatory Hole No - PRAIRIE_AUK_TP165 Depth (m) - 1.80 Sample Type & No - B5 Specific Depth (m) - 1.80 Date Tested - 01/10/2020

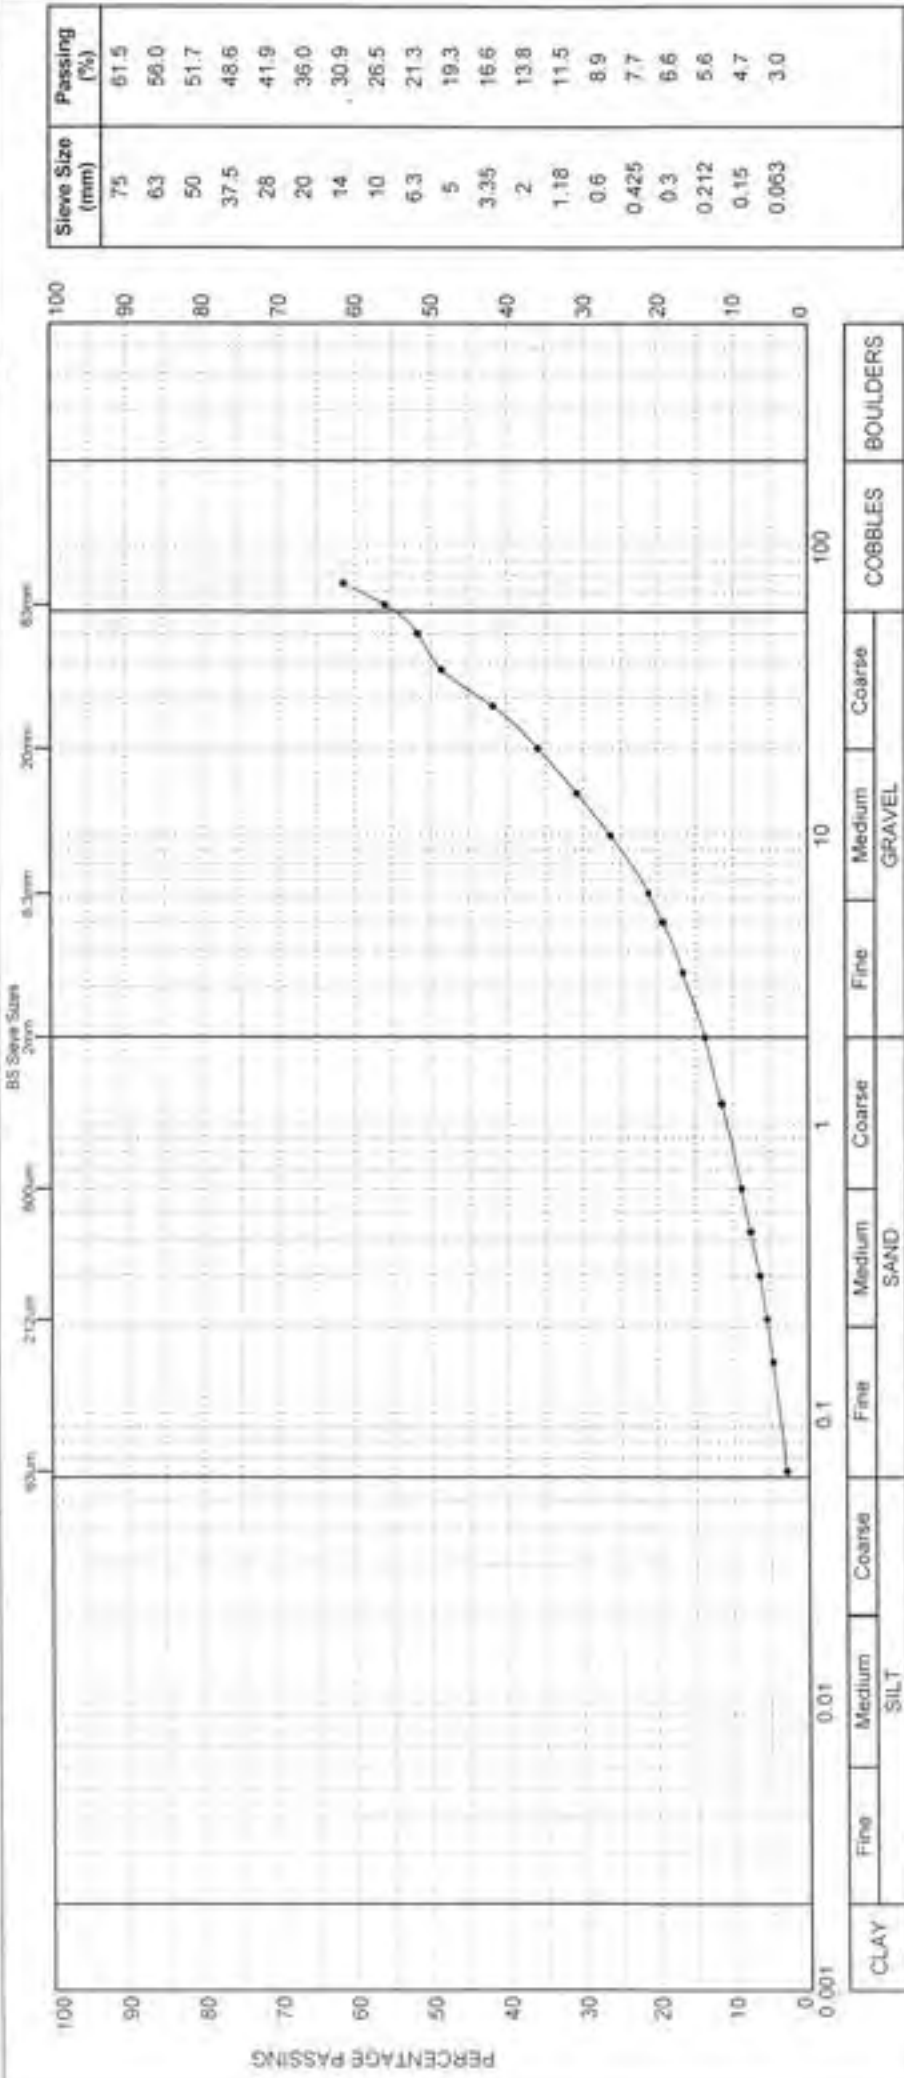

For description of sample please refer to the Laboratory Sample Description Sheet

Date of issue - 20/10/2020	Certificate No - PSD4251/PRAIRIE_AUK_TP165/B5/1 80	Signed - <i>msore</i>	Name - <i>SELKIRK</i>	Page 1 of 1
Client - South Tees Development Corporation	Contract Title - Prairie Site Ground Investigation Works	AEG Contract No - 4251		




ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clauses 9.2 & 9.4 : 1990
(Test deviated from standard due to insufficient sample mass)

Project No: **FRAIRIE_AUK_1P165** Department: **2.80** Sample type & no: **B7** Specific Depth (m): **2.80** Date Tested: **30/08/2020**

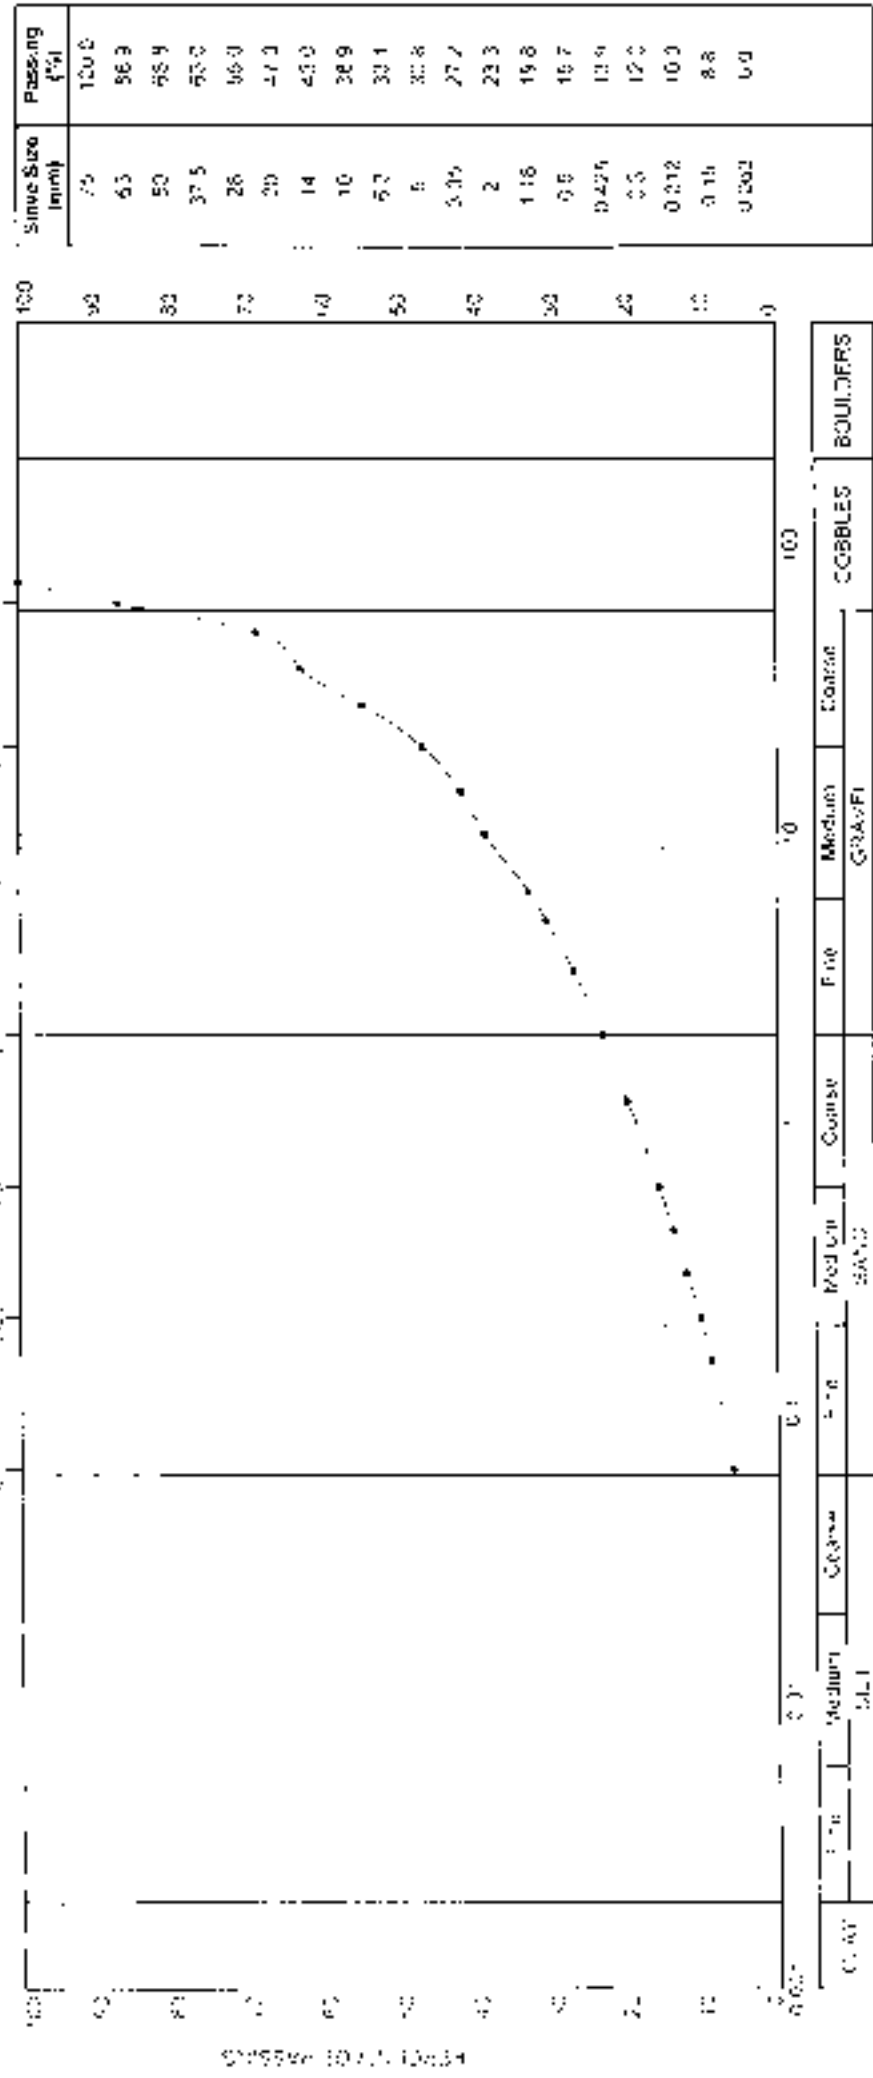

Soil description of sample is as per notes to the left of the table. (Sample Description: Clay)



Page 1 of 1
ACGS Contract No: 4251

Date of Issue: 20/08/2020
Contract Title: _____


Certificate Ref: 95114251 P0423 E AUC 11165 (S.G. 2.80)
Name: _____

Client: South Tyneside Council
Project Site: Ground Investigation Works

Signature: *msone*
Contract Title: _____

Author: _____
Contract Title: _____

Client: South Tyneside Council
Project Site: Ground Investigation Works



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 - Part 2 - Clause 9.2 & 9.4 - 1990
 (Test deviated from standard due to insufficient sample mass)


Logbook Number: **PRMRE AUK TP167**

Depth (m): **1.80**

Sample Type & No.: **B4**

Specific Gravity: **1.80**

Date Tested: **30/08/2020**

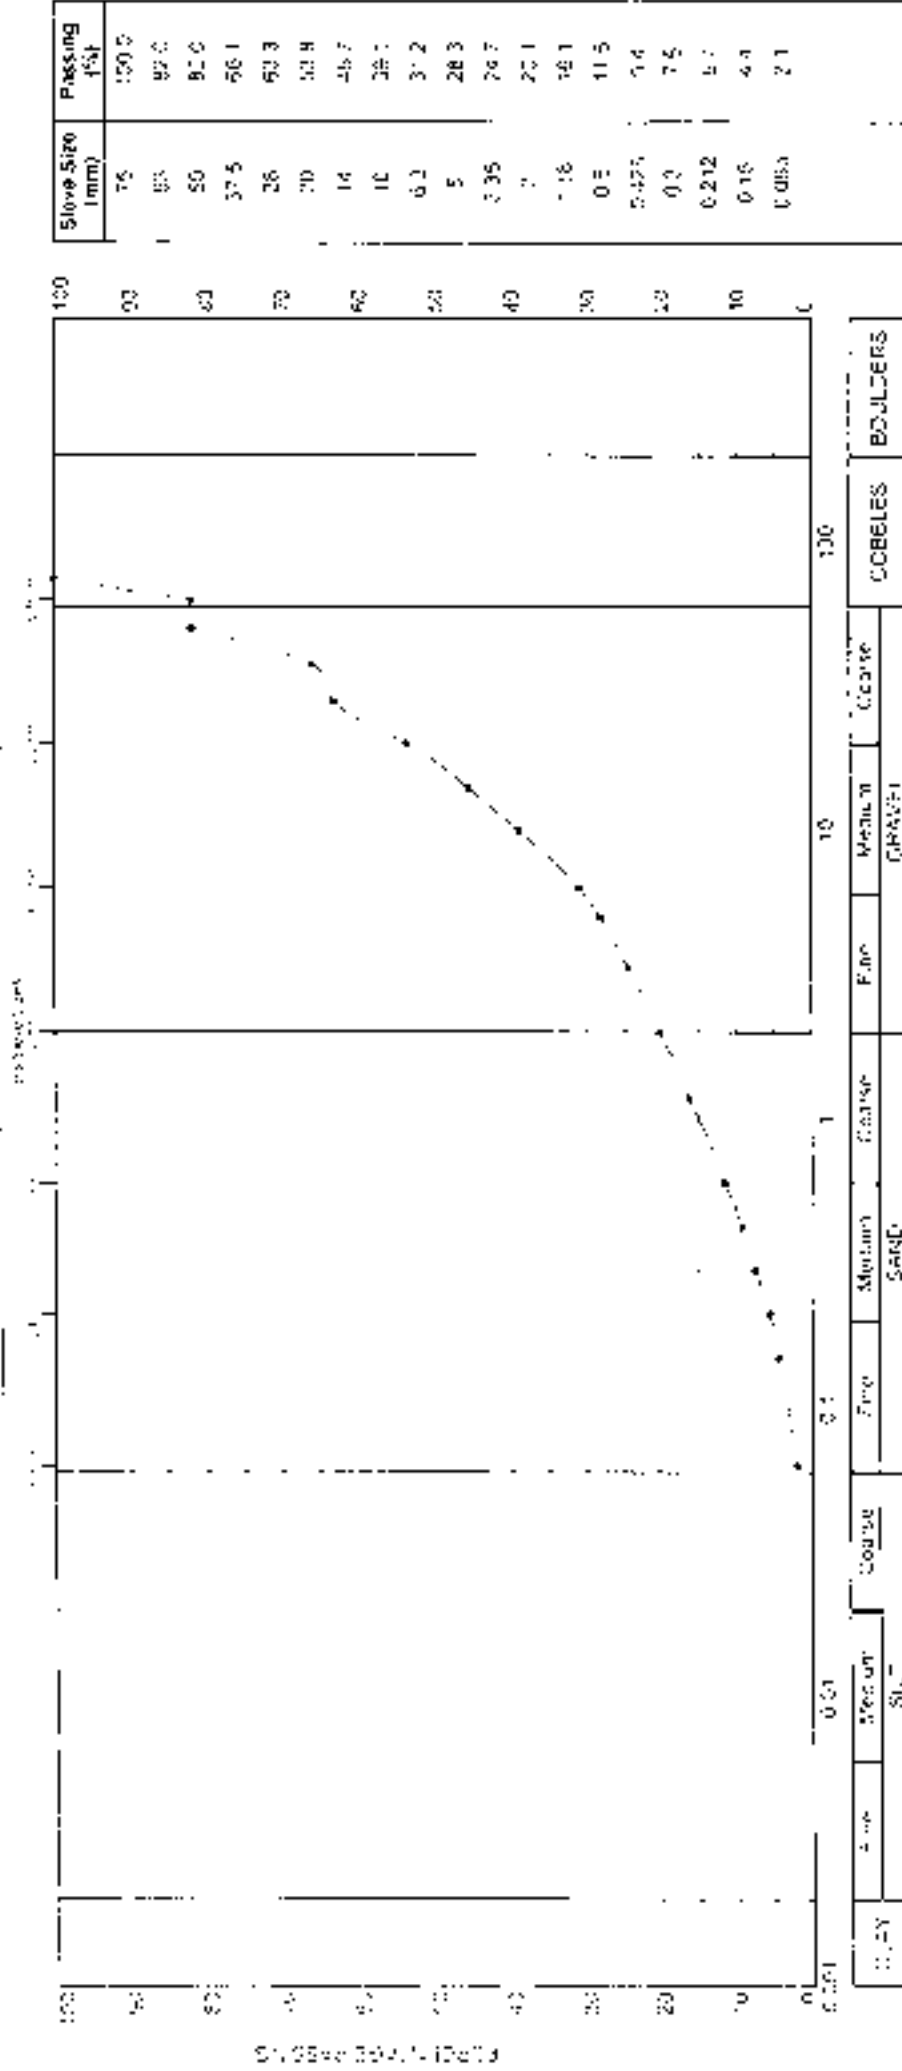

Coarse	Medium	Coarse	Fine	Medium	Coarse	Coarse	COBBLES	BOULDERS
75	150	300	600	1.18	2.5	5	20	75
0	0	0	0	0	0	0	0	0

Consolidation of sample possible during laboratory Sieve Test on Steel

Date of Issue: **21/10/2020**

Client Code: **40**

Project: **PRMRE AUK TP167**

Signer: **MSone**

Name: **MSone**

Contract No: **4201**

Page 1 of 1

Page 1 of 1



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 Part 2, Clauses 9.2 & 9.4 : 1990


Lot Code / Sample No : PRAIRIE AUK_TP168

Depth (m) : 1.80

Sample Type & No : B7

Specific Gravity (m) : 1.60

Date Tested : 30/09/2020

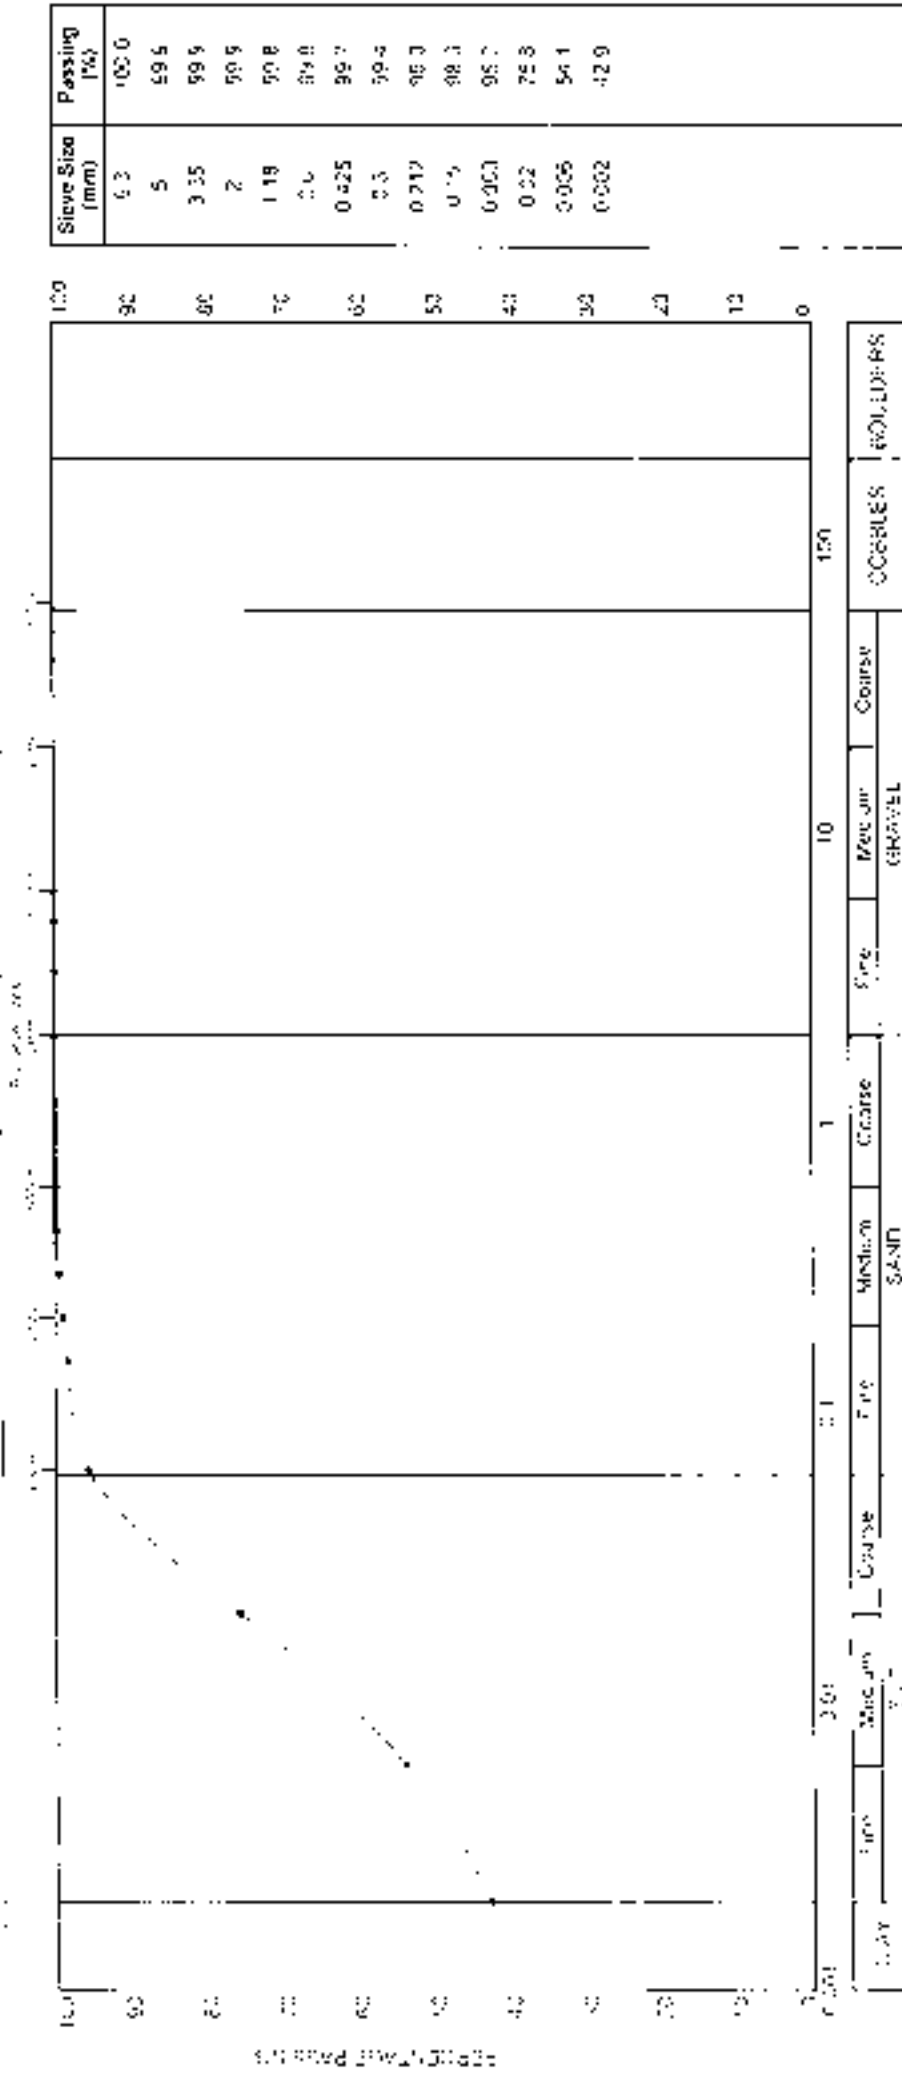

Layer	Top	Bottom	Course	Material	Course	Material	Course	Material	Course	Material
				Fine		Coarse		Medium		SAND
										GRAVEL
										COBBLES
										BOULDERS

For description of nature of each type of soil, refer to appropriate part of description sheet

Order No: 10-0020

Contract No: 4251

Client: South Tees Development Corporation

Contract Title:

Name:

Misra



ALLIED EXPLORATION & GEOTECHNICS LIMITED


Head Office: 144-20, Salsburgh Drive, Easingwold, East Yorkshire, YO21 2SE, Tel: 01753 851500 Fax: 01753 861474
Regional Office: 144-20, Salsburgh Drive, Easingwold, East Yorkshire, YO21 2SE, Tel: 01753 755500 Fax: 01753 755500

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

(Test deviated from standard due to insufficient sample mass)

Exploratory Hole No :- PRAIRIE_AUK_TP169	Depth (m) :- 0.80	Sample Type & No :- B2	Specific Depth (m) :- 0.80	Date Tested :- 29/09/2020
--	-------------------	------------------------	----------------------------	---------------------------

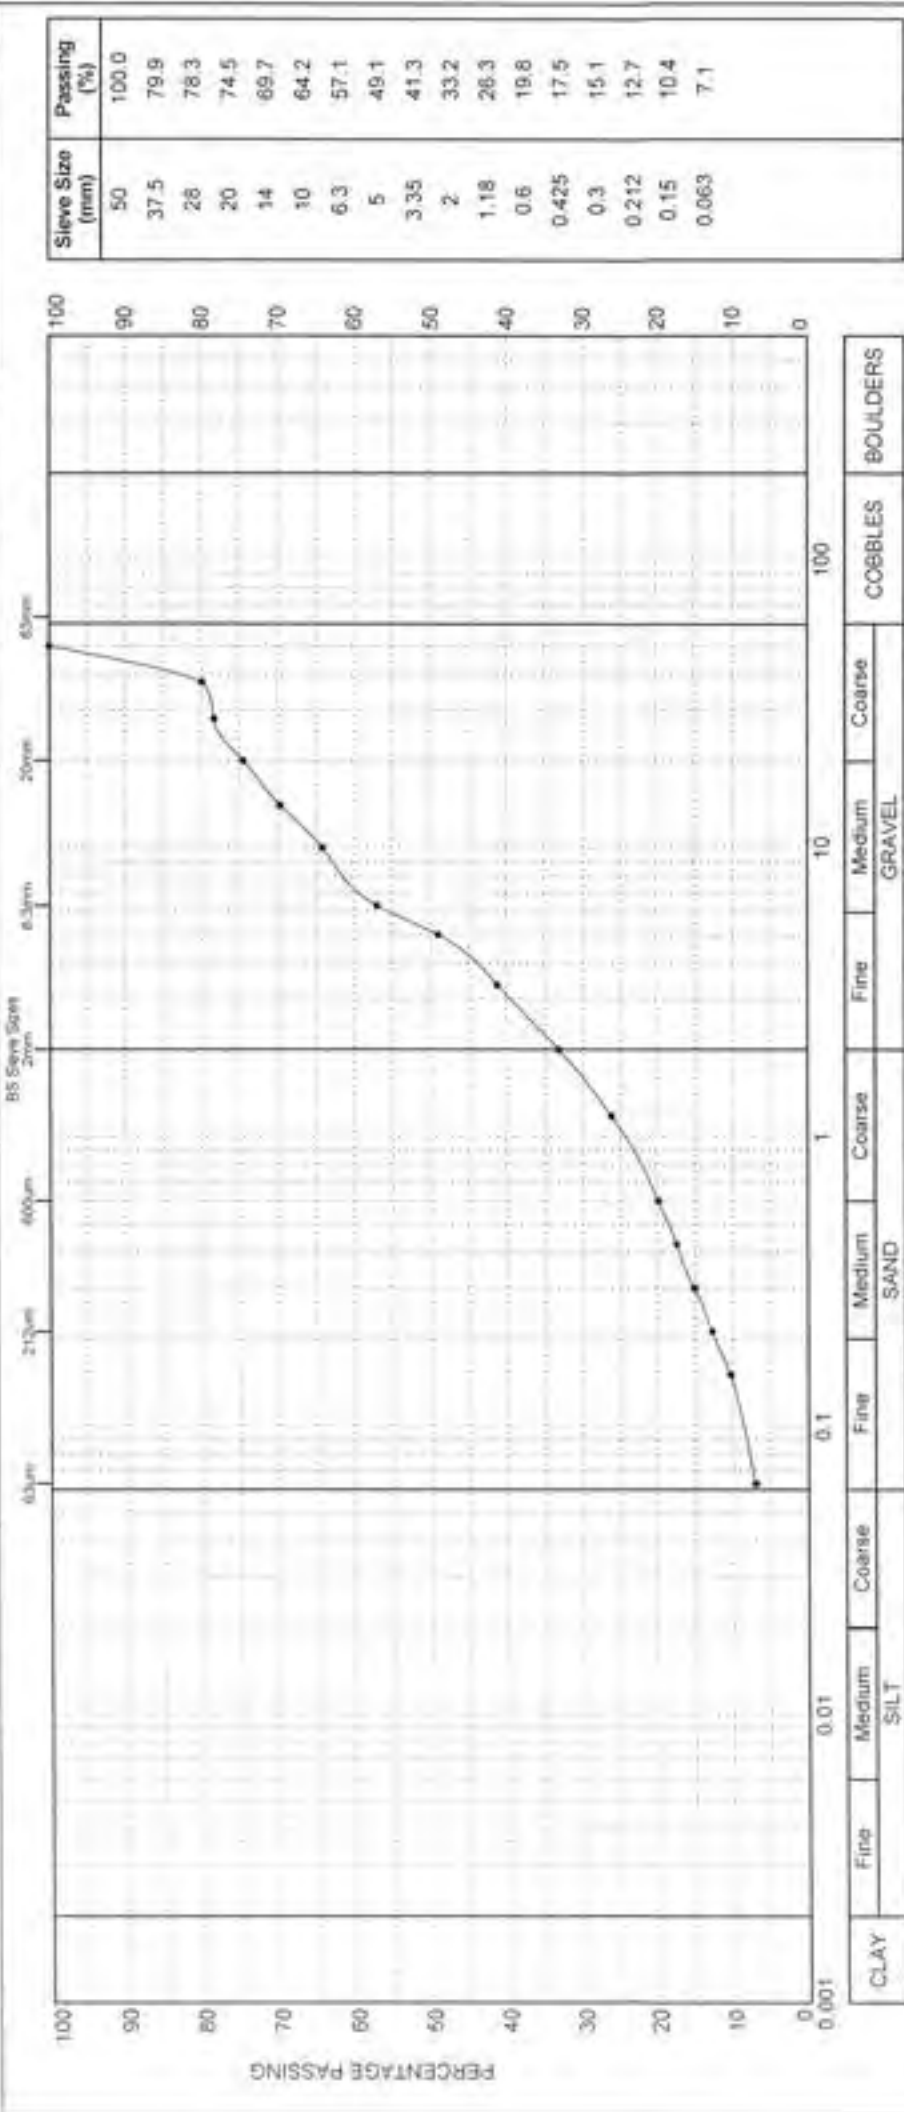

For description of sample please refer to the Laboratory Sample Description Sheet.

Date of issue :- 20/10/2020	Certificate No :- PSD/4251/PRAIRIE_AUK_TP169/B2/0.80	Signed :- <i>msone</i>	Name :- SELKIRK	Page 1 of 1
Client :- South Tees Development Corporation	Contract Title :- Prairie Site Ground Investigation Works	AEG Contract No :- 4251		




ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 - Part 2 : Clauses 9.2 & 9.4 - 1990
 (Test deviated from standard due to insufficient sample mass)

Eng. Certificate No: **PREMIRE AOKI TP172** Exp. No.: **060** Sample Type: **6710 - B2** Specific Depth: **0.60** Date Tested: **01/11/2020**

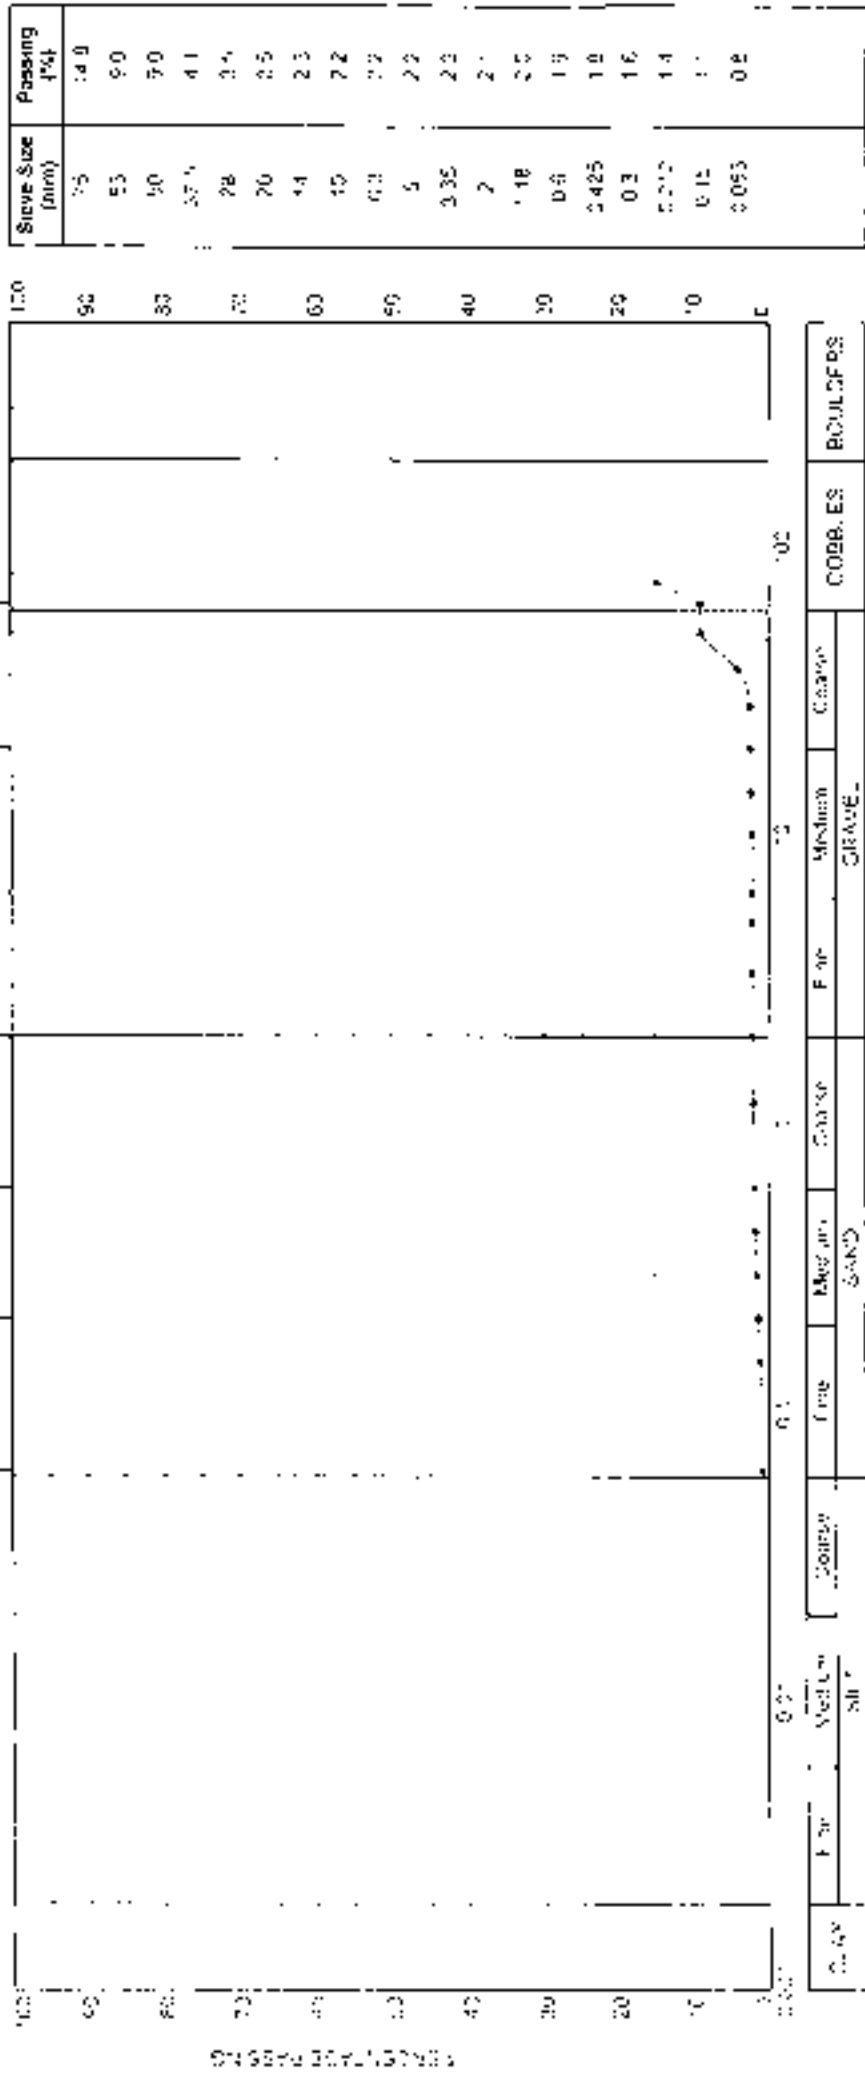

Coarse	Fine	Medium	Coarse	Fine	Medium	Coarse	Coarse	ES	ROULDFOS

Soil description: **SAND** Material: **STEEL**

Date of Issue: **20/10/2020**
 Certificate No.: **15047581 PREMIRE AOKI TP172 DS 003**
 Issued by: **PREMIRE AOKI TP172 DS 003** Signed: **[Signature]** Name: **[Name]**



Page 1 of 1
 AEG Certificate No: **425**



Control: **Geotechnical Development Corporation**
 Project Site Ground Investigation Works


ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 100/110 Greenfield Estate, Park Road, Chester-le-Street, Gateshead, Tyne and Wear, NE12 8JQ. Tel: 0191 357 4700 Fax: 0191 367 4716
Regional Office: 107/25, Blenheim Commercial Centre, Blenheim Road, Macclesfield, Cheshire, SK11 5LJ. Tel: 01753 735 300 Fax: 01753 735 999

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

Exploratory Hole No :- PRAIRIE_AUK_TP173	Depth (m) :- 0.80	Sample Type & No :- B2	Specific Depth (m) :- 0.80	Date Tested :- 30/09/2020
--	-------------------	------------------------	----------------------------	---------------------------

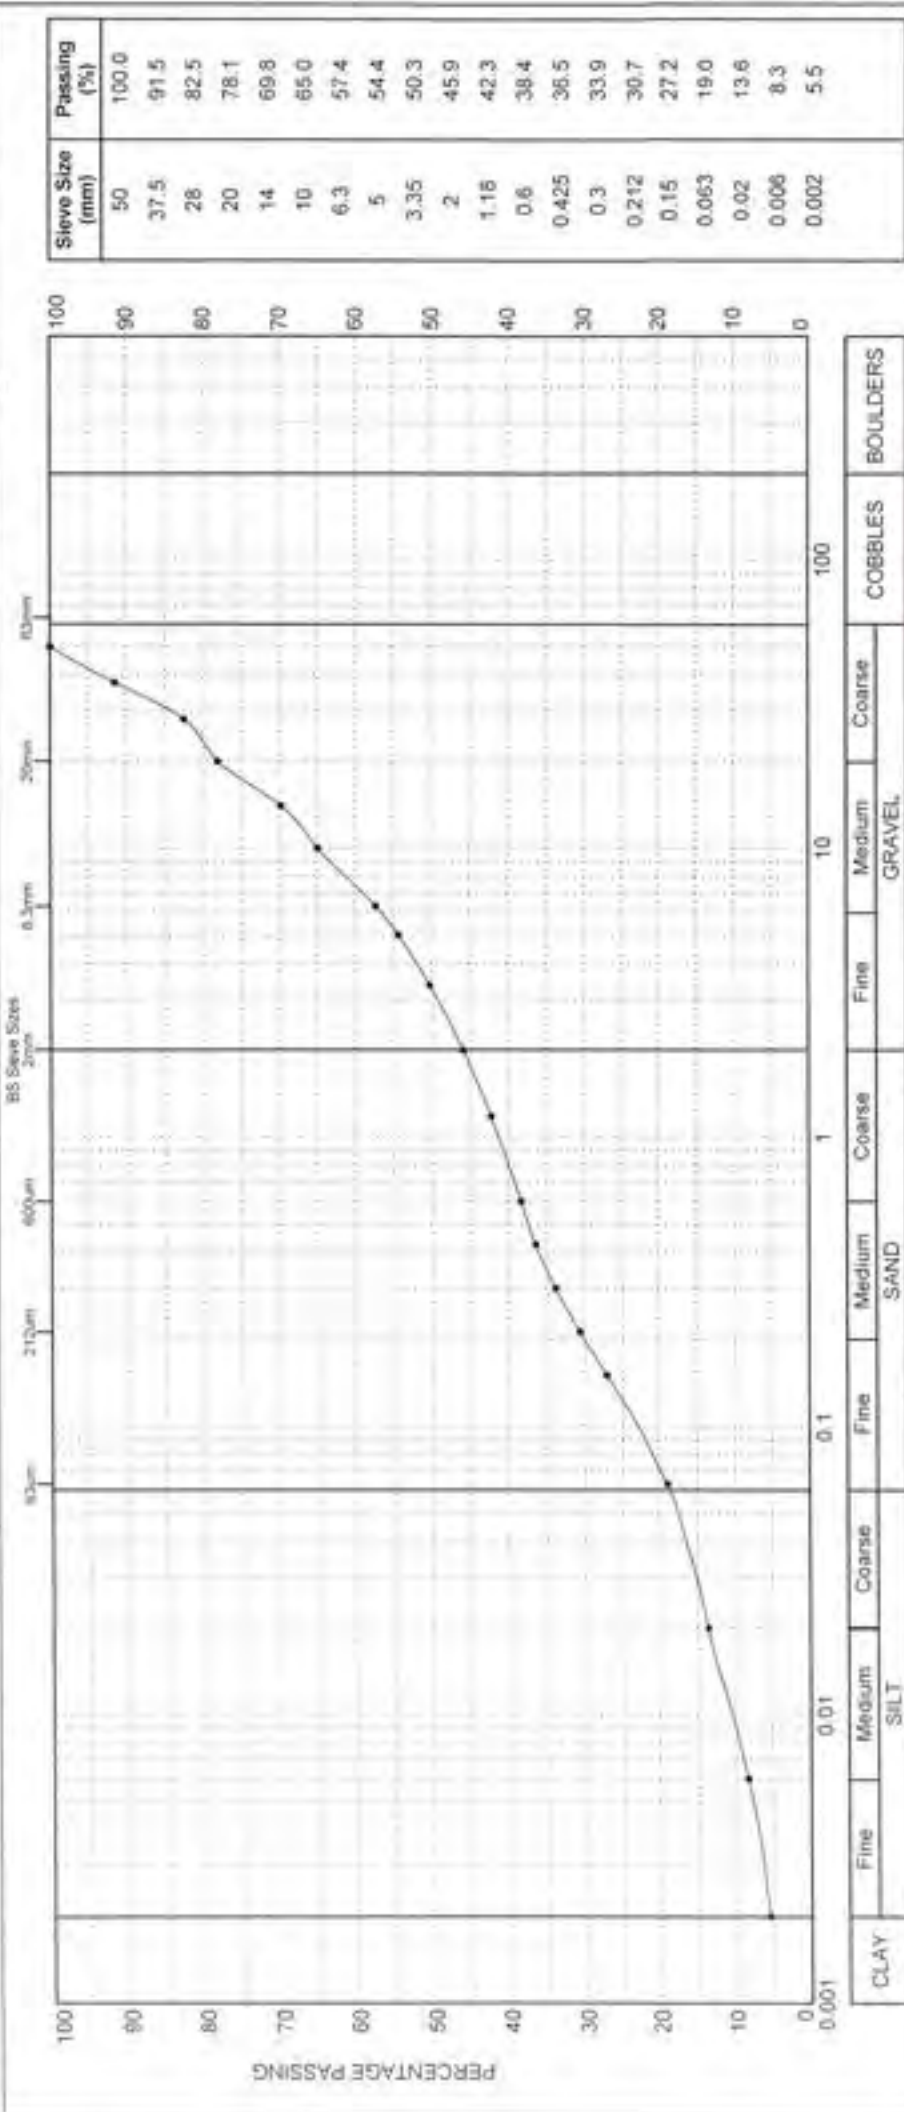

For description of sample please refer to the Laboratory Sample Description Sheet

Date of Issue :- 20/10/2020	Certificate No :- PSD/4251/PRAIRIE_AUK_TP173/B2/0.80	Signed :- <i>msaw</i>	Name :- SELKIRK	Page 1 of 1
Client :- South Tees Development Corporation	Contract Title :- Prairie Site Ground Investigation Works	AEG Contract No :- 4251		



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377, Part 2, Clauses 9.2 & 9.4, 1990
 (Test deviated from standard due to insufficient sample mass)


Job Number: PRAIRIL_AUK_IP175

Report No.: 0.00

Sample Type & No.: BZ

Specific Depth (m): 0.60

Date: 01/10/2020

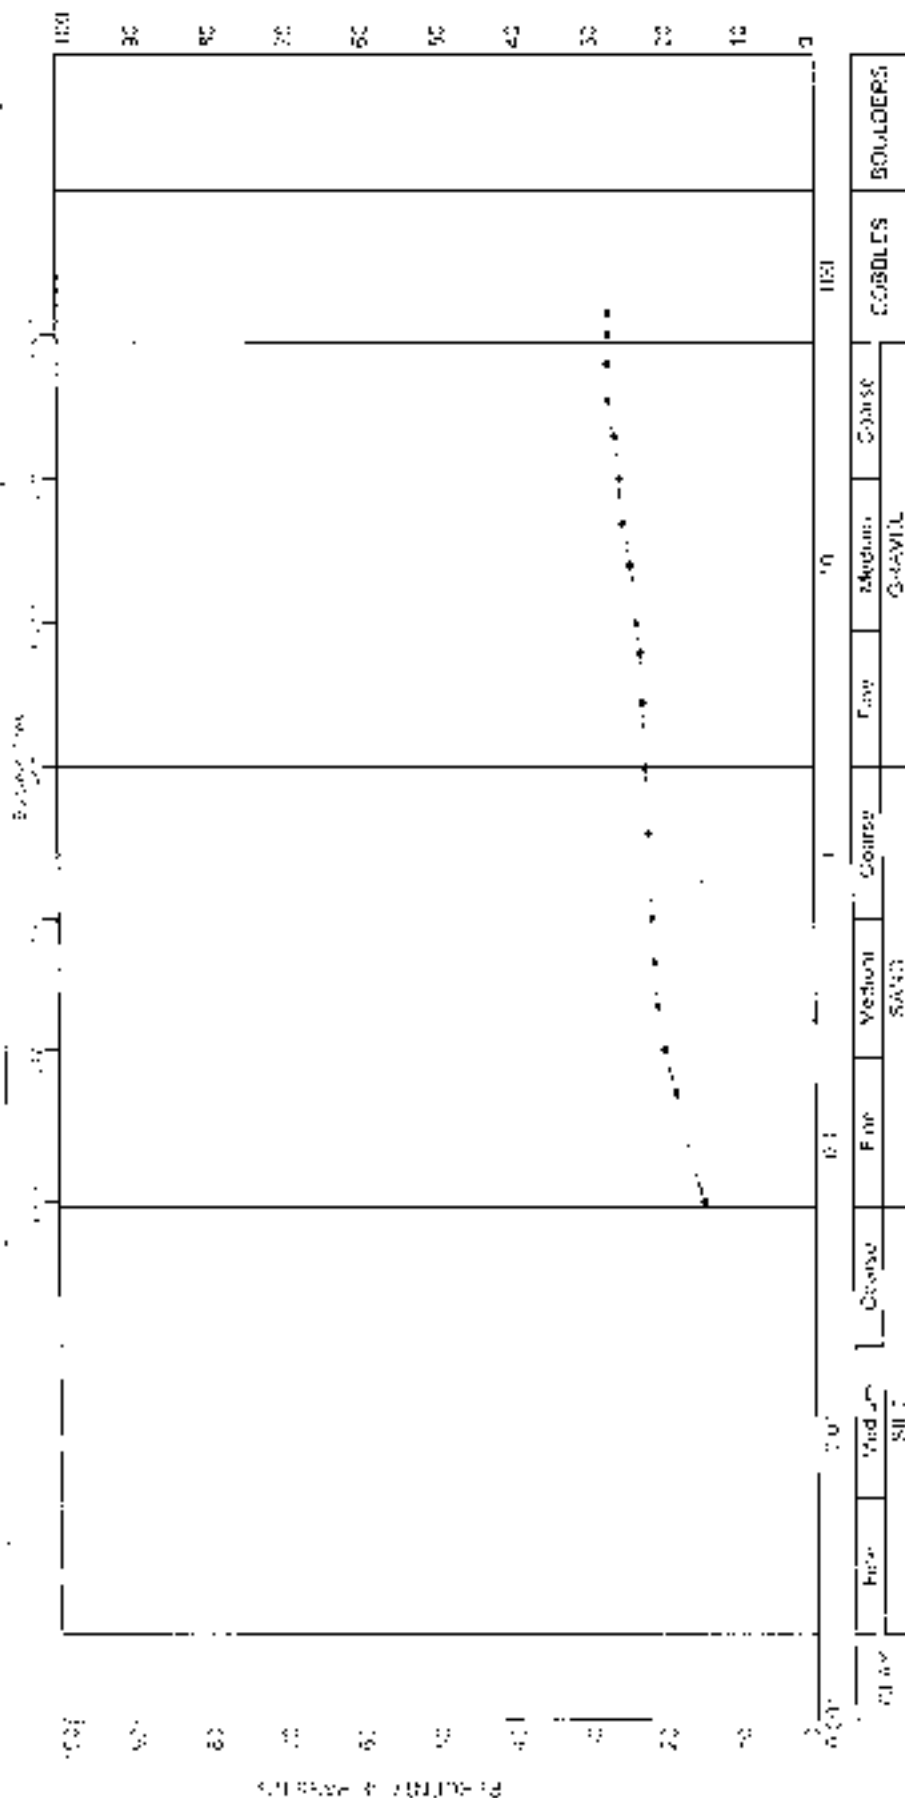

Clay	Fine	Med	Coarse	Very	Coarse	Coarse	Coarse	COBBLES	BOULDERS

Soils tested by MSA Ltd. Results are preliminary and subject to laboratory sample description.



Date of Issue: 01/10/2020

Certificate No: PSD 4251-PH01-01-AUK_IP-75-02-0.60

Scale: 1:10

Name: Nimit

MSA

Client: South West Earth and Construction

Contact: 176

Page No: Ground Investigation Works

Page 1 of 1



AFG Contract No: 4251

1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

DS1377 - Part 2 (Clause 9.2 & 9.4 1998)

(Test deviated from standard due to insufficient sample mass)


Project No: 10 - PRAIRIE_AUK_IP176

Depth (m) = 0.50

Sample Type & No. = BZ

Specie Depth (m) = 0.50

Date Tested = 29/09/2020

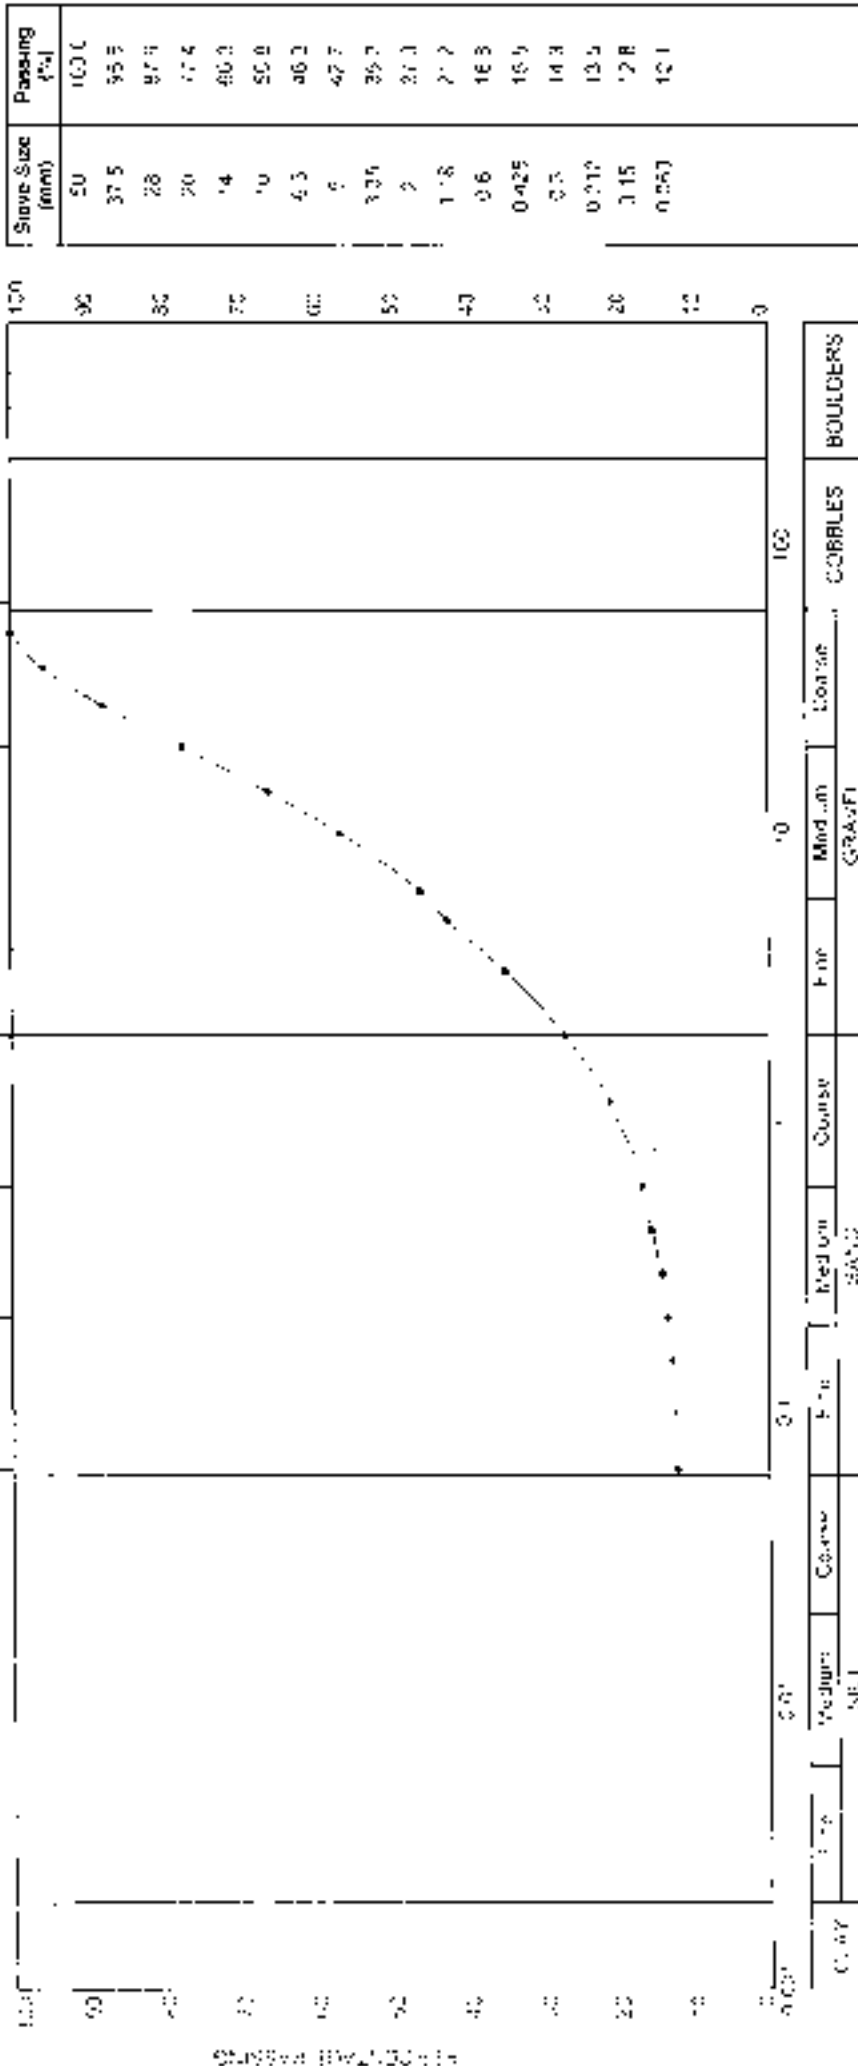

Clay		Fine		Coarse		Coarse		Coarse		Boulders	
Medium		Fine		Coarse		Medium		Coarse		Boulders	
SAND		FINE		SAND		FINE		SAND		FINE	
SAND		FINE		SAND		FINE		SAND		FINE	

Soil classification is based on the Laboratory Sample Description Sheet

Date of Issue: 10/10/2020
 Drawn: [Signature]
 Checked: [Signature]

Client name (to):
 2504251 PRAIRIE AUK INVESTIGATION
 Signed: [Signature]

Name: [Signature]
 Project: Site Ground Investigation Works
 Contract No: 475

Page 1 of 1




1387

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

Location: PIRAIRIE_AUG TP176 Depth: 2.00 Sample Type & No: R5 Specific Depth: 2.00 Date Tested: 29/09/2020

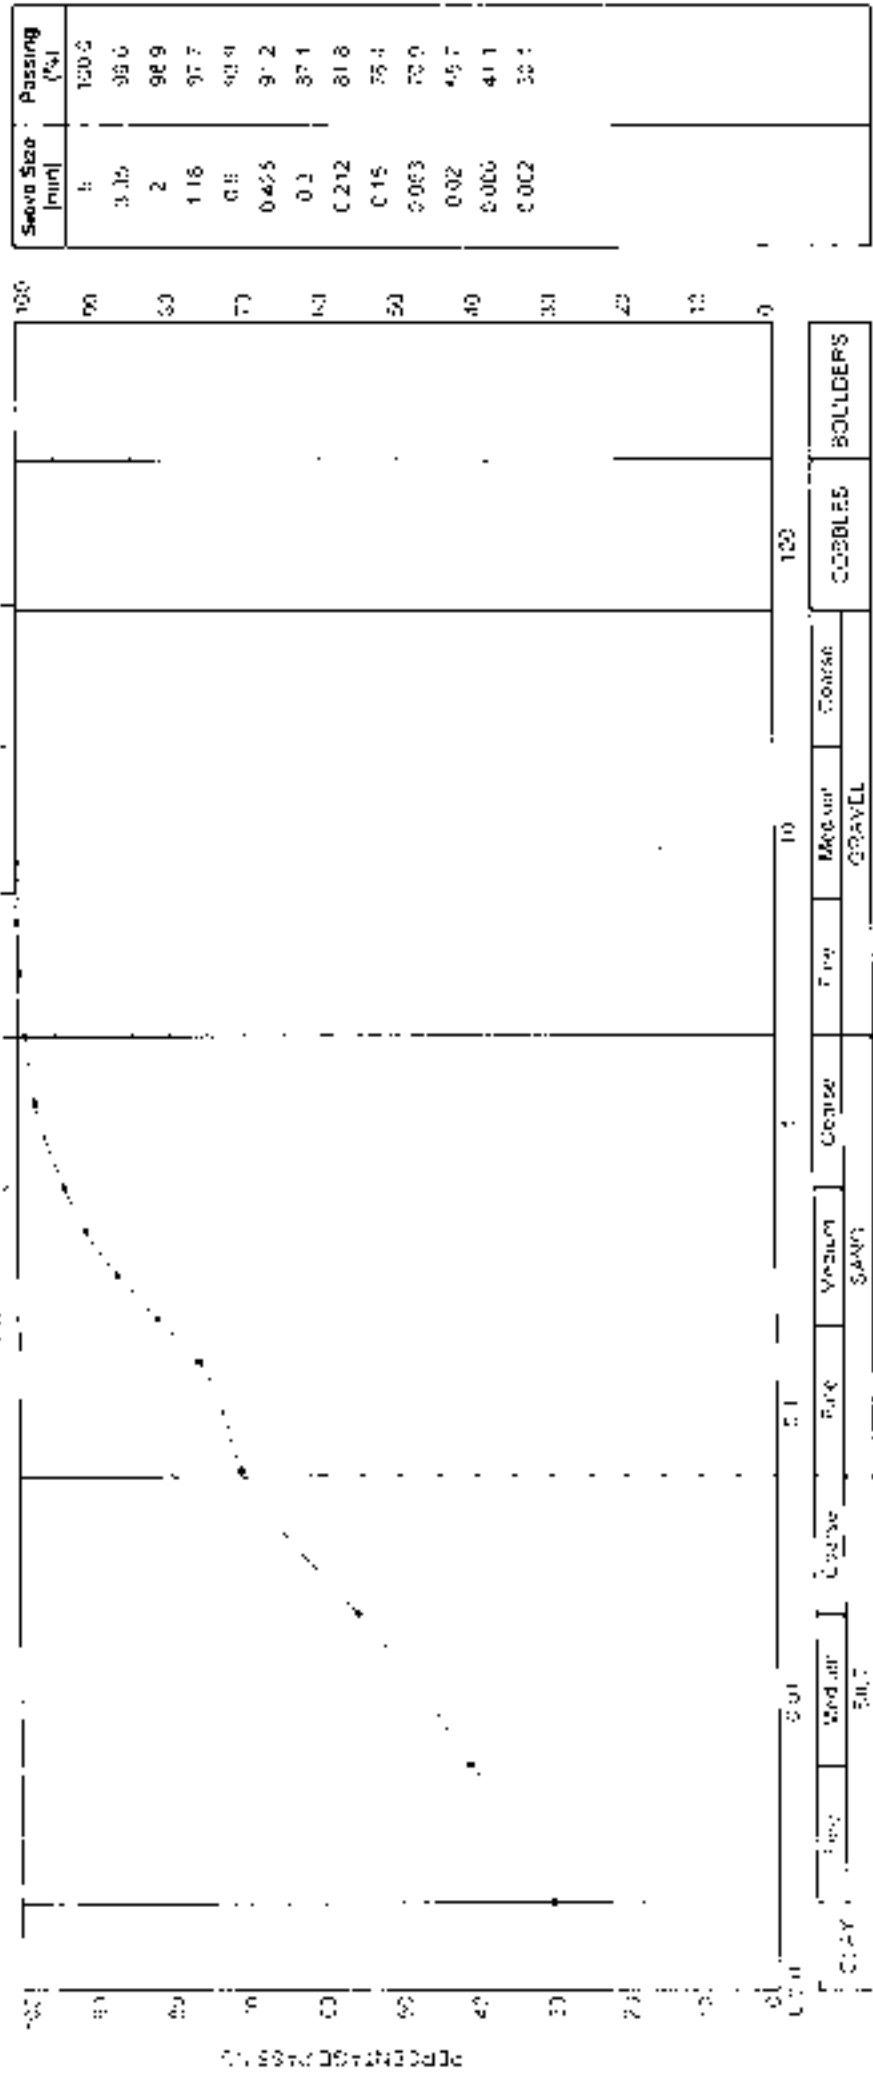

CLAY	Fine	Medium	Coarse	Fine	Medium	Coarse	COBBLES	Boulders
		SAND			GRAVEL			

For description of soil see Test Report No. 1901685200 for details of test

ALLS
 Soil Test Development Contractor
 2010 2020
 Certificate No: PSD 4291114416100K

Page 1 of 1
 Name: MSR
 Ref: Contract No: 4251

Contract No: _____

Ref: Contract No: **4251**

1367


ALLIED EXPLORATION & GEOTECHNICS LIMITED

Office: Unit 25, Middle Green, Euxine, Priors Park, Chester-le-Street, Co. Durham, DN4 2SD. Tel: 0191 487 4700 Fax: 0191 267 4710
 Regional Office: Unit 25, Euxine, Development Centre, Caxton Road, Whitburn, SC17 5B. Tel: 01717 325 320 Fax: 01717 733 999

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990
 (Test deviated from standard due to insufficient sample mass)

Exploratory Hole No - PRAIRIE_AUK_TP177 Depth (m) - 1.80 Sample Type & No - B7 Specific Depth (m) - 1.80 Date Tested - 30/09/2020

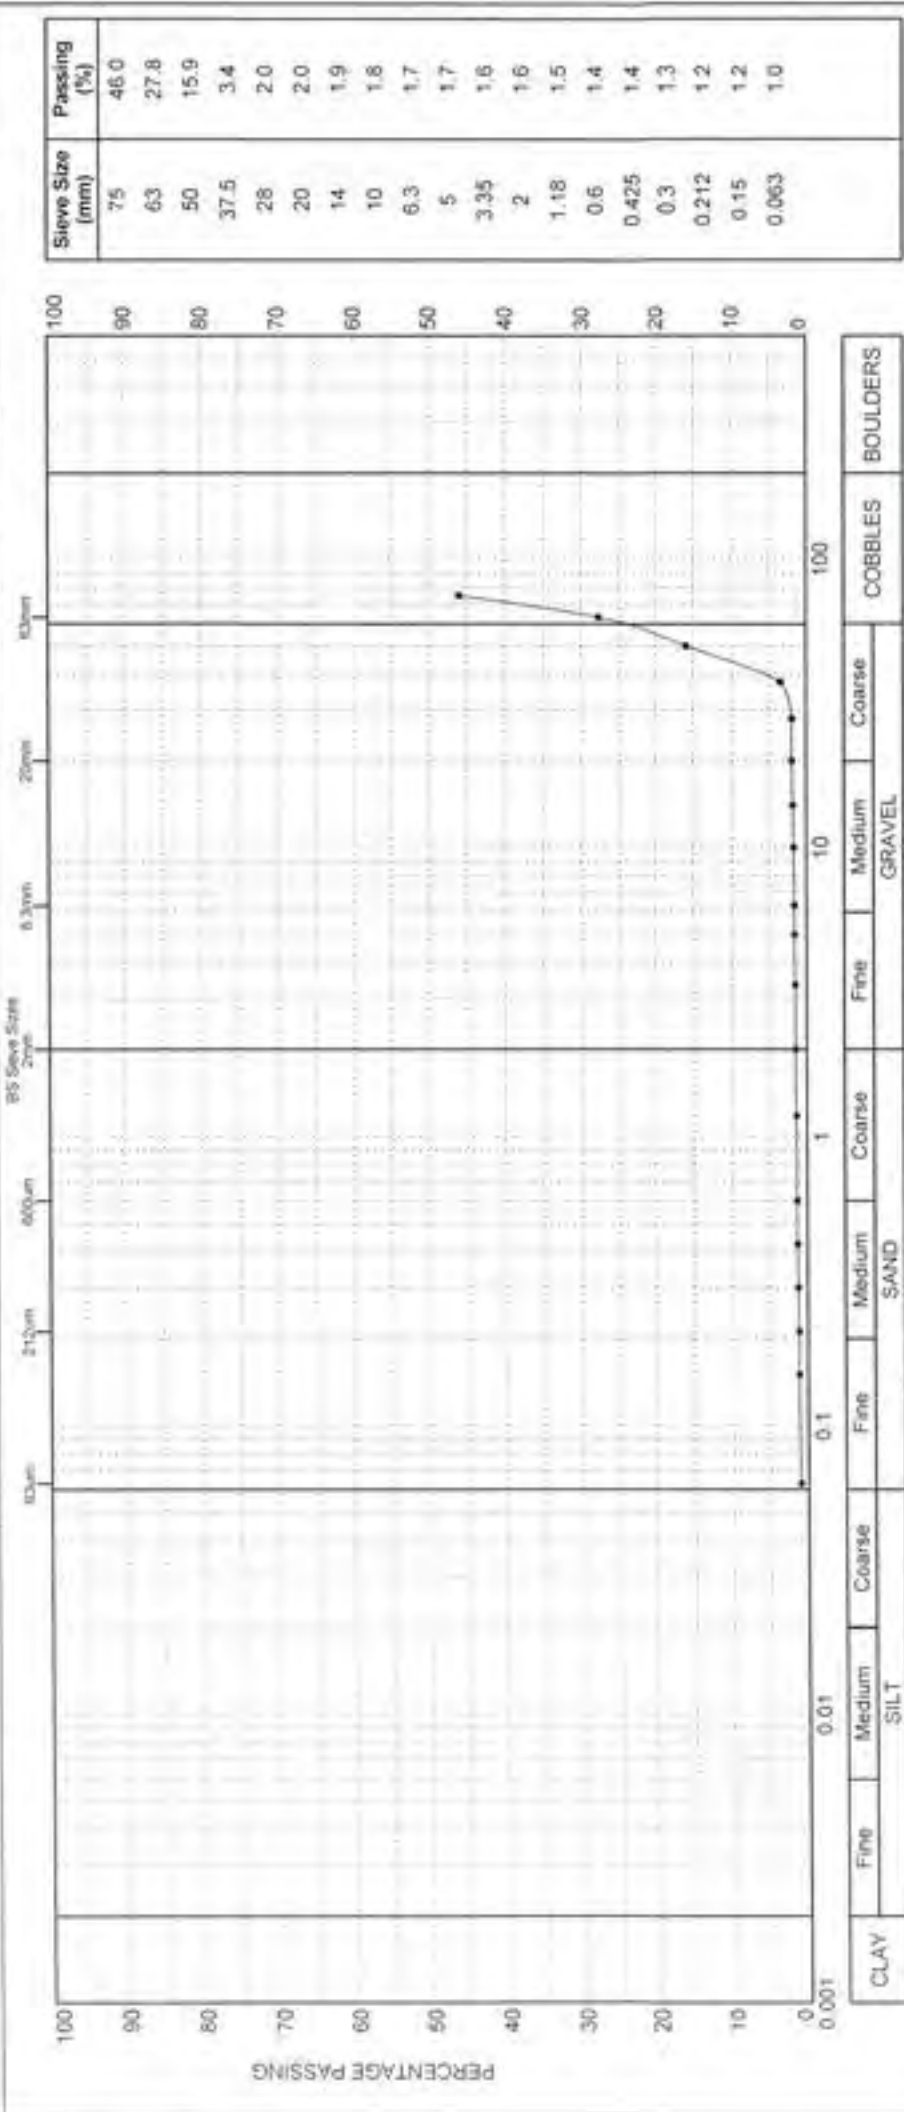

For description of sample please refer to the Laboratory Sample Description Sheet

	Date of issue - 20/10/2020	Certificate No - PSD/4251/PRAIRIE_AUK_TP177/B7/1.80	Signed - <i>msaw</i> Name - <i>MSAW</i>	Page 1 of 1 AEG Contract No - 4251
	Client - South Tees Development Corporation	Contract Title - Prairie Site Ground Investigation Works		

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

PS1377 Part 2 Cluded B.2 & 9.4: 1990


Location File No: PHOENIX_AUK_TF178

Depth (m) 0.60

Sample Type & No: BZ

Specific Depth (m) 0.60

Date Tested: 05/10/2020

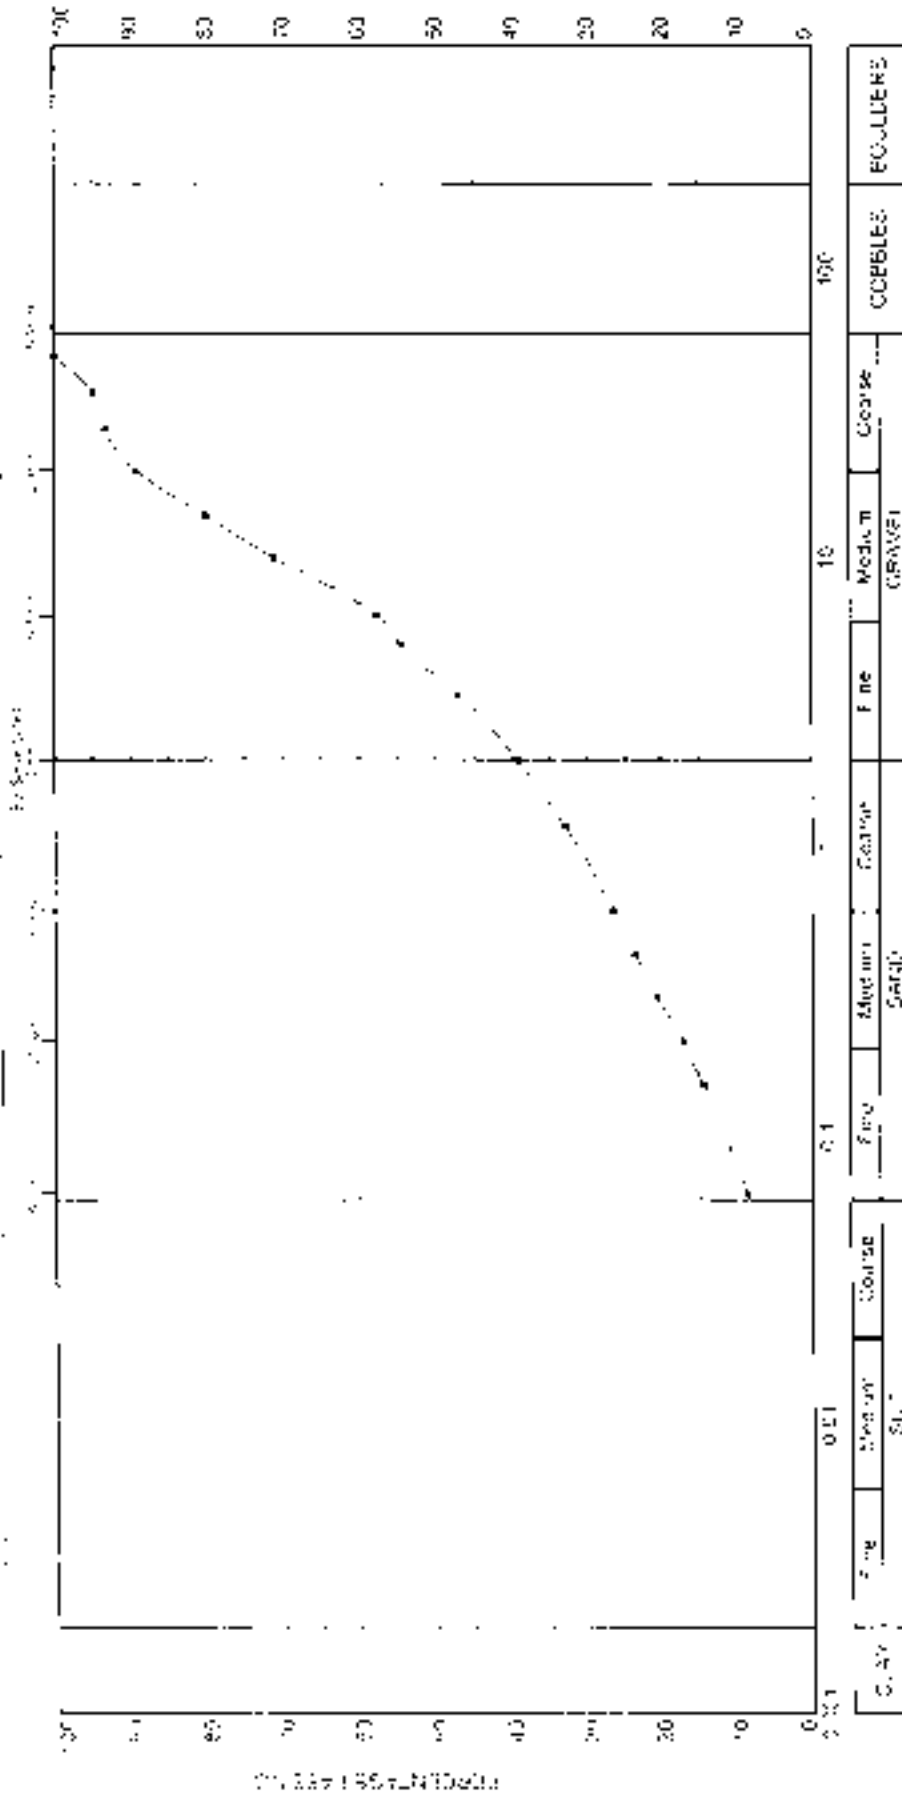

For description of symbols please refer to the applicable sample description sheet.

Date of Issue: 26/10/2020

Conf Case No: PS1377-1-REVISION 2

Signed: *MSB*

Name: MSB

Page 1 of 1



Site: Phoenix Development at Integration

Project: Site Ground Investigation Works

AEG Contract No: 4251


1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Business Development Centre, Easton Road, Chester, CH3 9JG, UK. Tel: 01244 363 4000 Fax: 01244 363 4714
 Regional Office: Unit 25, Business Development Centre, Easton Road, Chester, CH3 9JG, UK. Tel: 01244 363 4000 Fax: 01244 363 4714

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

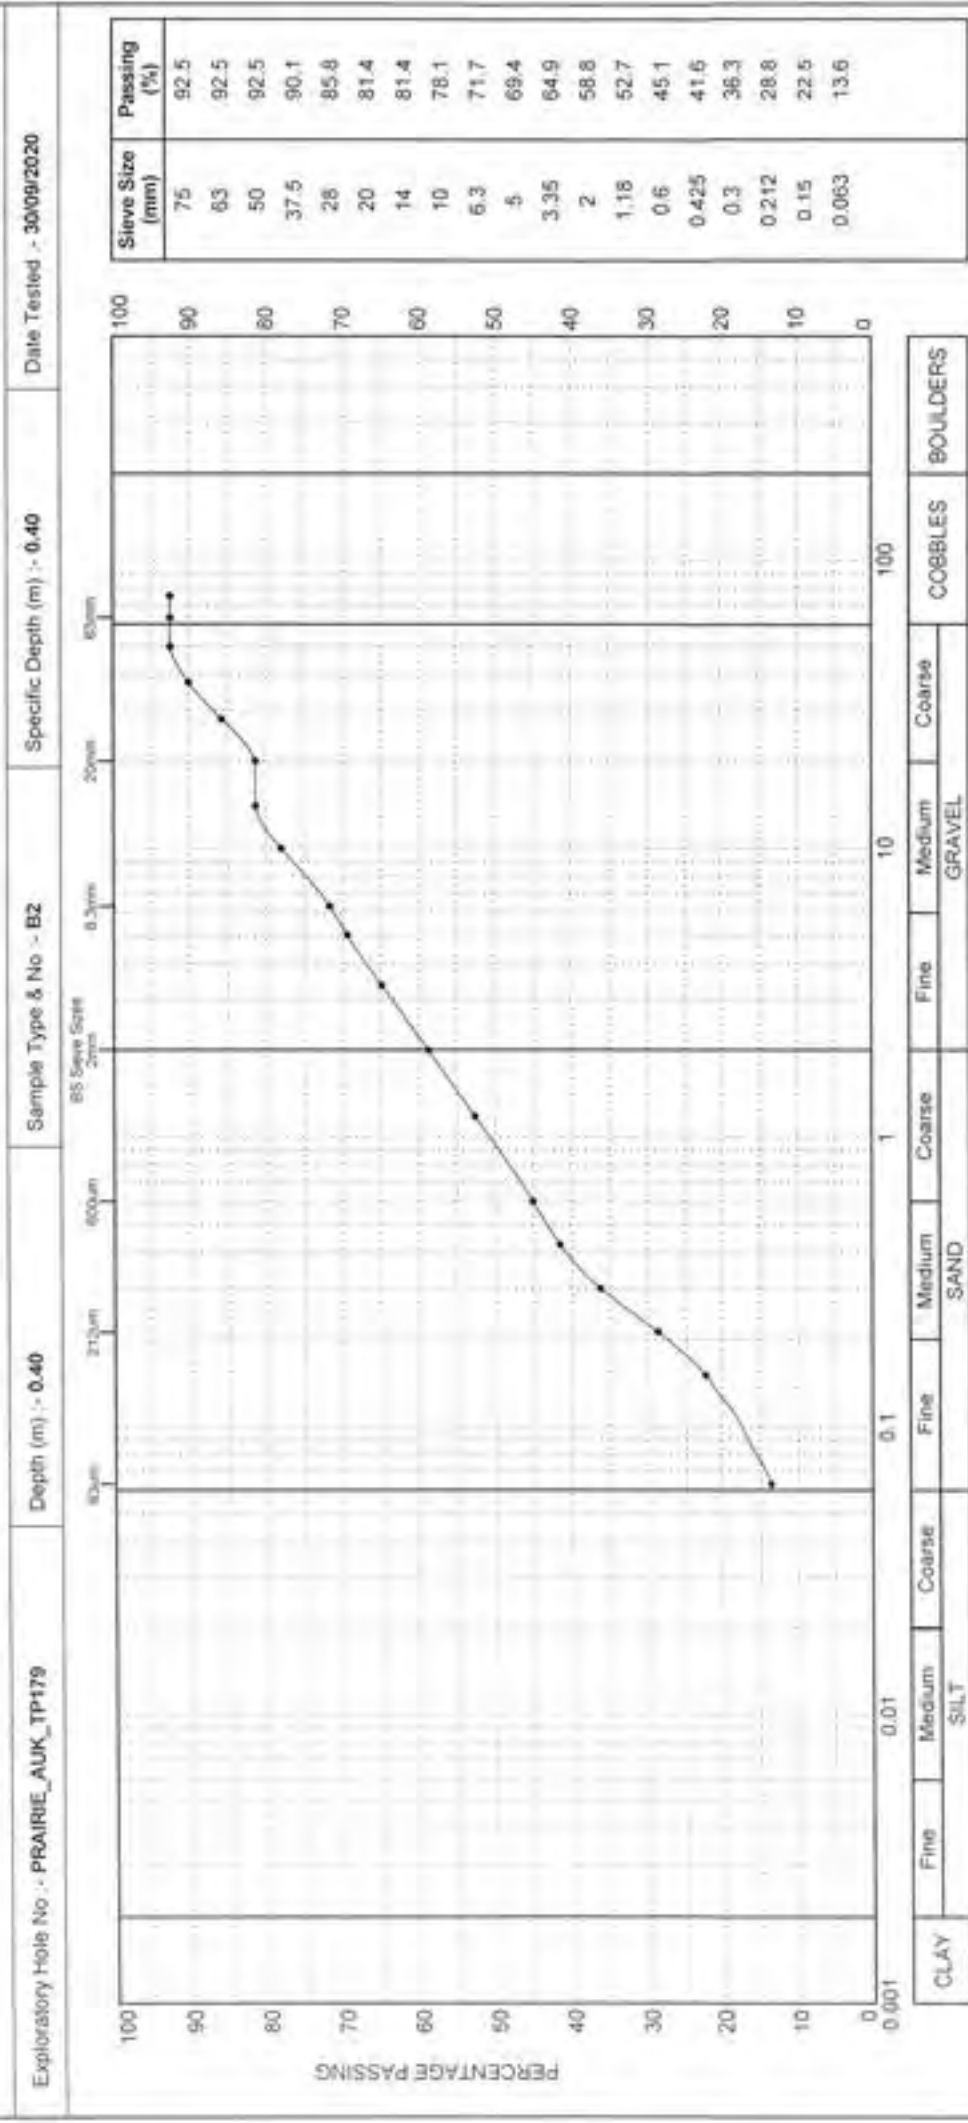

For description of sample please refer to the Laboratory Sample Description Sheet

Date of Issue :- 20/10/2020	Certificate No :- PSD/4251/PRAIRIE_AUK_TP179/B2/0.40	Signed :- <i>msore</i>	Name :- M. SELKIRK	Page 1 of 1
Client :- South Tees Development Corporation	Contract Title :- Prairie Site Ground Investigation Works	AEG Contract No :- 4251		



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

NS1377 Part 2 - Clause 9.2 & 9.4: 1990

(Test deviated from standard due to insufficient sample mass)


Exploration No: 16 - PRAIRIE_AUK_TM101

Depth (m) 0.50

Sample Type & No.: UZ

Specific Depth (m) 0.50

Date Tested: 02/10/2020

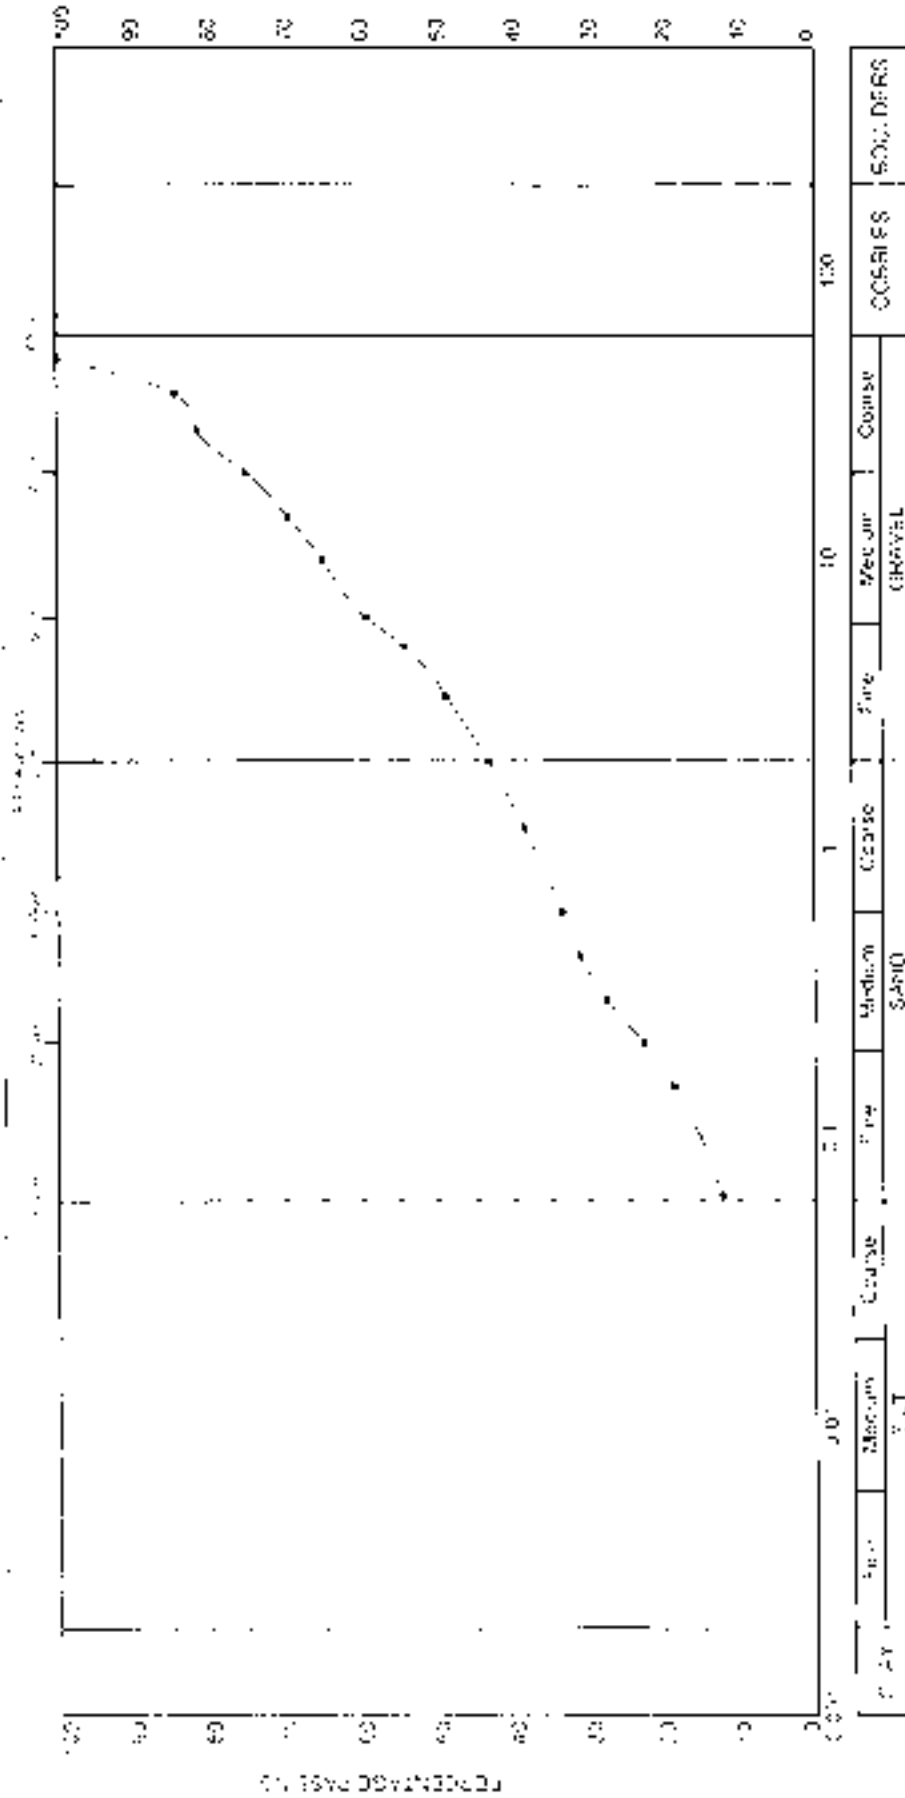

Grain Size	Coarse	Fine	Medium	Coarse	Fine	Secure	Course	COARSE	FINE
0.075									
0.15									
0.3									
0.6									
1.2									
2.5									
5.0									
10									
20									
40									
80									
150									

For detailed analysis procedure refer to the laboratory sample description sheet



Date of Issue: 02/10/20

Client: South West Development Corporation

Project: 429 - PRAIRIE_AUK_TM101 - 02-0-50 - Signed -

Name: *MSD*

Page: 1 of 1



Contract: 165

Frame Site Ground Investigation Works

455 Contract No: 42/51

ALLIED EXPLORATION & GEOTECHNICS LIMITED


Head Office: Unit 25, Middleport Industrial Estate, Park Road, Chester-le-Street, Co. Durham, DA2 2SD. Tel: 0191 857 4100 Fax: 0191 857 4716
Regional Office: Unit 20, Alnport Development Centre, Easton Wharfedale, Throckmorton, Wetherby, Wetherby, LS23 7JQ. Tel: 01937 545 300 Fax: 01937 545 300

PARTICLE SIZE DISTRIBUTION

BS1377 : Part 2 : Clause 9.2 & 9.4 : 1990

(Test deviated from standard due to insufficient sample mass)


Exploratory Hole No. : PRAIRIE_AUK_TP181 Depth (m) :- 1.10 Sample Type & No. :- B4 Specific Depth (m) :- 1.10 Date Tested :- 30/09/2020

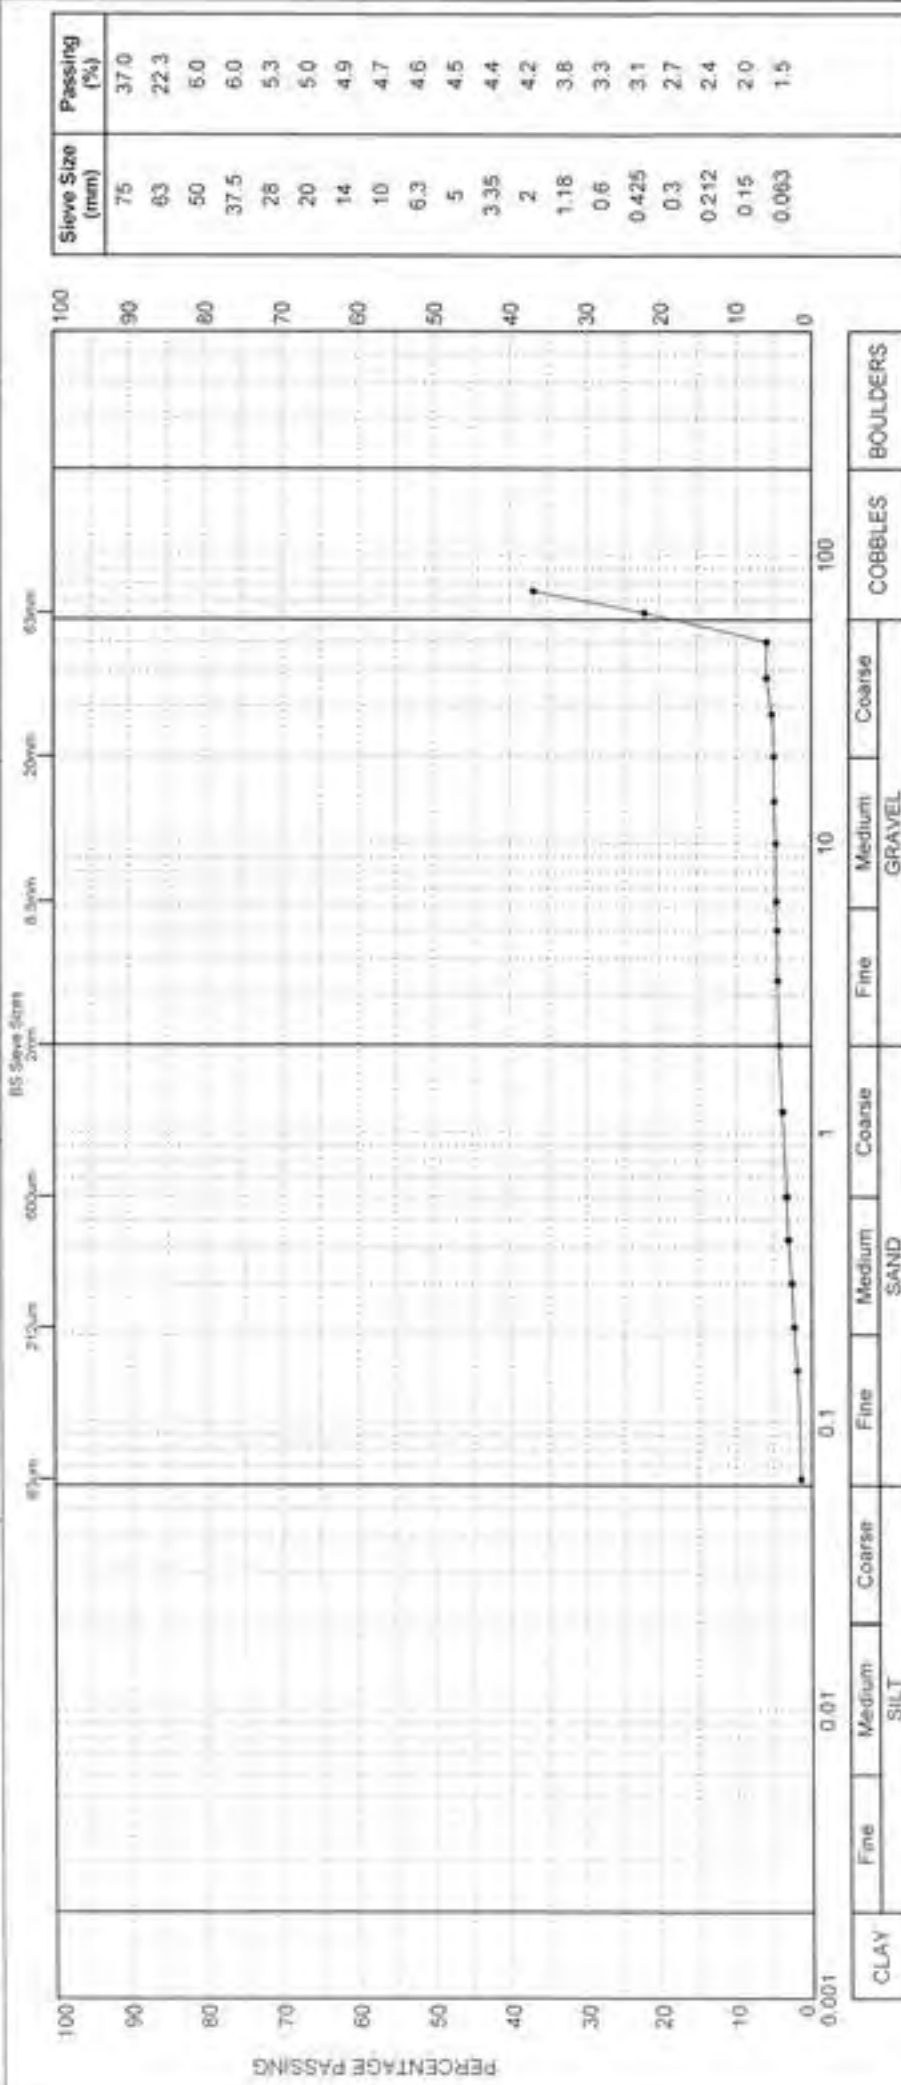

For description of sample please refer to the Laboratory Sample Description Sheet

CLAY FINE MEDIUM COARSE FINE MEDIUM COARSE FINE MEDIUM COARSE COBBLES BOULDERS

SILT SAND GRAVEL

	Date of Issue :- 20/10/2020	Certificate No :- PSD/4251/PRAIRIE_AUK_TP181/B4/1.10	Name :- <i>M. DELKIN</i>	Page 1 of 1
	Client :- South Tees Development Corporation	Contract Title :- Prairie Site Ground Investigation Works	Signed :- <i>msae</i>	AEG Contract No :- 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

RS1377 Part 2 Clause B.2 & 9.4 - 1990


System of Tests: **PRAIRIE_AUK_TPR2**

Moisture: **0.60**

Sample Type & No.: **U2**

Specific Depth (m): **0.60**

Date Tested: **28/09/2020**

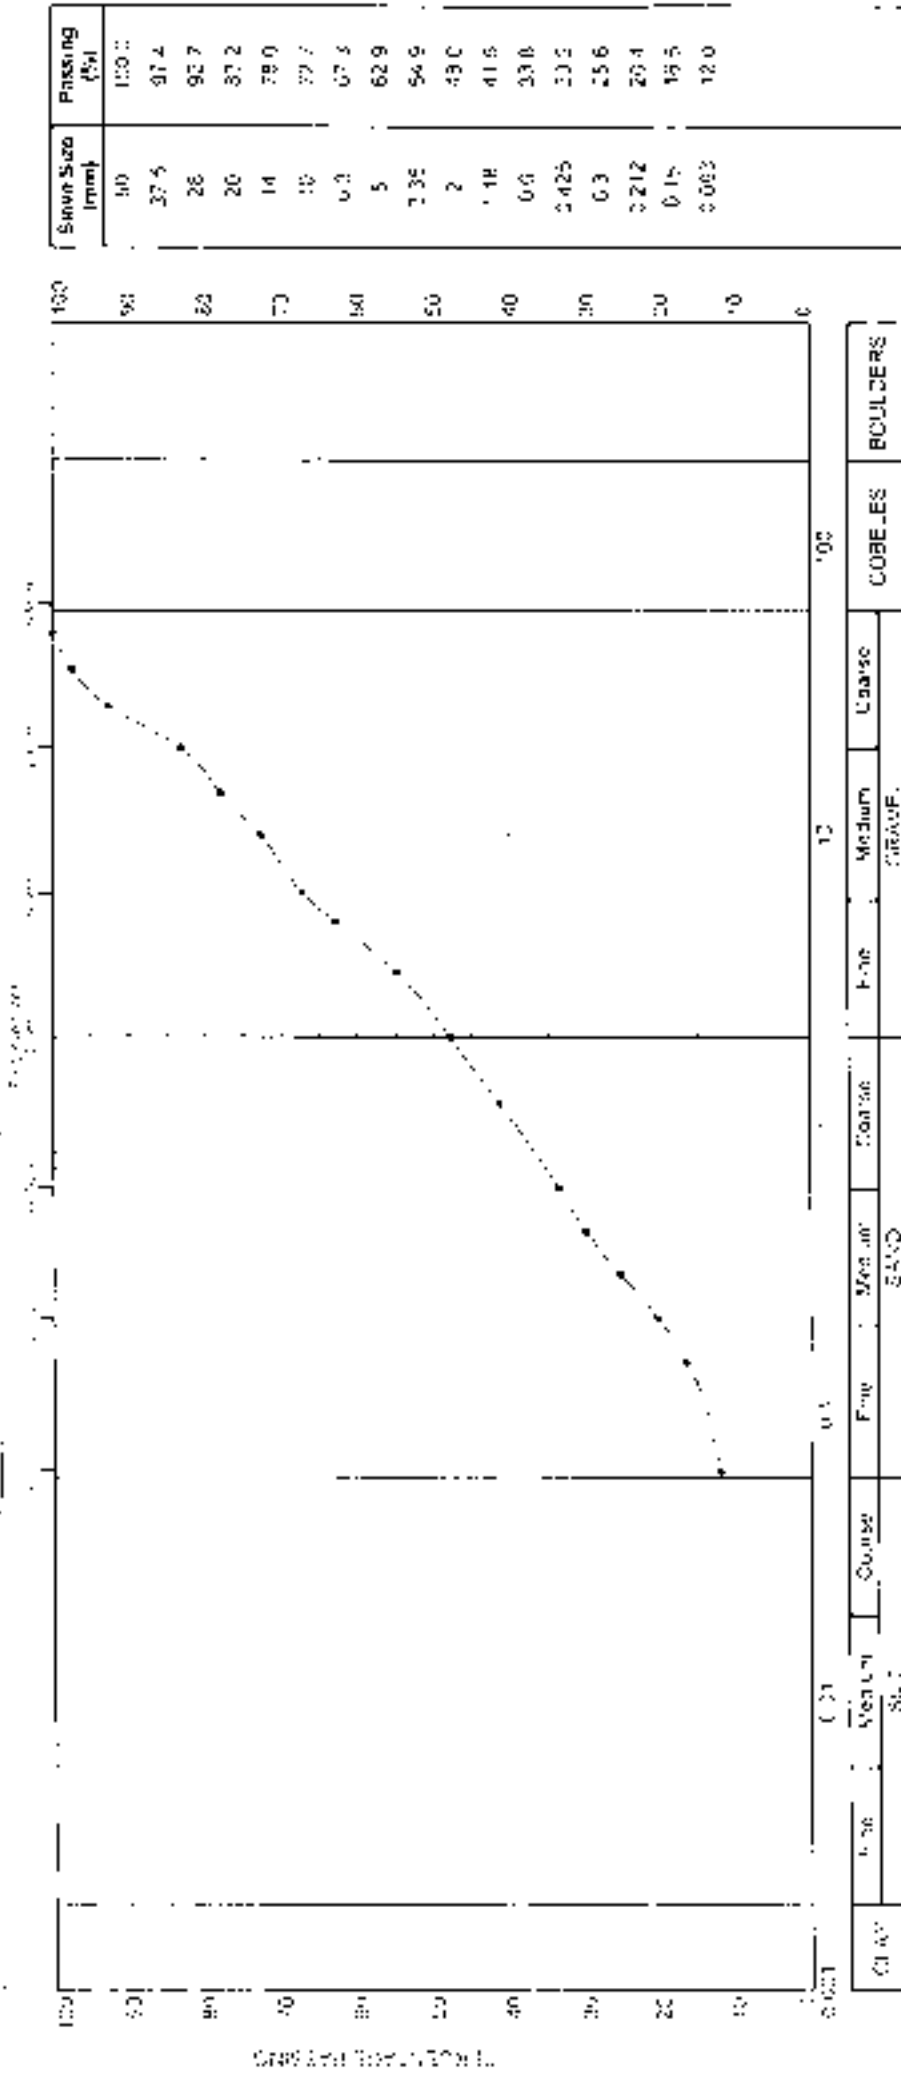

Indicate the test temperature in the Laboratory Quality Control Report



Date of Issue: **28/10/2020**

Control No.: **MSD 4251 PR212_AUK_TPR2_03**

Signed: **MSD**

Name: **MSD**

Page 1 of 1

AGG Contract No.: **4251**

Client: **South West Drive Joint Venture Construction**

Contract File: **MSD**

Project Site Group: **Westgate Works**



1357

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

OS1077 - Part 2 - Clause 9.2 & 9.4 - 1990


Exp. No. / Job No.: **PIB-RIE AUK_IP185**

Depth (m): **3.50**

Sample Type & No.: **BZ**

Specific Depth (m): **3.50**

Date Tested: **28/09/2020**

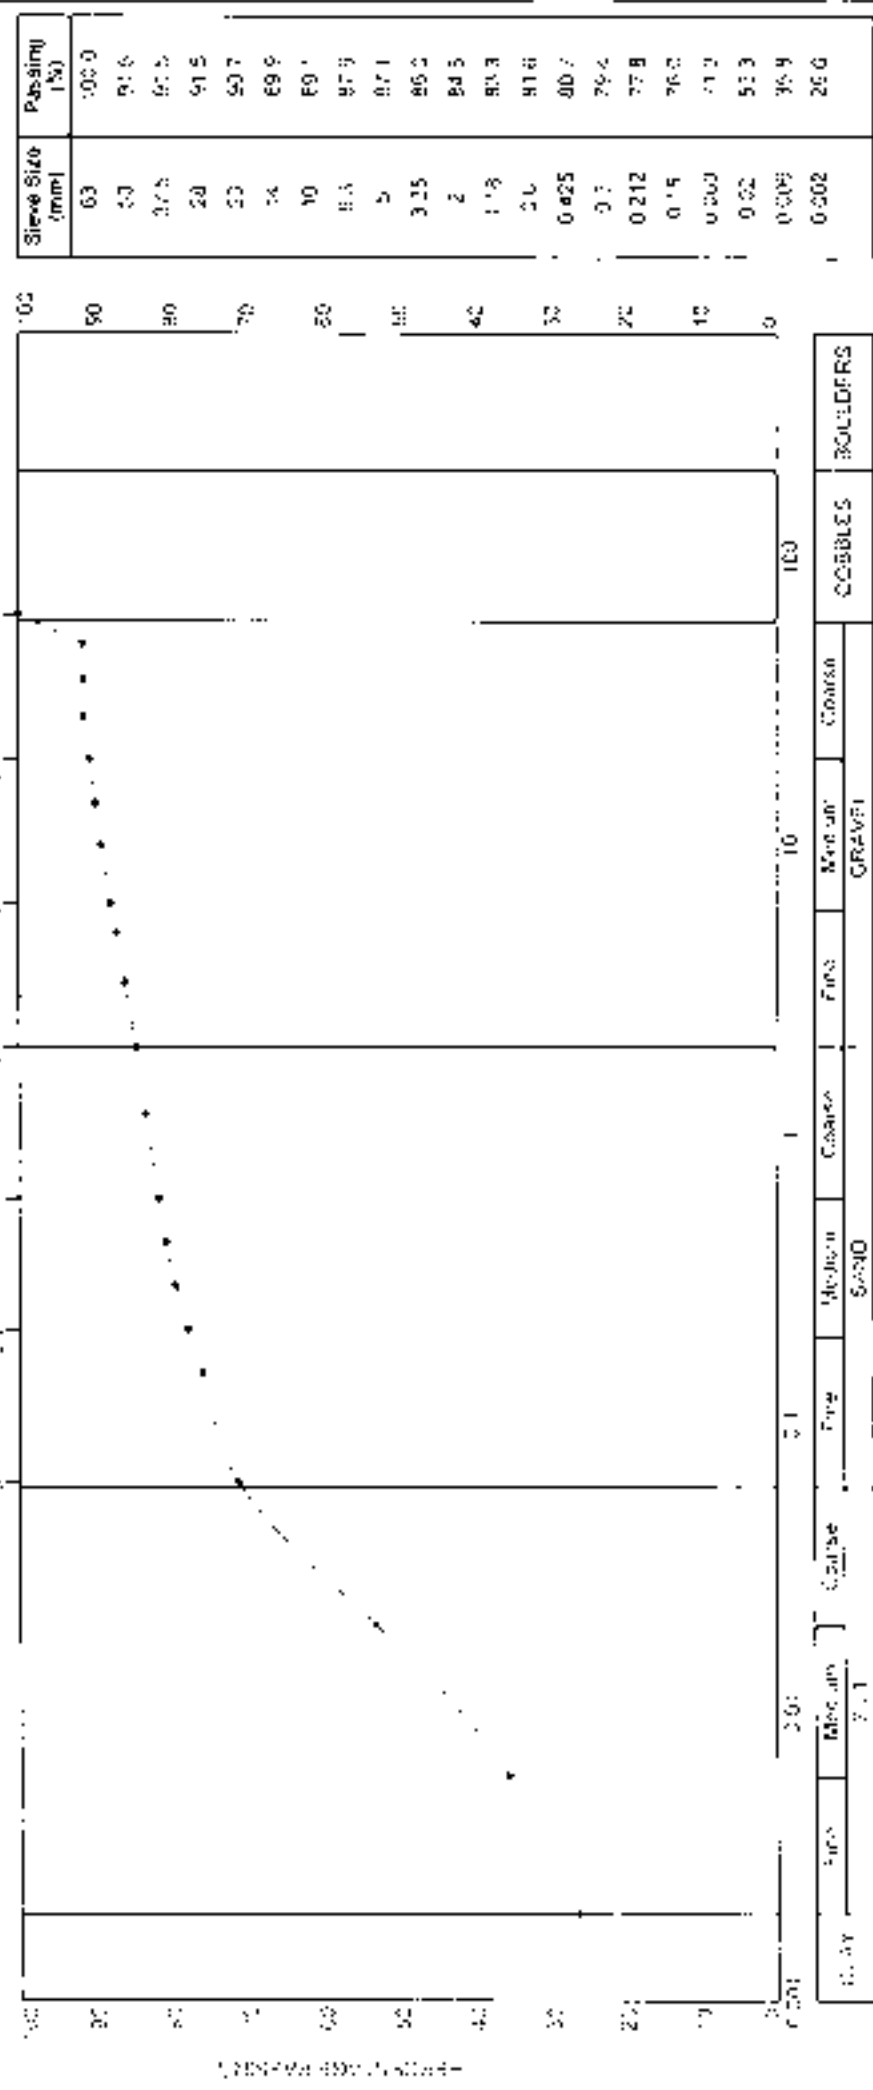

Coarse	Medium	Coarse	Fine	Medium	Fine	Coarse	Coarse	Coarse	Coarse
SAND		SILT		CLAY		GRAVEL			

Figure 9.2.1.1 - Particle Size Distribution of Soil



Date of Issue: **28/10/2020**

Contract No.: **P201821 - RESURF_AUK_IP185-BZ 3.50**

Site No.: **3.50**

Name: **MSWD**



Page: **of 1**

Drawn: **South Tiers Design/Project Coordinator**

Geotrial Title:

Figure 9.2.1.1 - Particle Size Distribution of Soils

ALL Contract No.: **4251**


1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

RS1377 Part 2 - Clause 9.2 & 9.4 - 1990
(Test deviated from standard due to insufficient sample mass)

Sample No. : PRAIRIE_AUK TP188 Depth (m) : 0.60 Specific Dmppt (m) : 0.60 Date Tested : 28/09/2020

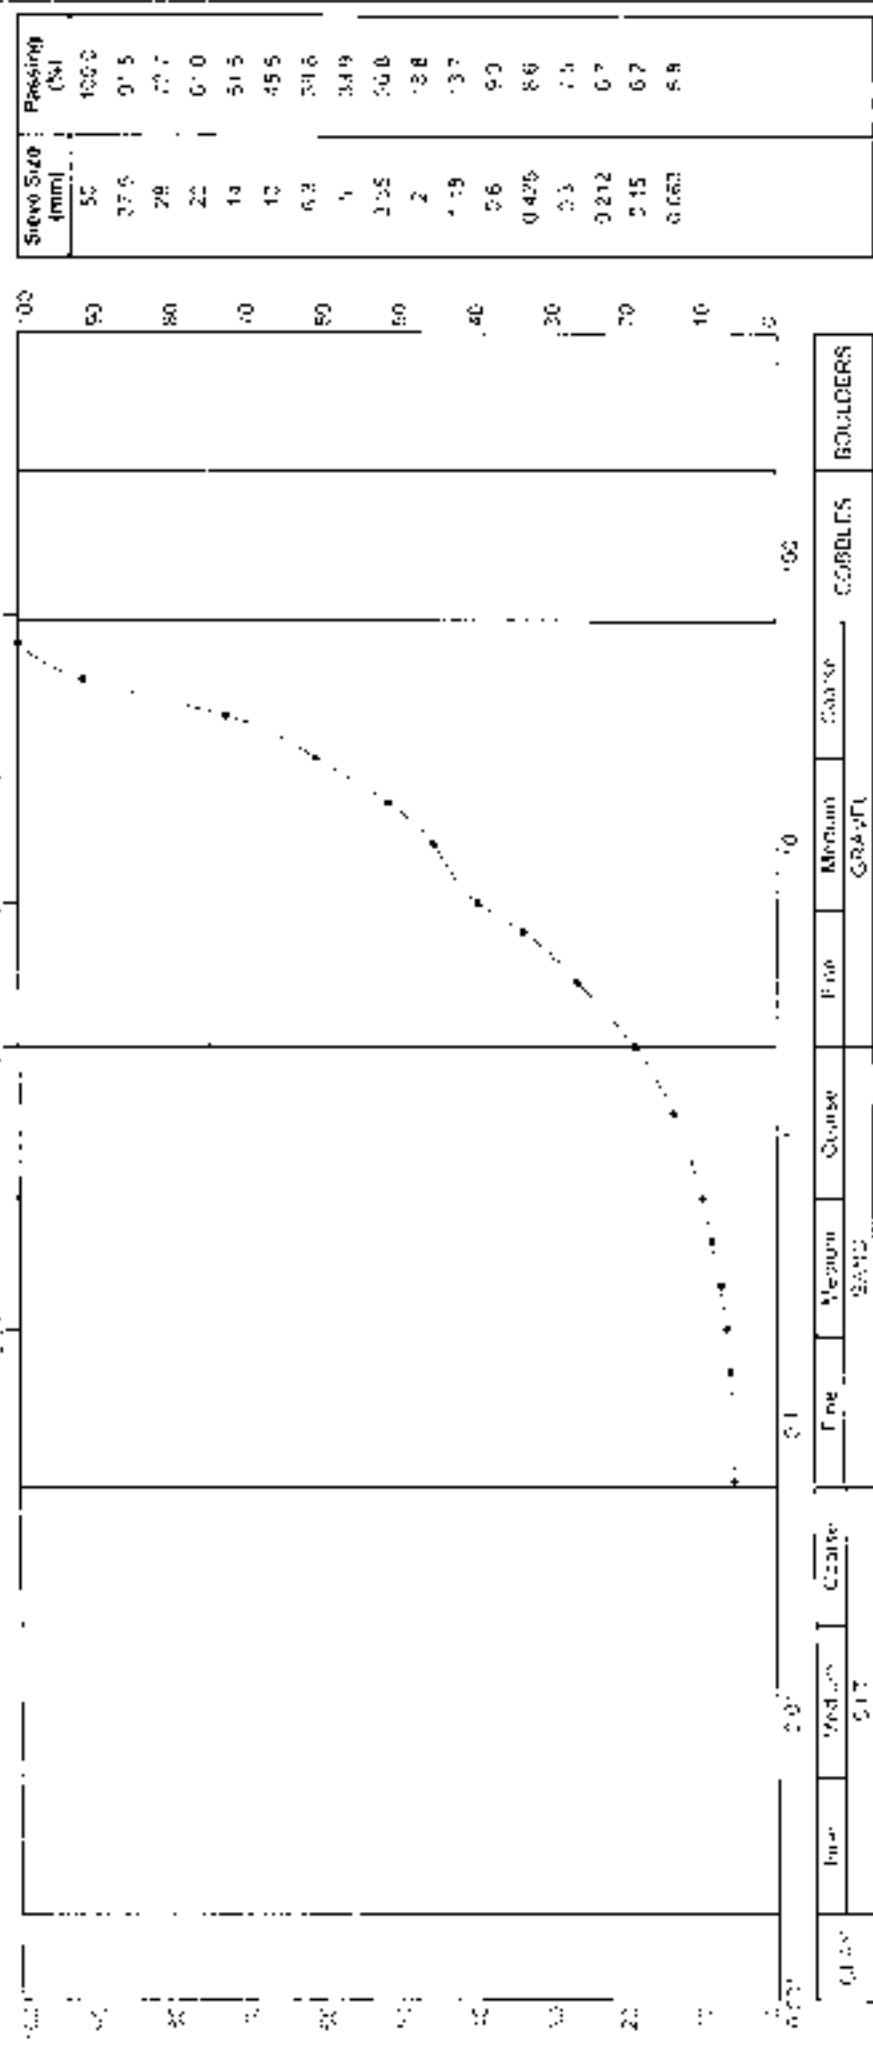

Client : South Tees Development Corporation

Project : PRAIRIE_AUK_TP188

Contract No. : 42.51

Page 1 of 1

42.51

Contract No. : 42.51

Contract Title : South Tees Development Corporation

Name : *Misra*

Contract Title : South Tees Development Corporation

Contract Title : PRAIRIE_AUK_TP188

Contract Title : South Tees Development Corporation

Contract Title : South Tees Development Corporation

Contract Title : PRAIRIE_AUK_TP188

Contract Title : South Tees Development Corporation

Contract Title : South Tees Development Corporation



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

BS1377 Part 2, Clause 9.2 & 9.4 : 1990


Location: **PROBHE, AUK YP189**

Depth: **0.50**

Soil type: **Sp. No. B2**

Specific Depth: **0.50**

Date tested: **01/10/2020**

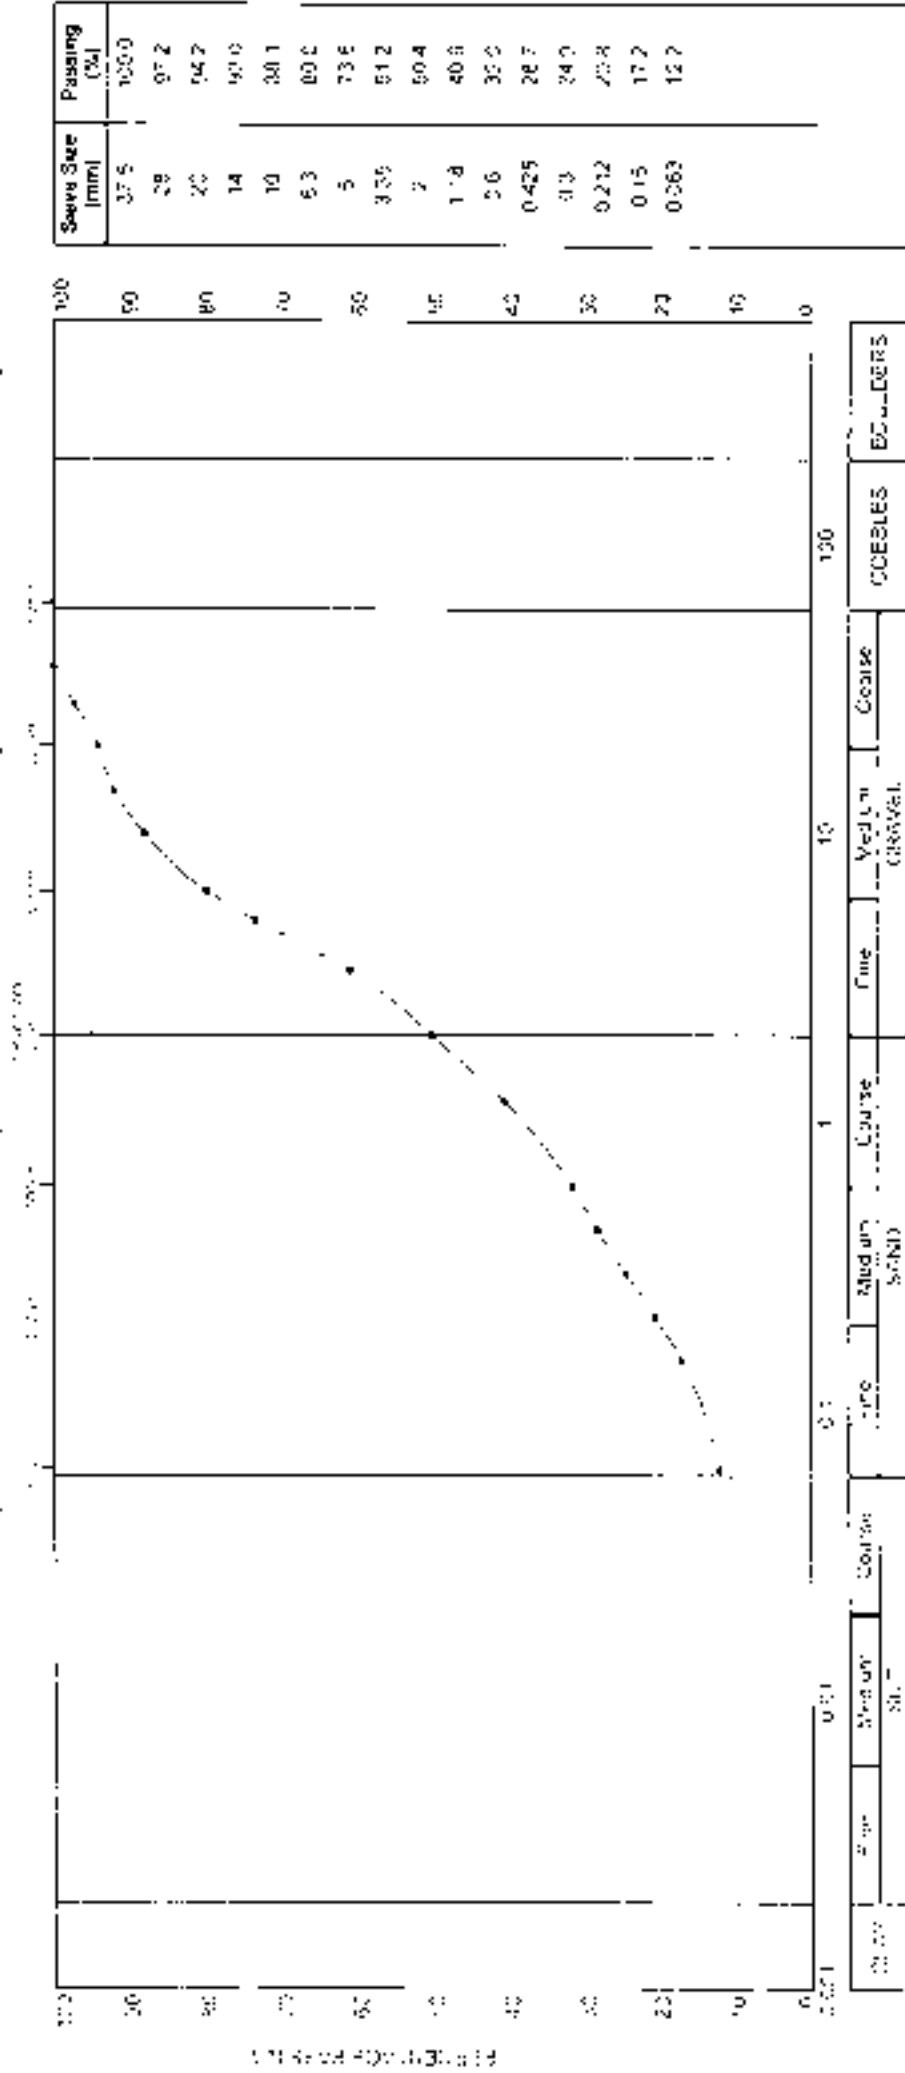

Presentation of sample test results based on the current test plan used

Soil	Clay	Medium	Coarse	Fine	Very fine	Coarse	Coarse
Gravel	Sand	Sand	Sand	Sand	Gravel	Gravel	Gravel

Client Name: _____ Client No.: _____
 Date: 20/10/2020 Project: **ALC 4251** Signed: **MSB** Name: _____
 Location: **Probhe Development Compound** Contact No: _____
 Project: **Probhe Site Ground Investigation Works** Contact No: **4251**

Page 1 of 1




ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

DS1377 Part 2 Clause B.2 R 9.4. 1990

Extruder No. - PHAIRIE_AUK_TM189 Depth (m) - 1.50 Sample Type & No. - B4 Specific Depth (m) - 1.50 Date tested - 24/09/2020

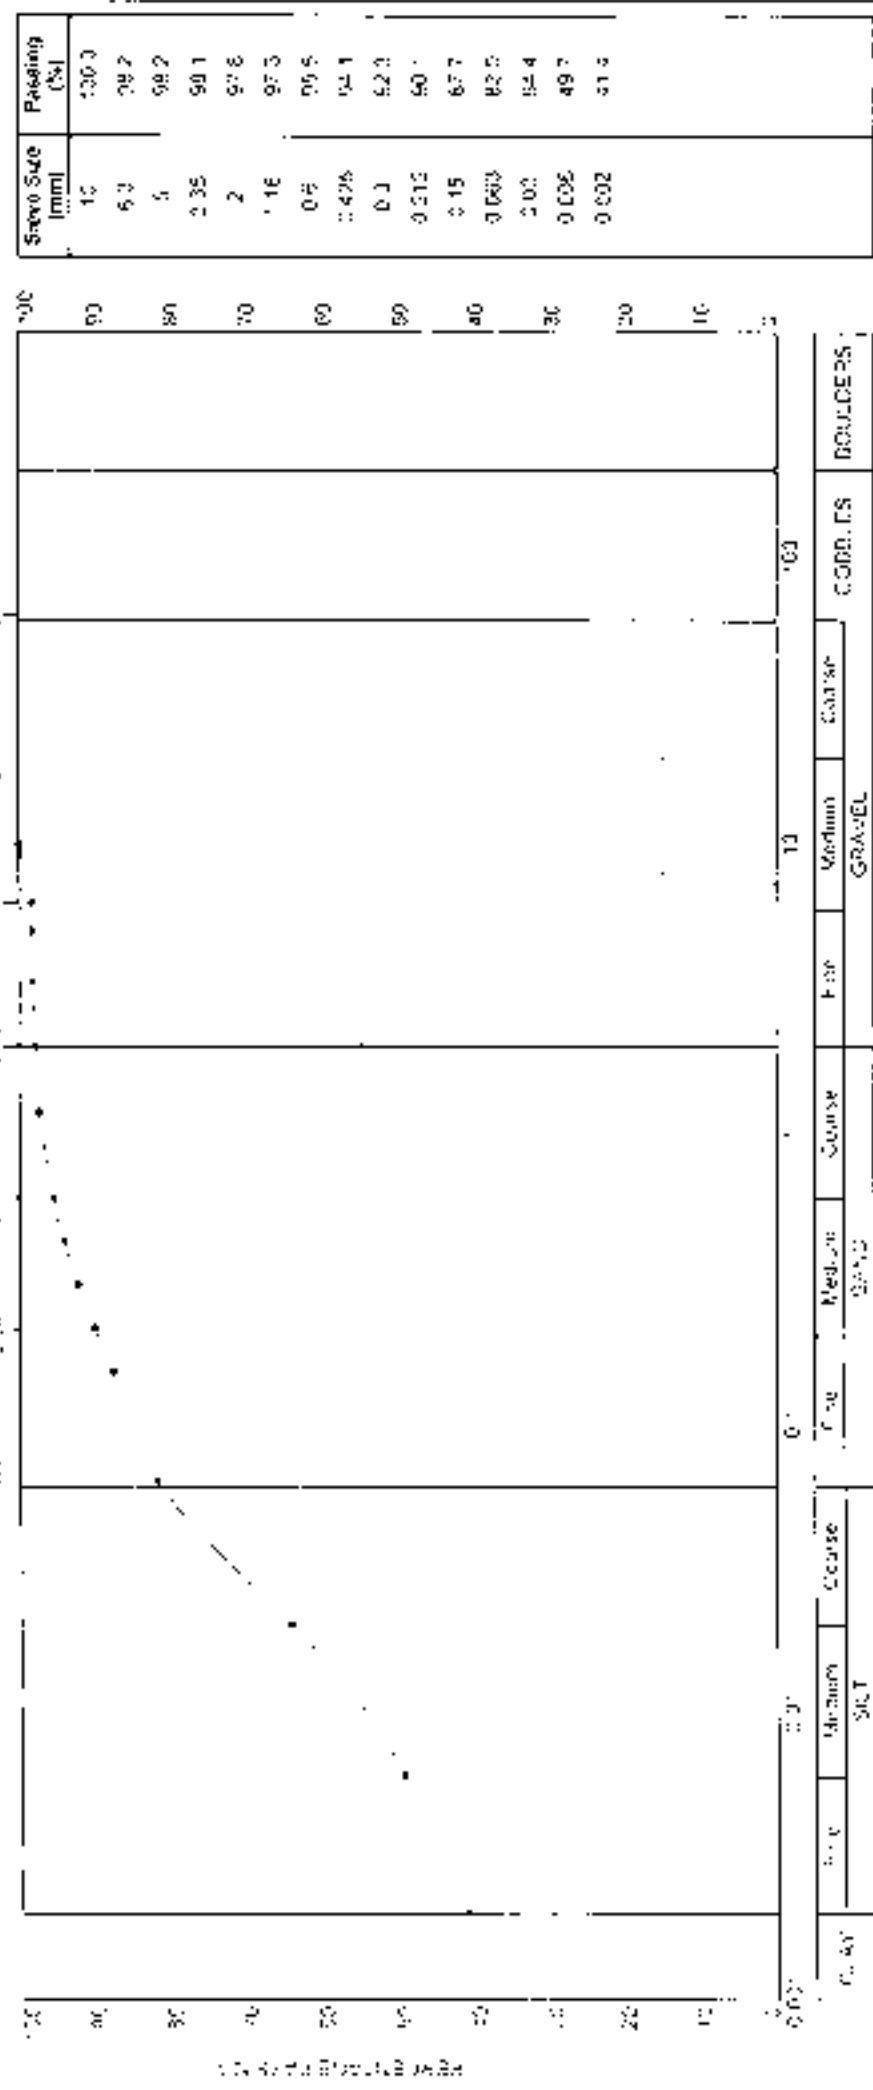

Coarse	Medium	Coarse	Fine	Medium	Coarse	Fine	Medium	Coarse	COBBLES	BOULDERS
SILT			SAND			GRAVEL				

The distribution of sample is as per the results of Sample Description Sheet

AECS
 23/10/2020
 South East Development Consultant

Certificate No. -
 PSN-4251-PR-1414-01-AK-17188-5411-01 Signed: *MSB* Name: _____
 Date: 24/09/2020 Page 1 of 1
 Job Name: PHAIRIE_AUK_TM189 Date of Issue: 24/09/2020 Job No: 4251

ALLIED EXPLORATION & GEOTECHNICS LIMITED

PARTICLE SIZE DISTRIBUTION

GS1377 - Part 2 - Clause 9.2 & 9.4 - 1998


Soil Category Code No: **PRAIR F_AIK_1P189**

Depth (m): **2.90**

Sample Type & No: **B6**

Seismic Depth (m): **2.90**

Date Tested: **30/08/2020**

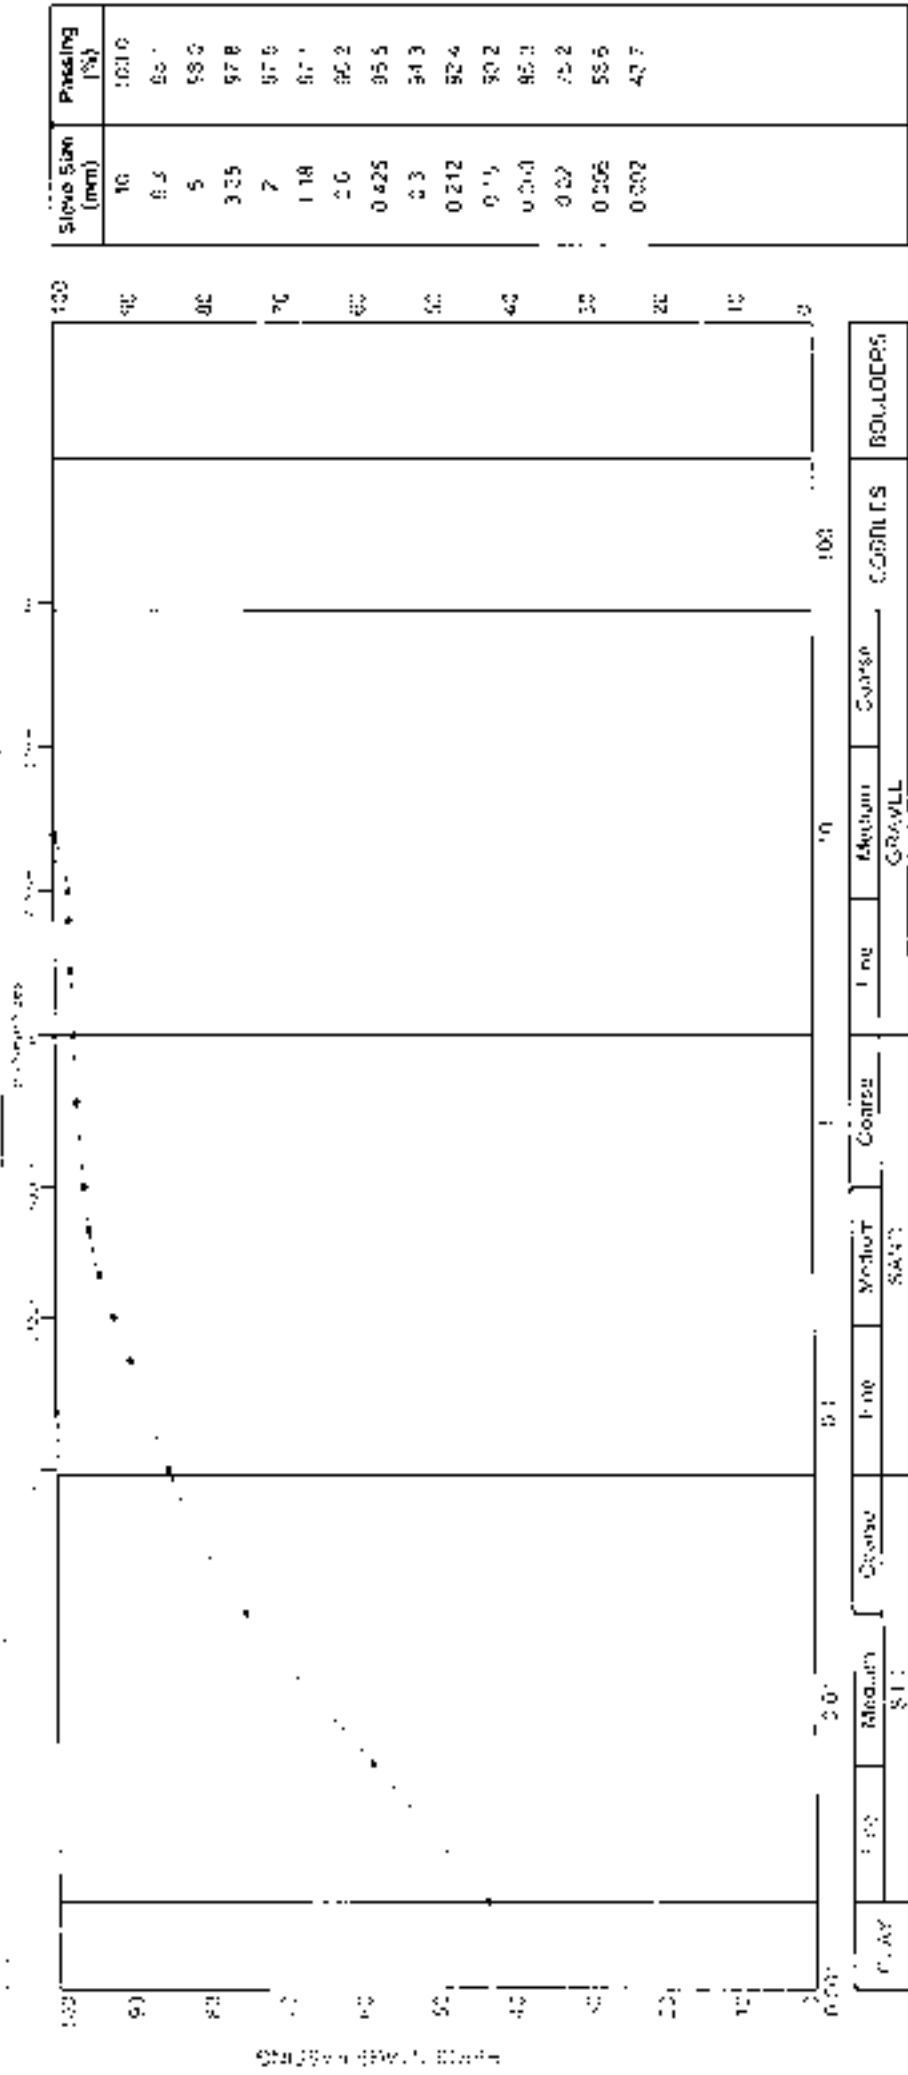

CLAY: MEDIUM SILT: FINE SILT: COARSE SILT: SAND: MEDIUM SAND: COARSE SAND: GRAVEL: MEDIUM GRAVEL: COARSE GRAVEL: BOULDER:

Soil description: **Medium clay with some laboratory sample description**

Client Name: **53112323**

Soil Name: **53112323**

Soil Type: **South West Development Corporation**

Soil Code: **53112323**

Soil Name: **53112323**

Soil Type: **South West Development Corporation**

Page 1 of 1

ALG Contract No: **4251**

**Determination of Calorific Value,
Organic Matter Content, Sulphate and pH
(Tested Externally)**





DETS

Certificate of Analysis

Certificate Number 20-21273

28-Oct-20

Client Allied Exploration & Geotechnics Limited
Unit 25
Stella Gill Industrial Estate
Pelton Fell
DH2 2RG

Our Reference 20-21273

Client Reference 4251

Order No LA 2399

Contract Title Prairie Site Ground Investigation Works

Description 13 Soil samples.

Date Received 22-Oct-20

Date Started 22-Oct-20

Date Completed 28-Oct-20

Test Procedures Identified by prefix DETSn (details on request).

Notes Opinions and interpretations are outside the laboratory's scope of ISO 17025 accreditation. This certificate is issued in accordance with the accreditation requirements of the United Kingdom Accreditation Service. The results reported herein relate only to the material supplied to the laboratory. This certificate shall not be reproduced except in full, without the prior written approval of the laboratory.

Approved By



Adam Fenwick
Contracts Manager





Summary of Chemical Analysis Soil Samples

Our Ref: 20-21273

Client Ref: 4251

Contract Title: Prairie Site Ground Investigation Works

Lab No	1749354	1749355	1749356	1749357	1749358	1749359	1749360
Sample ID	PR103	PR104	PR104	PR106	PR106	PR108	PR112
Depth	13.00	5.95	11.00	5.50	9.50	8.00	1.00
Other ID	27	3	13	2	10	15	3
Sample Type	3	3	1	3	1	1	1
Sampling Date	09/04/2020	03/04/2020	03/04/2020	06/04/2020	06/04/2020	15/04/2020	22/04/2020
Sampling Time	N/A	N/A	N/A	N/A	N/A	N/A	N/A

Test	Method	LOD	Units
Inorganics			
pH	DETSC 2008#	8.2	pH
Colorific Value	DETSC 5098	1	MU/kg
Organic matter	DETSC 2002#	0.1	%
Sulphate-Aqueous Extract as SO4	DETSC 2076#	10	mg/l
		220	140
		120	610
		50	110
		8.6	8.2
		8.3	11.7
		8.0	2.2

Information in Support of the Analytical Results

Our Ref: 20-21273

Client Ref: 4251

Contract: Prairie Site Ground Investigation Works

Containers Received & Deviating Samples

Lab No	Sample ID	Date Sampled	Containers Received	Holding time exceeded for tests	Inappropriate container for tests
1749354	PRAIRIE_AUK_BH103 13.00 SOIL	03/04/20	PT 1L	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1749355	PRAIRIE_AUK_BH104 5.95 SOIL	03/04/20	PT 1L	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1749356	PRAIRIE_AUK_BH104 11.00 SOIL	03/04/20	PT 1L	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1749357	PRAIRIE_AUK_BH106 5.50 SOIL	06/04/20	PT 1L	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1749358	PRAIRIE_AUK_BH106 9.50 SOIL	06/04/20	PT 1L	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1749359	PRAIRIE_AUK_BH108 8.00 SOIL	15/04/20	PT 1L	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1749360	PRAIRIE_AUK_TP112 1.00 SOIL	22/04/20	PT 1L	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1749361	PRAIRIE_AUK_TP115 2.40 SOIL	08/04/20	PT 1L	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1749362	PRAIRIE_AUK_TP116 1.50 SOIL	23/04/20	PT 1L	Anions 2:1 (30 days), Organic Matter (Manual) (28 days), pH + Conductivity (7 days)	
1749363	PRAIRIE_AUK_TP118 1.50 SOIL	23/04/20	PT 1L	Organic Matter (Manual) (28 days)	
1749364	PRAIRIE_AUK_TP120 0.50 SOIL	20/04/20	PT 1L		
1749365	PRAIRIE_AUK_TP140 1.80 SOIL	09/04/20	PT 1L	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1749366	PRAIRIE_AUK_TP154 0.60 SOIL	11/04/20	PT 1L	Anions 2:1 (30 days), pH + Conductivity (7 days)	

Key: P=Plastic T=Tab

DETS cannot be held responsible for the integrity of samples received whereby the laboratory did not undertake the sampling. In this instance samples received may be deviating. Deviating Sample criteria are based on British and International standards and laboratory trials in conjunction with the UKAS note 'Guidance on Deviating Samples'. All samples received are listed above. However, those samples that have additional comments in relation to hold time, inappropriate containers etc are deviating due to the reasons stated. This means that the analysis is accredited where applicable, but results may be compromised due to sample deviations. If no sampled date (soils) or date+time (waters) has been supplied then samples are deviating. However, if you are able to supply a sampled date (and time for waters) this will prevent samples being reported as deviating where specific hold times are not exceeded and where the container supplied is suitable.

Soil Analysis Notes

Inorganic soil analysis was carried out on a dried sample, crushed to pass a 425µm sieve, in accordance with BS3377.

Organic soil analysis was carried out on an 'as received' sample. Organics results are corrected for moisture and expressed on a dry weight basis.

The Loss on Drying, used to express organics analysis on an air dried basis, is carried out at a temperature of 28°C ±/3°C.

Disposal

From the issue date of this test certificate, samples will be held for the following times prior to disposal:

Soils - 1 month, Liquids - 2 weeks, Asbestos (test portions) - 6 months

End of Report



Certificate of Analysis

Certificate Number 20-10974

25-Jun-20

Client Allied Exploration & Geotechnics Limited
Unit 25
Stella Gill Industrial Estate
Pelton Fell
DH2 2RG

Our Reference 20-10974

Client Reference 4251

Order No LA 2358

Contract Title Prairie Site Ground Investigation Works

Description 4 Soil samples.

Date Received 22-Jun-20

Date Started 22-Jun-20

Date Completed 25-Jun-20

Test Procedures Identified by prefix DETSn (details on request)

Notes Opinions and interpretations are outside the laboratory's scope of ISO 17025 accreditation. This certificate is issued in accordance with the accreditation requirements of the United Kingdom Accreditation Service. The results reported herein relate only to the material supplied to the laboratory. This certificate shall not be reproduced except in full, without the prior written approval of the laboratory.

Approved By

A handwritten signature in black ink, appearing to read "Adam Fenwick".

Adam Fenwick
Contracts Manager



Summary of Chemical Analysis Soil Samples

Our Ref 20-10974

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1687327	1687328	1687329	1687330
	PRAIRIE	PRAIRIE	PRAIRIE	PRAIRIE
	AUK_BH1	AUK_BH1	AUK_BH1	AUK_BH1
Sample ID	01	01	01	01
Depth	4.00	9.00	17.00	18.00
Other ID	4	14	30	33
Sample Type	J	J	I	J
Sampling Date	27/04/2020	27/04/2020	28/04/2020	29/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Inorganics							
pH	DETSC 2008#		pH			7.8	8.2
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	1100	270	2400	3000

Information in Support of the Analytical Results

Our Ref: 20-10974

Client Ref: 4251

Contract: Prairie Site Ground Investigation Works

Containers Received & Deviating Samples

Lab No	Sample ID	Date		Containers Received	Holding time exceeded for tests	Inappropriate container for tests
		Sampled				
1687327	PRAIRIE_AUK_BH101 4.00 SOIL	27/04/20		PT 1L	Anions 2:1 (30 days)	
1687328	PRAIRIE_AUK_BH101 5.00 SOIL	27/04/20		PT 1L	Anions 2:1 (30 days)	
1687329	PRAIRIE_AUK_BH101 17.00 SOIL	28/04/20		PT 1L	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1687330	PRAIRIE_AUK_BH101 18.00 SOIL	29/04/20		PT 1L	Anions 2:1 (30 days), pH + Conductivity (7 days)	

Key: P-Plastic T-Tub

DETS cannot be held responsible for the integrity of samples received whereby the laboratory did not undertake the sampling. In this instance samples received may be deviating. Deviating Sample criteria are based on British and International standards and Laboratory trials in conjunction with the UKAS note 'Guidance on Deviating Samples'. All samples received are listed above. However, those samples that have additional comments in relation to hold time, inappropriate containers, etc are deviating due to the reasons stated. This means that the analysis is accredited where applicable, but results may be compromised due to sample deviations. If no sampled date (soils) or date+time (waters) has been supplied then samples are deviating. However, if you are able to supply a sampled date (and time for waters) this will prevent samples being reported as deviating where specific hold times are not exceeded and where the container supplied is suitable.

Soil Analysis Notes

Inorganic soil analysis was carried out on a dried sample, crushed to pass a 425µm sieve, in accordance with BS1377.

Organic soil analysis was carried out on an 'as received' sample. Organics results are corrected for moisture and expressed on a dry weight basis.

The Loss on Drying, used to express organics analysis on an air dried basis, is carried out at a temperature of 28°C ± 2°C.

Disposal

From the issue date of this test certificate, samples will be held for the following times prior to disposal:

Soils - 1 month, Liquids - 3 weeks, Asbestos (test portion) - 6 months.



DETS

Certificate of Analysis

Certificate Number 20-12672-1

20-Jul-20

Client Allied Exploration & Geotechnics Limited
Unit 25
Stella Gill Industrial Estate
Pelton Fell
DH2 2RG

Our Reference 20-12672-1

Client Reference 4251

Order No LA 2358

Contract Title Prairie Site Ground Investigations Works

Description 7 Soil samples.

Date Received 15-Jul-20

Date Started 15-Jul-20

Date Completed 20-Jul-20

Test Procedures Identified by prefix DETSn (details on request).

Notes **This report supersedes 20-12672, amendments.**

Opinions and interpretations are outside the laboratory's scope of ISO 17025 accreditation. This certificate is issued in accordance with the accreditation requirements of the United Kingdom Accreditation Service. The results reported herein relate only to the material supplied to the laboratory. This certificate shall not be reproduced except in full, without the prior written approval of the laboratory.

Approved By



Adam Fenwick
Contracts Manager

Summary of Chemical Analysis Soil Samples

Our Ref 20-12672-1

Client Ref 4251

Contract Title Prairie Site Ground Investigations Works

Lab No	1697828	1697829
Sample ID	PRAIRIE_AUK_BH107	PRAIRIE_AUK_BH107
Depth	3.45	7.50
Other ID	3	12
Sample Type	J	J
Sampling Date	24/04/2020	24/04/2020
Sampling Time	n/a	n/a

Test	Method	LOD	Units		
Inorganics					
pH	DETSC 2008#		pH	8.0	7.9
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	110	250

Summary of Chemical Analysis Soil Samples

Our Ref 20-12672-1

Client Ref 4251

Contract Title Prairie Site Ground Investigations Works

Lab No	1697830	1697831
Sample ID	PRAIRIE_AUK_BH107	PRAIRIE_AUK_BH108
Depth	9.00	7.00
Other ID	1E	14
Sample Type	J	B
Sampling Date	24/04/2020	15/04/2020
Sampling Time	n/c	n/c

Test	Method	LOD	Units		
Inorganics					
pH	DETSC 2008#		pH	7.9	8.1
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	1700	640

Summary of Chemical Analysis

Soil Samples

Our Ref 20-12672-1

Client Ref 4251

Contract Title Prairie Site Ground Investigations Works

Lab No	1697834
Sample ID	PRAIRIE_AUK_BH110
Depth	15.00
Other ID	27
Sample Type	1
Sampling Date	22/04/2020
Sampling Time	n/a

Test	Method	LOD	Units	
Inorganics				
pH	DETSC 2008#		pH	8.3
Sulphate Aqueous Extract as SO ₄	DETSC 2076#	10	mg/l	2200

Information in Support of the Analytical Results

Our Ref: 20-12672-1
 Client Ref: 4251
 Contract: Prairie Site Ground Investigations Works

Containers Received & Deviating Samples

Lab No	Sample ID	Date Sampled	Containers Received	Holding time exceeded for tests	Inappropriate container for tests	Headspace in container for tests
1697828	PRAIRIE_AUK_BH10 7 3.45 SOIL	24/04/20	PT 900ml	Anions 2-1 (30 days), pH + Conductivity (7 days)		
1697829	PRAIRIE_AUK_BH10 7 7.50 SOIL	24/04/20	PT 100ml	Anions 2-1 (30 days), pH + Conductivity (7 days)		
1697830	PRAIRIE_AUK_BH10 7 9.00 SOIL	24/04/20	PT 900ml	Anions 2-1 (30 days), pH + Conductivity (7 days)		
1697831	PRAIRIE_AUK_BH10 8 7.00 SOIL	15/04/20	PT 500ml	Anions 2-1 (30 days), pH + Conductivity (7 days)		
1697832	PRAIRIE_AUK_BH10 8 9.00 SOIL	15/04/20	PT 900ml	Anions 2-1 (30 days), pH + Conductivity (7 days)		
1697833	PRAIRIE_AUK_BH11 0 11.45 SOIL	21/04/20	PT 900ml	Anions 2-1 (30 days), pH + Conductivity (7 days)		
1697834	PRAIRIE_AUK_BH11 0 13.00 SOIL	22/04/20	PT 600ml	Anions 2-1 (30 days), pH + Conductivity (7 days)		

Key: P=Plastic T-Tub

DETS cannot be held responsible for the integrity of samples received whereby the laboratory did not undertake the sampling. In this instance samples received may be deviating. Deviating Sample criteria are based on British and International standards and laboratory criteria in conjunction with the UKAS note 'Guidance on Deviating Samples'. All samples received are listed above. However, those samples that have additional comments in relation to hold time, inappropriate containers etc are deviating due to the reasons stated. This means that the analysis is accredited where applicable, but results may be compromised due to sample deviations. If no sampled date (soils) or date/time (waters) has been supplied then samples are deviating. However, if you are able to supply a sampled date (and time for waters) this will prevent samples being reported as deviating where specific hold times are not exceeded and where the container supplied is suitable.

Soil Analysis Notes

Inorganic soil analysis was carried out on a dried sample, retained to pass a 425um sieve, in accordance with BS1377.

Organic soil analysis was carried out on an 'as received' sample. Organic results are corrected for moisture and expressed as a dry weight basis.

The Loss on Drying, used to express organic analysis on an air dried basis, is carried out at a temperature of 20°C \pm 2°C.

Disposal

From the issue date of this test certificate, samples will be held for the following times prior to disposal:

Soils - 1 month, Liquids - 2 weeks, Asbestos (fast potting) - 6 months.



Certificate of Analysis

Certificate Number 20-19447

13-Oct-20

Client Allied Exploration & Geotechnics Limited
Unit 25
Stella Gill Industrial Estate
Pelton Fell
DH2 2RG

Our Reference 20-19447

Client Reference 4251

Order No LA 2399

Contract Title Prairie Site Ground Investigation Works

Description 21 Soil samples.

Date Received 05-Oct-20

Date Started 05-Oct-20

Date Completed 13-Oct-20

Test Procedures Identified by prefix DETSn (details on request).

Notes Opinions and interpretations are outside the laboratory's scope of ISO 17025 accreditation. This certificate is issued in accordance with the accreditation requirements of the United Kingdom Accreditation Service. The results reported herein relate only to the material supplied to the laboratory. This certificate shall not be reproduced except in full, without the prior written approval of the laboratory.

Approved By

A handwritten signature in black ink, appearing to read "Adam Fenwick".

Adam Fenwick
Contracts Manager





Summary of Chemical Analysis Soil Samples

Our Ref: 20-19447

Client Ref: 4251

Contract Title: Prairie Site Ground Investigation Works

Lab No	1738055	1738056	1738057	1738058	1738059	1738060	1738061	1738062	1738063	1738064
PRAIRIE_AUK	PRAIRIE_AUK	PRAIRIE_AUK	PRAIRIE_AUK	PRAIRIE_AUK	PRAIRIE_AUK	PRAIRIE_AUK	PRAIRIE_AUK	PRAIRIE_AUK	PRAIRIE_AUK	PRAIRIE_AUK
TP101	TP101	TP104	TP107	TP124	TP132	TP146C	TP162	TP162	TP162	TP163
0.60	4.40	2.00	0.50	1.00	0.50	1.00	0.70	0.70	3.10	1.60
1	14	8	3	3	2	4	1	1	7	4
Sample Type										
Sampling Date	01/04/2020	01/04/2020	06/04/2020	08/04/2020	02/04/2020	14/04/2020	14/04/2020	14/04/2020	14/04/2020	14/04/2020
Sampling Time	n/a	n/a	n/a	n/a	n/a	n/a	n/a	n/a	n/a	n/a
LOD										
Units										

Test

Test	Method	LOD	Units
Inorganics			
pH	DETSC 2008#		pH
			9.8
Calorific Value	DETSC 5008	1	MJ/kg
			4.8
Organic matter	DETSC 2002#	0.1	%
			3.2
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l
			890
			10.5
			4.6
			< 1.0
			3.5
			9.7
			3.6
			230
			250
			7.4

Summary of Chemical Analysis Soil Samples

Our Ref: 20-19447

Client Ref: 4251

Contract Title: Prairie Site Ground Investigation Works

Lab No	1736075
Sample ID	PRAMM_AJLK
Depth	TP189
Other ID	1.40
Sample Type	3
Sampling Date	7
Sampling Time	07/04/2020
LOD	n/a

Test	Method	LOD	Units
Inorganics			
pH	DETSC 2008B		pH
Calorific Value	DETSC S008	1	MJ/kg
Organic matter	DETSC 2002B	0.1	%
Sulphate Aqueous Extract as SO4	DETSC 2075B	10	mg/l
			570

Information in Support of the Analytical Results

Our Ref 20-19447

Client Ref 4251

Contract Prairie Site Ground Investigation Works

Containers Received & Deviating Samples

Lab No	Sample ID	Date Sampled	Containers Received	Holding time exceeded for tests	inappropriate container for tests
1738055	PRAIRIE_AUK_TP101 0.40 SOIL	01/04/20	PT 500ml	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1738056	PRAIRIE_AUK_TP101 4.40 SOIL	01/04/20	PT 500ml	Organic Matter (Manual) (28 days)	
1738057	PRAIRIE_AUK_TP104 2.00 SOIL	01/04/20	PT 500ml	Organic Matter (Manual) (28 days)	
1738058	PRAIRIE_AUK_TP107 0.50 SOIL	06/04/20	PT 500ml	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1738059	PRAIRIE_AUK_TP124 1.00 SOIL	08/04/20	PT 500ml		
1738060	PRAIRIE_AUK_TP132 0.50 SOIL	02/04/20	PT 500ml		
1738061	PRAIRIE_AUK_TP146C 1.00 SOIL	14/04/20	PT 500ml		
1738062	PRAIRIE_AUK_TP162 0.70 SOIL	14/04/20	PT 500ml	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1738063	PRAIRIE_AUK_TP162 1.10 SOIL	14/04/20	PT 500ml	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1738064	PRAIRIE_AUK_TP163 1.60 SOIL	14/04/20	PT 500ml	Organic Matter (Manual) (28 days)	
1738065	PRAIRIE_AUK_TP165 1.50 SOIL	15/04/20	PT 500ml	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1738066	PRAIRIE_AUK_TP165 2.50 SOIL	15/04/20	PT 500ml		
1738067	PRAIRIE_AUK_TP173 0.60 SOIL	09/04/20	PT 500ml	Anions 2:1 (30 days), Organic Matter (Manual) (28 days), pH + Conductivity (7 days)	
1738068	PRAIRIE_AUK_TP176 1.50 SOIL	07/04/20	PT 500ml	Anions 2:1 (30 days), Organic Matter (Manual) (28 days), pH + Conductivity (7 days)	
1738069	PRAIRIE_AUK_TP178 0.40 SOIL	06/04/20	PT 500ml	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1738070	PRAIRIE_AUK_TP178 1.60 SOIL	06/04/20	PT 500ml	Organic Matter (Manual) (28 days)	
1738071	PRAIRIE_AUK_TP179 0.20 SOIL	09/04/20	PT 500ml	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1738072	PRAIRIE_AUK_TP182 0.30 SOIL	09/04/20	PT 500ml		
1738073	PRAIRIE_AUK_TP183 0.40 SOIL	08/04/20	PT 500ml	Anions 2:1 (30 days), pH + Conductivity (7 days)	
1738074	PRAIRIE_AUK_TP189 0.30 SOIL	07/04/20	PT 500ml		
1738075	PRAIRIE_AUK_TP189 1.40 SOIL	07/04/20	PT 500ml	Anions 2:1 (30 days), Organic Matter (Manual) (28 days), pH + Conductivity (7 days)	

Key: P-Plastic 1-Tub

DETS cannot be held responsible for the integrity of samples received whereby the laboratory did not undertake the sampling. In this instance samples received may be deviating. Deviating Sample criteria are based on British and International standards and laboratory trials in conjunction with the UKAS note 'Guidance on Deviating Samples'. All samples received are listed above. However, those samples that have additional comments in relation to hold time, inappropriate container etc are deviating due to the reasons stated. This means that the analysis is accredited where applicable, but results may be compromised due to sample deviating. If no sampled date (soils) or date+time (waters) has been supplied then samples are deviating. However, if you are able to supply a sampled date (and time for waters) this will prevent samples being reported as deviating where specific hold times are not exceeded and where the container supplied is suitable.

Information in Support of the Analytical Results

Our Ref 20-19447

Client Ref 4251

Contract Prairie Site Ground Investigation Works

Soil Analysis Notes

Inorganic soil analysis was carried out on a dried sample, crushed to pass a 425µm sieve, in accordance with BS1377.

Organic soil analysis was carried out on an 'as received' sample. Organics results are corrected for moisture and expressed on a dry weight basis.

The Loss on Drying, used to express organics analysis on an air dried basis, is carried out at a temperature of 28°C ± 2°C.

Disposal

From the issue date of this test certificate, samples will be held for the following times prior to disposal:

Soils - 1 month, Liquids - 2 weeks, Asbestos (test portion) - 6 months

End of Report

Determination of Dry Density/Moisture Content Relationship



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 27, Moor Lane Industrial Estate, Harington, Chester-le-Street, Co. Durham, (UK) (NE) Tel: 0191 387 4720 Fax: 0191 387 4751
Regional Office: Unit 20, Riverside Development Centre, Easton Green, Sedgefield, (UK) (NE) Tel: 0191 353 3344 Fax: 0191 373 1989

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 Part 4: 1990

Specimen Identification

Exploratory Hole No - PRAIRIE_AUK_BH107 Depth (m) - 4.00

Sample Type & No - B5

Test Method 2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 17.0

Particle Density (Assumed) = 2.70


Maximum Dry Density (Mg/m³) = 1.75

Retained on 20mm Sieve (%) = 0.0

Date Tested = 14/07/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

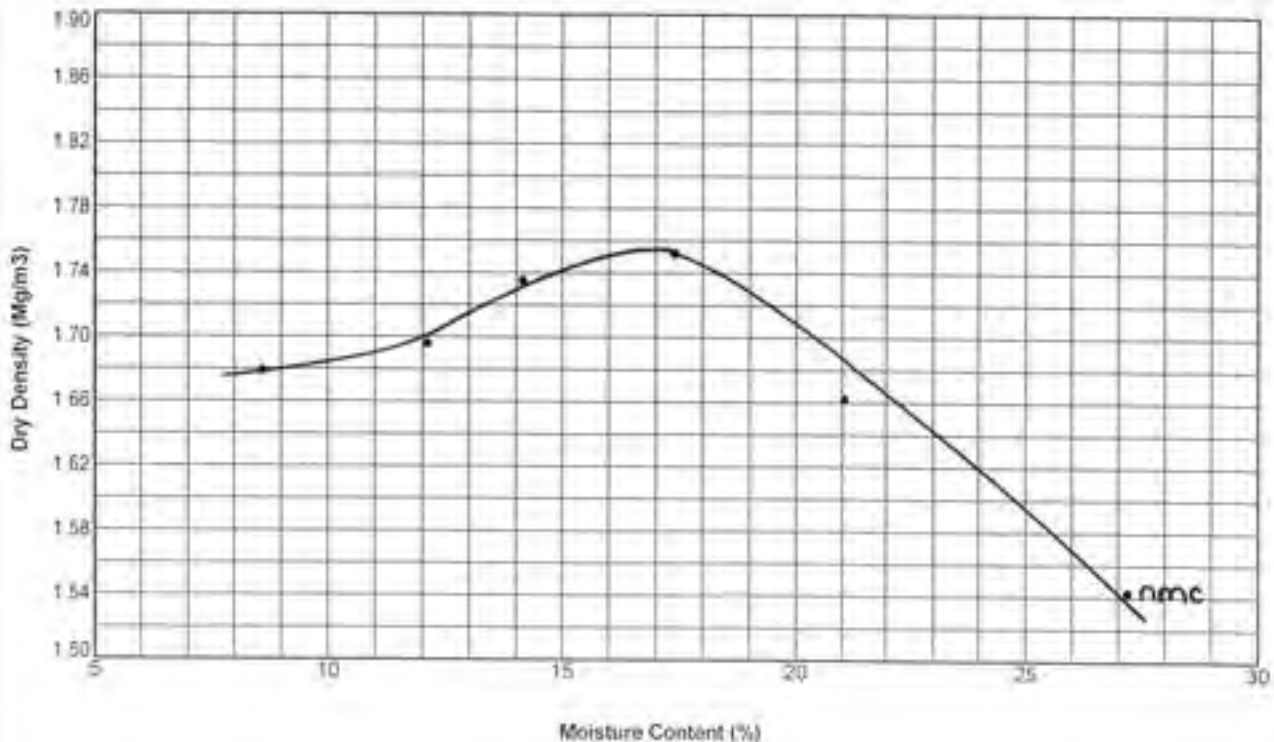

For description of sample please refer to the Laboratory Sample Description Sheet

Contact Title - Prairie Site Ground Investigation Works

Client - South Tees Development Corporation



Signature - *mscho*

Name - *M. Schofield*

Page 1 of 1

Date of issue - 14/07/2020

Certificate No. - COMP42511

AEIG Contact No. - 4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21, Gower Park Industrial Estate, Potters Park, St Albans, Herts, SG8 5JG. Tel: 01763 207400 Fax: 01763 201421
Regional Office: Unit 20, Business Development Centre, Kilmarnock, East Ayrshire, SA11 5SL. Tel: 01772 705300 Fax: 01772 735988

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 : Part 4 : 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_BH109 Depth (m) - 2.00

Sample Type & No :- B10

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 18.0

Particle Density (Assumed) = 2.70


Maximum Dry Density (Mg/m³) = 1.70

Retained on 20mm Sieve (%) = 0.0

Date Tested = 14/07/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

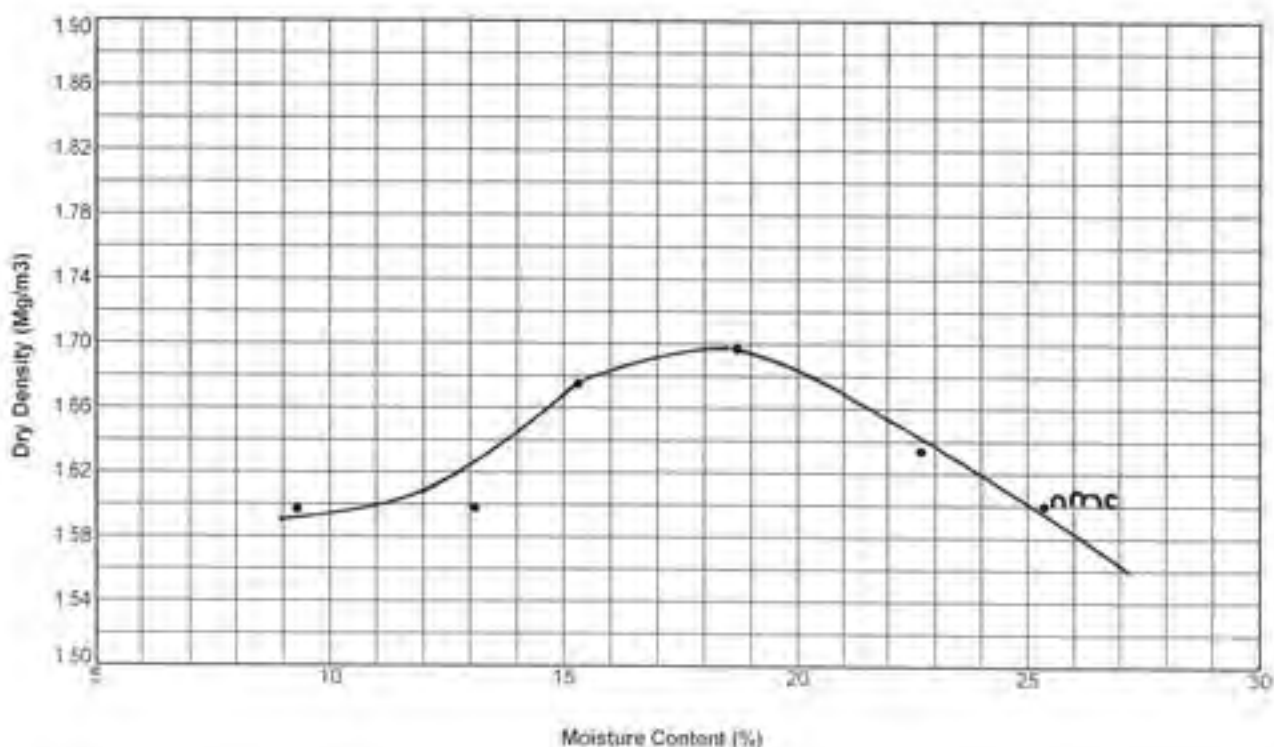

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed - *msene*

Name - *JCLN*

Page 1 of 1

Date of issue - 14/07/2020

Certificate No - GDMR/4251/1

AEG Contract No - 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25 100fta Old Industrial Estate, Potters Field, Clonville, Ayrshire, Co. Durham, DA1 2NS, Tel: 0191 287 4766 Fax: 0191 287 4734
Regional Office: Unit 20, Business Centre, Colindale Avenue, Uxbridge, Middlesex, UB8 3PH, Tel: 01772 775 000 Fax: 01772 775 000

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP BS 1377 : Part 4 : 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_BH110 Depth (m) :- 6.50

Sample Type & No :- B10

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 15.0

Particle Density (Assumed) = 2.70


Maximum Dry Density (Mg/m³) = 1.73

Retained on 20mm Sieve (%) = 0.0

Date Tested = 14/07/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

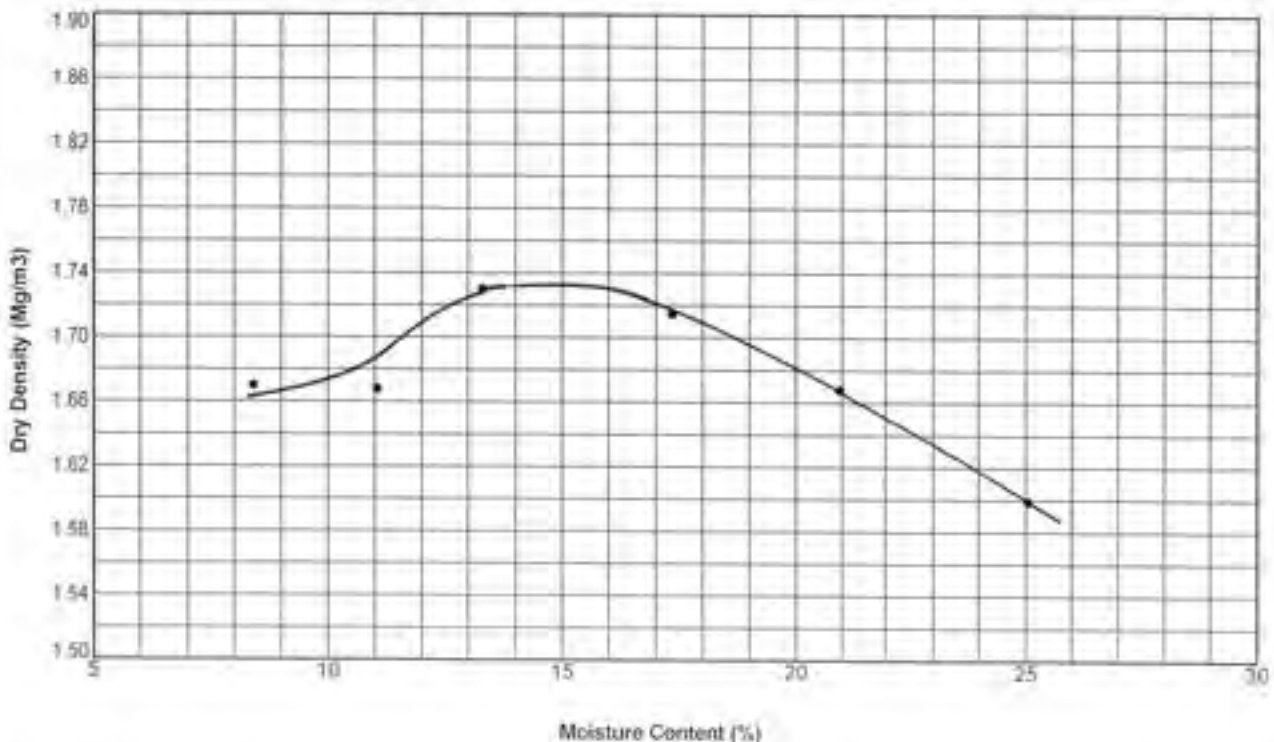

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed :-

msone

Name :-

MSONE

Page 1 of 1

Date of issue :-

11/07/2020

Certificate No :-

COMB4251/1

REG Contract No :-

4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 100-25 Area 041 Industrial Estate, Pickett Park, Chester-le-Street, Co. Durham, DA2 2AD. Tel: 0191 267 4700 Fax: 0191 267 4710
Regional Office: Unit 21, Business Development Centre, Enterprise Park, Broomby, BS1 1BL. Tel: 0117 251 7000 Fax: 0117 251 7001

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP BS 1377 - Part 4, 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP105 Depth (m) :- 2.00

Sample Type & No :- B5

Test Method 2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 17.0

Particle Density (Assumed) = 2.65


Maximum Dry Density (Mg/m³) = 1.65

Retained on 20mm Sieve (%) = 2.0

Date Tested = 30/09/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

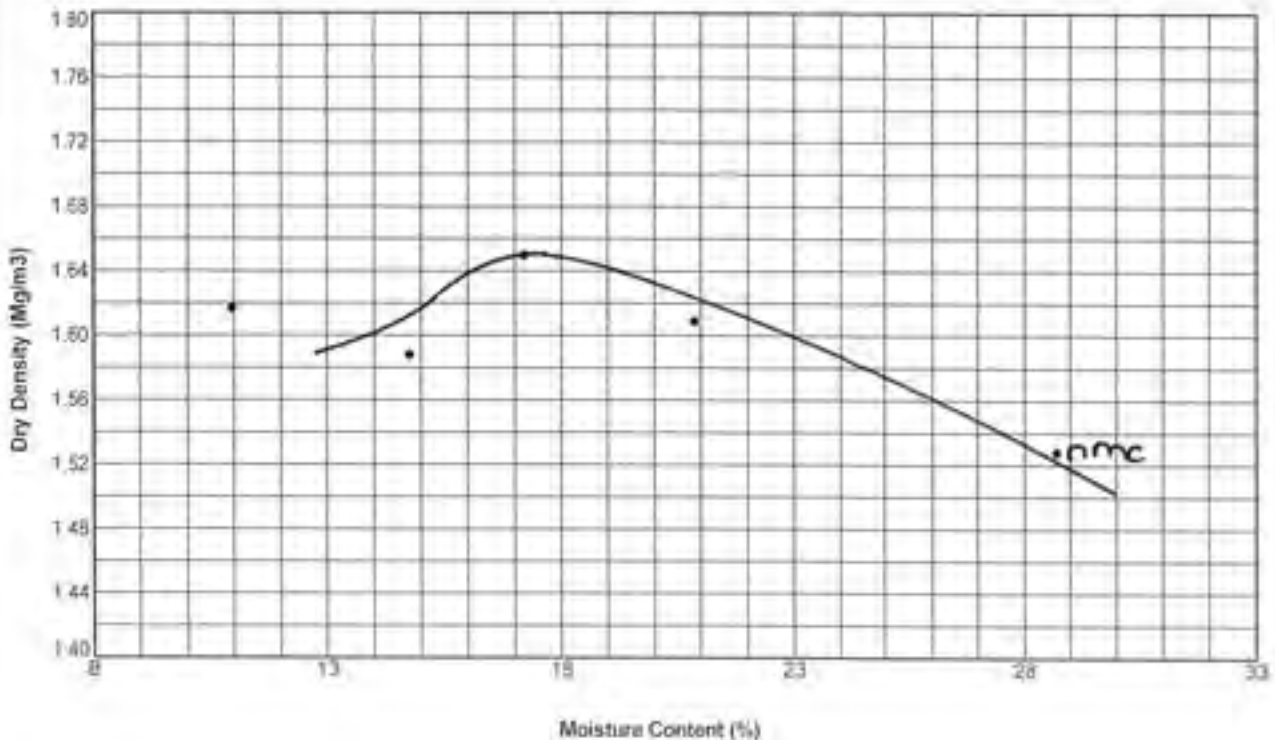

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works

Client :- South Tates Development Corporation



Signed :- *msene*

Name :-

Page 1 of 1

Date of issue
02/11/2020

Certificate No >
COMB/4251/1

AEG Contract No. >
4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Widdow's Gar Industrial Estate, Widdow's Park, Chester-le-Street, Co. Durham, DA5 2JG. Tel: 0191 287 8796 Fax: 0191 687 1160
Regional Office: Unit 20, Seabank Development Centre, Easton-le-Moors, Barnsley, S71 5NL. Tel: 01223 191 386 Fax: 01223 191 388

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP BS 1377 - Part 4 : 1990

Specimen Identification

Exploratory Hole No - PRAIRIE_AUK_TP107 Depth (m) - 1.00

Sample Type & No - B4

Test Method 2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 17.5

Particle Density (Assumed) = 2.70


Maximum Dry Density (Mg/m³) = 1.71

Retained on 20mm Sieve (%) = 5.0

Date Tested = 30/09/2020

Retained on 37.5mm Sieve (%) = 4.0

Remarks :

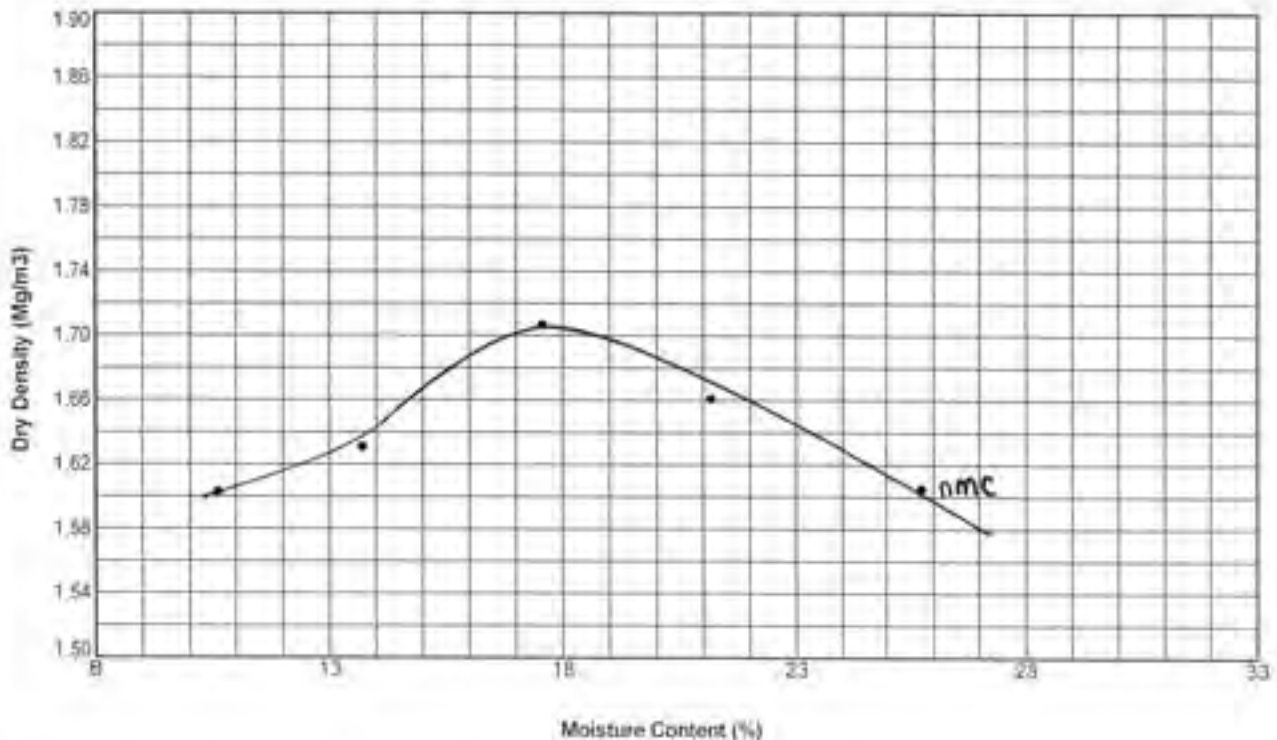

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title:-

Prairie Site Ground Investigation Works

Client:-

South Tees Development Corporation



Signed:-

mserp

Name:-

M. Serp

Page 1 of 1

Date of issue

02/11/2020

Certificate No:-

COMP42511

AEG Contract No:-

4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21, Bally, 28, Buntingford Road, Tipton Park, Chorley, Greater Manchester, Co. Lancashire, M40 2PQ - Tel: 01257 347410 Fax: 01257 347411
Regional Offices: Unit 20, Business Development Centre, Tropic Street, Bournemouth, BH1 1SB - Tel: 01202 757000 Fax: 01202 757001

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 Part 4: 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP110 Depth (m) :- 3.00

Sample Type & No :- B8

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 21.0

Particle Density (Assumed) = 2.65


Maximum Dry Density (Mg/m³) = 1.60

Retained on 20mm Sieve (%) = 0.0

Date Tested = 16/10/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

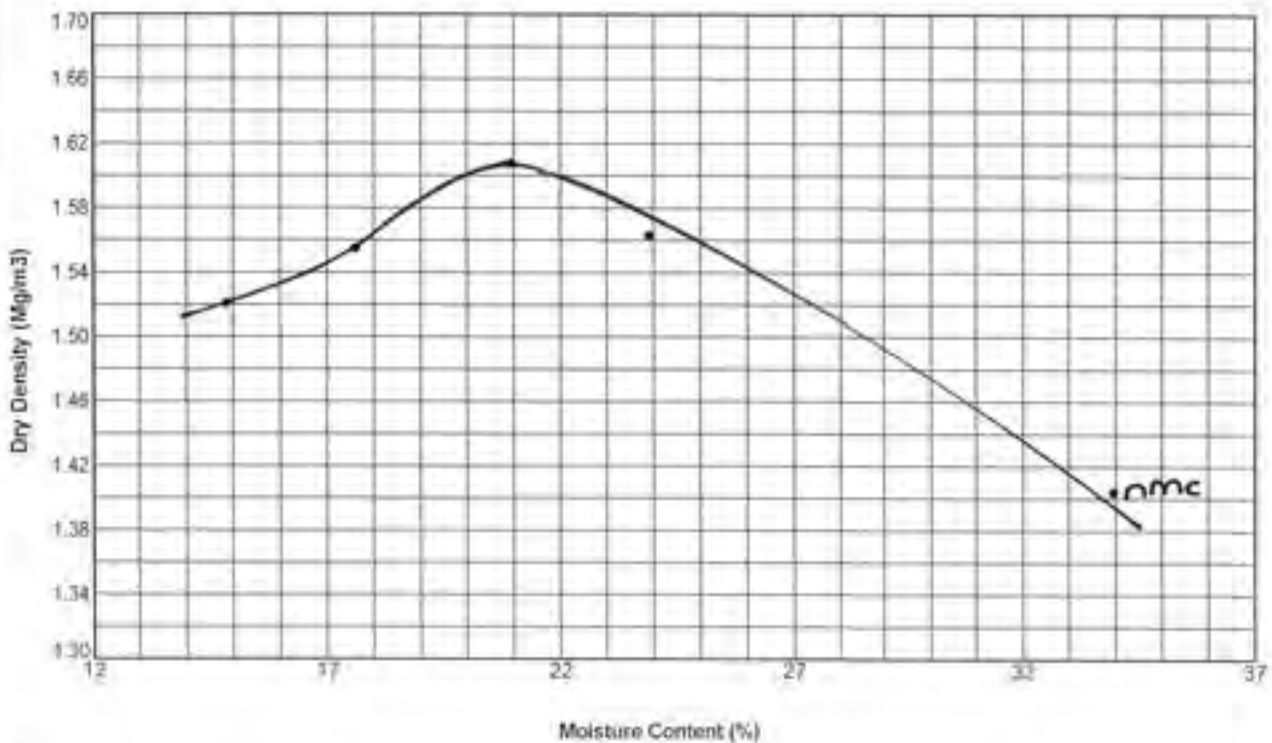

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed :- *msene*

Name :- M. SENE

Page 1 of 1

Date of Issue :- 02/11/2020

Certificate No. :- GOMR/4251/1

AEG Contract No. :- 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, 2000 International Business Park, Park Road, Chesham, Bucks, UK, Bucks HP80 2NS - Tel: 01494 381470 Fax: 01494 381471
Regional Office: Unit 25, Enterprise Development Centre, Station Wharf, Banbury, Oxon OX1 5BL - Tel: 01235 725300 Fax: 01235 725301

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP BS 1377 - Part 4 : 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP112 Depth (m) :- 1.70

Sample Type & No :- B5

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 20.5

Particle Density (Assumed) = 2.35


Maximum Dry Density (Mg/m³) = 1.52

Retained on 20mm Sieve (%) = 28.0

Date Tested = 19/10/2020

Retained on 37.5mm Sieve (%) = 10.0

Remarks :

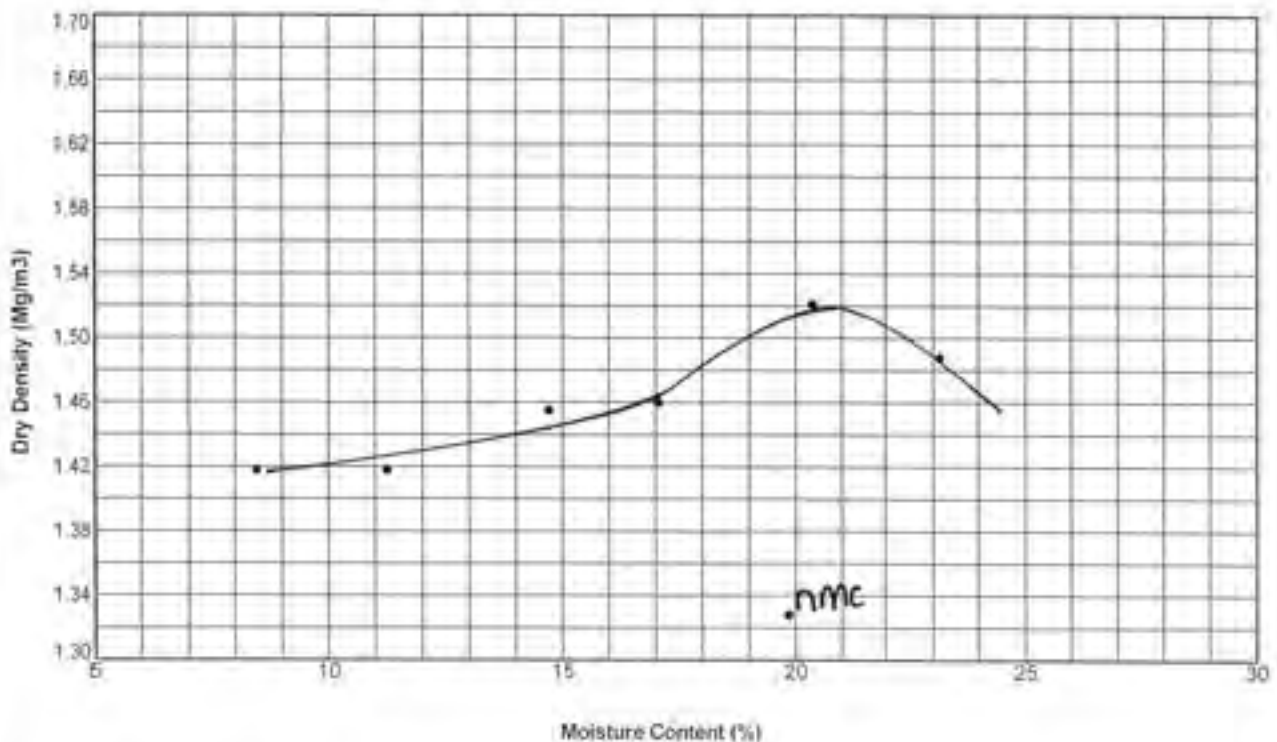

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed :- *msene*

Name :-

Page 1 of 1

Date of issue :-
02/11/2020

Certificate No :-
COMP4251/1

AEG Contract No :-
4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21, Broomfield Industrial Estate, Filton, Bristol, Gloucestershire, UK. Phone: 01275 425600 Fax: 01275 425601
Regional Office: Unit 21, Broomfield Industrial Estate, Filton, Bristol, Gloucestershire, UK. Phone: 01275 425600 Fax: 01275 425601

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 - Part 4 - 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP112 Depth (m) :- 3.20

Sample Type & No :- B11

Test Method

2.5kg Compaction

Separate Samples

Test Results

Optimum Moisture Content (%) = 16.5

Particle Density (Assumed) = 2.65


Maximum Dry Density (Mg/m³) = 1.70

Retained on 20mm Sieve (%) = 0.0

Date Tested = 16/10/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

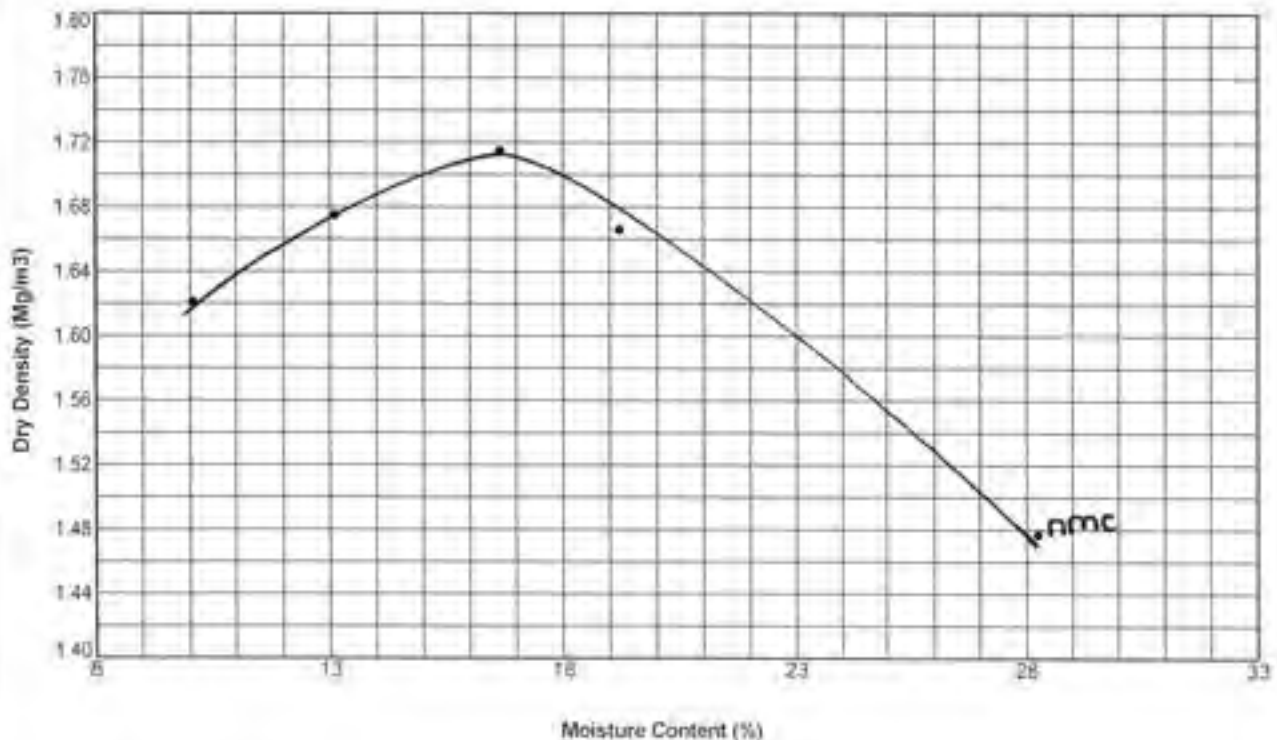

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed - *msone*

Name :-

Page 1 of 1

Date of issue :-
02/11/2020

Certificate No :-
COMP/4251/1

AEG Contract No :-
4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: LUTON, Bucks MK14 7JQ, UK. Tel: 01135 524444 Fax: 01135 524444
Regional Office: 27, Sowerby Road, South Tees, Middlesbrough, Cleveland, UK. Tel: 01642 750000 Fax: 01642 750000

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 - Part 4: 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP116 Depth (m) :- 2.50

Sample Type & No :- B8

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 20.0

Particle Density (Assumed) = 2.65


Maximum Dry Density (Mg/m³) = 1.65

Retained on 20mm Sieve (%) = 0.0

Date Tested = 16/10/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

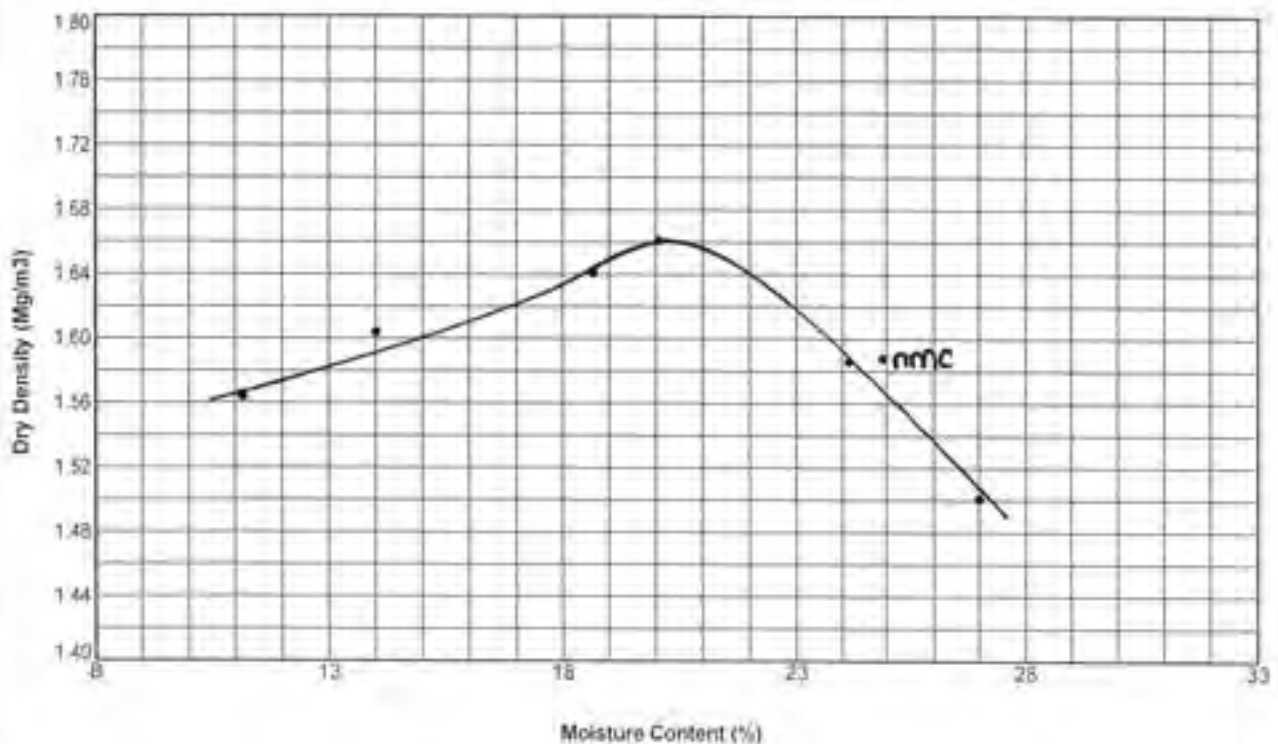

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed :-

[Handwritten Signature]

Name :-

[Handwritten Name]

Page 1 of 1

Date of Issue :-

02/11/2020

Certificate No.:-

COMPM251/1

AEG Contract No. :-

4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21, Mill Lane, Huddersfield, West Yorkshire, HD1 2HS. Tel: 01484 595100 Fax: 01484 595110
Regional Office: Unit 20, Sowerby Development Centre, Sowerby Wharfedale, Huddersfield, HD1 3SE. Tel: 01484 595110 Fax: 01484 595110

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP BS 1377 - Part 4 : 1990

Specimen Identification

Exploratory Hole No - PRAIRIE_AUK_TP116 Depth (m) - 3.50

Sample Type & No - B10

Test Method

2.5kg Compaction

Separate Samples

Test Results

Optimum Moisture Content (%) = 14.0

Particle Density (Assumed) = 2.65


Maximum Dry Density (Mg/m³) = 1.85

Retained on 20mm Sieve (%) = 3.2

Date Tested = 19/10/2020

Retained on 37.5mm Sieve (%) = 1.8

Remarks :

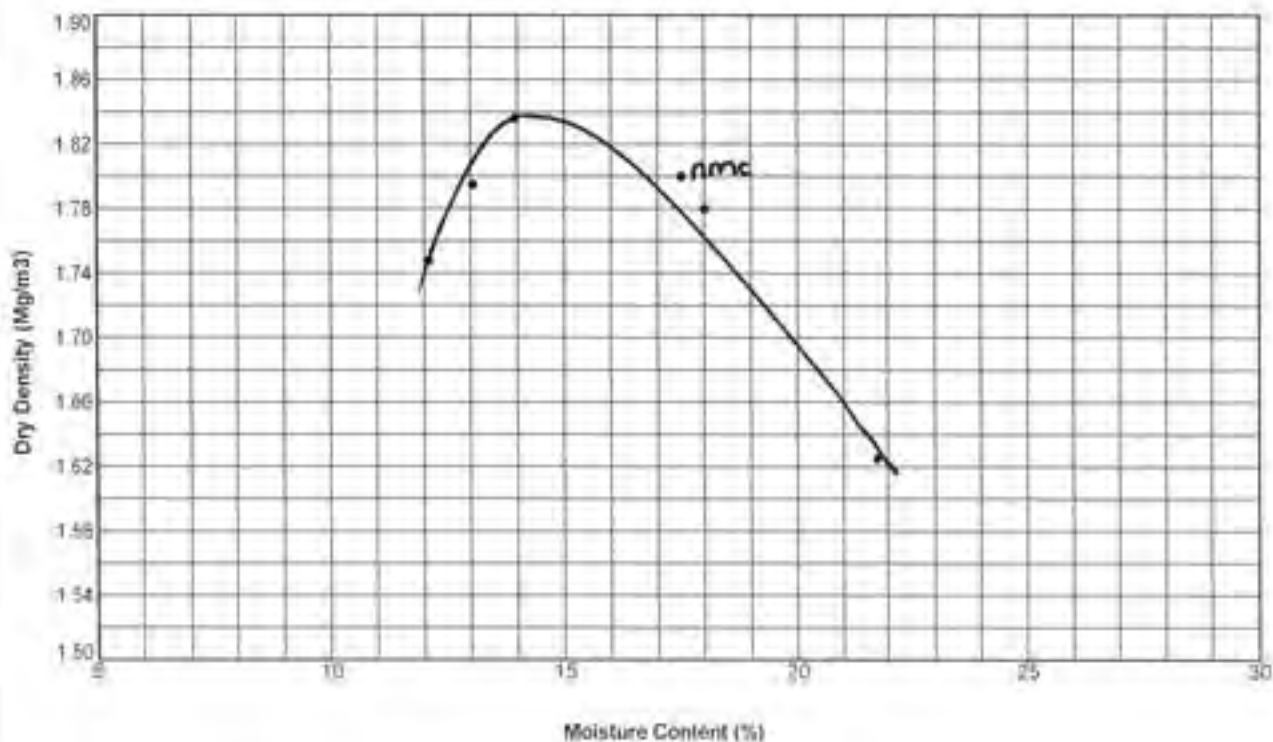

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed :-

msene

Name :-

CLAYTON

Page 1 of 1

Date of Issue :-

02/11/2020

Certificate No :-

COMR/4251/1

AEG Contract No :-

4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Sevinge, 24 Industrial Estate, Evesham, Warwickshire, CV22 6JG, UK. Tel: 01454 302470 Fax: 01454 302475
Regional Office: Unit 20, Business Development Centre, Evesham Road, Stratford-upon-Avon, CV37 9BL, UK. Tel: 01773 751200 Fax: 01773 751201

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 : Part 4 : 1990

Specimen Identification

Exploratory Hole No - PRAIRIE_AUK_TP118 Depth (m) :- 2.50

Sample Type & No :- B7

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 23.5

Particle Density (Assumed) = 2.65


Maximum Dry Density (Mg/m³) = 1.55

Retained on 20mm Sieve (%) = 0.0

Date Tested = 19/10/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

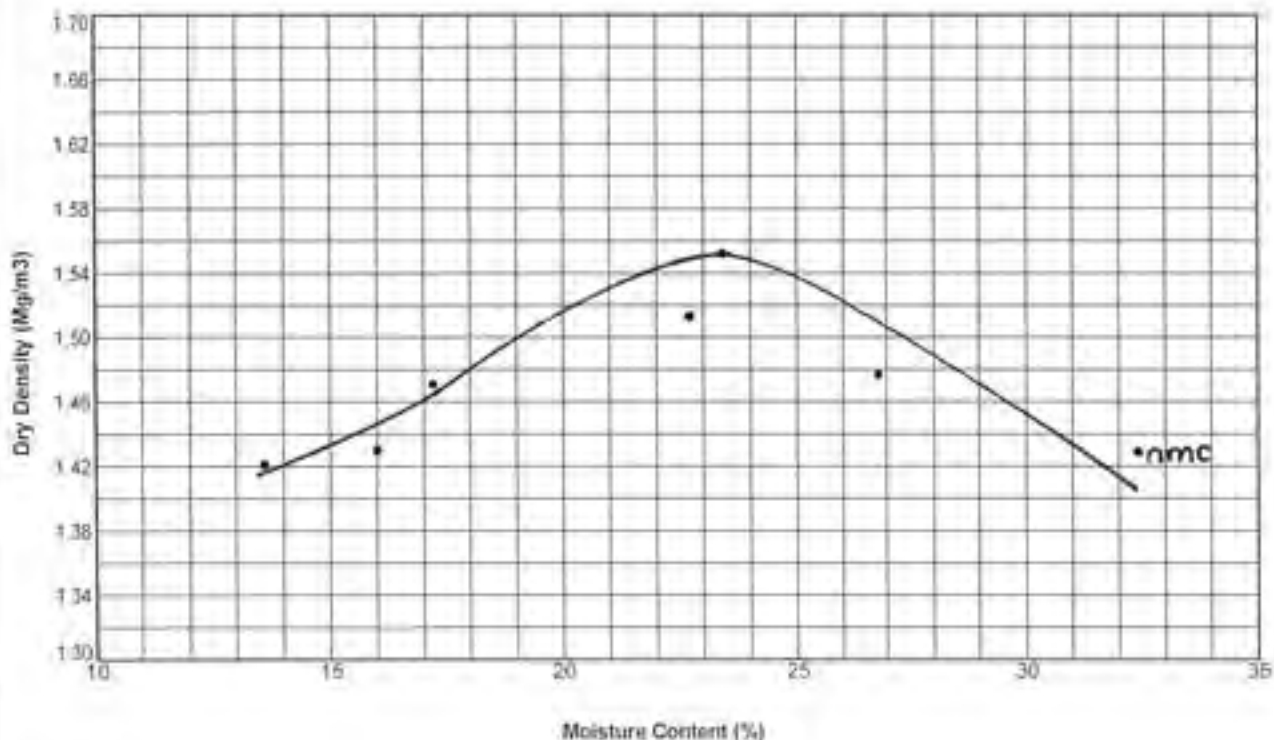

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed *msene*

Name - *M. SELKIRK*

Page 1 of 1

Date of issue :-
02/11/2020

Certificate No. :-
COMR/4251/1

AEG Contract No. :-
4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office Unit 25 (2nd) Westborough Works, Fulford Park, Doncaster, DN2 2SQ - Tel: 01522 567476 Fax: 01522 567477
Regional Office Unit 12 Business Centre, Gillingham, Dorset, DT2 8SL - Tel: 01722 276307 Fax: 01722 276308

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377: Part 4: 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP119 Depth (m) :- 2.00

Sample Type & No :- B5

Test Method 2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 18.5

Particle Density (Assumed) = 2.85


Maximum Dry Density (Mg/m³) = 1.87

Retained on 20mm Sieve (%) = 17.0

Date Tested = 19/10/2020

Retained on 37.5mm Sieve (%) = 9.0

Remarks :

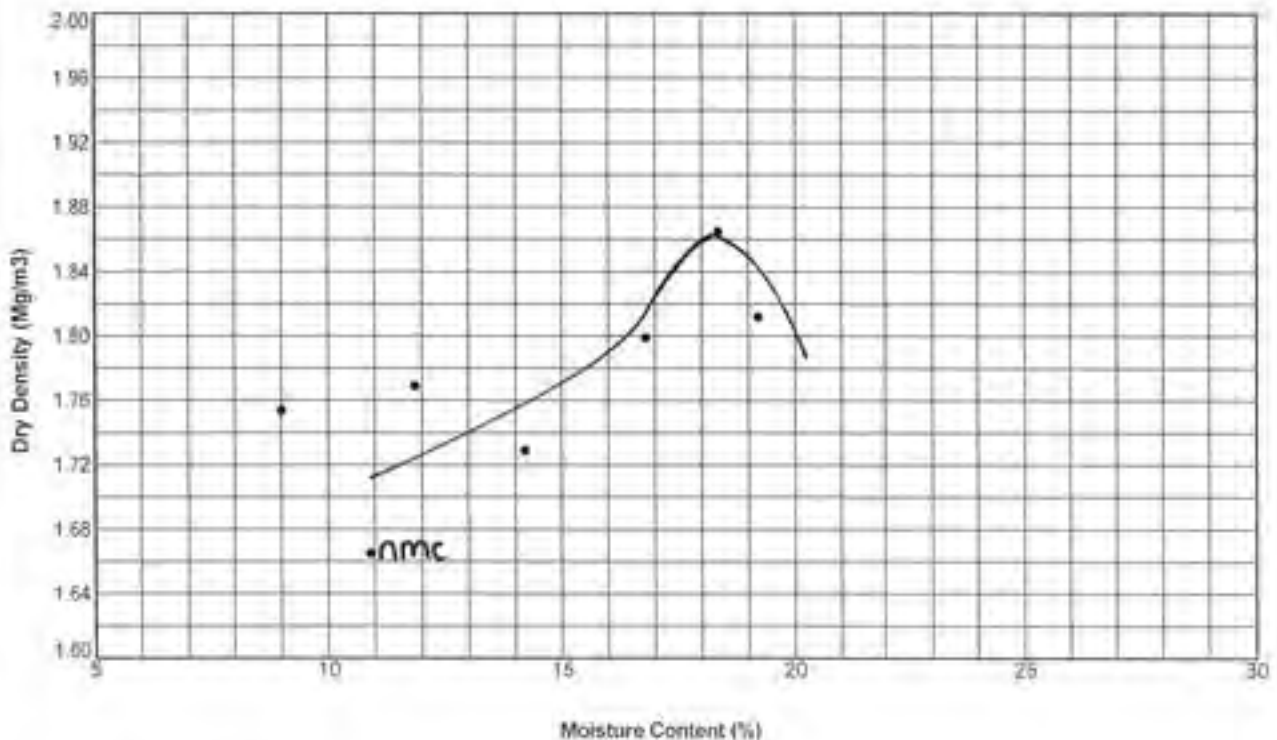

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works

Client :- South Tees Development Corporation



Signed :- *msene*

Name :- *[Signature]*

Page 1 of 1

Date of issue :- 02/11/2020

Certificate No :- COMR/4251/1

AEG Contract No :- 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Via 25 Males Oil Industrial Estate, Perton Park, Dinnington, Co. Durham, DL2 2JG - Tel: 0191 387 4399 Fax: 0191 207 4751
Regional Office: Unit 20, Business Development Centre, Selsby, North Yorkshire, YO21 5BQ - Tel: 01723 225 282 Fax: 01723 225 289

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 - Part 4: 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP119 Depth (m) :- 3.00

Sample Type & No :- B8

Test Method 2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 23.5

Particle Density (Assumed) = 2.70


Maximum Dry Density (Mg/m³) = 1.60

Retained on 20mm Sieve (%) = 0.0

Date Tested = 16/10/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

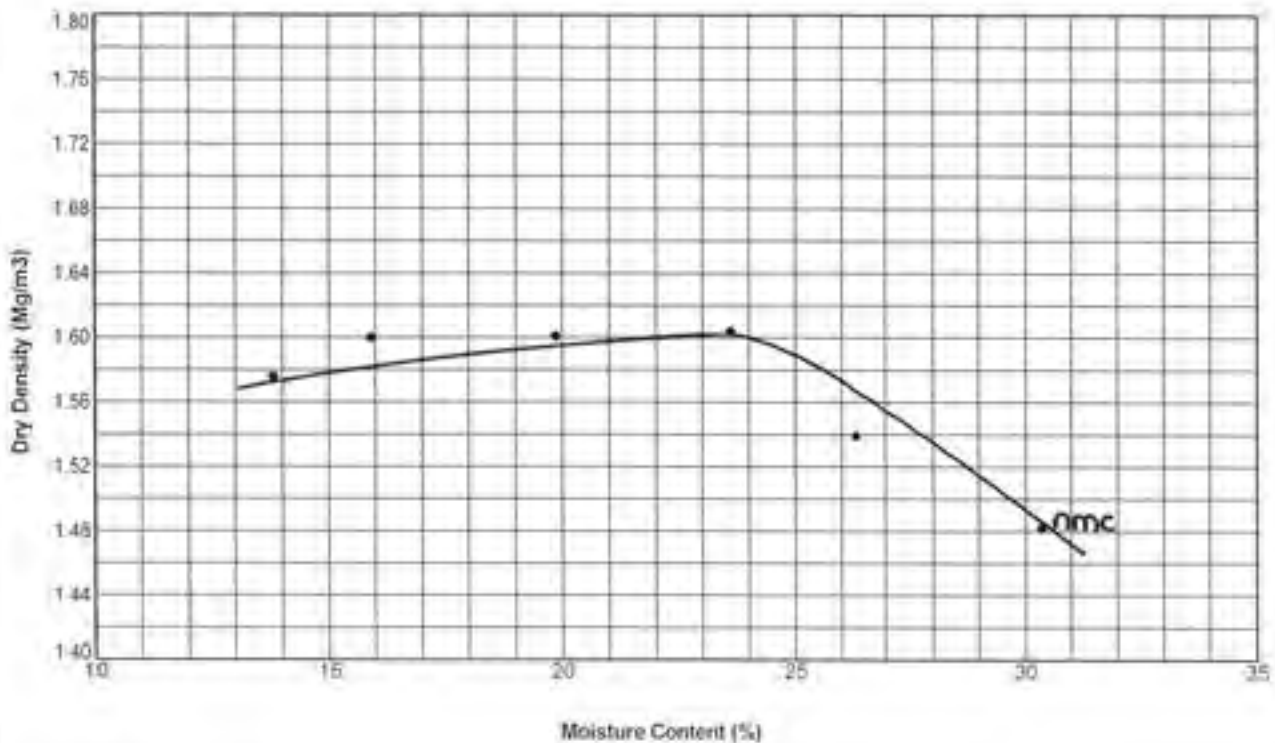

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works

Client :- South Tees Development Corporation



Signed - *mson*

Name -

Page 1 of 1

Date of issue - 02/11/2020

Certificate No - GDMR/4251/1

AEG Contract No - 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25 Area 58 Industrial Estate, Park Hill, Chester-le-Street, Co. Durham, DA2 2DZ. Tel: 0191 387 4700 Fax: 0191 387 4710
Regional Office: Unit 25, Southwood Development Centre, Easingham Road, Southwood, B81 5BL. Tel: 01753 705 000 Fax: 01753 705 001

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP BS 1377 - Part 4 : 1990

Specimen Identification

Exploratory Hole No :- **PRAIRIE_AUK_TP120** Depth (m) :- **1.80**

Sample Type & No :- **B5**

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = **20.0**

Particle Density (Assumed) = **2.65**


Maximum Dry Density (Mg/m³) = **1.67**

Retained on 20mm Sieve (%) = **0.0**

Date Tested = **15/10/2020**

Retained on 37.5mm Sieve (%) = **0.0**

Remarks :

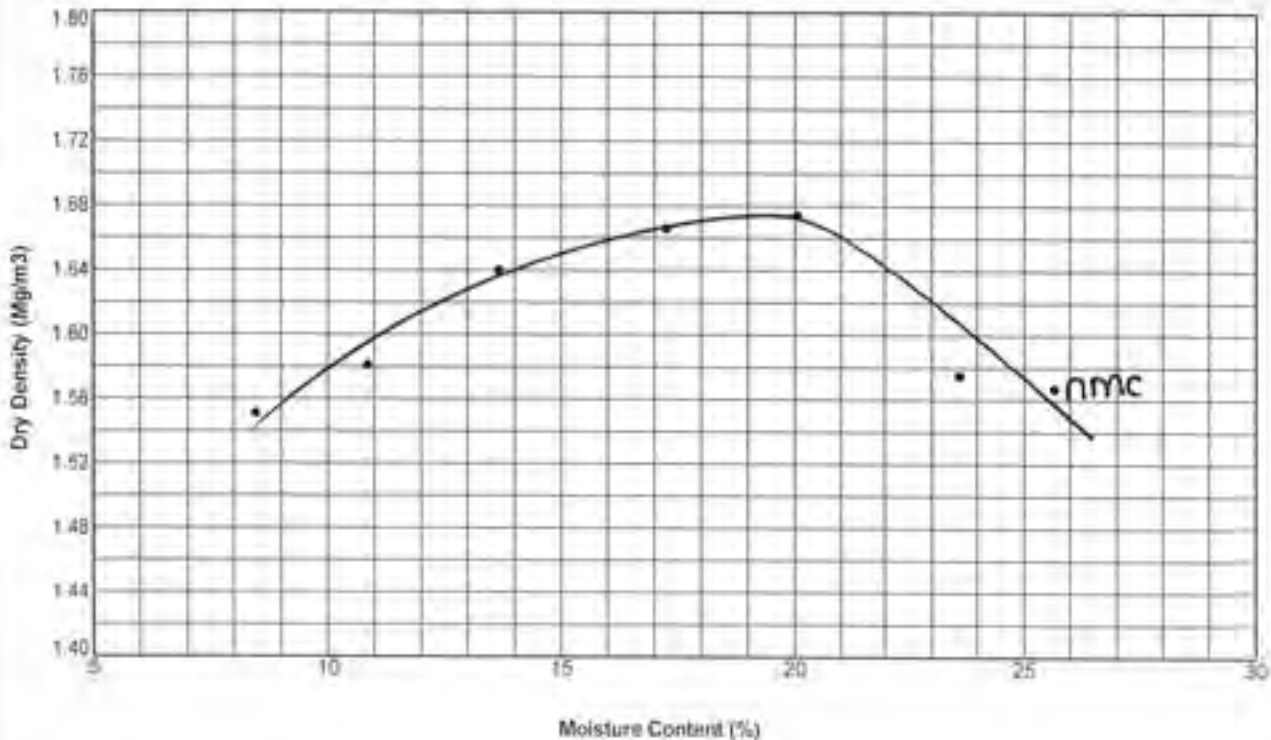

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed :-

msone

Name :-

MSONE

Page 1 of 1

Date of issue :-

02/11/2020

Certificate No :-

COM/4251/1

AEG Contract No :-

4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 1st Flr 27, Wileys Rd, Industrial Estate, Thessalon, Cheshire, Cheshire, UK. (Lancaster LA2 2PQ) Tel: 01752 387472 Fax: 01752 387473
Regional Office: 1st Flr 27, Wileys Rd, Industrial Estate, Thessalon, Cheshire, Cheshire, UK. (Lancaster LA2 2PQ) Tel: 01752 387472 Fax: 01752 387473

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 - Part 4: 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP121 Depth (m) :- 0.80

Sample Type & No :- B2

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 14.0

Particle Density (Assumed) = 2.75


Maximum Dry Density (Mg/m³) = 1.93

Retained on 20mm Sieve (%) = 1.0

Date Tested = 01/10/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

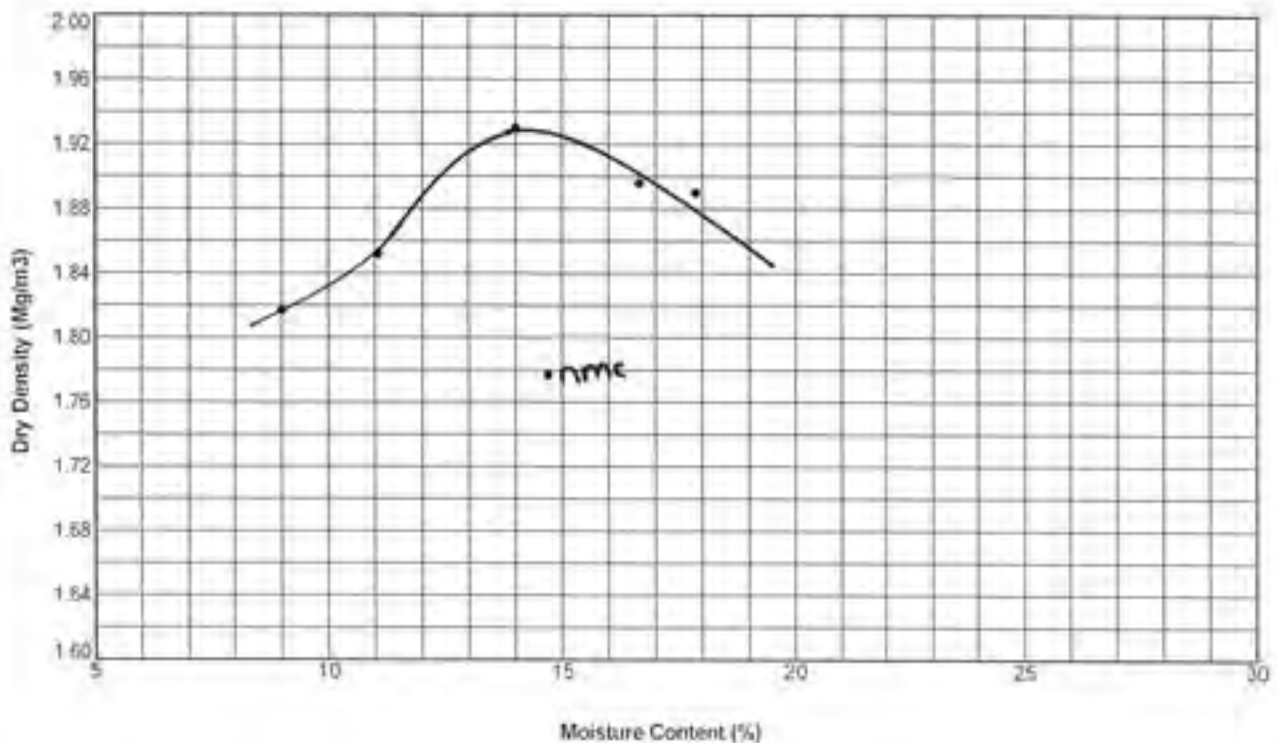

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed :-

msone

Name :-

MSONE

Page 1 of 1

Date of issue :-

02/11/2020

Certificate No :-

COMP4251/1

AEG Contract No :-

4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Allied Exploration & Geotechnics Limited, 200 Industrial Estate, North Hill, Chatteris, Cambs, Cambridgeshire, UK. Cambs, CB4 2PG. Tel: 01353 762410 Fax: 01353 681471
 Registered Office: 1, 2 & 3, Goswell Road, Goswell Road, Ipswich, Suffolk, UK. Suffolk, IP1 3DU. Tel: 01473 725125 Fax: 01473 725126

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 Part 4: 1990

Specimen Identification

Exploratory Hole No :- **PRAIRIE_AUK_TP124** Depth (m) :- **1.50**

Sample Type & No :- **B4**

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = **16.0**

Particle Density (Assumed) = **2.55**


Maximum Dry Density (Mg/m³) = **1.62**

Retained on 20mm Sieve (%) = **9.0**

Date Tested = **29/09/2020**

Retained on 37.5mm Sieve (%) = **3.0**

Remarks :

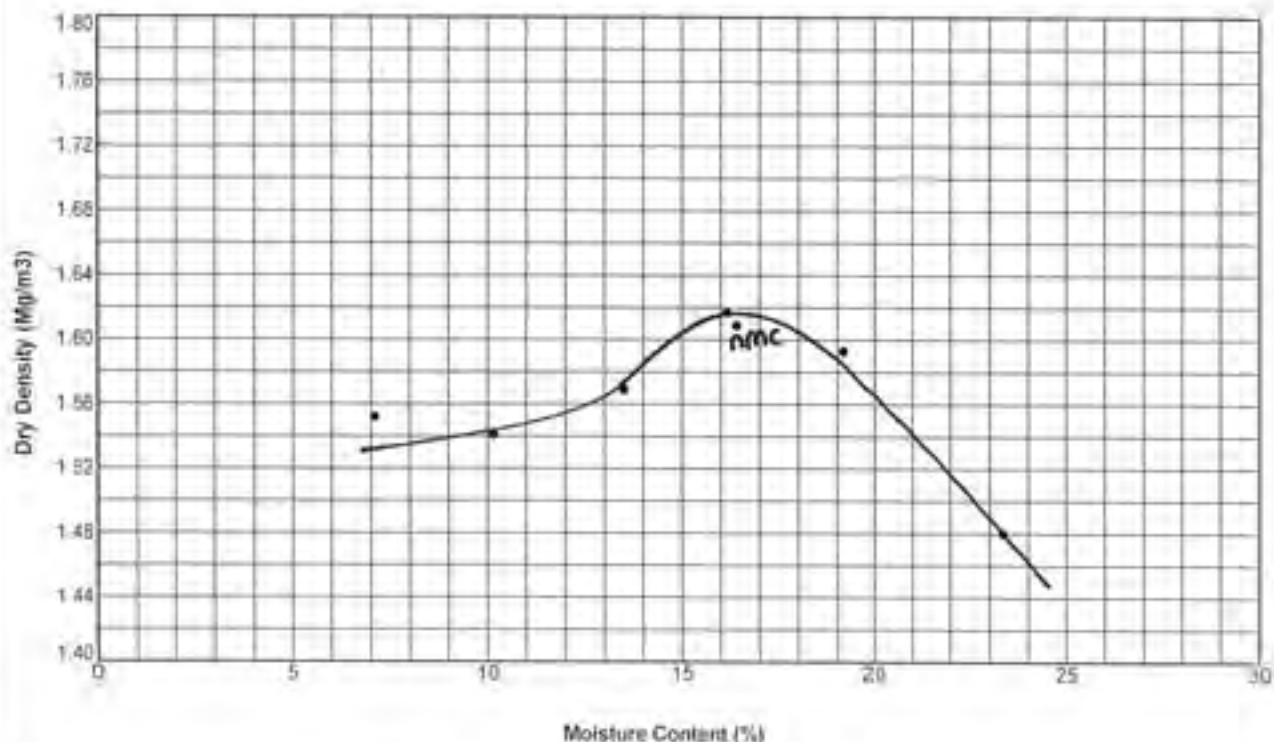

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed :- *m.sone*

Name :-

M. Sone

Page 1 of 1

Date of issue :-
02/11/2020

Certificate No :-
GDMR/4251/1

AEG Contract No :-
4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 20, Bala Gas Industrial Estate, Bala Park, Cwmrhyll, Ceredigion, SA31 3LQ, UK. Tel: 01274 561400 Fax: 01274 561401
Regional Office: Unit 10, Bannock Investment Centre, Bannockburn, Shropshire, SY1 5LJ, UK. Tel: 01752 755337 Fax: 01752 755367

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 / Part 4 : 1990

Specimen Identification

Exploratory Hole No - PRAIRIE_AUK_TP131 Depth (m) :- 3.80

Sample Type & No :- B10

Test Method

2.5kg Compaction

Separate Samples

Test Results

Optimum Moisture Content (%) = 21.0

Particle Density (Assumed) = 2.75


Maximum Dry Density (Mg/m³) = 1.60

Retained on 20mm Sieve (%) = 0.0

Date Tested = 01/10/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

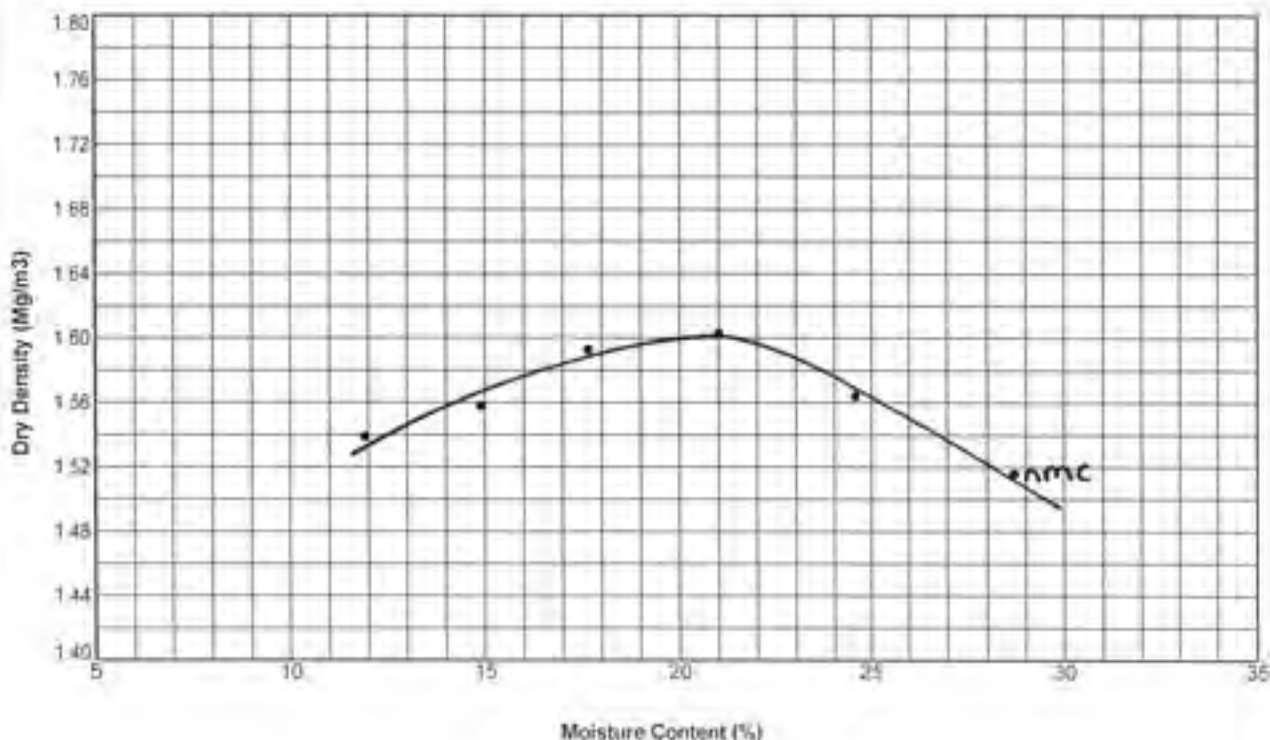

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed -

msene

Name :-

Page 1 of 1

Date of Issue

02/11/2020

Certificate No:-

COMPA4251/1

AEG Contract No. :-

4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 70, Brook Hill Industrial Estate, Patten Park, Croxall Drive, Leamington Spa, CV32 2PL. Tel: 01922 477474 Fax: 01922 471111
Regional Office: Unit 20, Business Development Centre, Gosport Wharf, Southampton, SO1 9SL. Tel: 02382 731 88 Fax: 02382 731 88

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 : Part 4 : 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP137 Depth (m) :- 2.00

Sample Type & No :- B7

Test Method

2.5kg Compaction

Separate Samples

Test Results

Optimum Moisture Content (%) = 17.0

Particle Density (Assumed) = 2.65


Maximum Dry Density (Mg/m³) = 1.70

Retained on 20mm Sieve (%) = 0.0

Date Tested = 15/10/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

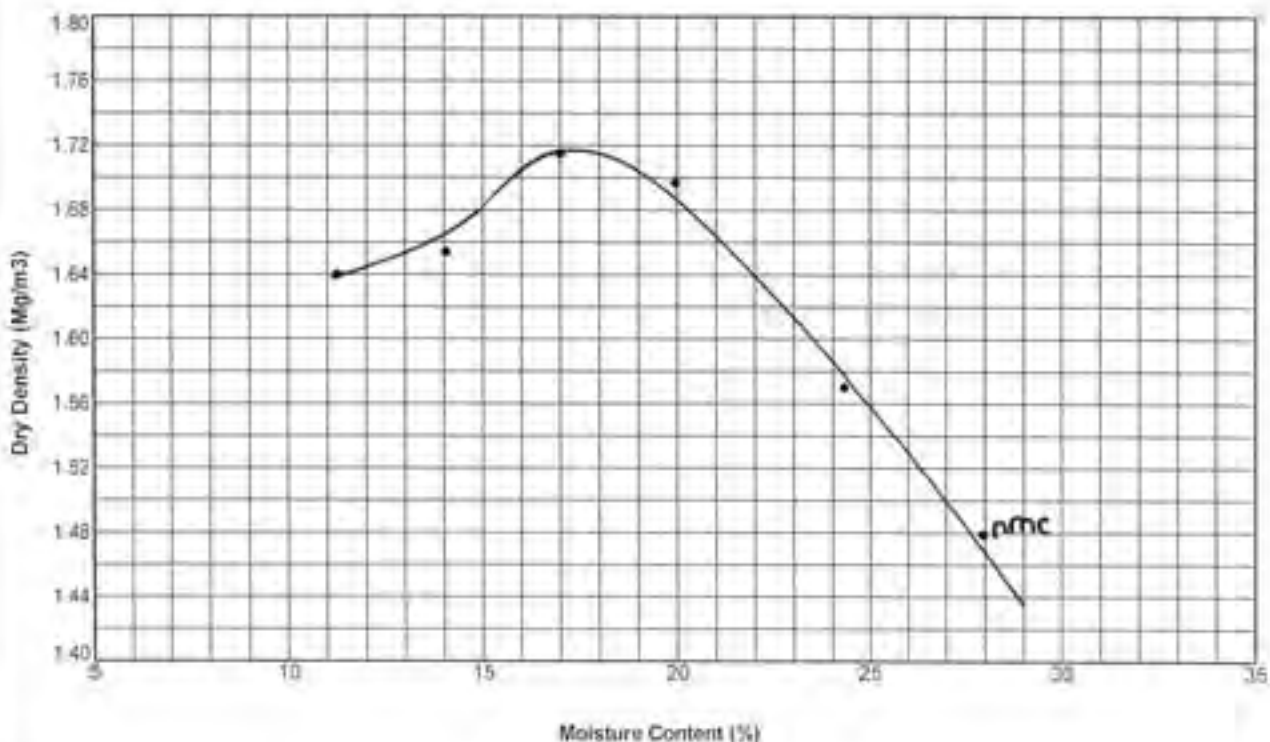

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed :-

m.sone

Name :-

Page 1 of 1

Date of issue :-

02/11/2020

Certificate No :-

COMP/4251/1

AEG Contract No :-

4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, 26/27, Old Industrial Estate, Green Park, Chesham-Bosham, Ch. District, GU20 2BQ - Tel: 01296 387470/8 Fax: 01296 387473
Regional Office: Unit 21, Salsford, Development Centre, Salsford Road, Boreham, Essex, SS11 5BA - Tel: 01773 435 388 Fax: 01773 515 061

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP BS 1377 : Part 4 : 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP145 Depth (m) :- 1.00

Sample Type & No :- B3

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 17.5

Particle Density (Assumed) = 2.55


Maximum Dry Density (Mg/m³) = 1.68

Retained on 20mm Sieve (%) = 19.0

Date Tested = 29/09/2020

Retained on 37.5mm Sieve (%) = 5.0

Remarks :

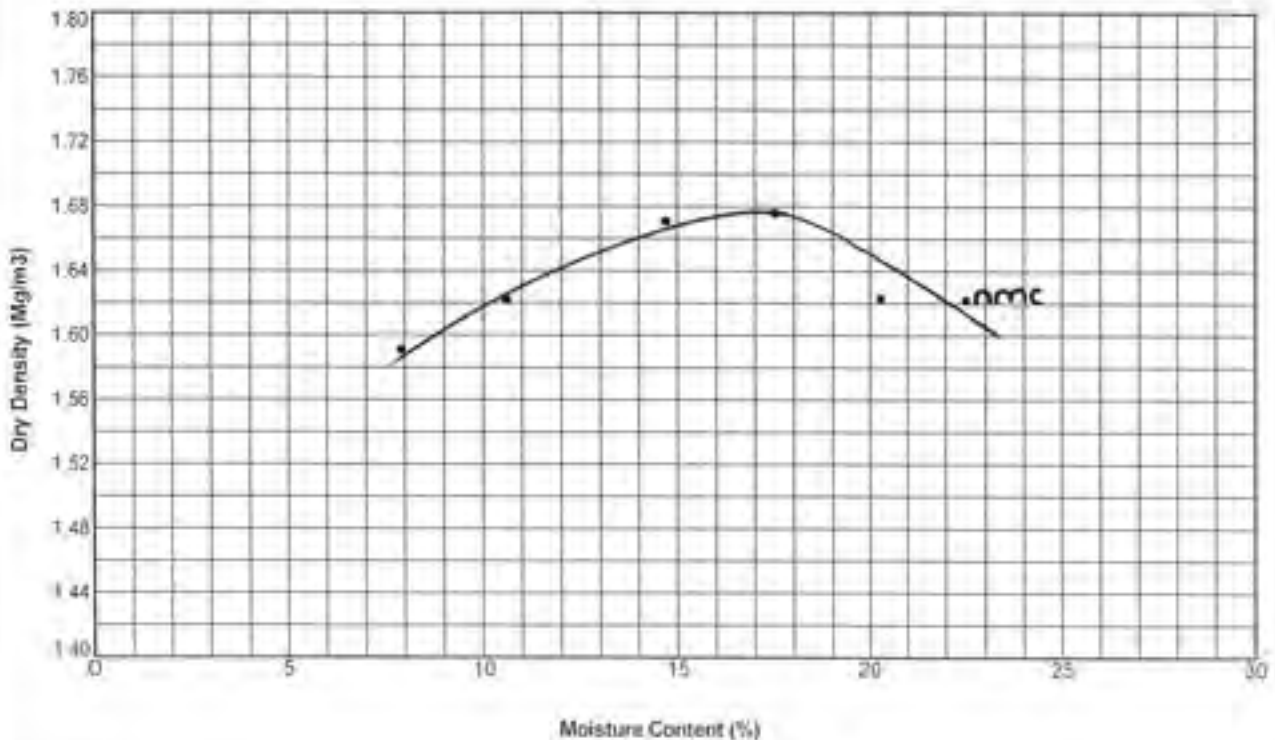

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed -

msone

Name :-

msone

Page 1 of 1

Date of issue :-

02/11/2020

Certificate No :-

COMB/425111

AEG Contract No :-

4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 1st & 2nd Floors, 146, Victoria Street, Ipswich, Suffolk, IP1 1JF, UK. Tel: 01473 285473 Fax: 01473 287478
Regional Office: 1st & 2nd Floors, 100, Commercial Centre, Cannon Wharf, Southampton, SO9 1BB, UK. Tel: 01703 031983 Fax: 01703 210988

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 - Part 4 - 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP145 Depth (m) :- 2.40

Sample Type & No :- B6

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 21.0

Particle Density (Assumed) = 2.70


Maximum Dry Density (Mg/m³) = 1.63

Retained on 20mm Sieve (%) = 0.0

Date Tested = 30/09/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

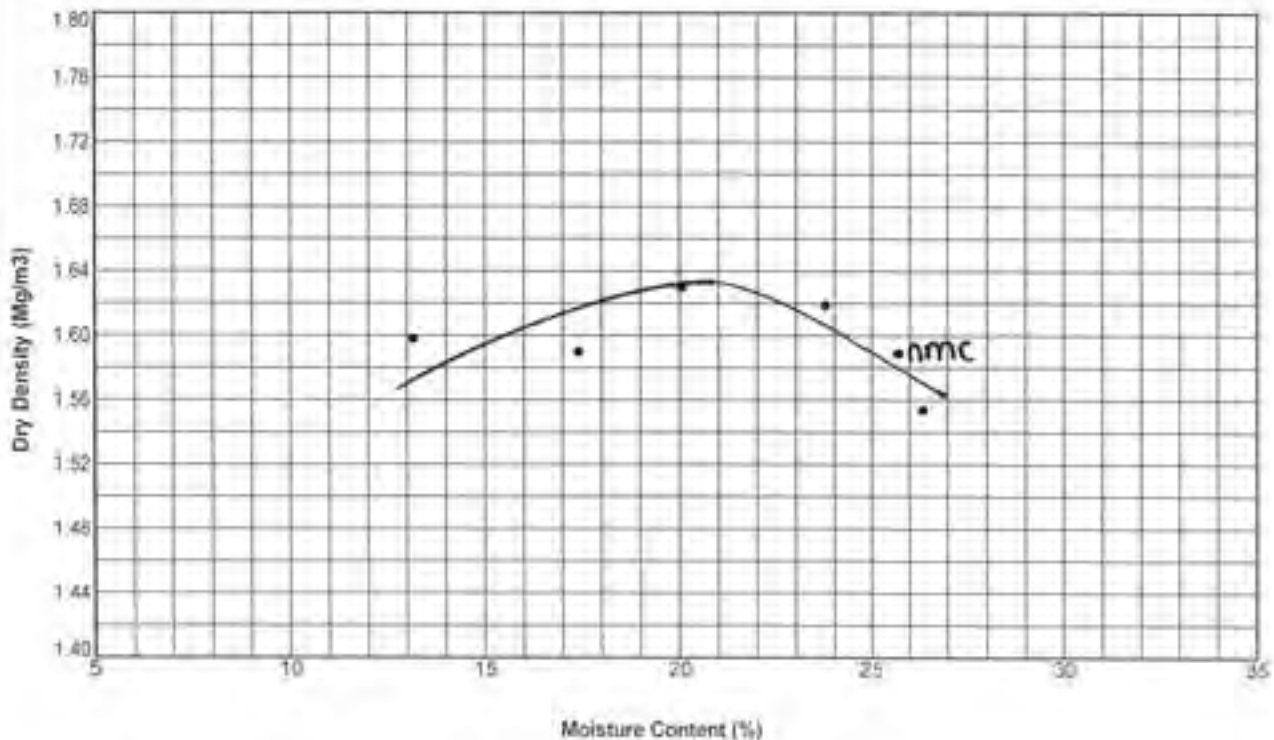

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed :-

msene

Name :-

Page 1 of 1

Date of issue :-

02/11/2020

Certificate No :-

COMP4251/T

AEG Contract No :-

4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21, Broomfield Industrial Estate, Poles Road, Chatteris, Cambs, Cambridgeshire, UK. Tel: 01455 507414 Fax: 01455 511474
Regional Office: Unit 21, Broomfield Industrial Estate, Poles Road, Chatteris, Cambridgeshire, UK. Tel: 01455 507414 Fax: 01455 511474

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 : Part 4 : 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP146 Depth (m) :- 1.30

Sample Type & No :- B6

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 17.5

Particle Density (Assumed) = 2.65


Maximum Dry Density (Mg/m³) = 1.69

Retained on 20mm Sieve (%) = 14.0

Date Tested = 02/10/2020

Retained on 37.5mm Sieve (%) = 6.0

Remarks :

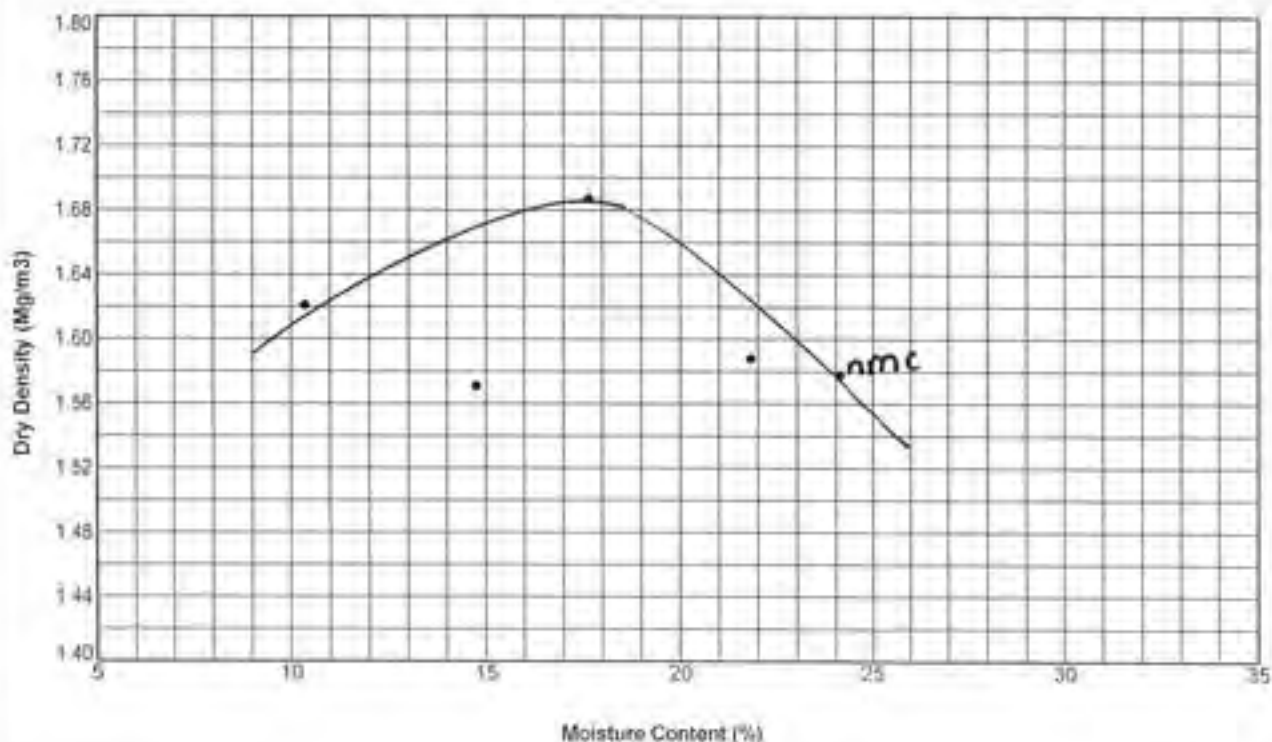

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed :- *msone*

Name :-

[Signature]

Page 1 of 1

Date of issue :-

02/11/2020

Certificate No :-

COMP/4251/1

AEG Contract No :-

4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Kings Gate Industrial Estate, Forest Park, Chesham Street, Col. Dunton, DA0 2WZ. Tel: 01773 284219 Fax: 01773 284218
Regional Office: Unit 26, Seaboard Development Centre, Capenhurst, Sandhurst, RG40 1BB. Tel: 01753 755285 Fax: 01753 755286

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 - Part 4 : 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP146 Depth (m) :- 2.30

Sample Type & No :- B8

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 18.5

Particle Density (Assumed) = 2.70


Maximum Dry Density (Mg/m³) = 1.67

Retained on 20mm Sieve (%) = 0.0

Date Tested = 01/10/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

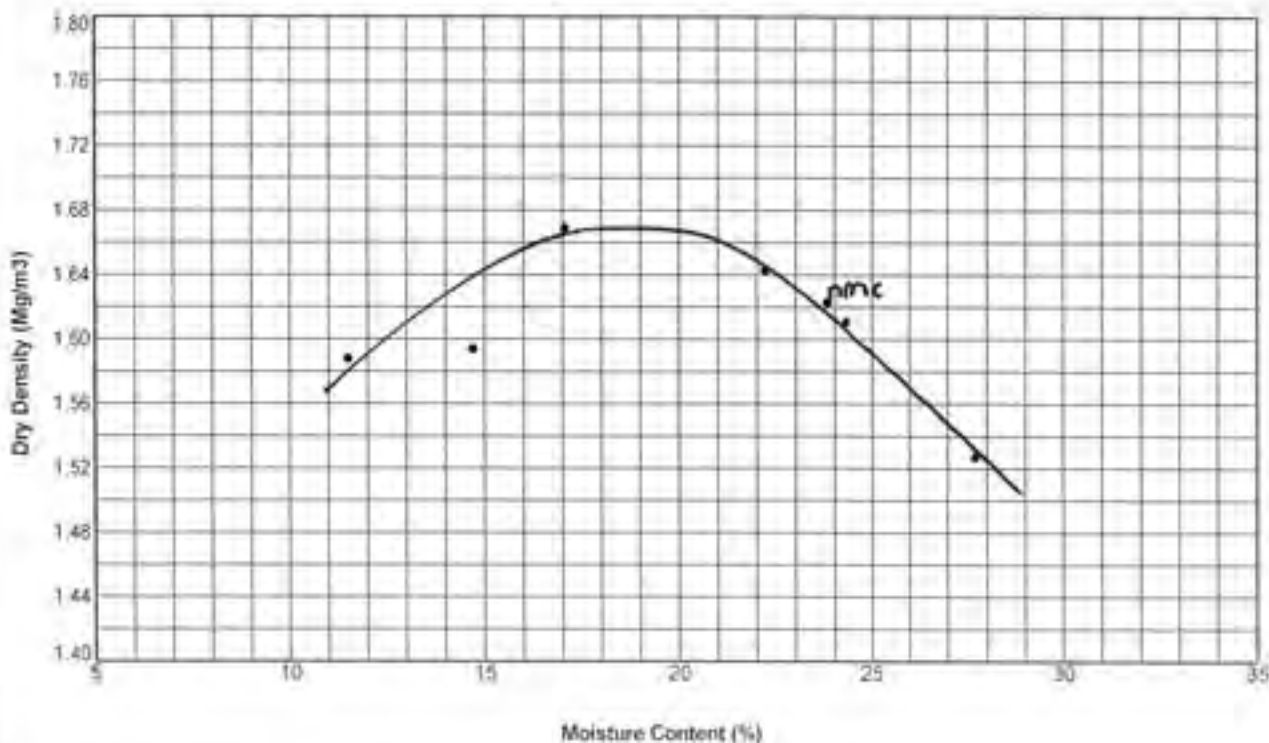

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed: *msone*

Name :-

[Handwritten signature]

Page 1 of 1

Date of issue :-
02/11/2020

Certificate No :-
COMPI425111

REG Contract No :-
4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Rye, 25 Industrial Estate, Rye, East Sussex, TN37 6YU. Tel: 01323 470444 Fax: 01323 471479
Regional Office: Unit 20, Business Development Centre, London-Village, Barnham, B24 3SL. Tel: 01753 725746 Fax: 01753 725 959

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP BS 1377 : Part 4 : 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP149 Depth (m) :- 2.20

Sample Type & No :- B5

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 22.5

Particle Density (Assumed) = 2.70


Maximum Dry Density (Mg/m³) = 1.57

Retained on 20mm Sieve (%) = 0.0

Date Tested = 16/10/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

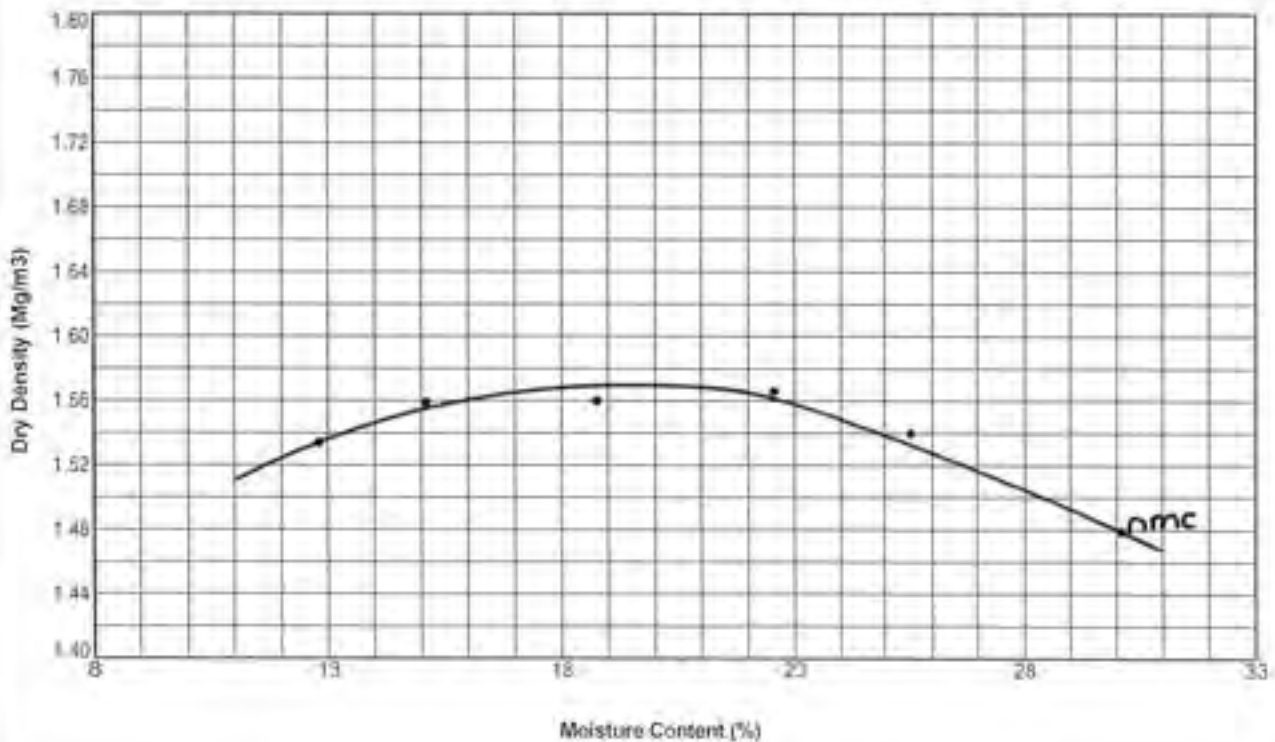

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed :- *msene*

Name :-

Page 1 of 1

Date of Issue :-
02/11/2020

Certificate No :-
COMP/4251/1

AEG Contract No. :-
4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25 MIRA, 100 Parkway Road, Milton Park, Bedfordshire, UK, Dunstable, MK12 0BN - Tel: 0111 361 476 Fax: 0111 361 471
Regional Office Unit 25 Business Centre, 100 Parkway Road, Milton Park, Bedfordshire, MK12 0BN - Tel: 01773 231 300 Fax: 01773 231 301

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377, Part 4 : 1990

Specimen Identification

Exploratory Hole No - PRAIRIE_AUK_TP154 Depth (m) - 1.60

Sample Type & No - B5

Test Method 2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 24.0

Particle Density (Assumed) = 2.70


Maximum Dry Density (Mg/m³) = 1.57

Retained on 20mm Sieve (%) = 0.0

Date Tested = 20/10/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

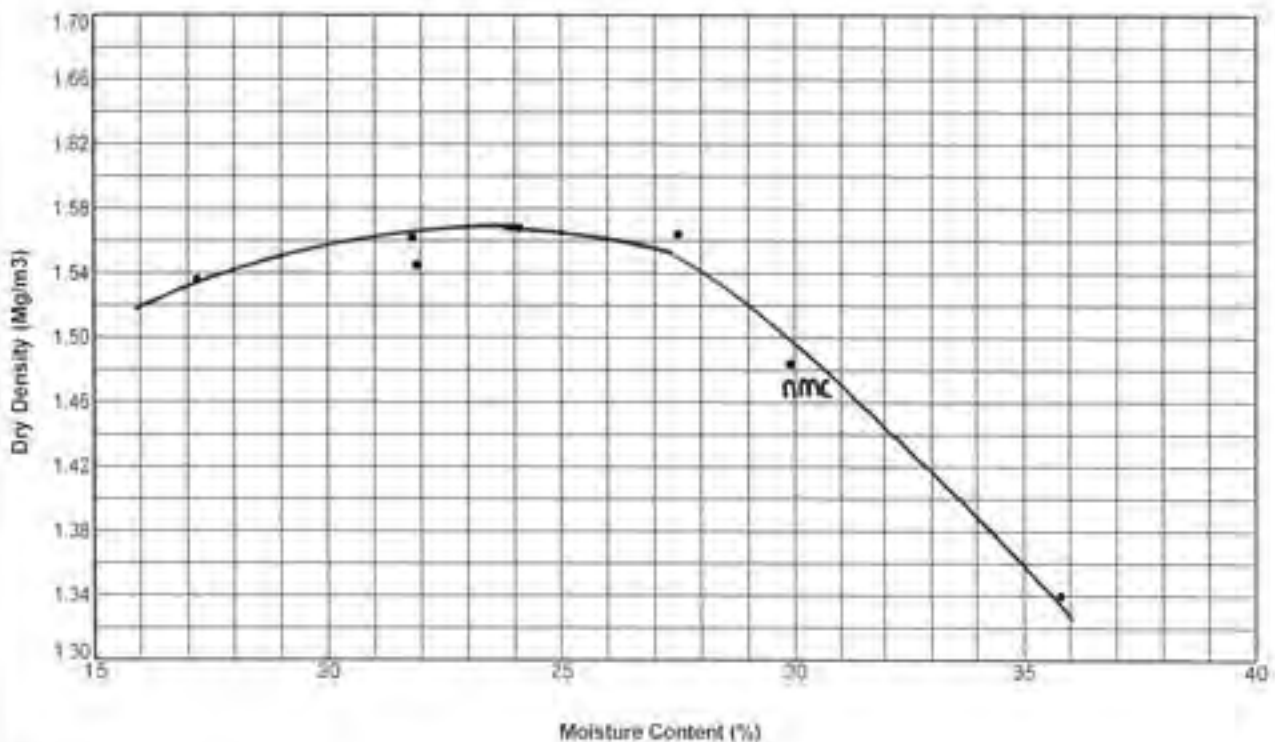

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- **Prairie Site Ground Investigation Works**

Client :- **South Tees Development Corporation**



Signed: - *msone*

Name: - *[Signature]*

Page 1 of 1

Date of issue - 02/11/2020

Certificate No - COMR/4251/T

AEG Contract No - 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 27, 50044 (ex 50044) Estate, Hylton Park, Cheshire Street, L1, Doncaster, DN1 2BG - Tel: 0115 951 4100 Fax: 0115 951 4111
Regional Office: Unit 25, Business Development Centre, Kippenhanger, Barnsley, S11 1BB - Tel: 0122 255 7000 Web: 0115 951 4100

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 : Part 4 : 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP162 Depth (m) :- 2.50

Sample Type & No :- B6

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 21.0

Particle Density (Assumed) = 2.75


Maximum Dry Density (Mg/m³) = 1.64

Retained on 20mm Sieve (%) = 0.0

Date Tested = 29/09/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

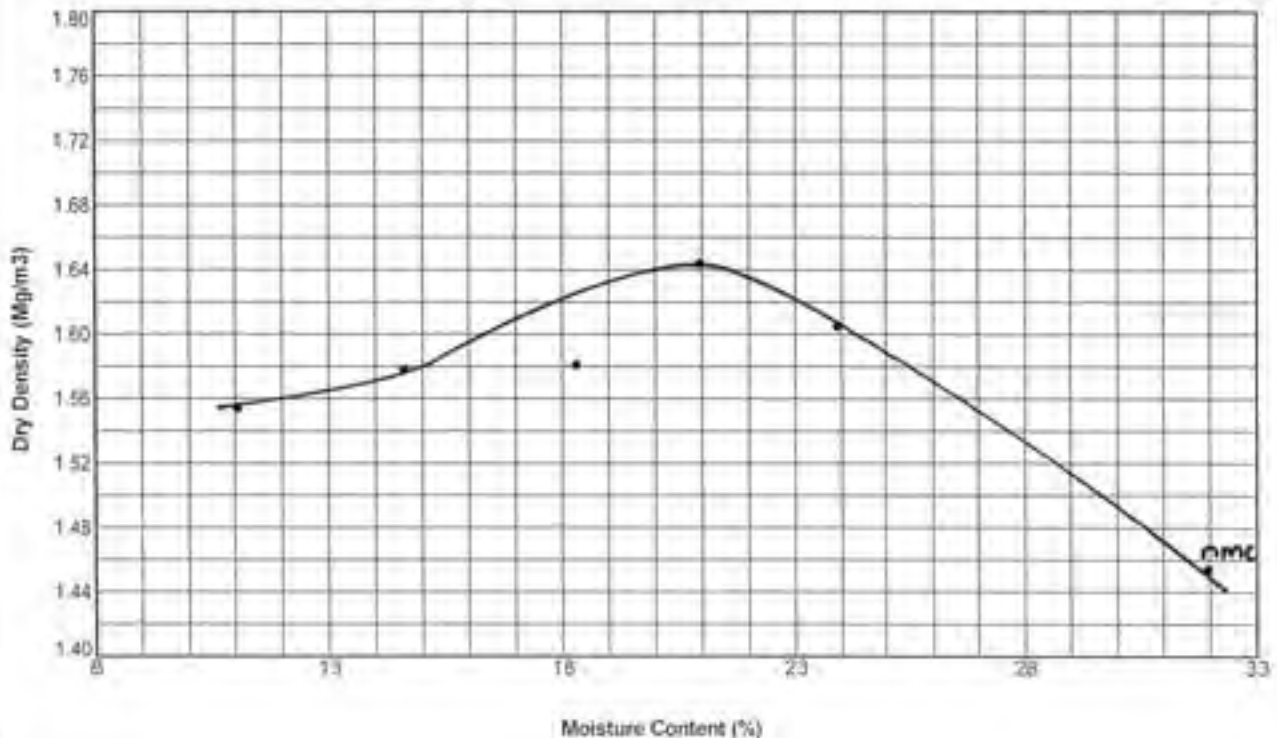

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed - *mshoe*

Name -

Page 1 of 1

Date of issue
02/11/2020

Certificate No :-
COMPR4251/1

AEG Contract No :-
4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Brierley Industrial Estate, Fyfe Road, Consett, Co. Durham, DL23 1ND. Tel: 0191 387 4279 Fax: 0191 387 4713
Regional Office: LINCOS Business Development Centre, Exploration, Broomby, B'n'G, Tel: 01752 751465 Fax: 01752 751368

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377: Part 4: 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP163 Depth (m) :- 0.80

Sample Type & No :- B2

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 18.0

Particle Density (Assumed) = 1.70


Maximum Dry Density (Mg/m³) = 1.23

Retained on 20mm Sieve (%) = 14.0

Date Tested = 05/10/2020

Retained on 37.5mm Sieve (%) = 1.0

Remarks :

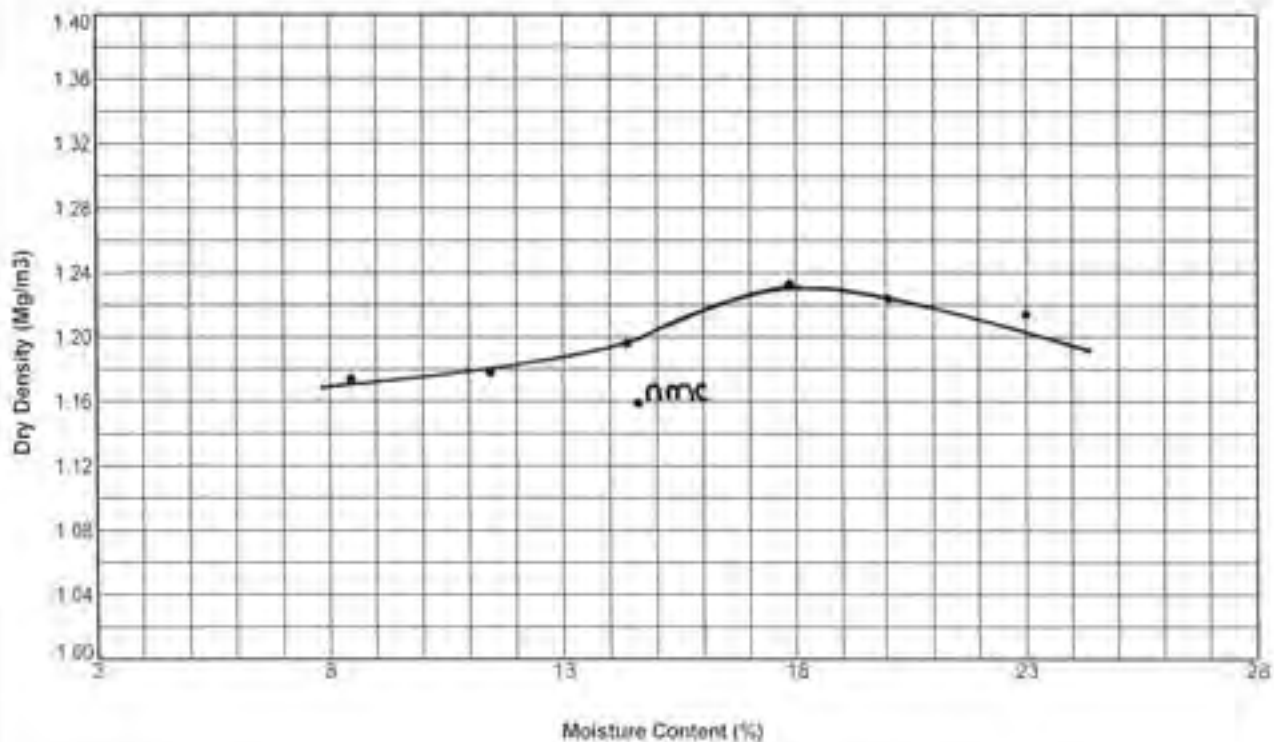

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed - *msene*

Name :-

Page 1 of 1

Date of issue :-
02/11/2020

Certificate No :-
COMR/4251/1

AEG Contract No :-
4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office Unit 25 Greys (24 Industrial Estate), Palace Road, Farnborough, Hampshire, GU14 7JG, UK. Tel: 01256 307410 Fax: 01256 307411
Regional Office Unit 25, Business Development Centre, Church Wharf, Southampton, SO1 7JG, UK. Tel: 01703 751100 Fax: 01703 751101

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP BS 1377 : Part 4 : 1990

Specimen Identification

Exploratory Hole No - PRAIRIE_AUK_TP163 Depth (m) - 1.70

Sample Type & No - B5

Test Method

2.5kg Compaction

Separate Samples

Test Results

Optimum Moisture Content (%) = 18.3

Particle Density (Assumed) = 2.75


Maximum Dry Density (Mg/m³) = 1.70

Retained on 20mm Sieve (%) = 0.0

Date Tested = 01/10/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

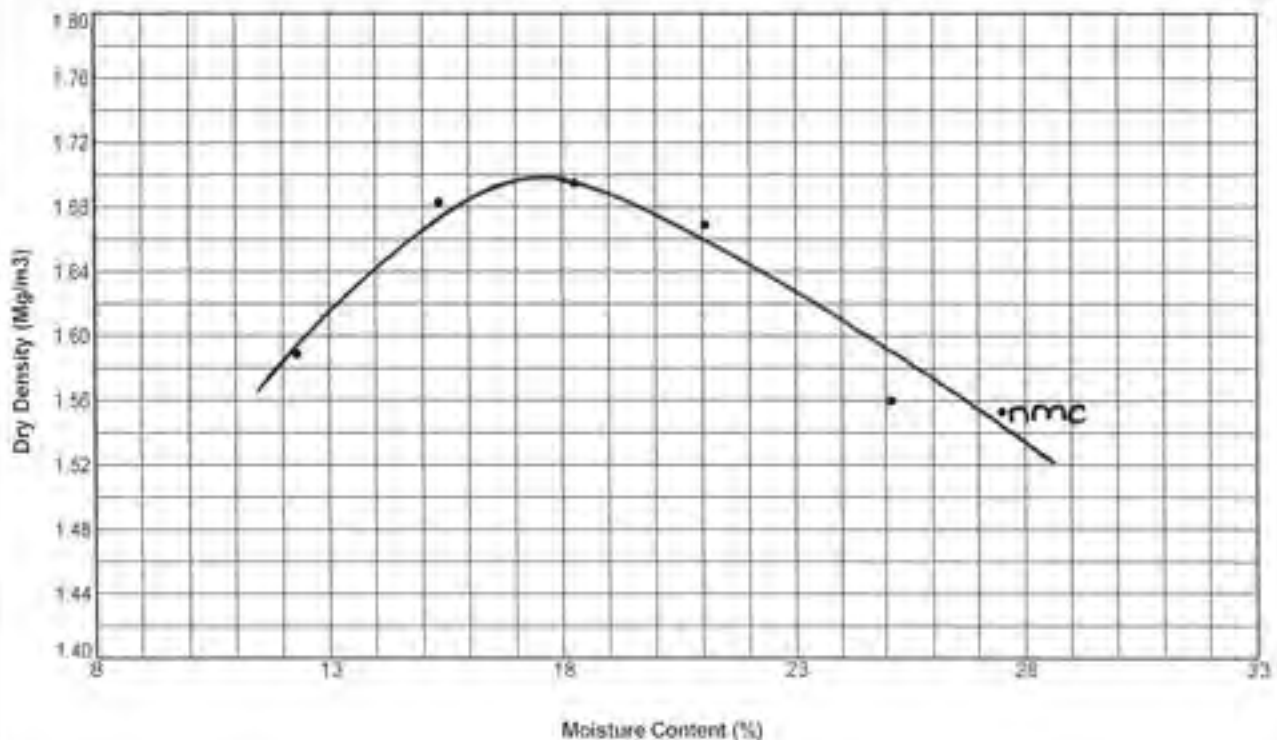

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed - *msene*

Name -

Page 1 of 1

Date of issue -
02/11/2020

Certificate No -
COMR(2511)

AEG Contract No -
4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 22, South 2nd Industrial Estate, Millers Hill, Cheshire, M20 9JL, UK. Tel: 01256 351470 Fax: 01256 351471
 Regional Office: Unit 15, Science Development Centre, Kingsford Road, Manchester, M20 9BA, UK. Tel: 01256 351472 Fax: 01256 351473

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 - Part 4 : 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP168 Depth (m) :- 1.60

Sample Type & No :- B7

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 24.0

Particle Density (Assumed) = 2.70


Maximum Dry Density (Mg/m³) = 1.60

Retained on 20mm Sieve (%) = 0.0

Date Tested = 01/10/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

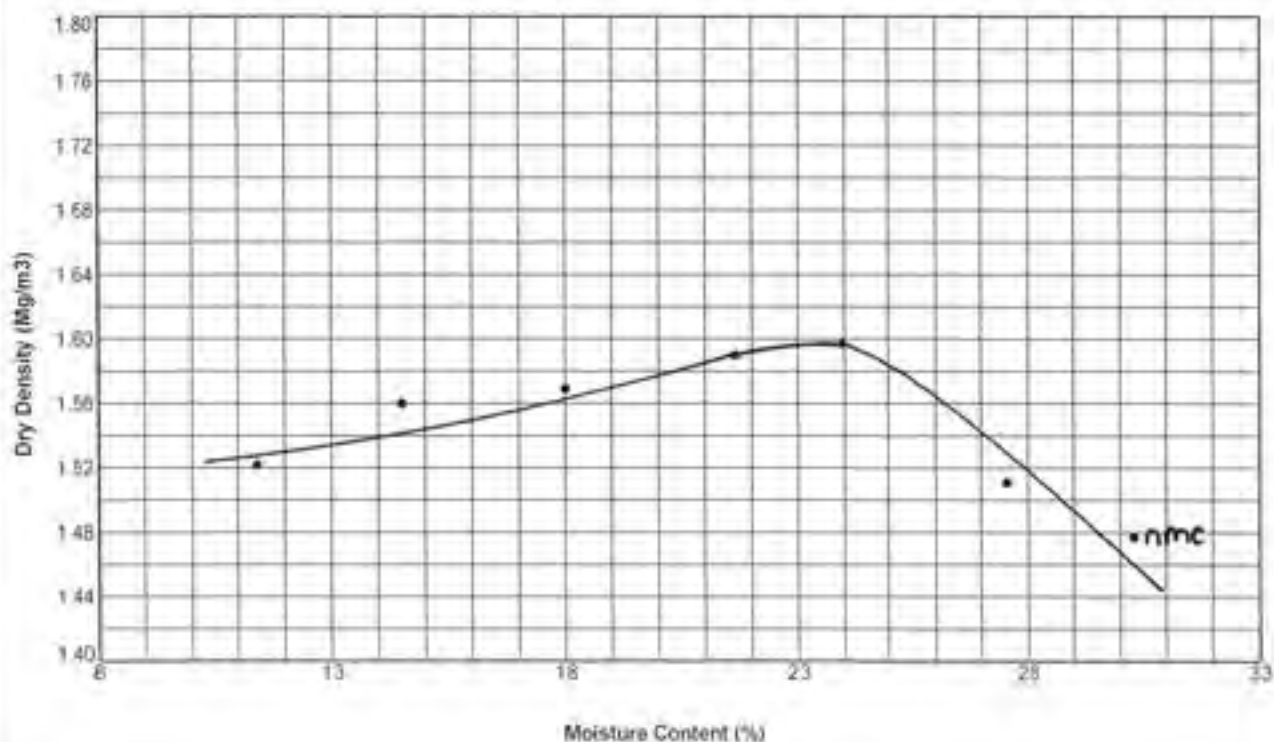

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed - *msone*

Name :-

Page 1 of 1

Date of issue - 02/11/2020

Certificate No:- COMPI4251/1

AEG Contract No :- 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Belfry, Old Victoria Works, Wetherby Park, Cheshire Road, Co. Down, BT62 2DQ, Northern Ireland. Tel: 01763 801470 Fax: 01763 801471
 Regional Office: Unit 21, Riverside Development Centre, Eastern Wood, Blackburn, BB1 9BL, Lancashire. Tel: 01524 775 200 Fax: 01524 775 201

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 : Part 4 : 1990

Specimen Identification

Exploratory Hole No - PRAIRIE_AUK_TP173 Depth (m) - 0.80

Sample Type & No - B2

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 18.0

Particle Density (Assumed) = 2.55


Maximum Dry Density (Mg/m³) = 1.53

Retained on 20mm Sieve (%) = 22.0

Date Tested = 30/09/2020

Retained on 37.5mm Sieve (%) = 8.0

Remarks :

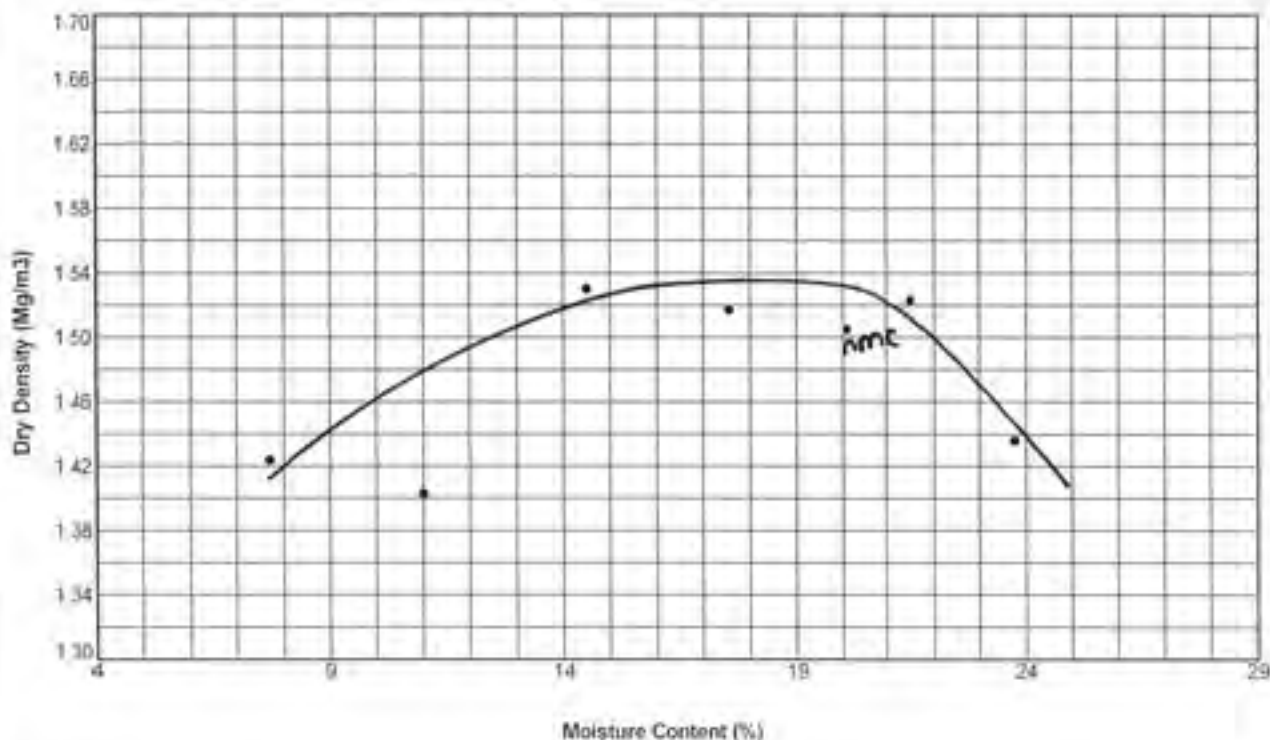

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title -

Prairie Site Ground Investigation Works

Client -

South Tees Development Corporation



Signed - *msene*

Name -

Page 1 of 1

Date of issue -
02/11/2020

Certificate No -
COMP4251/1

AEG Contract No -
4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21 Waterhill Industrial Estate, Park Road, Chesterfield, Derbyshire, S40 2NS. Tel: 01276 346111 Fax: 01276 346112
Regional Office: Unit 25, Business Development Centre, "Kingsmead" Southway, Barnsley, S70 2BQ. Tel: 01227 725336 Fax: 01227 725337

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 : Part 4 : 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP176 Depth (m) :- 2.00

Sample Type & No :- B5

Test Method 2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 18.0

Particle Density (Assumed) = 2.70


Maximum Dry Density (Mg/m³) = 1.74

Retained on 20mm Sieve (%) = 0.0

Date Tested = 29/09/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

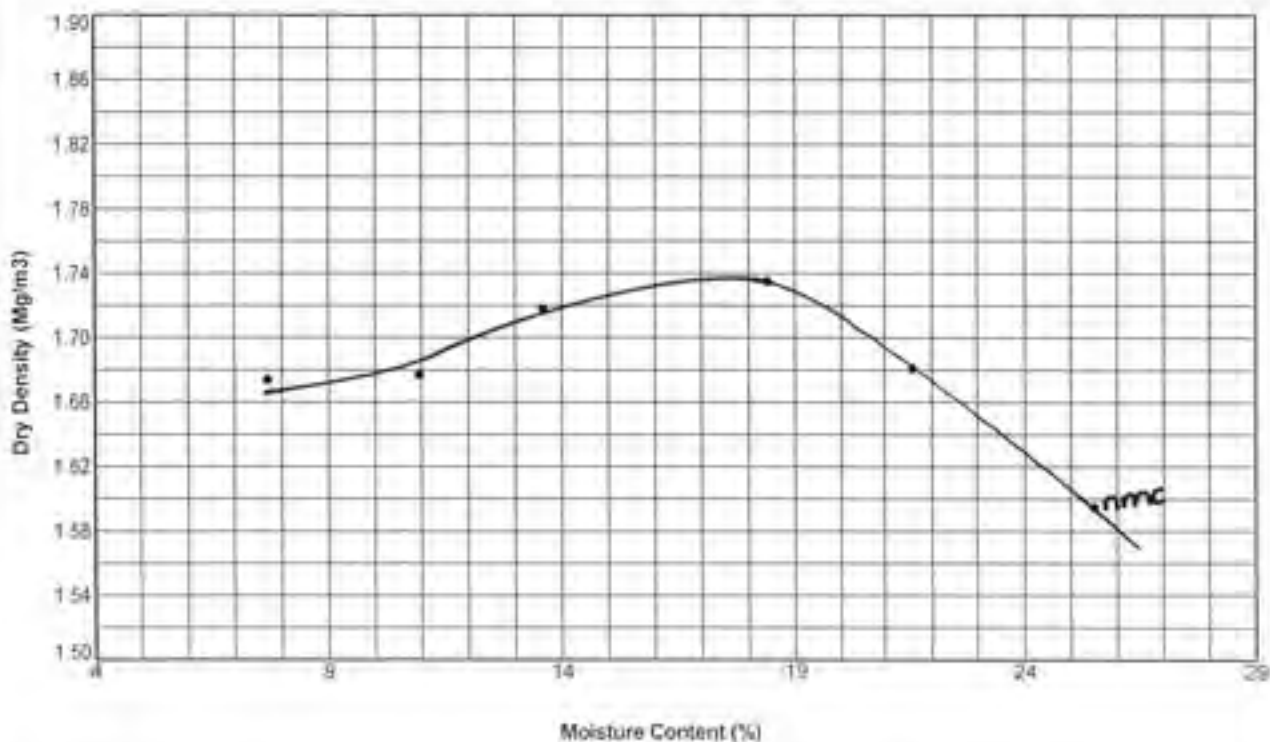

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works

Client :- South Tees Development Corporation



Signed :- *msene*

Name :-

Page 1 of 1

Date of Issue :- 02/11/2020

Certificate No :- COMP4251/1

AEG Contract No :- 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office Unit 25, Brook Industrial Estate, Park Road, Chester-le-Street, Co. Durham, DL3 5JF, UK. Tel: 0191 457 4768 Fax: 0191 457 4115
Regional Office Unit 25, Business Centre, Cumbrian Way, Macclesfield, Cheshire, SK11 7JL, UK. Tel: 01625 765 900 Fax: 01625 751 086

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 : Part 4 : 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP178 Depth (m) :- 0.60

Sample Type & No :- B2

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 21.7

Particle Density (Assumed) = 2.00


Maximum Dry Density (Mg/m³) = 1.22

Retained on 20mm Sieve (%) = 11.0

Date Tested = 05/10/2020

Retained on 37.5mm Sieve (%) = 5.0

Remarks :

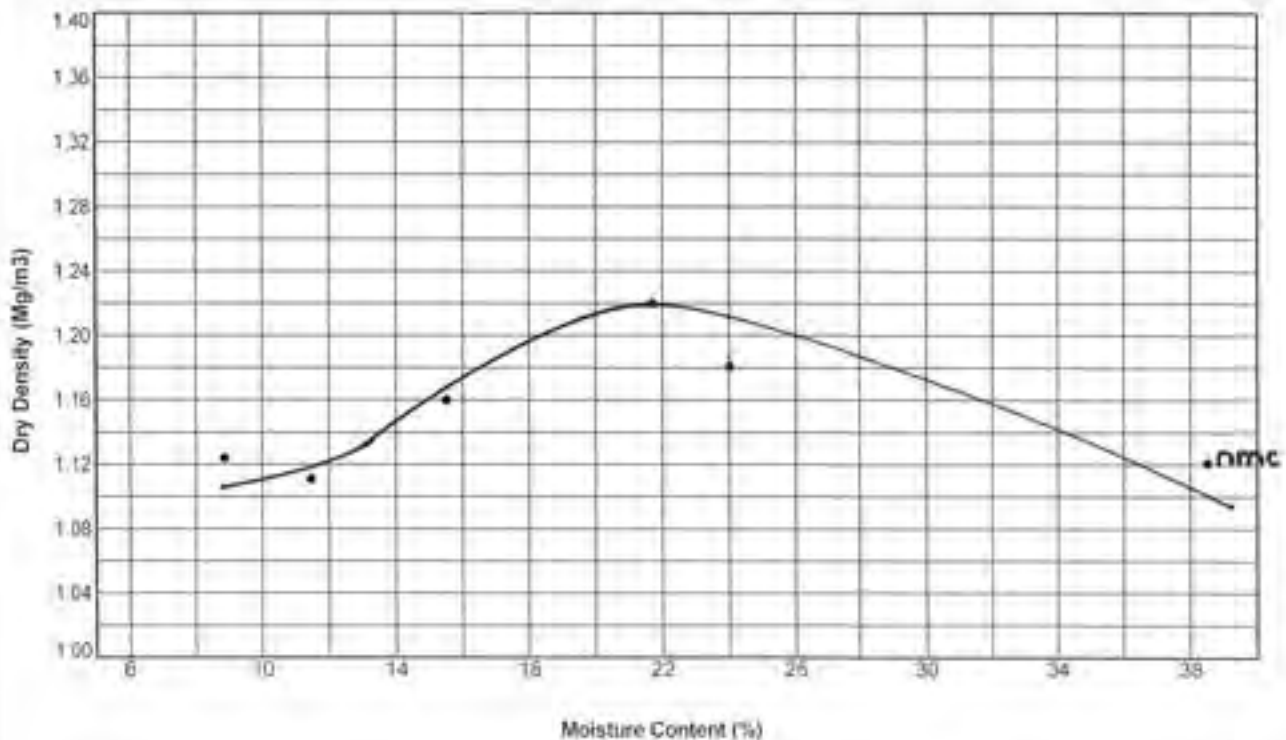

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- **Prairie Site Ground Investigation Works**

Client :- **South Tees Development Corporation**



Signed :- *msene*
Date of issue :- 02/11/2020

Name :- *[Signature]*
Certificate No :- COMB4251/1

Page 1 of 1
AEG Contract No :- 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21, West of Industrial Estate, Furness Road, Cockerham, Preston, Lancashire, PR1 0SD. Tel: 01773 600 610 Fax: 01773 600 611
Regional Office: 1, Moorfields Business Development Centre, "Kilnsey Wharf", Southtown, Barnsley, S70 2RT. Tel: 01759 241300 Fax: 01759 241301

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 : Part 4 : 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP178 Depth (m) :- 1.60

Sample Type & No :- B5

Test Method 2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 24.0

Particle Density (Assumed) = 2.40


Maximum Dry Density (Mg/m³) = 1.42

Retained on 20mm Sieve (%) = 0.0

Date Tested = 30/09/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

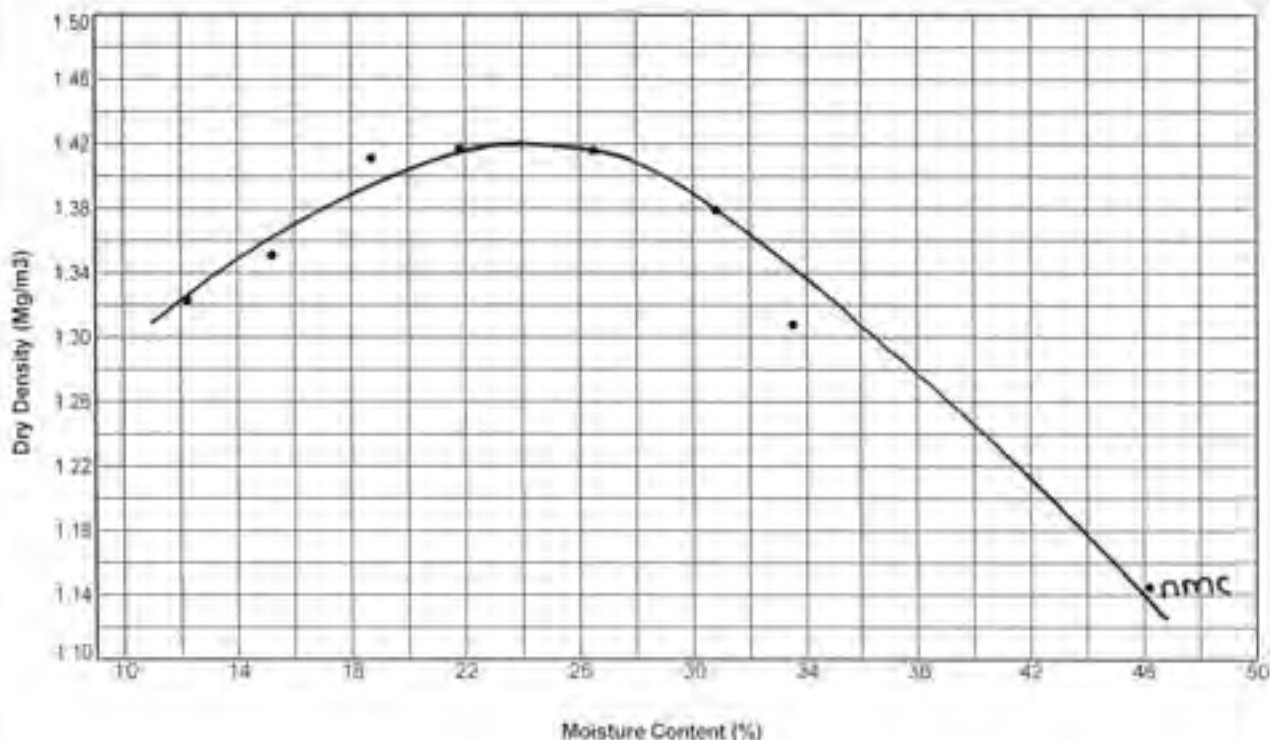

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works

Client :- South Tees Development Corporation



Signed :- *msene*

Name :-

Page 1 of 1

Date of issue :- 02/11/2020

Certificate No :- COMP4251/1

AEG Contract No :- 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 23 (over) Commercial Centre, West Park, Stretton-le-Stroud, Co. Dornich, GLOUCESTERSHIRE, GL9 5YU, UK. Tel: 01292 527 470 Fax: 01292 527 471
Regional Office: Unit 23, (over) Commercial Centre, West Park, Stretton-le-Stroud, Dornich, GLOUCESTERSHIRE, GL9 5YU, UK. Tel: 01292 751 350 Fax: 01292 751 351

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 Part 4: 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP179 Depth (m) :- 0.40

Sample Type & No :- B2

Test Method

2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 16.0

Particle Density (Assumed) = 2.05


Maximum Dry Density (Mg/m³) = 1.48

Retained on 20mm Sieve (%) = 19.0

Date Tested = 30/09/2020

Retained on 37.5mm Sieve (%) = 10.0

Remarks ::

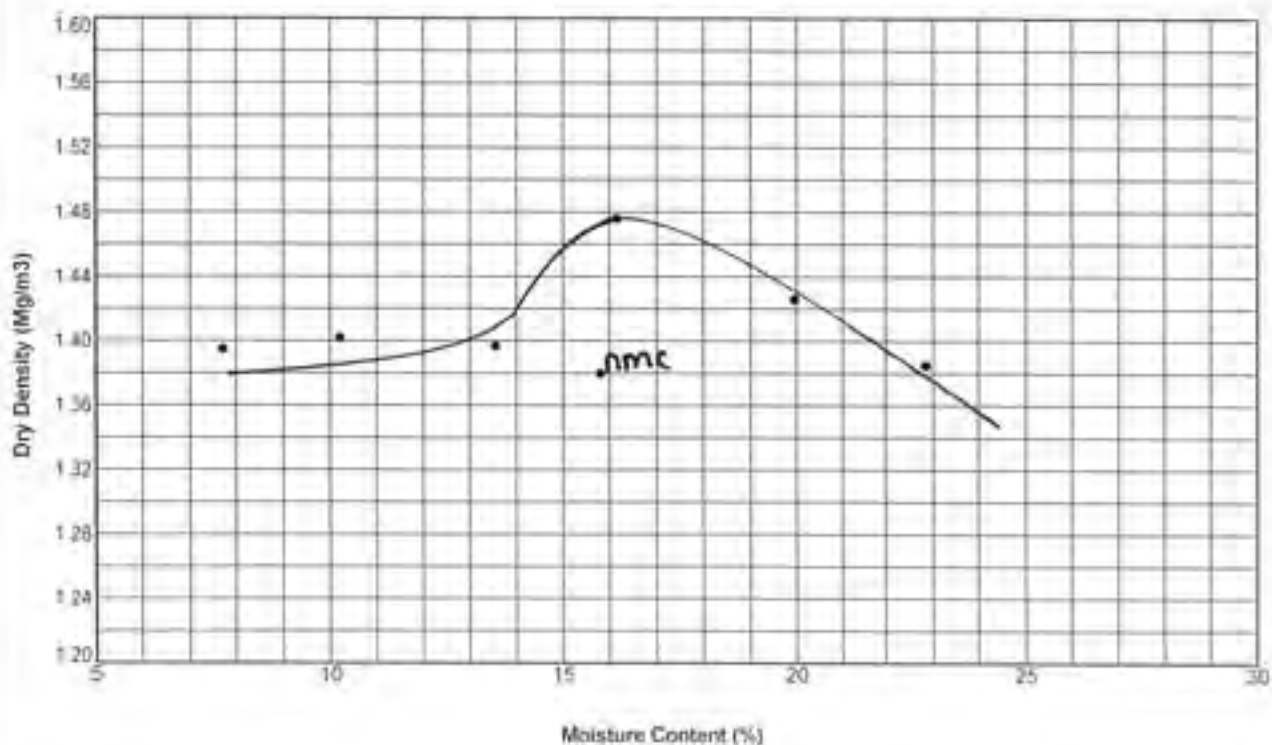

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :-

Prairie Site Ground Investigation Works

Client :-

South Tees Development Corporation



Signed :- *msene*

Name :-

MSENE

Page 1 of 1

Date of issue :-
02/11/2020

Certificate No :-
COMP4251/1

AEG Contract No :-
4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Wield (a) Industrial Estate, Forest Farm, Chatteris, Huntingdon, Cambs, Cambridgeshire, UK. Tel: 01455 561200 Fax: 01455 561210
 Regional Office: Unit 21, Business Gateway, Churchfields, Epsom, Surrey, Surrey, UK. Tel: 01753 751100 Fax: 01753 751101

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 Part 4: 1990

Specimen Identification

Exploratory Hole No - PRAIRIE_AUK_TP182 Depth (m) - 0.60

Sample Type & No - B2

Test Method 2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 17.5

Particle Density (Assumed) = 1.95


Maximum Dry Density (Mg/m³) = 1.35

Retained on 20mm Sieve (%) = 17.0

Date Tested = 28/09/2020

Retained on 37.5mm Sieve (%) = 3.0

Remarks :

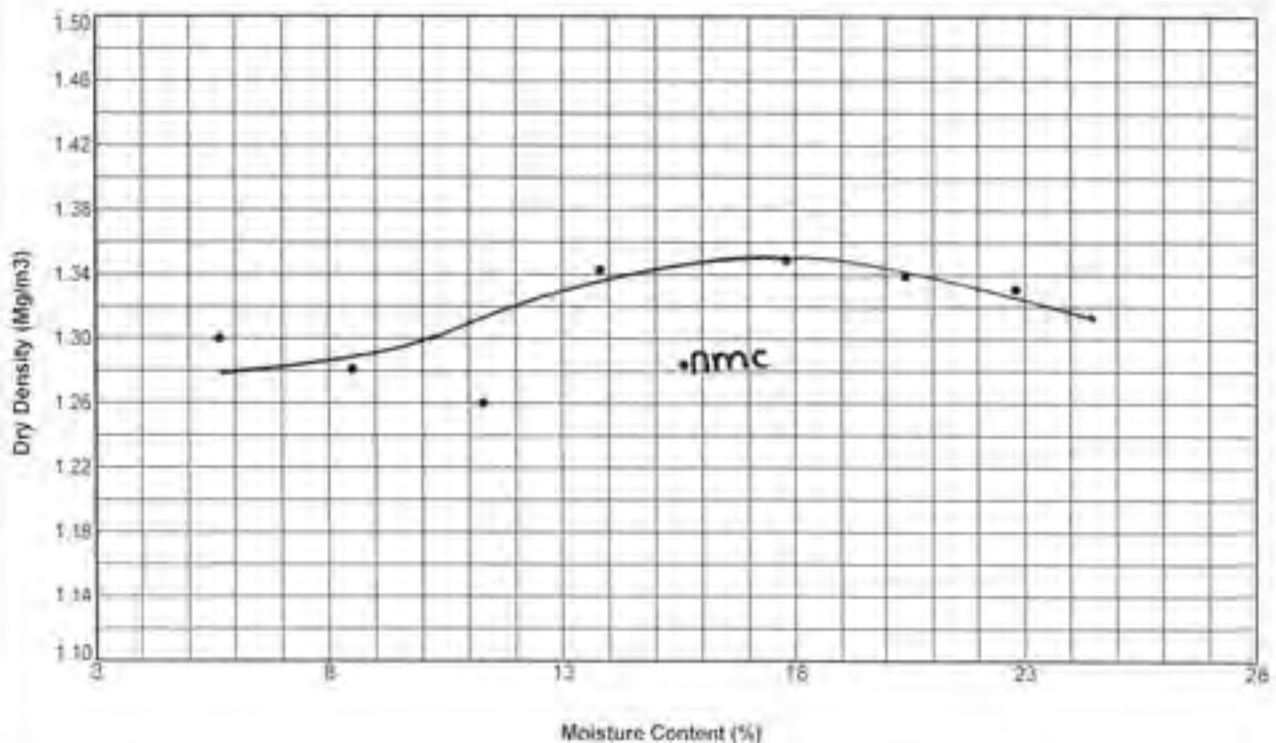

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title - Prairie Site Ground Investigation Works

Client - South Tees Development Corporation



Signed - *msone*

Name -

Page 1 of 1

Date of issue - 02/11/2020

Certificate No - COMP/4251/1

AEG Contract No - 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Brookside Enterprise Centre, North Street, Darlington, Co. Durham, DL1 1BS. Tel: 01779 367498 Fax: 01779 367410
Regional Office: Unit 25, Stannard Development Centre, "Kings Wood", Heslerton, BA 1 5B. Tel: 01753 371331 Fax: 01753 371332

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP

BS 1377 - Part 4 : 1990

Specimen Identification

Exploratory Hole No - PRAIRIE_AUK_TP189 Depth (m) - 1.50

Sample Type & No - B4

Test Method 2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 21.0

Particle Density (Assumed) = 2.65


Maximum Dry Density (Mg/m³) = 1.62

Retained on 20mm Sieve (%) = 0.0

Date Tested = 30/09/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

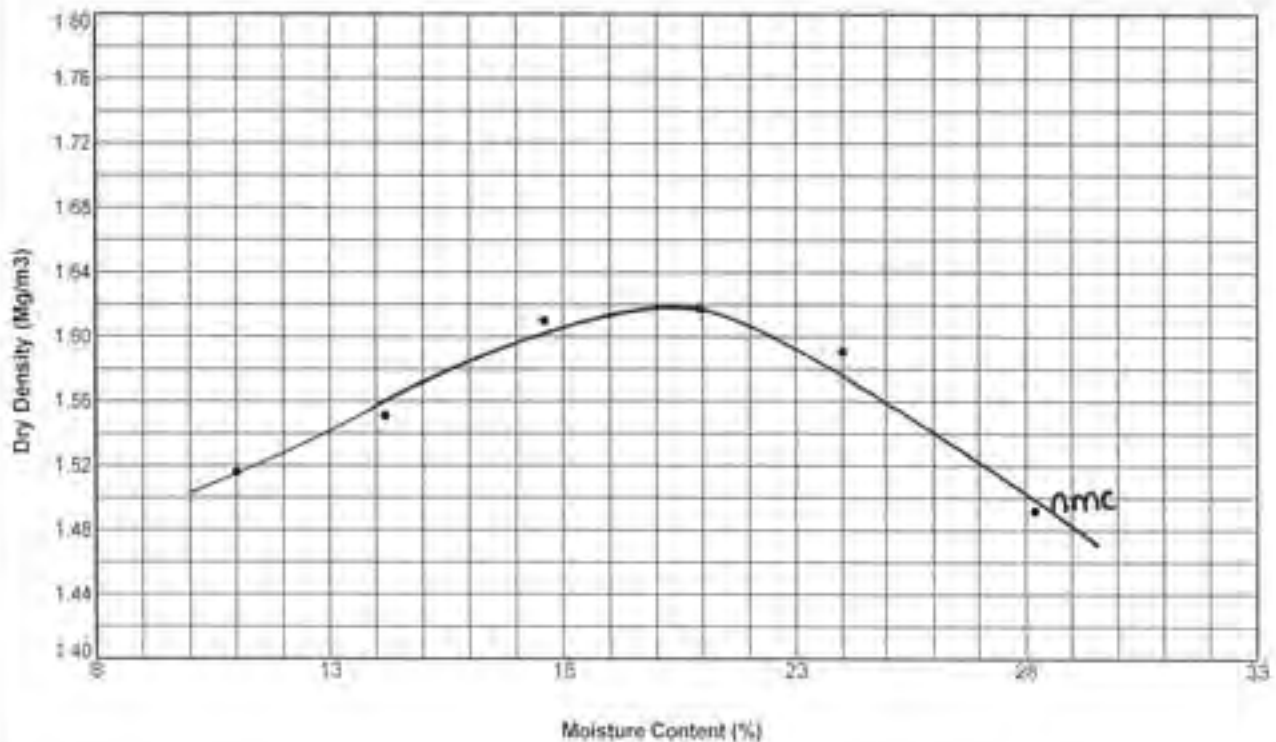

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title - Prairie Site Ground Investigation Works

Client - South Tees Development Corporation



Signed - *mserle*

Name - *M. Serle*

Page 1 of 1

Date of issue - 02/11/2020

Certificate No - COMP/4251/1

AEG Contract No - 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21, The Old School House, High Road, Chesham, Bucks, UK. Dunstable: (01462) 430000. Tel: 0117 327 4700 Fax: 0117 327 4710
 Regional Offices: Unit 21, The Old School House, High Road, Chesham, Bucks, UK. Tel: 0117 327 4700 Fax: 0117 327 4710

MOISTURE CONTENT/DRY DENSITY RELATIONSHIP BS 1377 Part 4: 1990

Specimen Identification

Exploratory Hole No :- PRAIRIE_AUK_TP189 Depth (m) :- 2.90

Sample Type & No :- B6

Test Method 2.5kg Compaction

Single Sample

Test Results

Optimum Moisture Content (%) = 21.5

Particle Density (Assumed) = 2.70


Maximum Dry Density (Mg/m³) = 1.65

Retained on 20mm Sieve (%) = 0.0

Date Tested = 30/09/2020

Retained on 37.5mm Sieve (%) = 0.0

Remarks :

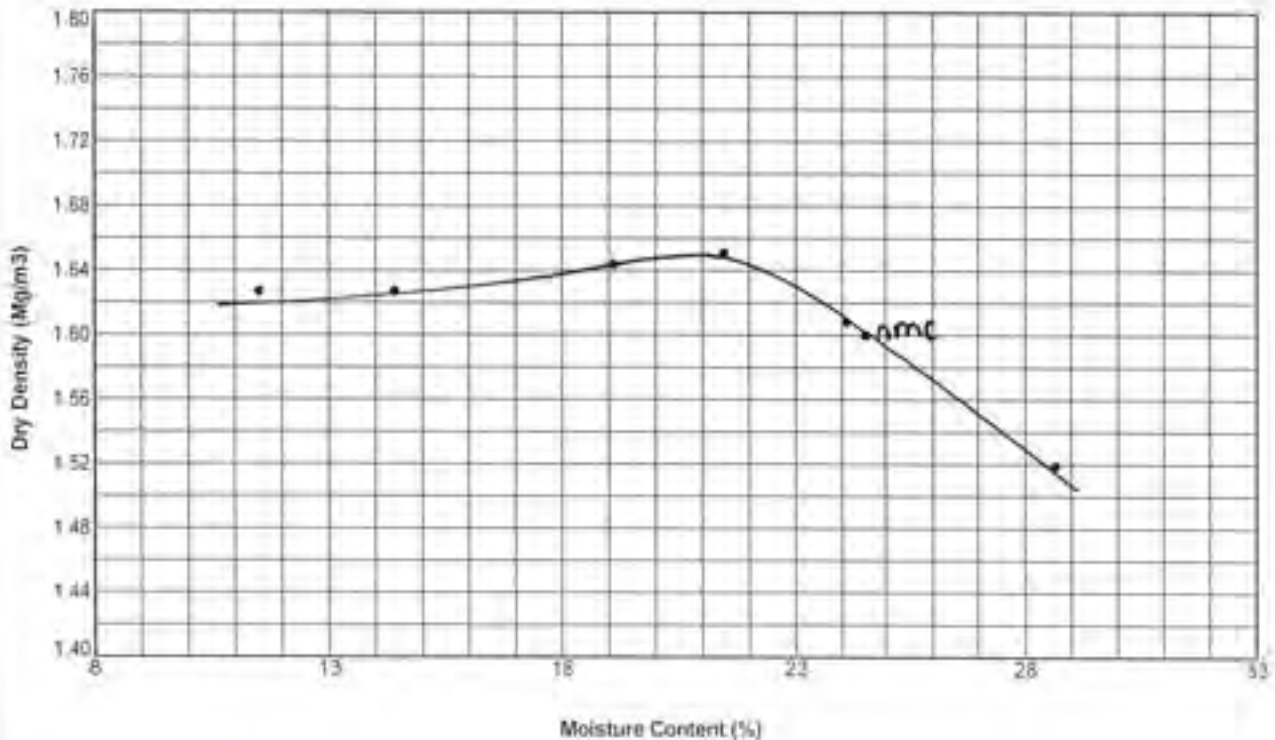

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works

Client :- South Tees Development Corporation



Signed: *msene*

Name :-

Page 1 of 1

Date of Issue :- 02/11/2020

Certificate No :- COMP/251/1

AEG Contract No :- 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office Unit 25, South Quay Business Park, South Quay, Liverpool, L3 5QY, Merseyside, UK. Tel: 0151 494 4444 Fax: 0151 494 4445
Regional Office Unit 25, Business Development Centre, Kingswood, Braintree, Essex, UK. Tel: 01276 344444 Fax: 01276 344445

ATTEMPTED AND ABORTED TESTING

Exploratory Hole No.	Sample Depth (m)	Sample ID	Test Type	Retained on 20mm (%)	Retained on 37.5mm (%)	Remarks
PRAIRIE_AJK_TP109	0.90	B4	2.5kg Compaction	55.0	45.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP110	1.00	B2	2.5kg Compaction	29.0	15.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP111	1.00	B5	2.5kg Compaction	48.0	37.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP113	1.80	B6	2.5kg Compaction	86.0	40.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP114	0.40	B4	2.5kg Compaction	23.0	12.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP117	2.00	B5	2.5kg Compaction	65.0	39.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP132	2.00	B6	2.5kg Compaction	57.0	37.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP137	1.00	B4	2.5kg Compaction	38.0	6.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP155A	0.70	B4	2.5kg Compaction	82.0	81.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP164	1.80	B5	4.5kg Compaction	64.0	51.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP169	0.80	B2	4.5kg Compaction	25.0	20.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP172	0.60	B2	2.5kg Compaction	97.0	96.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP177	1.80	B7	2.5kg Compaction	88.0	97.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP181	0.50	B2	2.5kg Compaction	25.0	16.0	Test Unsuitable due to excessive coarse material.
PRAIRIE_AJK_TP188	0.60	B2	2.5kg Compaction	39.0	8.0	Test Unsuitable due to excessive coarse material.

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works	Client :- South Tees Development Corporation
---	--

	Signed :- 	Page 1 of 1	
	Date of issue :- 03/11/2020	Certificate No :- USCR/M251/F	

Determination of California Bearing Ratio



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21 South Gate Industrial Estate, Priory Way, Chorleywood, Essex, Dunmow, CO9 2SD. Tel: 01992 387 438 Fax: 01992 387 439
Regional Office: Unit 21, Business Development Centre, Eastern Street, Buntingford, Cambs, CB11 1SA. Tel: 01773 735 260 Fax: 01773 735 261


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 - Part 4 : 1990 and Part 2 : Clause 3.2 : 1990

Exploratory Hole No.- **PRAIRIE_AUK_BH107** Sample No.- **B5**

Depth (m)- **4.00**

"As Received" Moisture Content (%) :	27.4	Surcharge (Kg) :	6
Retained on 20mm (%) :	0.0	Seating Load (N) :	Top 10 / Bottom 10
Correction Needed :	No	Test Moisture Content (%) :	Top 27.1 / Bottom 27.7
Soaking Time (Days) :	N/A	Bulk Density (Mg/m ³) :	1.96
Swelling (mm) :	N/A	Dry Density (Mg/m ³) :	1.54
Date Tested :	14/07/2020	CBR Value (%) :	Top 0.6 / Bottom 0.5
Preparation Method :	2.5kg Compaction		
Remarks :			

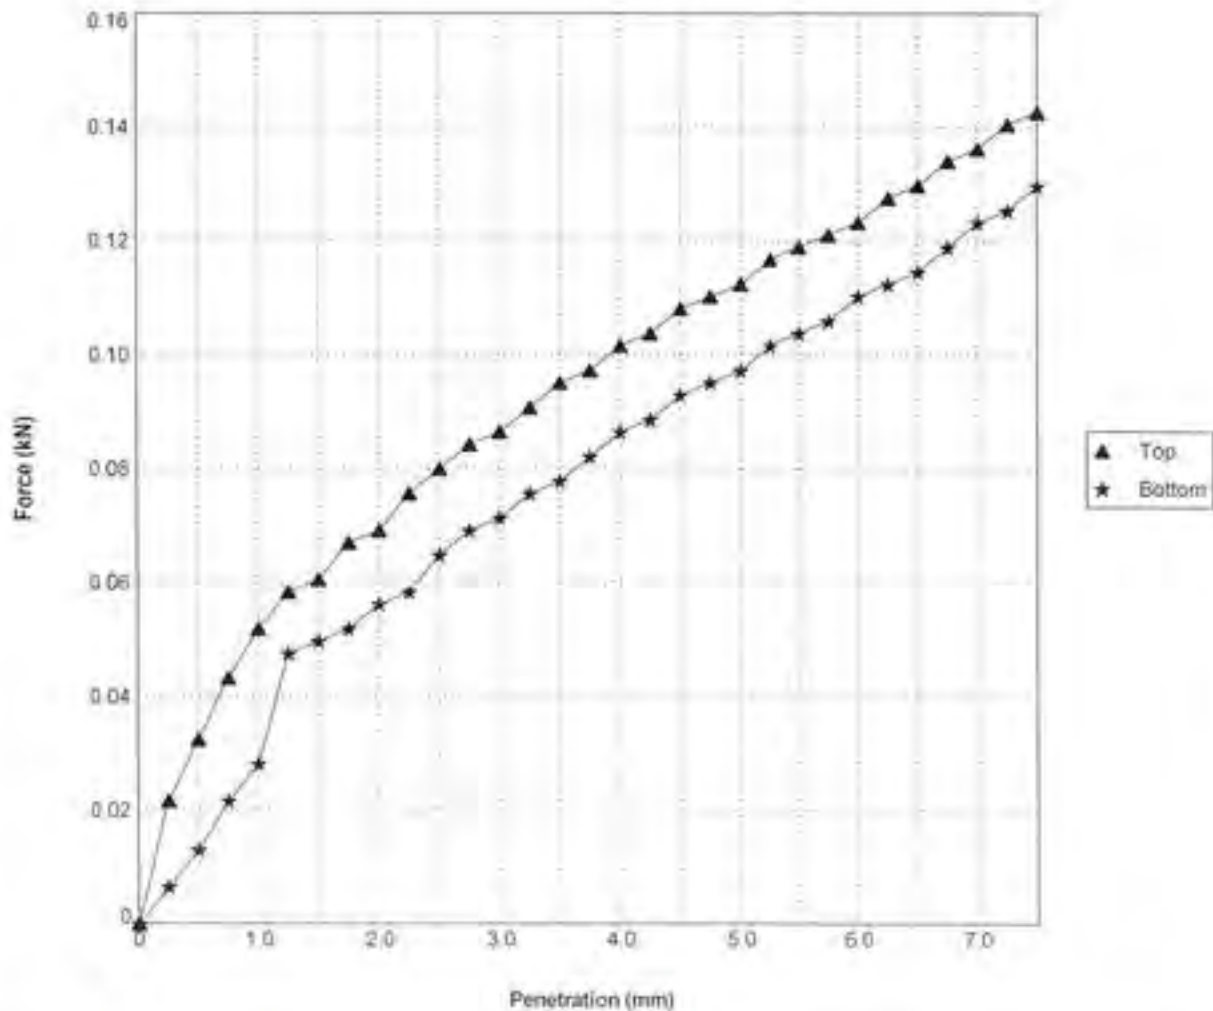

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- **Prairie Site Ground Investigation Works**

Client :- **South Tees Development Corporation**

Signed :- *msone*
Date of issue :- **31.07.2020**

Name :- **M. BELKIRK**
Certificate No. :- **CBR/4251/PRAIRIE_AUK_BH107/B5/4 001**

Page 1 of 1
AEG Contract No. :- **4251**



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21, Walsley Industrial Estate, Park Road, Chester-le-Street, Co. Durham, DN4 2BG. Tel: 0191 387 4770 Fax: 0191 287 4719
Regional Office: Unit 20, Business Development Centre, Eastern Wharf, Stockton, SS1 5NS. Tel: 01722 735 385 Fax: 01722 735 980


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 - Part 4 - 1990 and Part 2 - Clause 3.2 - 1990

Exploratory Hole No. - PRAIRIE_AUK_BH109 Sample No. - B4

Depth (m) - 0.50

"As Received" Moisture Content (%) :	23.8	Surcharge (Kg) :	6
Retained on 20mm (%) :	1.0	Seating Load (N) :	Top 10 / Bottom 10
Correction Needed :	No	Test Moisture Content (%) :	Top 23.3 / Bottom 24.2
Soaking Time (Days) :	N/A	Bulk Density (Mg/m ³) :	2.00
Swelling (mm) :	N/A	Dry Density (Mg/m ³) :	1.61
Date Tested :	14/07/2020	CBR Value (%) :	Top 2.5 / Bottom 2.4
Preparation Method :	2.5kg Compaction		
Remarks :			

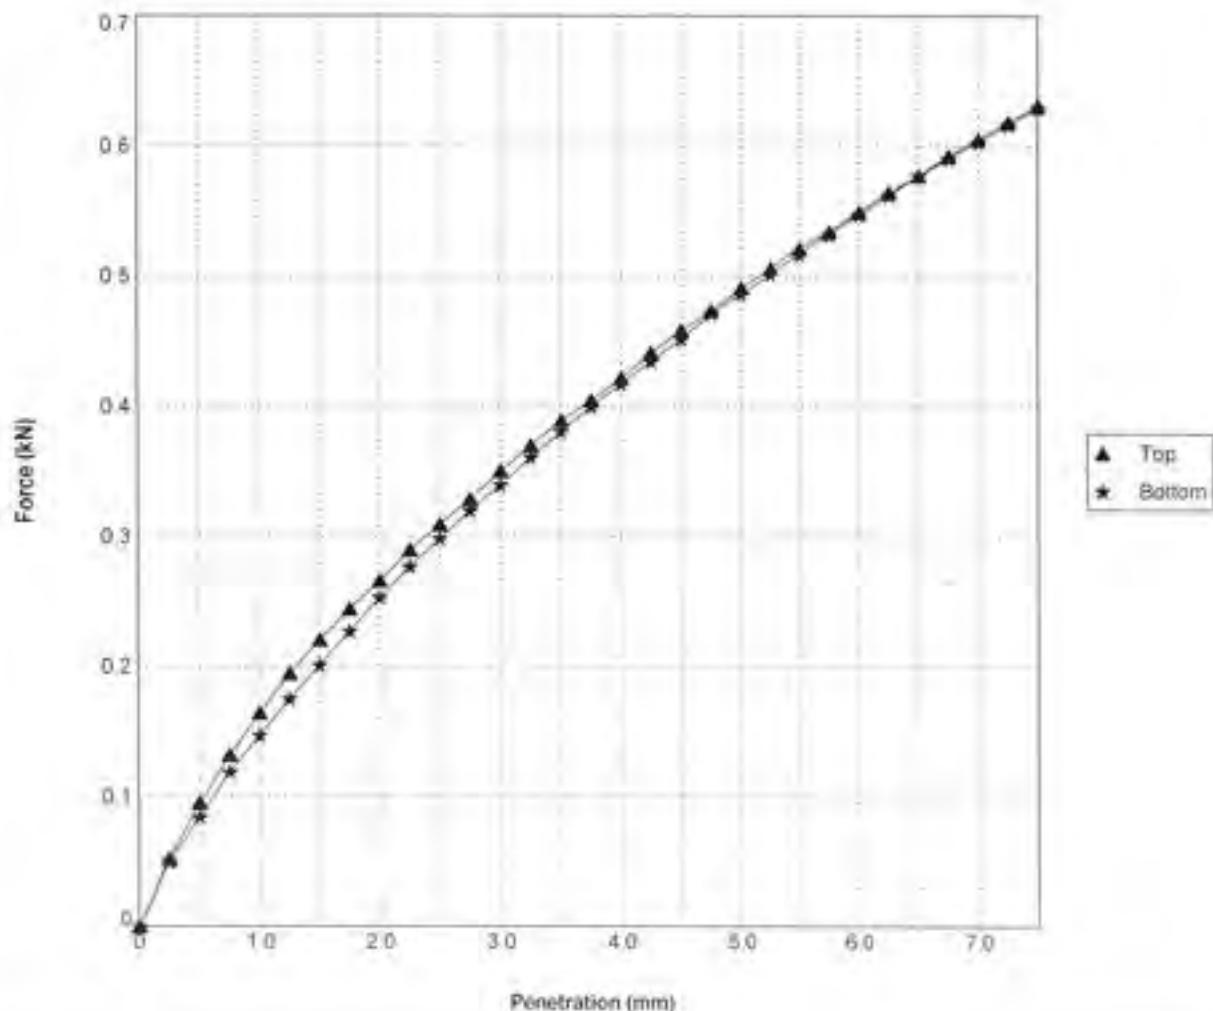

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works

Client :- South Tees Development Corporation



Signed :- *msone*

Name :- M. J. CLARKE

Page 1 of 1

Date of issue :- 31/07/2020

Certificate No. :- CBR/4351/PRAIRIE_AUK_BH109/B4/0.50/1

AEG Contract No. :- 4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21, Boreas (28 Industrial Estate), Porth Park, Clevedon Road, Cox Dorman, DND 28G, Tel: 01949 530 470 Fax: 01451 451 475
Regional Office: Unit 21, Business Development Centre, Eastern Wharf, Gosport, H01 5BB, Tel: 01703 735 305 Fax: 01703 735 300


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 : Part 4 : 1990 and Part 2 : Clause 3.2 : 1990

Exploratory Hole No - **PRAIRIE_AUK_BH109** Sample No - **B10**

Depth (m) - **2.00**

"As Received" Moisture Content (%) :	24.5	Surcharge (Kg) :	6
Retained on 20mm (%) :	0.0	Seating Load (N) :	Top 10 / Bottom 10
Correction Needed :	No	Test Moisture Content (%) :	Top 24.9 / Bottom 24.0
Soaking Time (Days) :	N/A	Bulk Density (Mg/m ³) :	2.00
Swelling (mm) :	N/A	Dry Density (Mg/m ³) :	1.60
Date Tested :	14/07/2020	CBR Value (%) :	Top 2.4 / Bottom 2.6
Preparation Method :	2.5kg Compaction		
Remarks :			

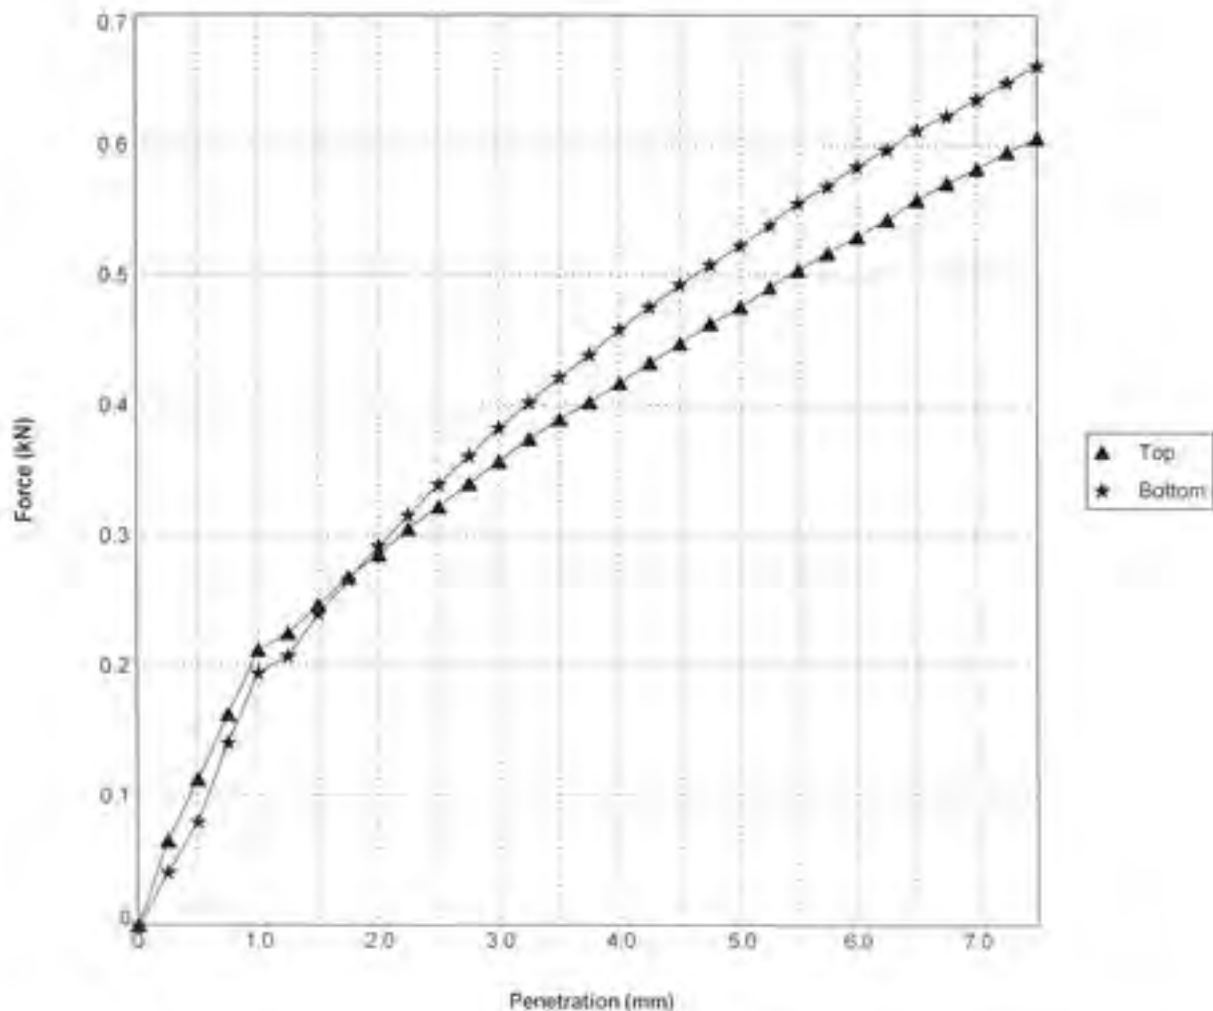

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title - **Prairie Site Ground Investigation Works**

Client - **South Tees Development Corporation**



Signed - *msene*

Name - *M. SENE*

Page 1 of 1

Date of issue - **31/07/2020**

Certificate No - **CBR/4251/PRAIRIE_AUK_BH109/B10/2.00/1**

AEG Contract No - **4251**



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Widdow's Industrial Estate, Preston Park, Chichester, W Sussex, PO19 1PL. Tel: 01243 831436 Fax: 01243 831478
Regional Office: Unit 20, Burgess Commercial Centre, Station Street, Burslem, Stoke-on-Trent, ST4 1NS. Tel: 01722 735300 Fax: 01722 735300


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 - Part 4 : 1990 and Part 2 : Clause 3.2 : 1990

Exploratory Hole No.- **PRAIRIE_AUK_BH110** Sample No.- **B10**

Depth (m)- **6.50**

"As Received" Moisture Content (%) :	25.9	Surcharge (Kg) :	5
Retained on 20mm (%) :	0.0	Seating Load (N) :	Top 10 / Bottom 10
Correction Needed :	No	Test Moisture Content (%) :	Top 25.6 / Bottom 26.2
Soaking Time (Days) :	N/A	Bulk Density (Mg/m ³) :	1.97
Swelling (mm) :	N/A	Dry Density (Mg/m ³) :	1.57
Date Tested :	14/07/2020	CBR Value (%) :	Top 1.3 / Bottom 1.1
Preparation Method :	2.5kg Compaction		
Remarks :			

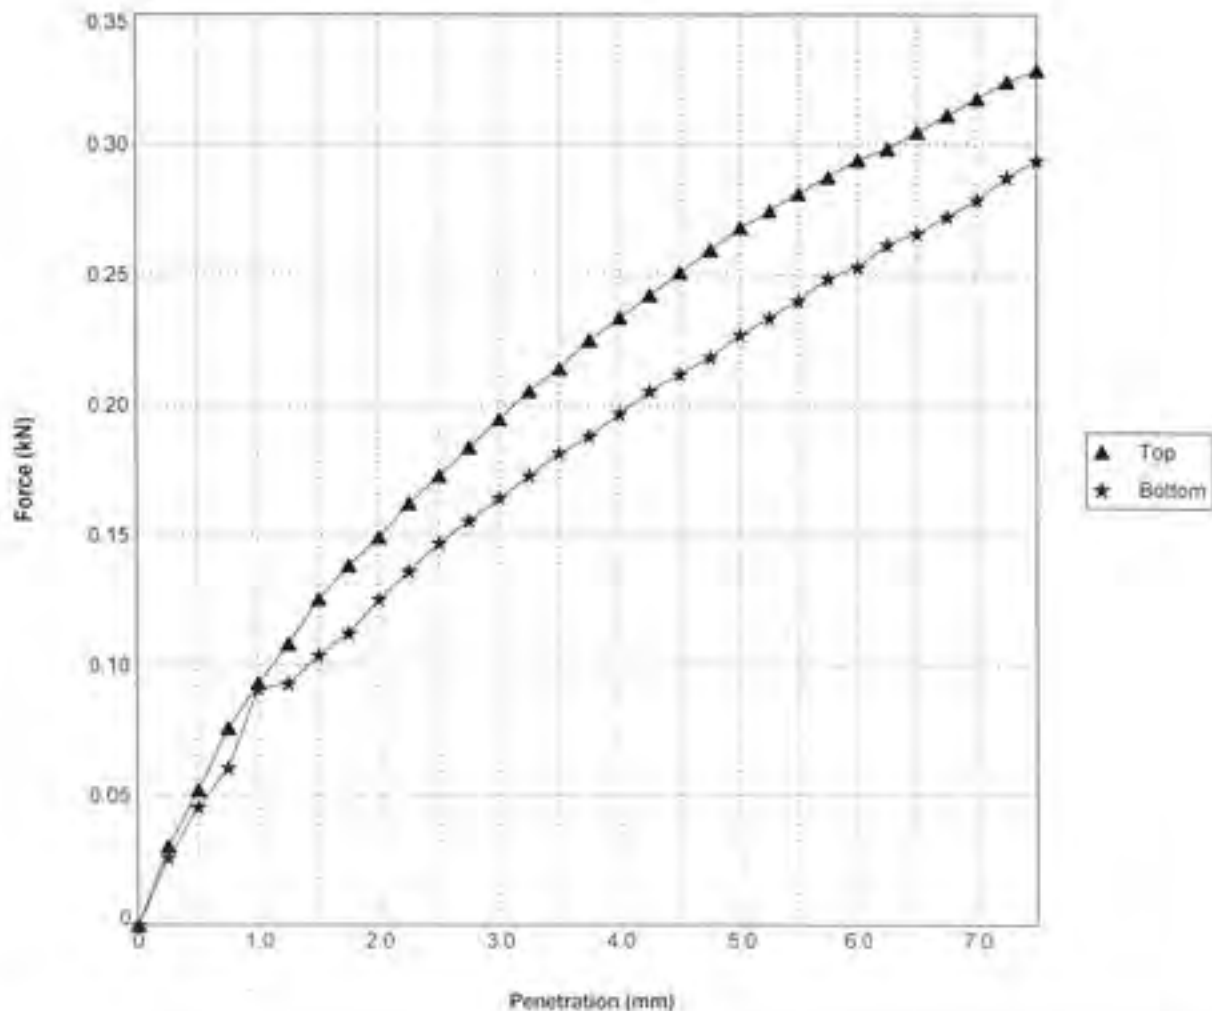

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title - **Prairie Site Ground Investigation Works**

Client - **South Tees Development Corporation**



Signed - *msone*
Date of issue - **31/07/2020**

Name - *M SOLARI*
Certificate No - **CBR4251/PRAIRIE_AUK_BH110/B10-5.50/1**

Page 1 of 1
AEG Contract No. - **4251**




DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377, Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No - **PRAIRIE_AUK_TP101** Sample No - **B4** Depth (m) - **0.90**

"As Received" Moisture Content (%)		Surcharge (Kg)	6
Retained on 20mm (%)	32.0	Seating Load (N)	Top 250 / Bottom 250
Corrector Needed	No	Test Moisture Content (%)	Top 17 / Bottom 16
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.94
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.67
Date Tested	01/10/2020	CBR Value (%)	Top 44 / Bottom 69
Preparation Method	2.5kg Compaction		
Remarks			

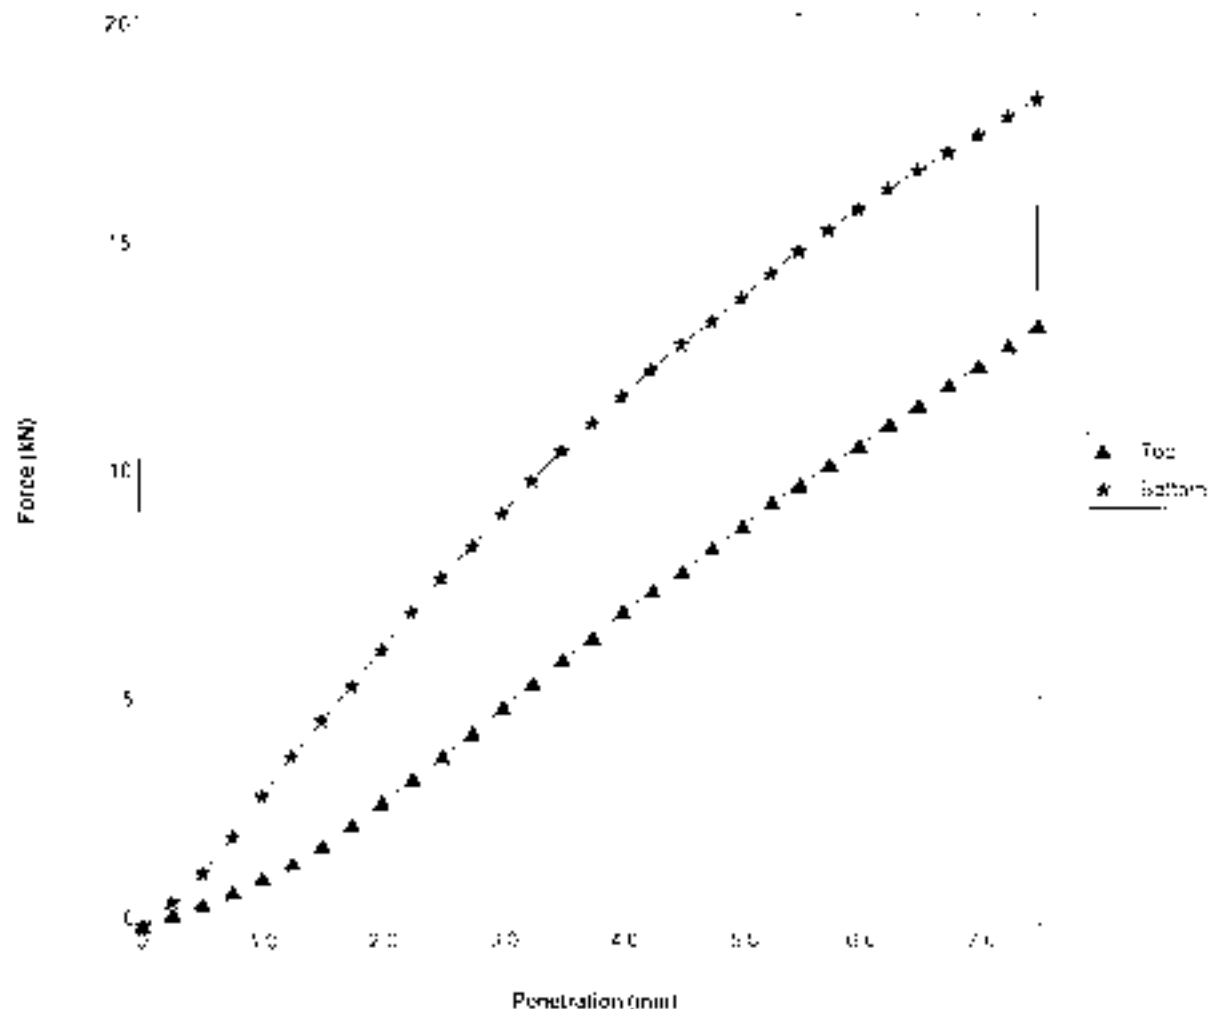

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Ref: _____

Prairie Site Ground Investigation Works

South Tees Development Corporation



Signature: *m.sone*
Date checked: 01/10/2020

Name: _____
Test Number: _____
Location: PRAIRIE_AUK_TP101/B4/1

Page 1 of 1
Allied Com. No: 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

INCORPORATED IN THE UNITED KINGDOM
REGISTERED OFFICE: 100, BRISTOL ROAD, BRISTOL, AVON, BS1 2YD, ENGLAND


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.3: 1990

Exploratory Hole No - **PRAIRIE_AUK_TP101** Sample No - **B11**

Depth (m) - **3.00**

"As Received" Moisture Content (%)		Surcharge (kg)	8
Retained on 20mm (%)	0.2	Seating Load (N)	Top 10 / Bottom 10
Correction Needed	No	Test Moisture Content (%)	Top 28 / Bottom 28
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.95
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.52
Date Tested	30/09/2020	CBR Value (%)	Top 3.6 / Bottom 3.0
Preparation Method	2.5kg Compaction		
Remarks			

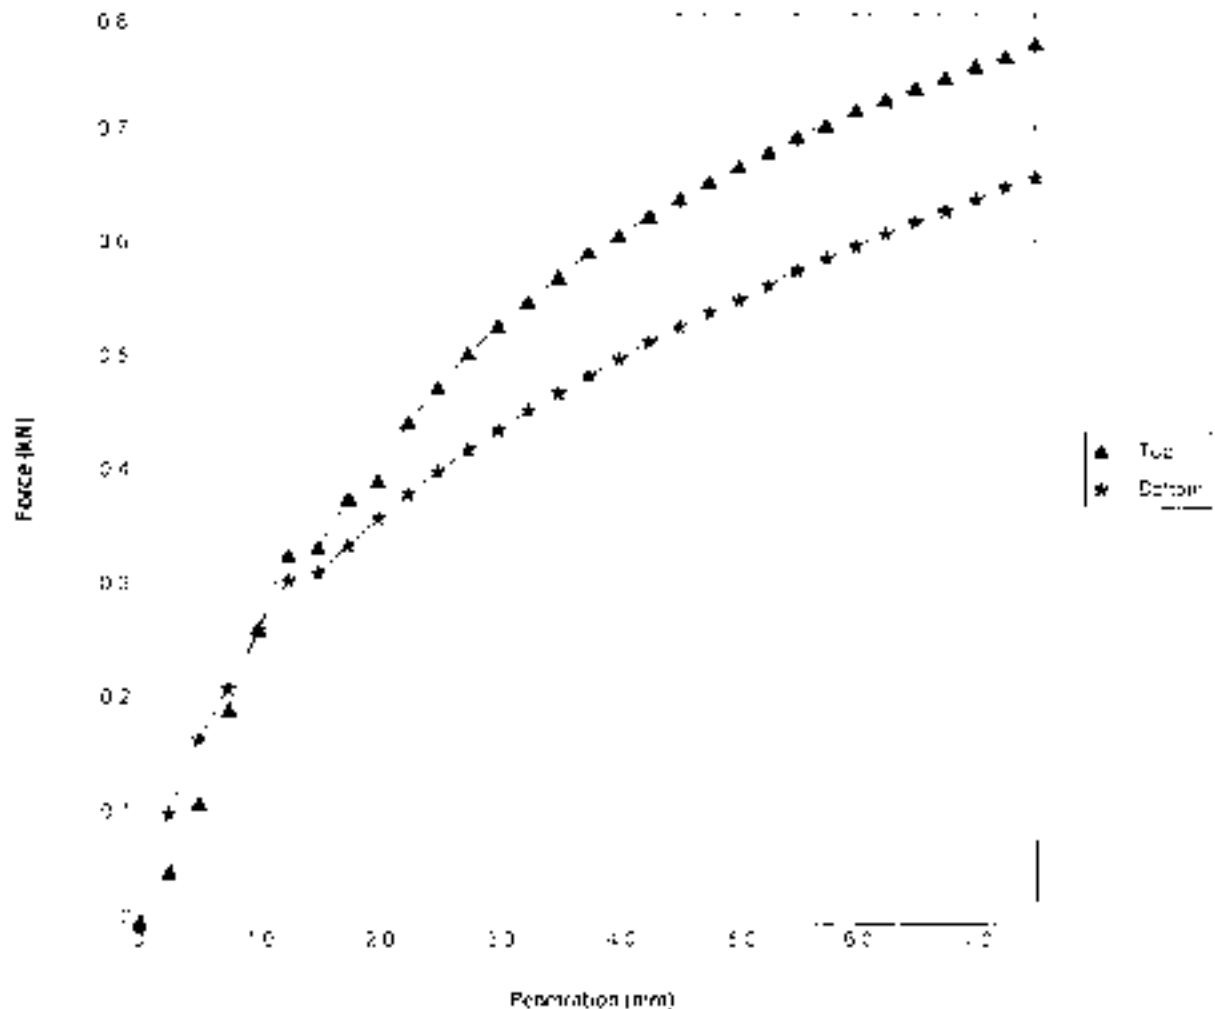

For details on all samples please refer to the Laboratory Sample Description Sheet

Contract Title

Prairie Site Ground Investigation Works

South Tees Development Corporation



Signature: *[Handwritten Signature]*
Date of Issue: 22/10/2020

Name: _____
Certificate No: _____
CBR 4251 PRAIRIE_AUK_TP101 B11 3.00

Ref: 4251
ACG Certificate No: **4251**



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Station Industrial Estate, Prince Park, Creighton Street, Co. Durham, UK, DL2 8BQ. Tel: 0191 387 4750 Fax: 0191 387 4715
Regional Office: Unit 20, Business Development Centre, Euston Square, Glasgow, G8 1JG. Tel: 01772 335 300 Fax: 01772 795 088


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377: Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No. - PRAIRIE_AUK_TP102 Sample No. - B8

Depth (m) - 2.00

"As Received" Moisture Content (%) :		Surcharge (Kg) :	6
Retained on 20mm (%) :	5.0	Seating Load (N) :	Top 10 / Bottom 10
Correction Needed :	No	Test Moisture Content (%) :	Top 22 / Bottom 23
Soaking Time (Days) :	N/A	Bulk Density (Mg/m ³) :	2.02
Swelling (mm) :	N/A	Dry Density (Mg/m ³) :	1.65
Date Tested :	19/10/2020	CBR Value (%) :	Top 1.6 / Bottom 1.6
Preparation Method :	2.5kg Compaction		
Remarks :			

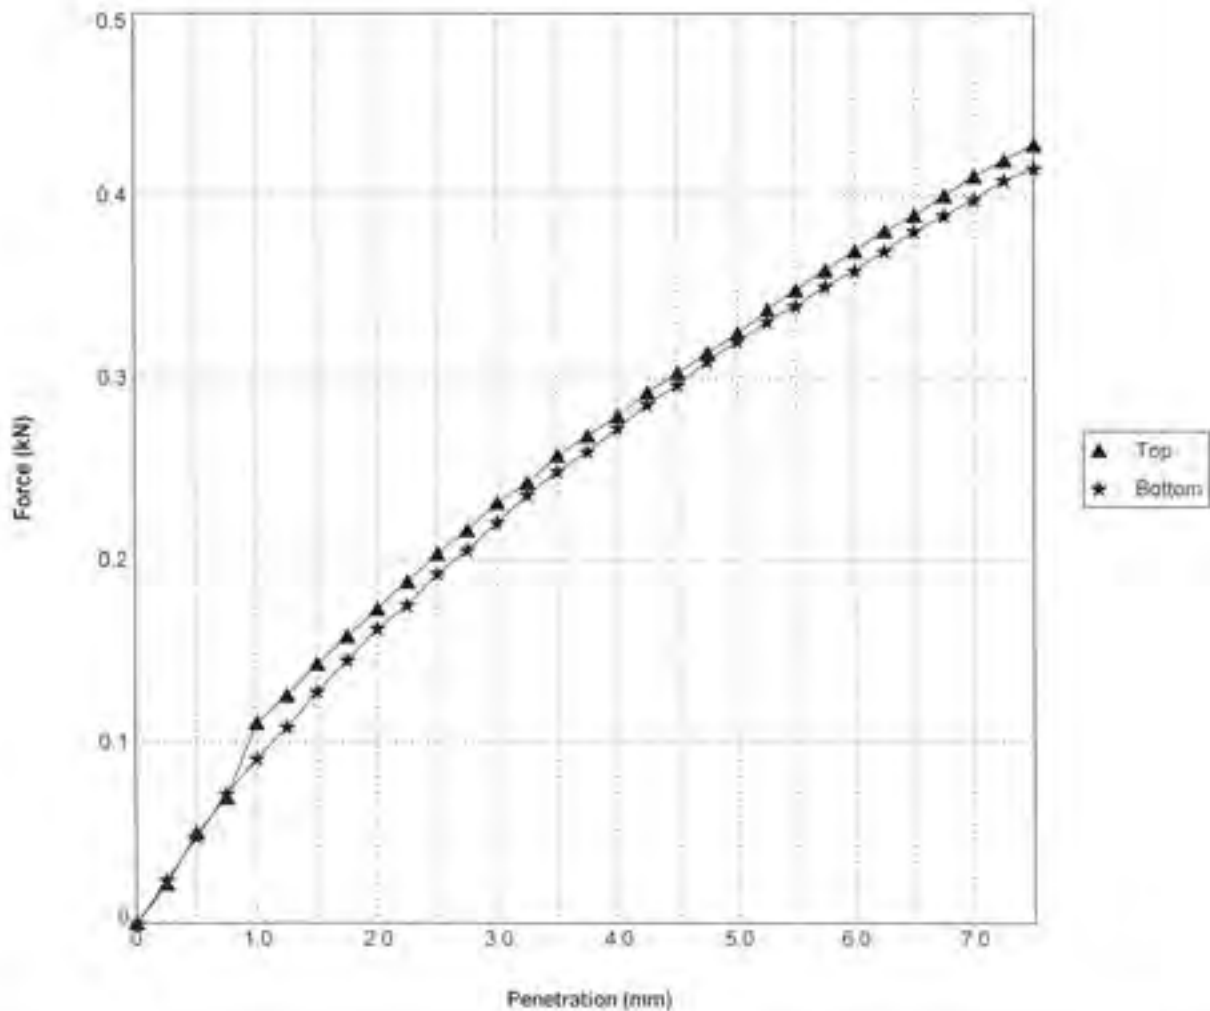

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works

Client :- South Tees Development Corporation



Signed :- *mserp*

Name :- *M. Serp*

Page 1 of 1

Date of issue :- 30/10/2020

Certificate No :- CBR/4251/PRAIRIE_AUK_TP102/B8/2 001

AEG Contract No :- 4251




DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 7: Clause 3.2: 1990

Exploratory Hole No - **PRAIRIE_AUK_TP105** Sample No - **B5** Depth (m) - **2.00**

As Received Moisture Content (%)		Surcharge (Kg)	5
Retained on 20mm (%)	2.0	Seating Load (N)	Top 10 / Bottom 10
Correction Needed	No	Test Moisture Content (%)	Top 27 / Bottom 27
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.95
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.53
Date Tested	30/09/2020	CBR Value (%)	Top 2.5 / Bottom 2.6
Preparation Method	2.5kg Compaction		
Remarks			

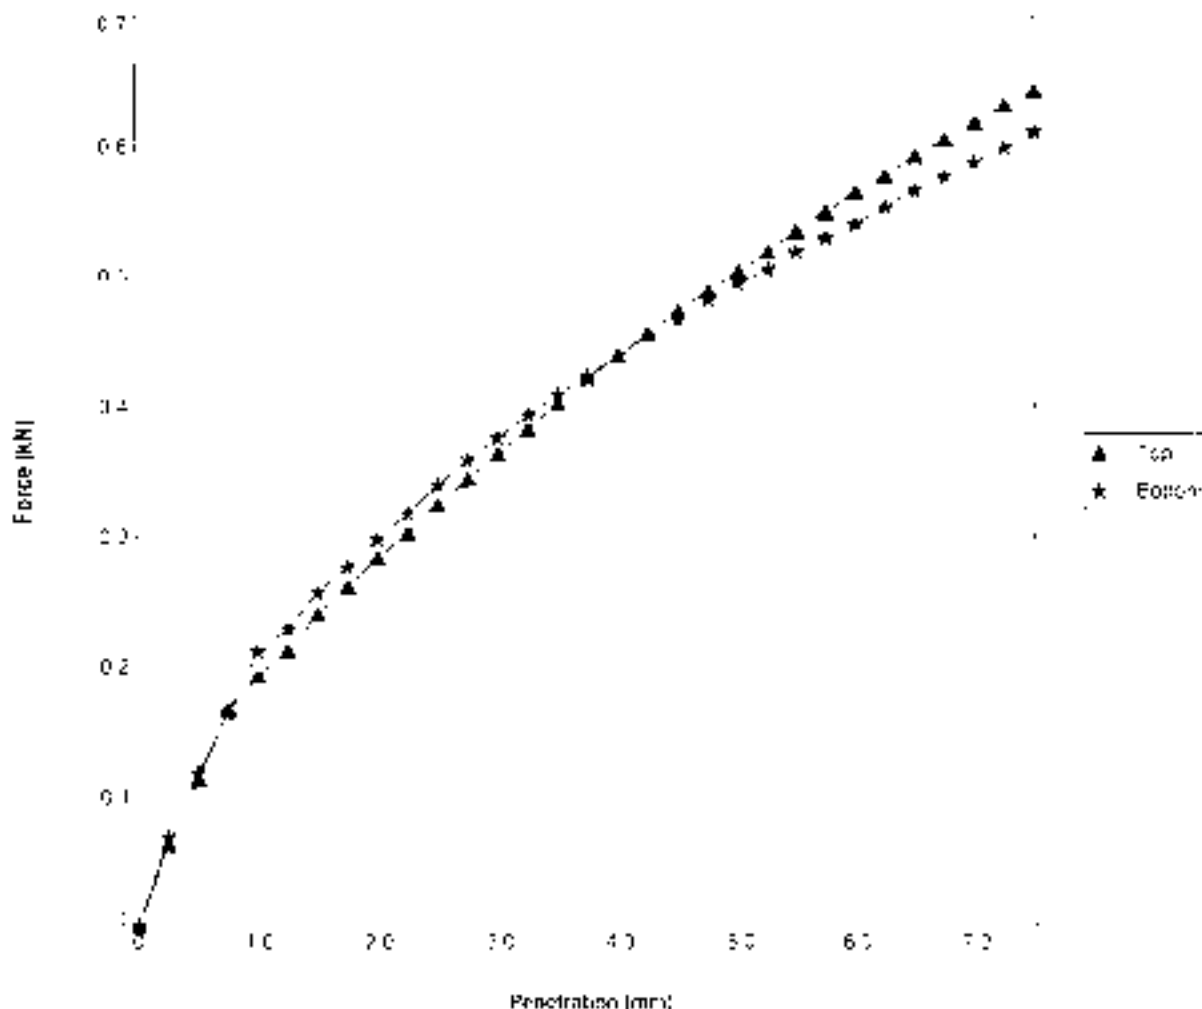

For coverage of sample please refer to the Laboratory Sample Description Sheet

Contract Title

Prairie Site Ground Investigation Works

Client

South Tees Development Corporation



Site No: **msaw**

Date of Issue: **20/10/2020**

Name

Client Reference: **CBR 4 - PRAIRIE_AUK_TP105_B5**

Page No. of 1

ASD Drawing No: **4251**



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

100, Garsington Road, Oxford, OX4 2DQ, UK. Tel: 01865 206200. Fax: 01865 206201. Email: sales@allied-geotech.co.uk


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No - PRAIRIE_AUK_TP107 Sample No - B4

Depth (m) - 1.00

As Received Moisture Content (%)		Surcharge (Kg)	6
Retained on 20mm (%)	5.0	Seating Load (N)	Top 10 / Bottom 10
Correction Needed	No	Test Moisture Content (%)	Top 25 / Bottom 24
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	2.00
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.51
Date Tested	30/09/2020	CBR Value (%)	Top 3.7 / Bottom 5.3
Preparation Method	2.5kg Compaction		
Remarks			

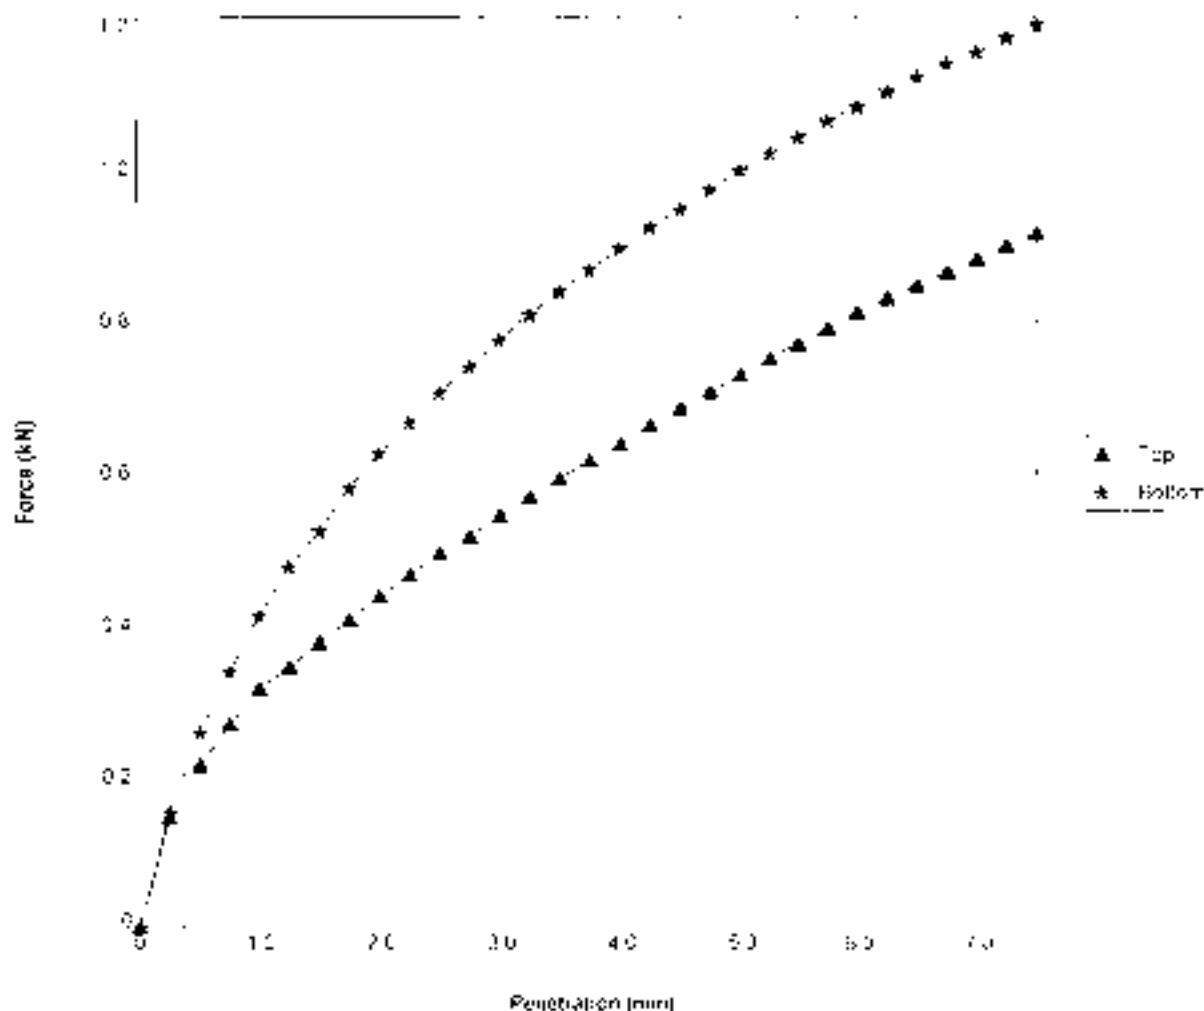

For detailed point of load curves please refer to the Laboratory Sample Description Sheet

Contract Ref:

Prairie Site Ground Investigation Works

Client:

South Tees Development Corporation



Signed:

Date of Issue:

[Signature]

30/09/2020

Name:

Certificate No:

CEP/01/PRAIRIE_AUK_TP107/B4/107

Page 1 of 1

APN/Contract No.:

4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Lot 21 Duffa (44) Industrial Estate, Peckham Park, Chesham in Street, Chesham, Bucks HP8 2RG - Tel: 0191 267 4700 Fax: 0191 267 4710
Regional Office: Unit 10, Resource Development Centre, Easton Wharf, Slough, SL1 1BL - Tel: 01753 755 300 Fax: 01753 755 300


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 : Part 4 : 1990 and Part 2 : Clause 3.2 : 1990

Exploratory Hole No - **PRAIRIE_AUK_TP110** Sample No - **B8**

Depth (m) - **3.00**

"As Received" Moisture Content (%) :		Surcharge (Kg) :	6
Retained on 20mm (%) :	0.0	Seating Load (N) :	Top 10 / Bottom 10
Correction Needed :	No	Test Moisture Content (%) :	Top 31 / Bottom 31
Soaking Time (Days) :	N/A	Bulk Density (Mg/m ³) :	2.27
Swelling (mm) :	N/A	Dry Density (Mg/m ³) :	1.73
Date Tested :	16/10/2020	CBR Value (%) :	Top 1.4 / Bottom 1.5
Preparation Method :	2.5kg Compaction		
Remarks :			

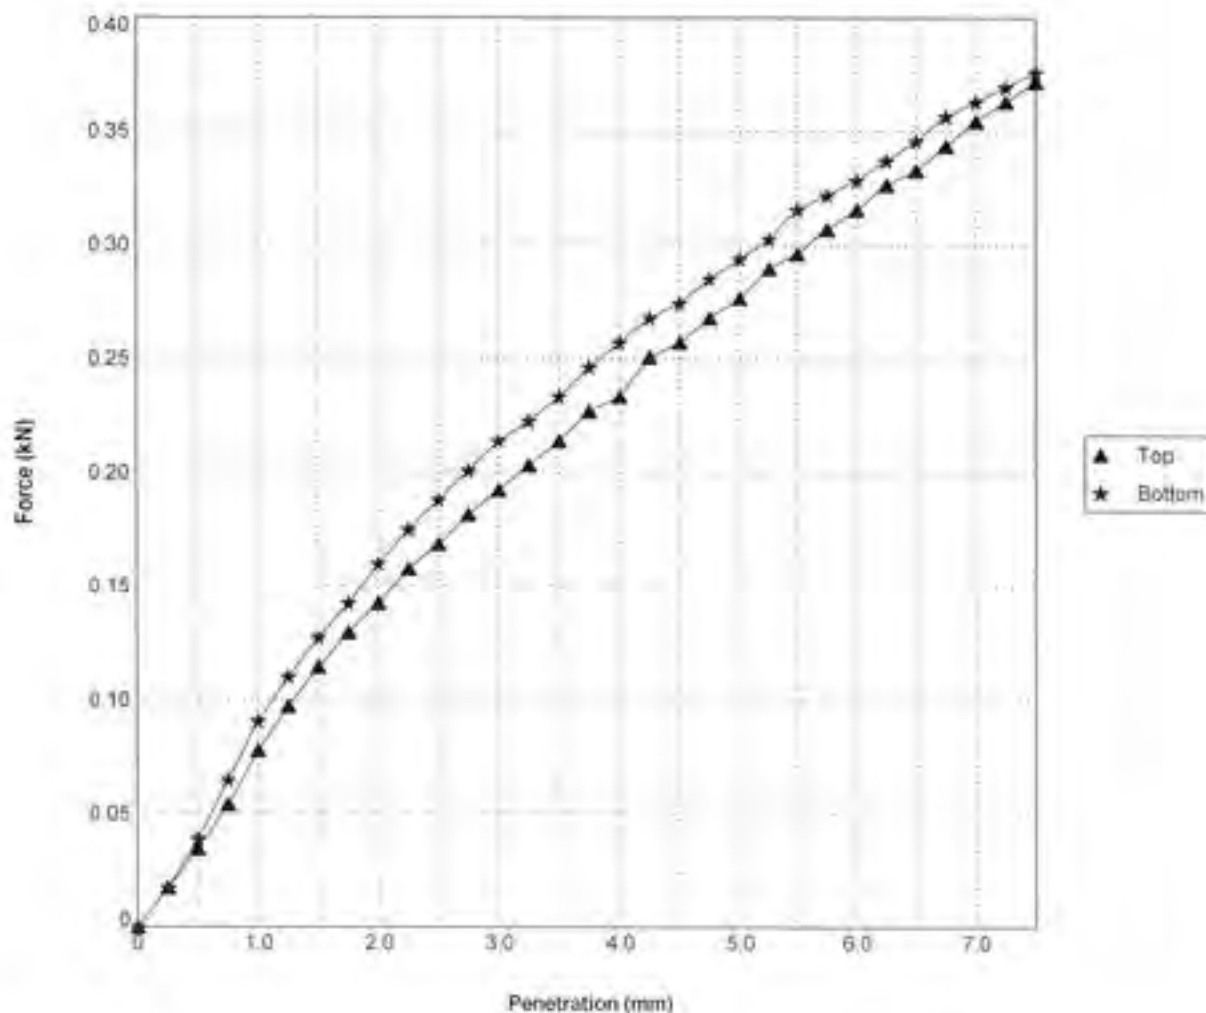

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- **Prairie Site Ground Investigation Works**

Client :- **South Tees Development Corporation**



Signed - *msore*

Name - *msore*

Page 1 of 1

Date of issue - **30/10/2020**

Certificate No - **CBR/4251/PRAIRIE_AUK_TP110/B8/3 00/1**

AEG Contract No - **4251**



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, South Tees Industrial Estate, Prince Park, Cleveland Street, South Shields, Co. Durham, DL15 2JG. Tel: 0191 267 4200 Fax: 0191 267 4716
Regional Office: Unit 20, Riverside Development Centre, Eborac Street, South Shields, Co. Durham, DL15 2JG. Tel: 0191 267 4200 Fax: 0191 267 4716


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 : Part 4 : 1990 and Part 2 : Clause 3.2 : 1990

Exploratory Hole No. - PRAIRIE_AUK_TP112 Sample No. - B5

Depth (m) - 1.70

"As Received" Moisture Content (%) :		Surcharge (Kg) :	6
Retained on 20mm (%) :	28.0	Seating Load (N) :	Top 250 / Bottom 250
Correction Needed :	No	Test Moisture Content (%) :	Top 20 / Bottom 18
Soaking Time (Days) :	N/A	Bulk Density (Mg/m ³) :	1.65
Swelling (mm) :	N/A	Dry Density (Mg/m ³) :	1.39
Date Tested :	19/10/2020	CBR Value (%) :	Top 28 / Bottom 41
Preparation Method :	2.5kg Compaction		
Remarks :			

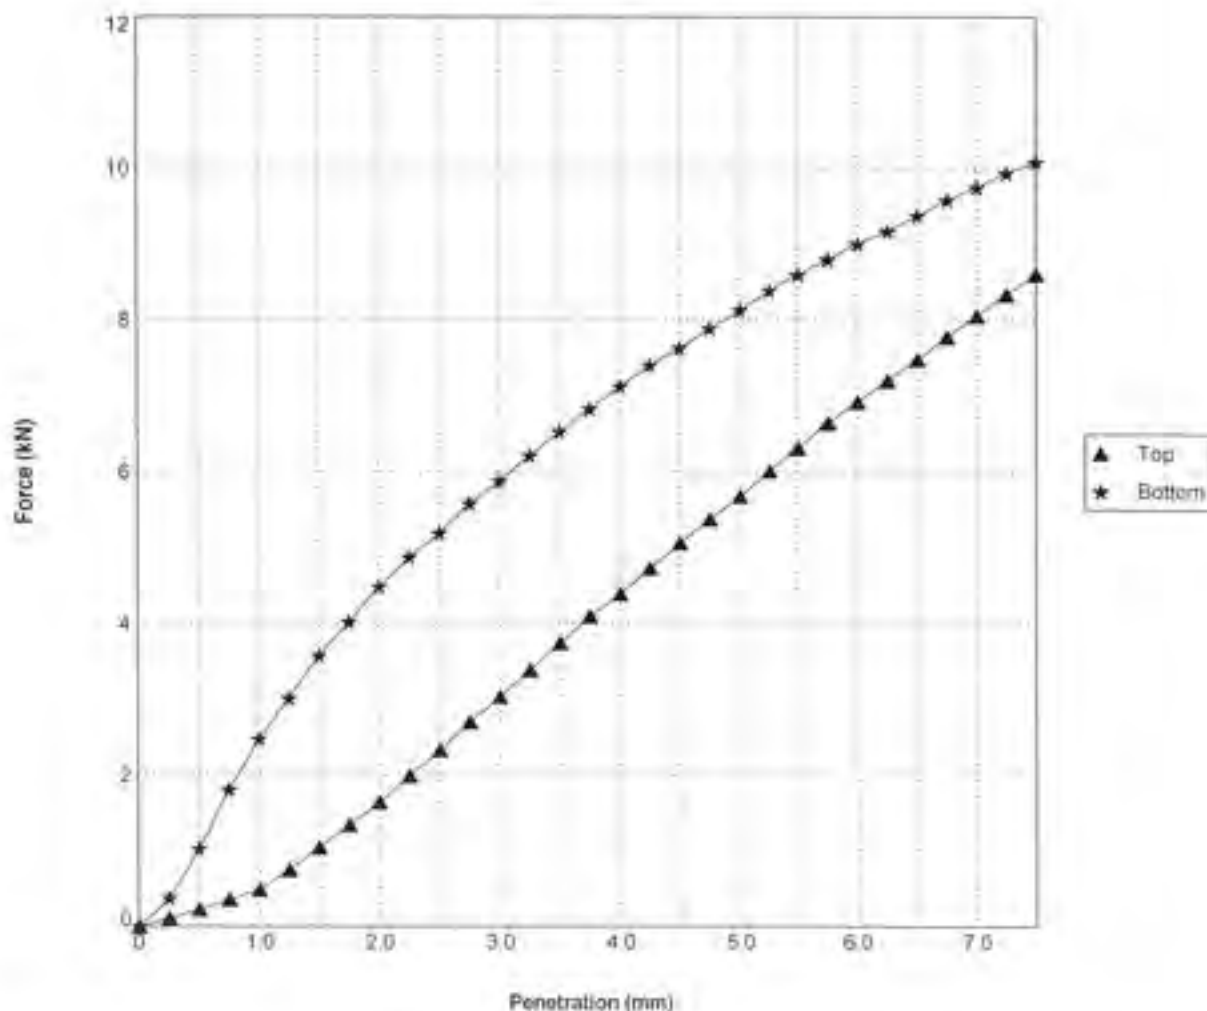

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works

Client :- South Tees Development Corporation



Signed :- *msore*

Name :-

Page 1 of 1

Date of issue :- 09/10/2020

Certificate No :- CBR/4251/PRAIRIE_AUK_TP112/B5/1.70/1

AEG Contract No :- 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 20, Seabra Old Industrial Estate, Filton Park, Crossenwither, Ux. (Bristol), G4 2JG. Tel: 01294 387470 Fax: 01294 387471
Regional Office: Unit 20, Business Development Centre, Eddon, Wigan, Lancashire, BB7 5SL. Tel: 01752 195266 Fax: 01752 426289


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 : Part 4 : 1990 and Part 2 : Clause 3.2 : 1990

Exploratory Hole No. - PRAIRIE_AUK_TP116 Sample No. - B8

Depth (m) - 2.50

"As Received" Moisture Content (%) :		Surcharge (Kg) :	6
Retained on 20mm (%) :	0.0	Seating Load (N) :	Top 50 / Bottom 50
Correction Needed :	No	Test Moisture Content (%) :	Top 24 / Bottom 24
Soaking Time (Days) :	N/A	Bulk Density (Mg/m ³) :	1.98
Swelling (mm) :	N/A	Dry Density (Mg/m ³) :	1.60
Date Tested :	16/10/2020	CBR Value (%) :	Top 4.5 / Bottom 5.6
Preparation Method :	2.5kg Compaction		
Remarks :			

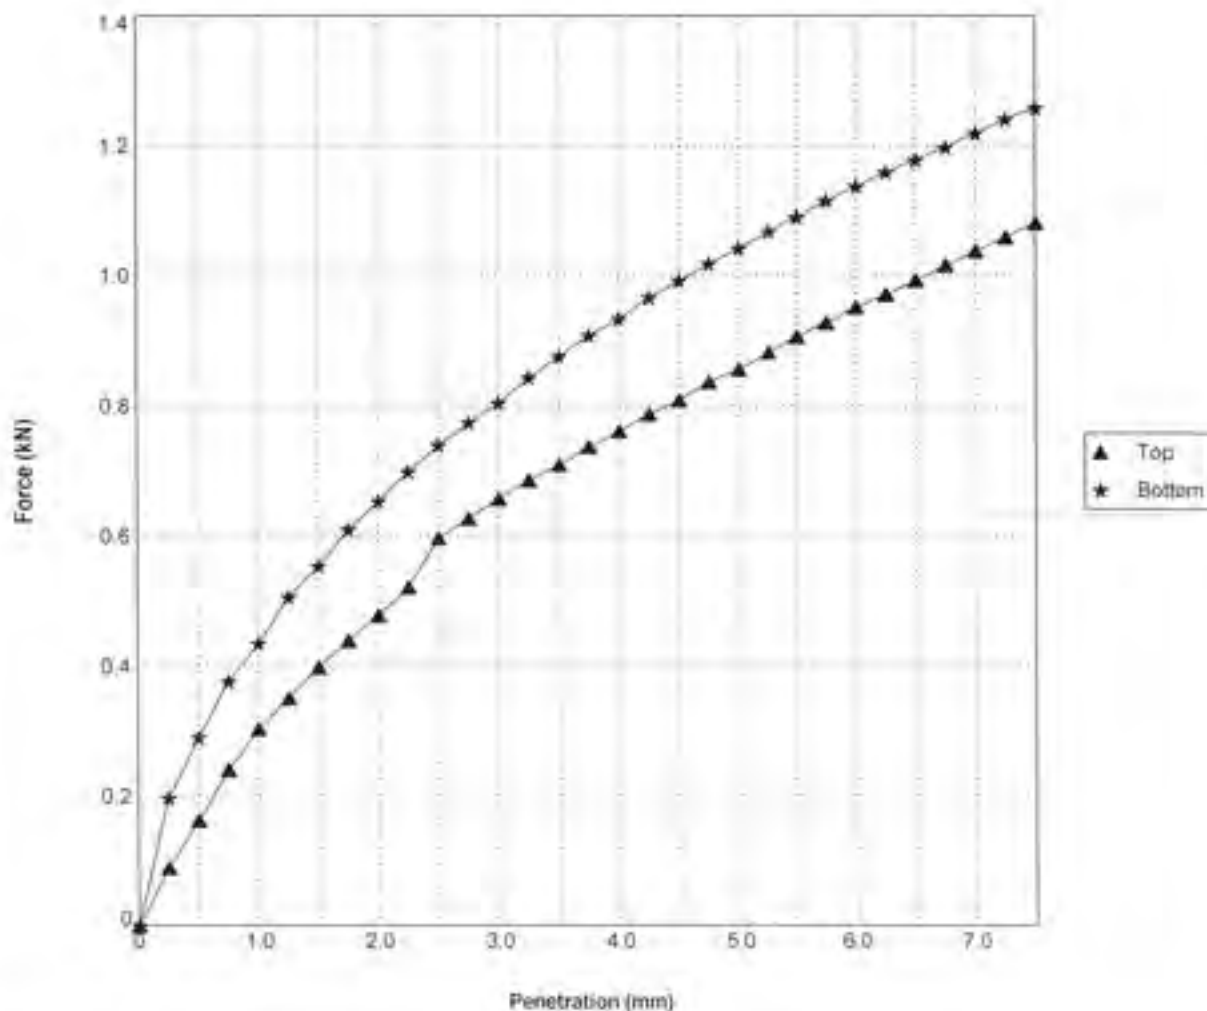

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works	Client :- South Tees Development Corporation
---	--

	Signed :- <i>msore</i>	Name :-	Page 1 of 1
	Date of issue :- 30/10/2020	Certificate No :- CBR/4251/PRAIRIE_AUK_TP116/B5/2 50/1	AEG Contract No :- 4251

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, Salford Industrial Estate, Pinfold Way, Clarendon Street, Co. Durham, DL10 2BQ - Tel: 0191 387 4700 Fax: 0191 387 4716
Regional Office: Unit 20, Business Development Centre, Eastern Wharf, Blakesburg, BS1 5BS - Tel: 01773 735 300 Fax: 01773 733 947


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No.- **PRAIRIE_AUK_TP116** Sample No.- **B10**

Depth (m)- **3.50**

"As Received" Moisture Content (%) :		Surcharge (Kg) :	6
Retained on 20mm (%) :	3.2	Seating Load (N) :	Top 50 / Bottom 50
Correction Needed :	No	Test Moisture Content (%) :	Top 17 / Bottom 17
Soaking Time (Days) :	N/A	Bulk Density (Mg/m ³) :	2.12
Swelling (mm) :	N/A	Dry Density (Mg/m ³) :	1.81
Date Tested :	19/10/2020	CBR Value (%) :	Top 7.4 / Bottom 8.5
Preparation Method :	2.5kg Compaction		
Remarks :			

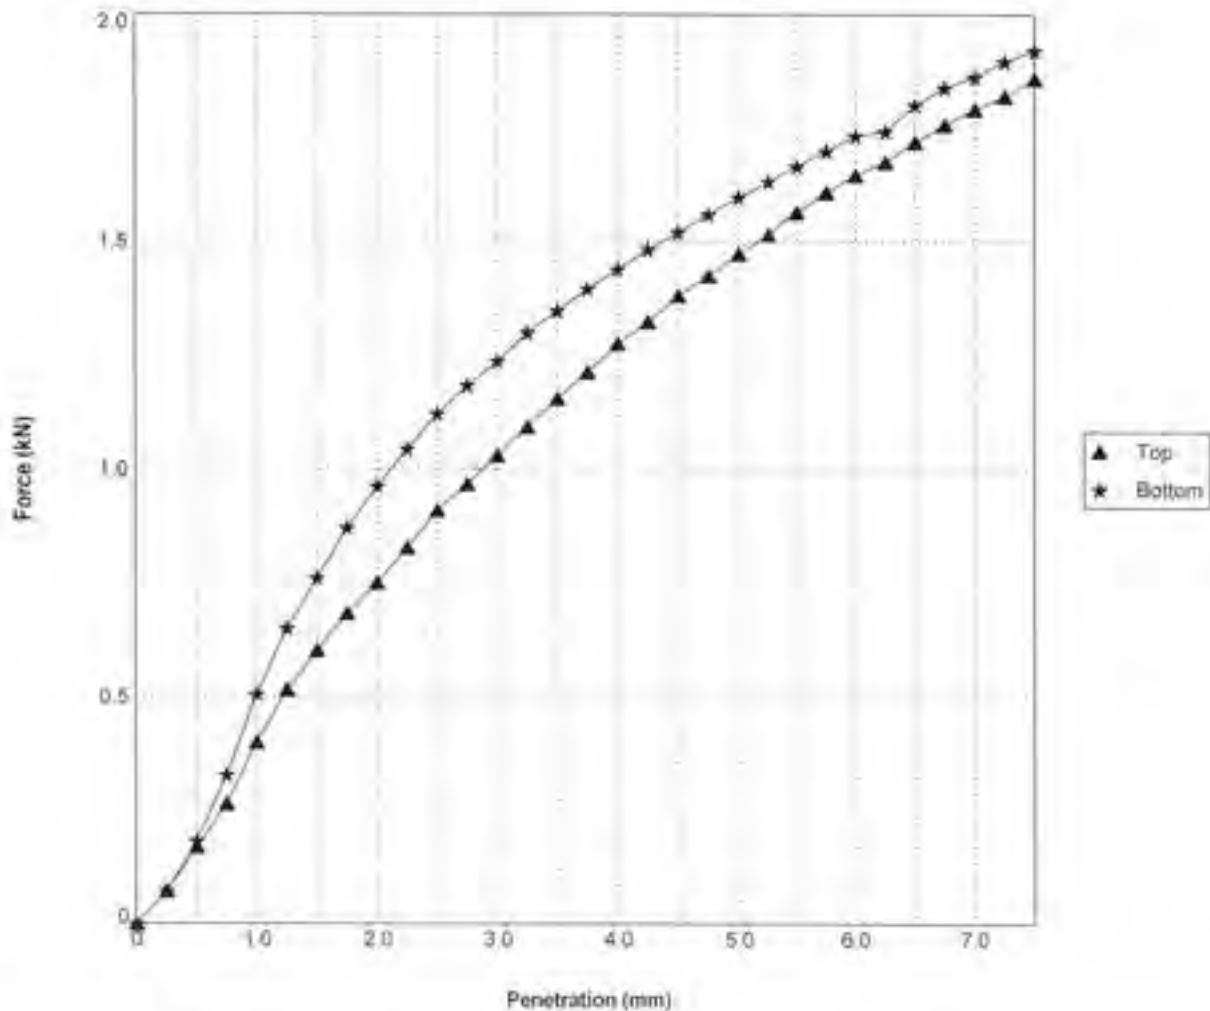

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- **Prairie Site Ground Investigation Works**

Client :- **South Tees Development Corporation**

Signed :- *msero*
Date of issue :- **20/10/2020**

Name :- *[Signature]*
Certificate No :- **CBR/4251/PRAIRIE_AUK_TP116/B10/3/501**

Page 1 of 1
AEG Contract No :- **4251**



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25 Stevia Oil Industrial Estate, Fusion Park, Cleasdale Green, Co. Durham, DN4 2PL - Tel: 0191 340 4700 Fax: 0191 340 4710
Regional Office: Unit 20, Business Development Centre, Salford Wharf, Salford, Greater Manchester, M6 6PU - Tel: 01753 525 300 Fax: 01753 525 305


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 - Part 4 : 1990 and Part 2 : Clause 3.2 : 1990

Exploratory Hole No. - **PRAIRIE_AUK_TP119** Sample No. - **B5**

Depth (m) - **2.00**

"As Received" Moisture Content (%) :		Surcharge (Kg) :	6
Retained on 20mm (%) :	17.0	Seating Load (N) :	Top 250 / Bottom 250
Correction Needed :	No	Test Moisture Content (%) :	Top 11 / Bottom 12
Soaking Time (Days) :	N/A	Bulk Density (Mg/m ³) :	1.90
Swelling (mm) :	N/A	Dry Density (Mg/m ³) :	1.71
Date Tested :	19/10/2020	CBR Value (%) :	Top 54 / Bottom 50
Preparation Method :	2.5kg Compaction		
Remarks :			

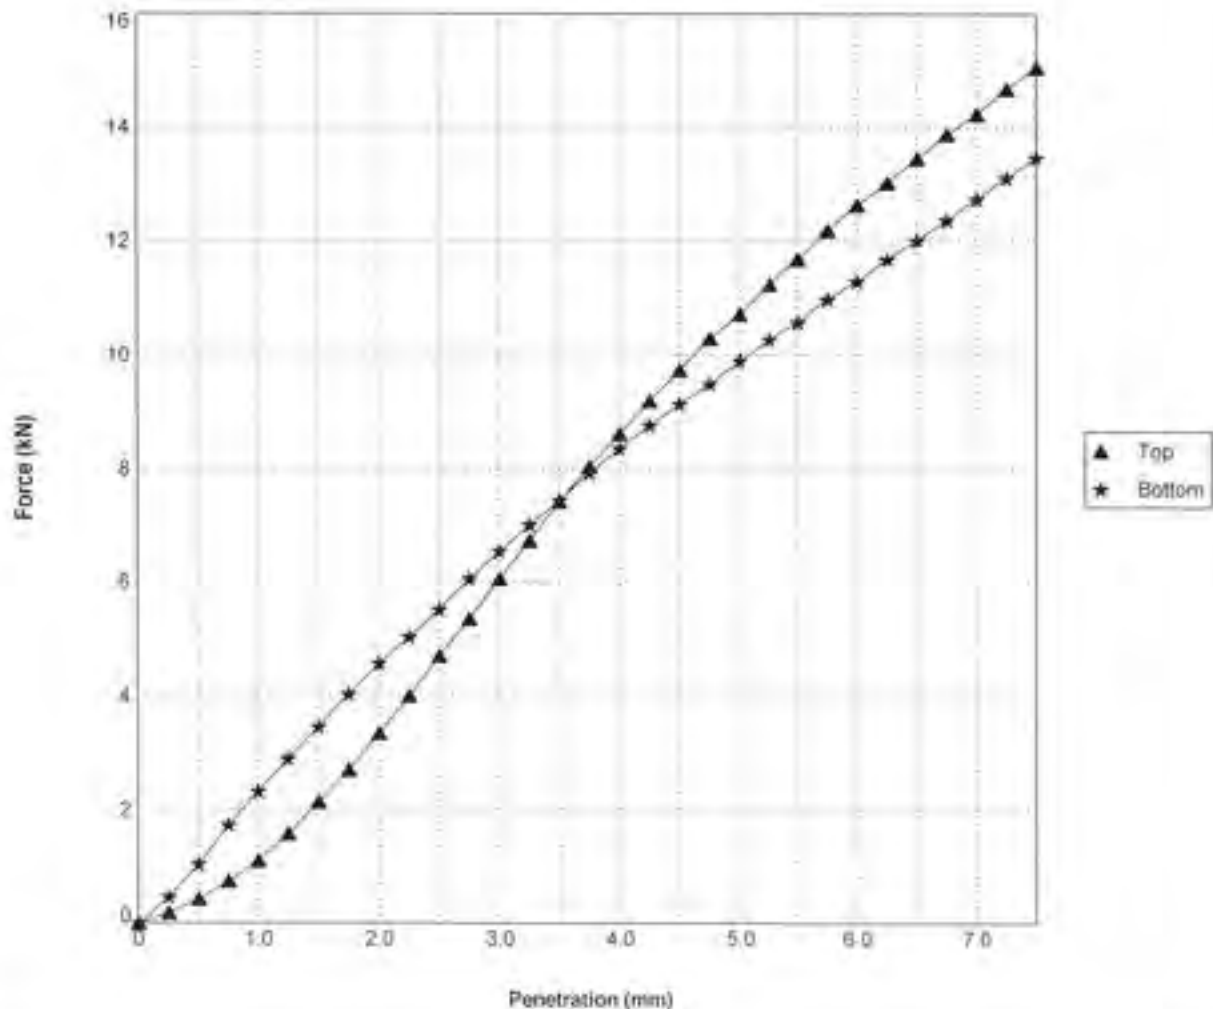

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- **Prairie Site Ground Investigation Works**

Client :- **South Tees Development Corporation**



Signed :- *msene*

Name :-

Page 1 of 1

Date of issue :-
30/10/2020

Certificate No. :-
CBR/4251/PRAIRIE_AUK_TP119/BS/2 00/1

AEG Contract No. :-
4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21, Juncos Gar Industrial Estate, Poyser Way, Chesham, Bucks., UK, Bucks, MK36 2BG - Tel: 01494 357470 Fax: 01494 357471
Regional Office: Unit 21, Business Development Centre, Eamon Wharf, Blackburn, BB1 5BB - Tel: 01524 721285 Fax: 01524 735999


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 : Part 4 : 1990 and Part 2 : Clause 3.2 : 1990

Exploratory Hole No.- **PRAIRIE_AUK_TP119** Sample No. - **B8**

Depth (m)- **3.00**

"As Received" Moisture Content (%) :		Surcharge (Kg) :	6
Retained on 20mm (%) :	0.0	Seating Load (N) :	Top 10 / Bottom 10
Correction Needed :	Yes	Test Moisture Content (%) :	Top 28 / Bottom 29
Soaking Time (Days) :	N/A	Bulk Density (Mg/m ³) :	1.93
Swelling (mm) :	N/A	Dry Density (Mg/m ³) :	1.50
Date Tested :	16/10/2020	CBR Value (%) :	Top 3.5 / Bottom 3.2
Preparation Method :	2.5kg Compaction		
Remarks :			

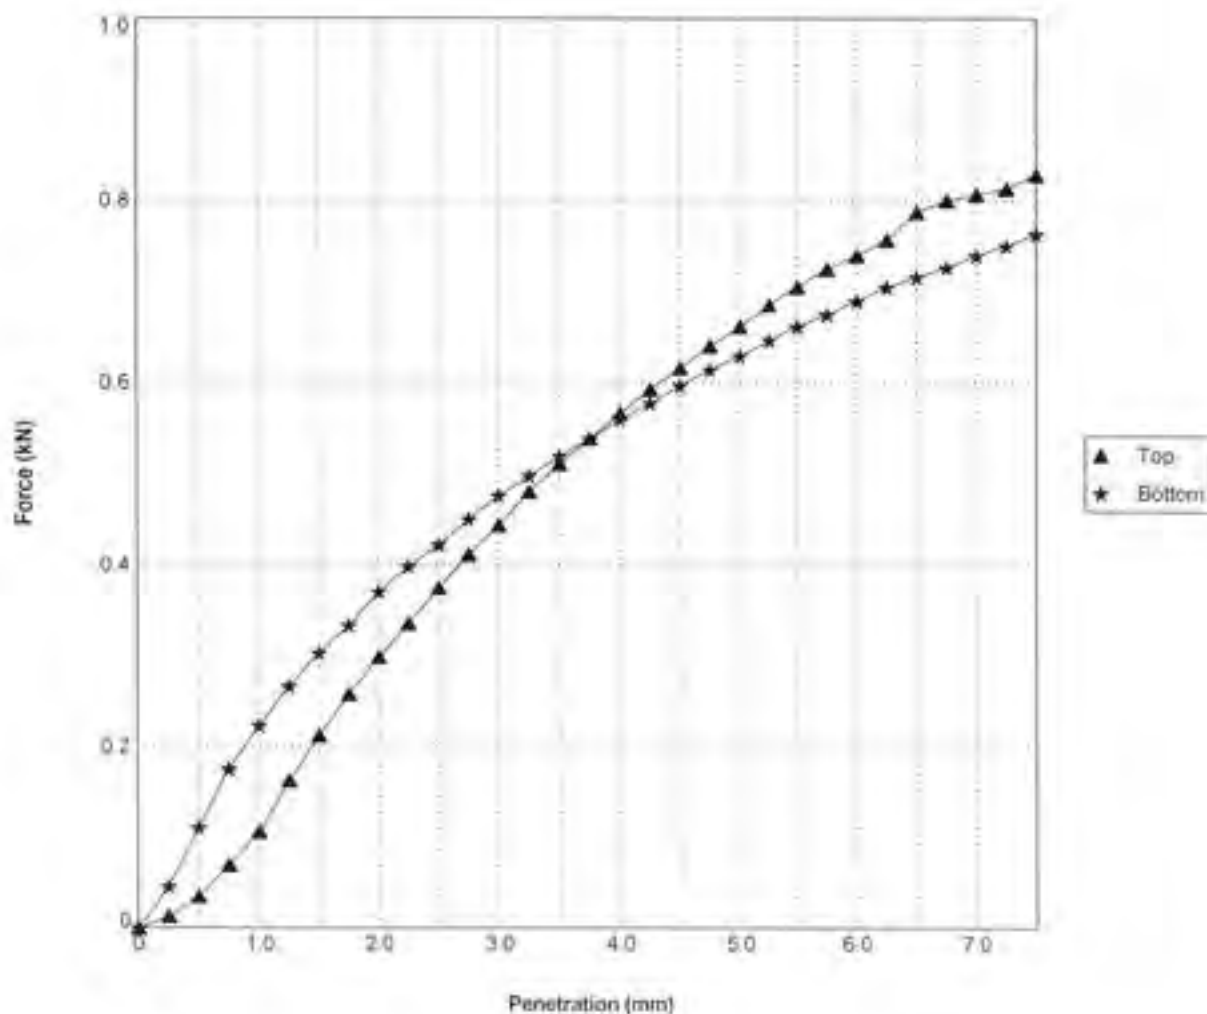

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- **Prairie Site Ground Investigation Works**

Client :- **South Tees Development Corporation**



Signed :- *msero*

Name :-

Page 1 of 1

Date of issue :- **30/10/2020**

Certificate No :- **CBR/4251/PRAIRIE_AUK_TP119/B8/3 00/1**

AEG Contract No. :- **4251**



ALLIED EXPLORATION & GEOTECHNICS LIMITED

(Incorporated in the State of New South Wales, Australia) (Company No. 1170227914/2017)


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1992

Exploratory Hole No - PRAIRIE_AUK_TP120A Sample No - 65

Depth (m) - 1.60

"As Received" Moisture Content (%)		Surcharge (Kg)	6
Retained on 20mm (%)	0.0	Seating Load (N)	Top 10 / Bottom 10
Correction Needed	No	Test Moisture Content (%)	Top 26 / Bottom 25
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.96
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.57
Date Tested	15/10/2020	CBR Value (%)	Top 1.7 / Bottom 1.5
Preparation Method	2.5kg Compaction		
Remarks			

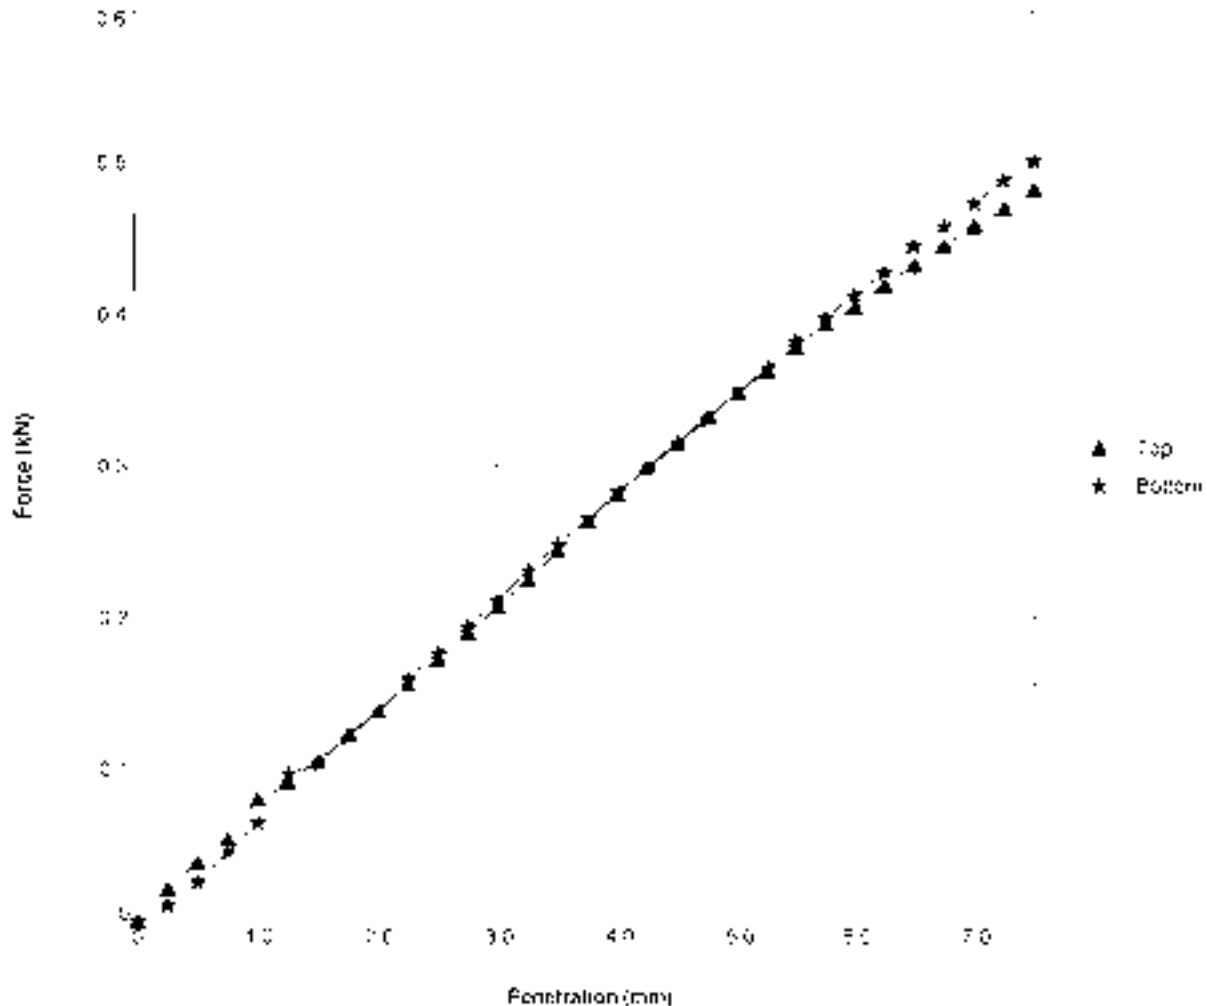

For use only in the sample log, use hole log, the Laboratory Log Sheet or Description Sheet

Contract Title -

Prairie Site Ground Investigation Works

Client -

South Trees Development Corporation



Signature

[Handwritten Signature]

Name

Page 1 of 1

Date of Issue -

15/10/2020

Method of Issue -

CBR 4251 PRAIRIE_AUK_TP120A B11 1514

APR Code of Ref -

4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED


*Allied Exploration & Geotechnics Limited is a registered company in the United Kingdom, registered number 02062411

DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No - **PRAIRIE_AUK_TP121** Sample No - **B2** Depth (m) - **0.80**

"As Received" Moisture Content (%)		Surcharge (Kg)	5
Retained on 20mm: (%)	1.0	Seating Load (N)	Top 250 / Bottom 250
Correction Needed	Yes	Test Moisture Content (%)	Top 14 / Bottom 15
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	2.04
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.78
Date Tested	01/10/2020	CBR Value (%)	Top 70 / Bottom 53
Preparation Method	2.5kg Compaction		
Remarks			

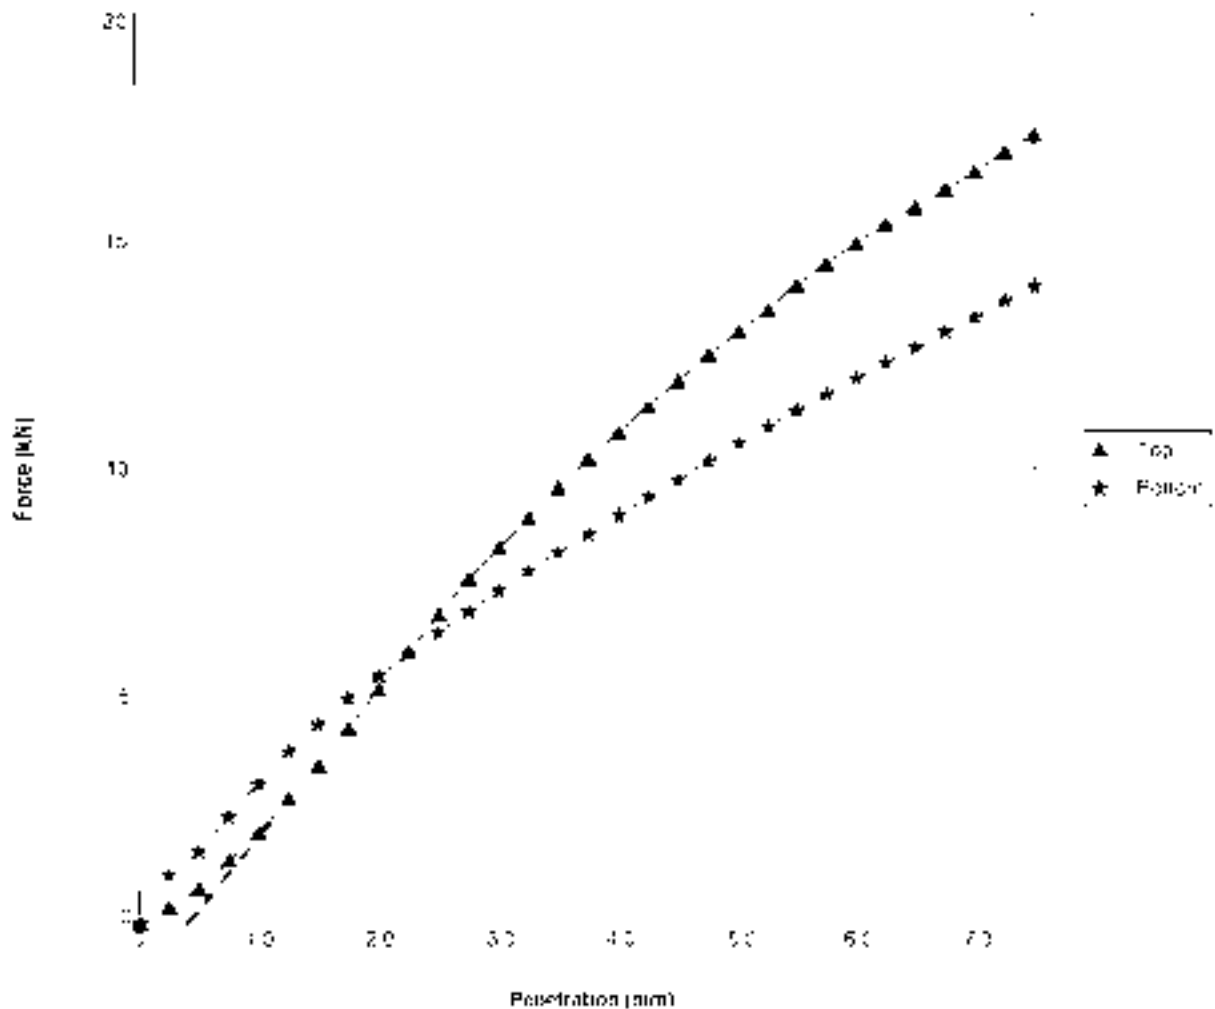

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title -

Prairie Site Ground Investigation Works

South Tees Development Corporation



Signature: *msae*
Date of Issue: 23/10/2020

Reference: GPR 4251
GPR 4251 (B&G) - PRAIRIE_AUK_TP121 (B2) (K1)

Project No: 4251
Allied Contract No: 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

(Incorporated in the United Kingdom) (Registered Office: 100, Victoria Road, Wigan, Lancashire, WN1 1LH, UK)


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.7: 1990

Exploratory Hole No - PRAIRIE_AUK_TP131 Sample No - B10

Depth Int: 3.60

"As Received" Moisture Content (%)		Surcharge (Kg)	9
Retained on 20mm (%)	0.0	Sealing Load (N)	Top 10 / Bottom 10
Correction Needed	No	Test Moisture Content (%)	Top 28 / Bottom 27
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.93
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.52
Date Tested	01/10/2020	CBR Value (%)	Top 4.6 / Bottom 4.9
Preparation Method	2.5kg Compaction		
Remarks			

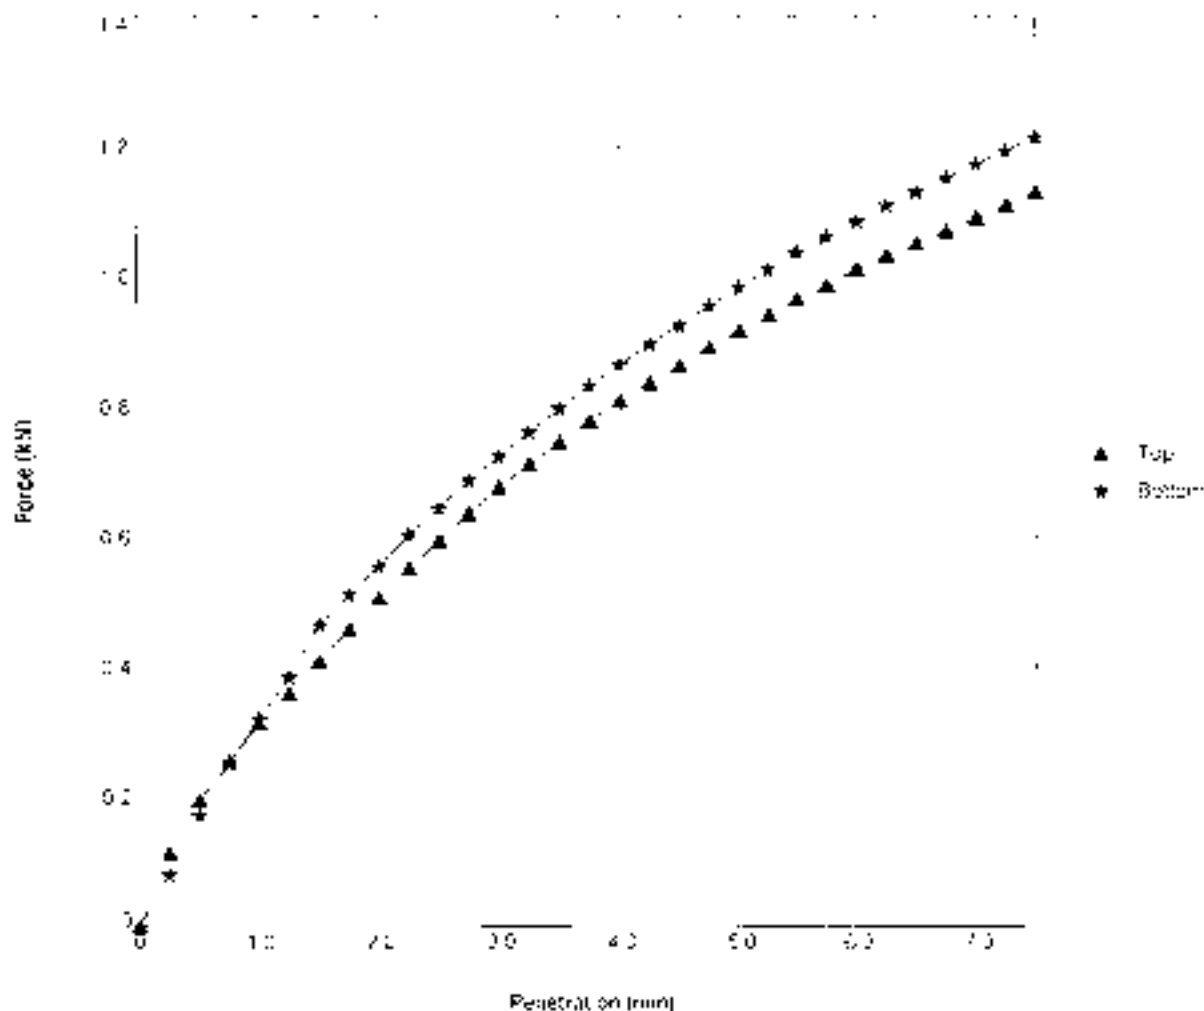

For description of test, please refer to the Laboratory Sample Order form Sheet

Customer File

Prairie Site Ground Investigation Works

South Tees Development Corporation



Serial

meane

Name

File Ref

Date of Issue

01/10/20

Customer Ref

CBR ADAPTATION AUK TP131 B10 3.60

ACR Control No

4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No - PRAIRIE_AUK_TP137 Sample No - B7

Depth (m) - 2.00

"As Received" Moisture Content (%)		Surcharge (Kg)	6
Retained on 20mm (%)	0.0	Seating Load (N)	Top 10 / Bottom 10
Correction Needed	No	Test Moisture Content (%)	Top 28 / Bottom 27
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.92
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.51
Date Tested	15/10/2020	CBR Value (%)	Top 0.72 / Bottom 0.58
Preparation Method	2.5kg Compaction		
Remarks			

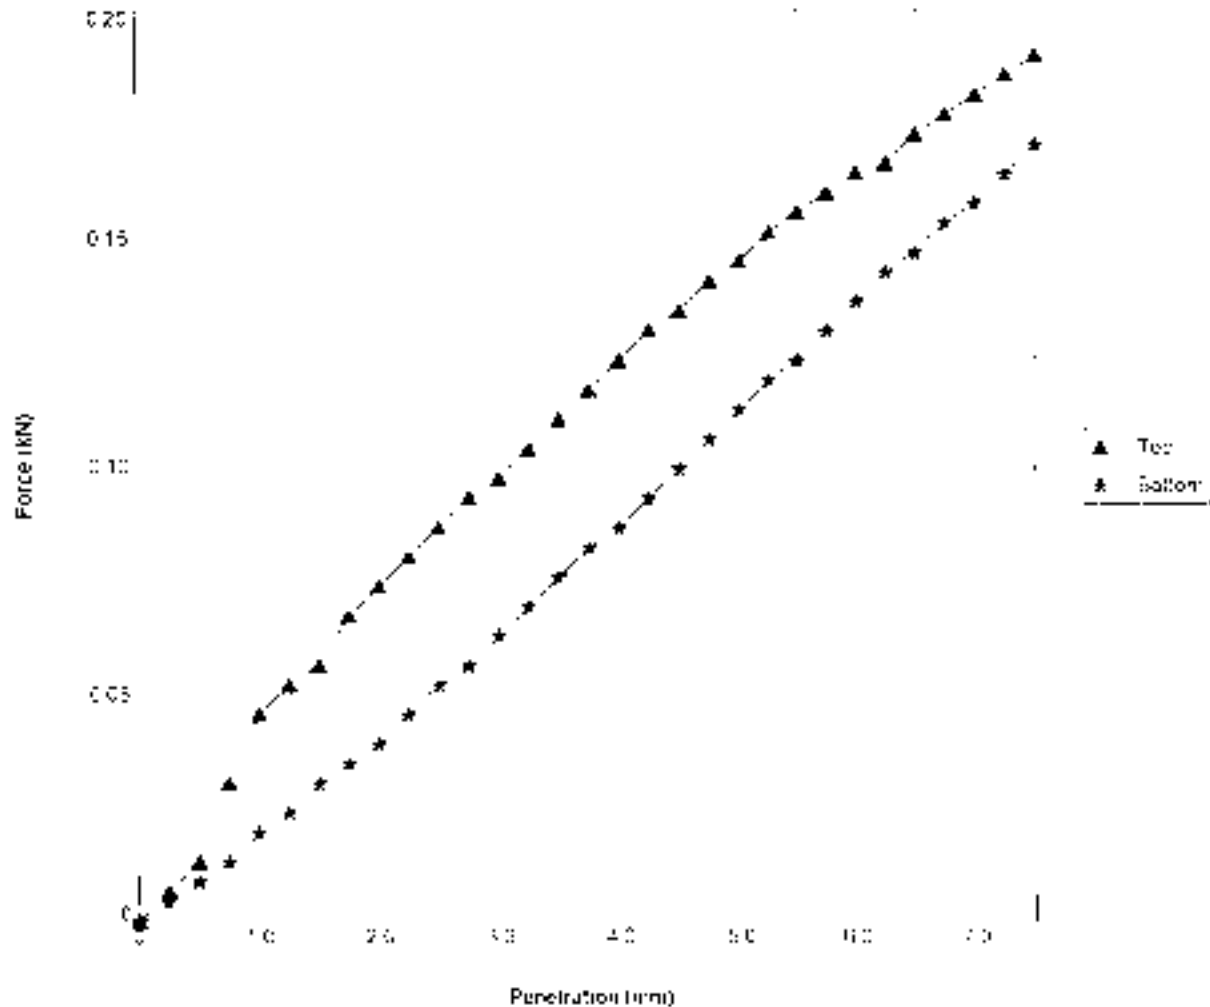

For full details of sample, please refer to the Laboratory Sample Description sheet

Company Name

Prairie Site Ground Investigation Works

Client

South Tees Development Corporation



Project

Date of Issue

21/10/2020

msw

Name

Investigator

2019-2020-2021 AUK TP137 - 15/10/2020

Page 1 of 1

As per Contract No.:

4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED


1000 Highway 101, Suite 100, Oakville, Ontario L6M 1H2, Canada
 Telephone: (905) 846-8888 Fax: (905) 846-8889 Email: info@allied-eg.com

DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause A2: 1990

Exploratory Hole No. **PRAIRIE_AUK TP145** Sample No. - **B6** Depth (m) - **2.40**

"As Received" Moisture Content (%)		Surcharge (Kg)	6
Retained on 20mm (%)	0.0	Sealing Load (N)	Top 10 / Bottom 10
Correction Needed	No	Test Moisture Content (%)	Top 24 / Bottom 25
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	2.09
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.08
Date Tested	30/09/2020	CBR Value (%)	Top 5.9 / Bottom 6.7
Preparation Method	2.5kg Compaction		
Remarks			

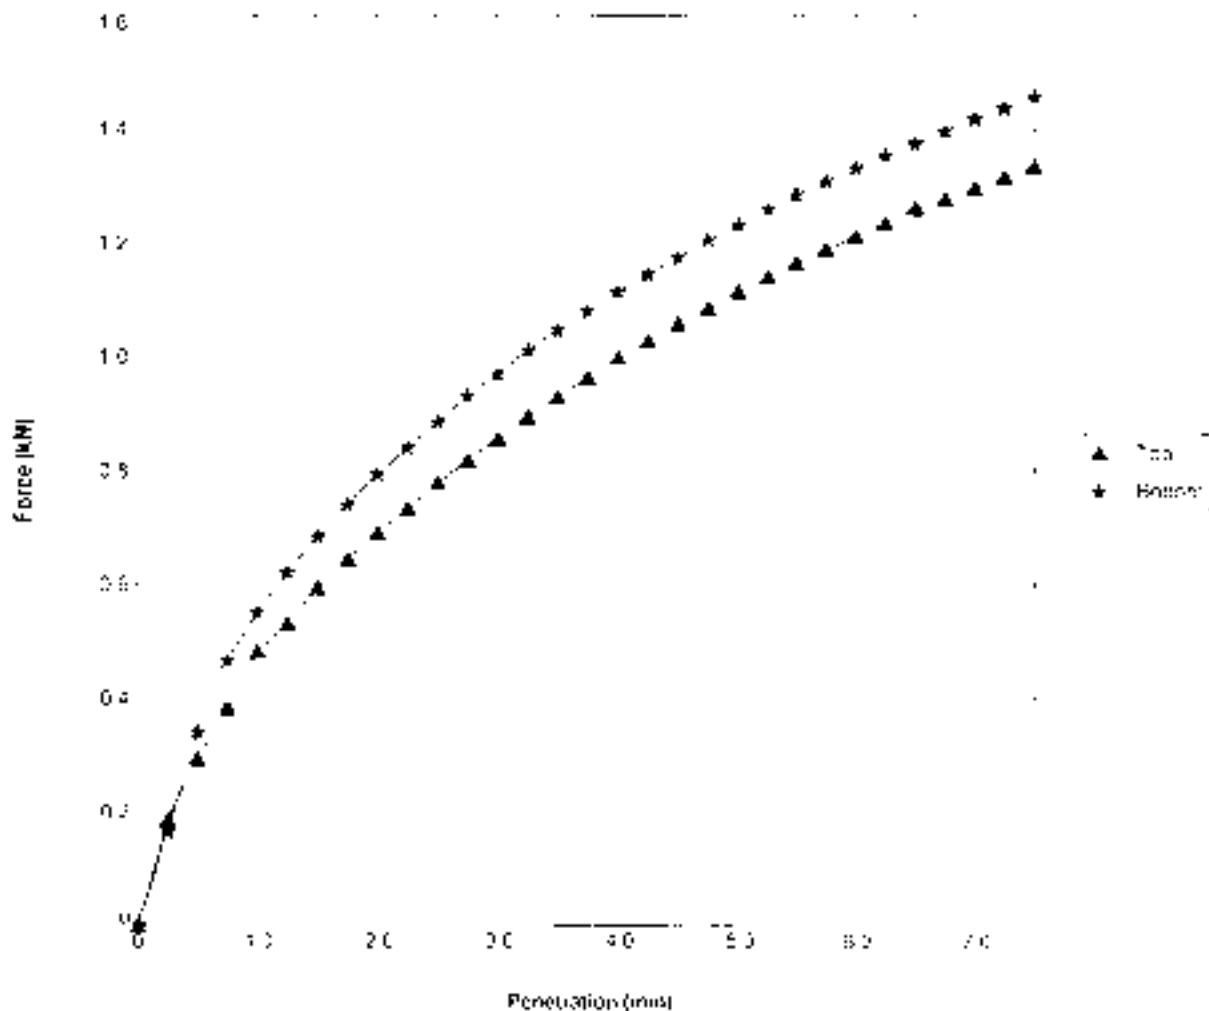

For determination of sample moisture refer to the Laboratory Sample Description Sheet

Contract Title:

Prairie Site Ground Investigation Works

Client:

South Tees Development Corporation



Agreed:

M. Sore

Page 1 of 1

Date of Issue:

28/10/2020

Call Reference:

0094281774-905-AUK-TP145-06-0401

Accession No:

4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

REGISTERED IN ENGLAND AND WALES COMPANY NO. 03182800
 REGISTERED OFFICE: 11, THE SQUARE, SOUTHAM, RUGBY, CV40 3JF


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No - PRAIRIE_AUK_TP146CSample No **B6**

Depth (m): **1.30**

"As Received" Moisture Content (%)		Surcharge (Kg)	5
Retained on 20mm (%)	14.0	Seating Load (N)	Top 250 / Bottom 250
Correction Needed	No	Test Moisture Content (%)	Top 24 / Bottom 24
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.98
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.60
Date Tested	02/10/2020	CBR Value (%)	Top 13 / Bottom 21
Preparation Method	2.5kg Compaction		
Remarks			

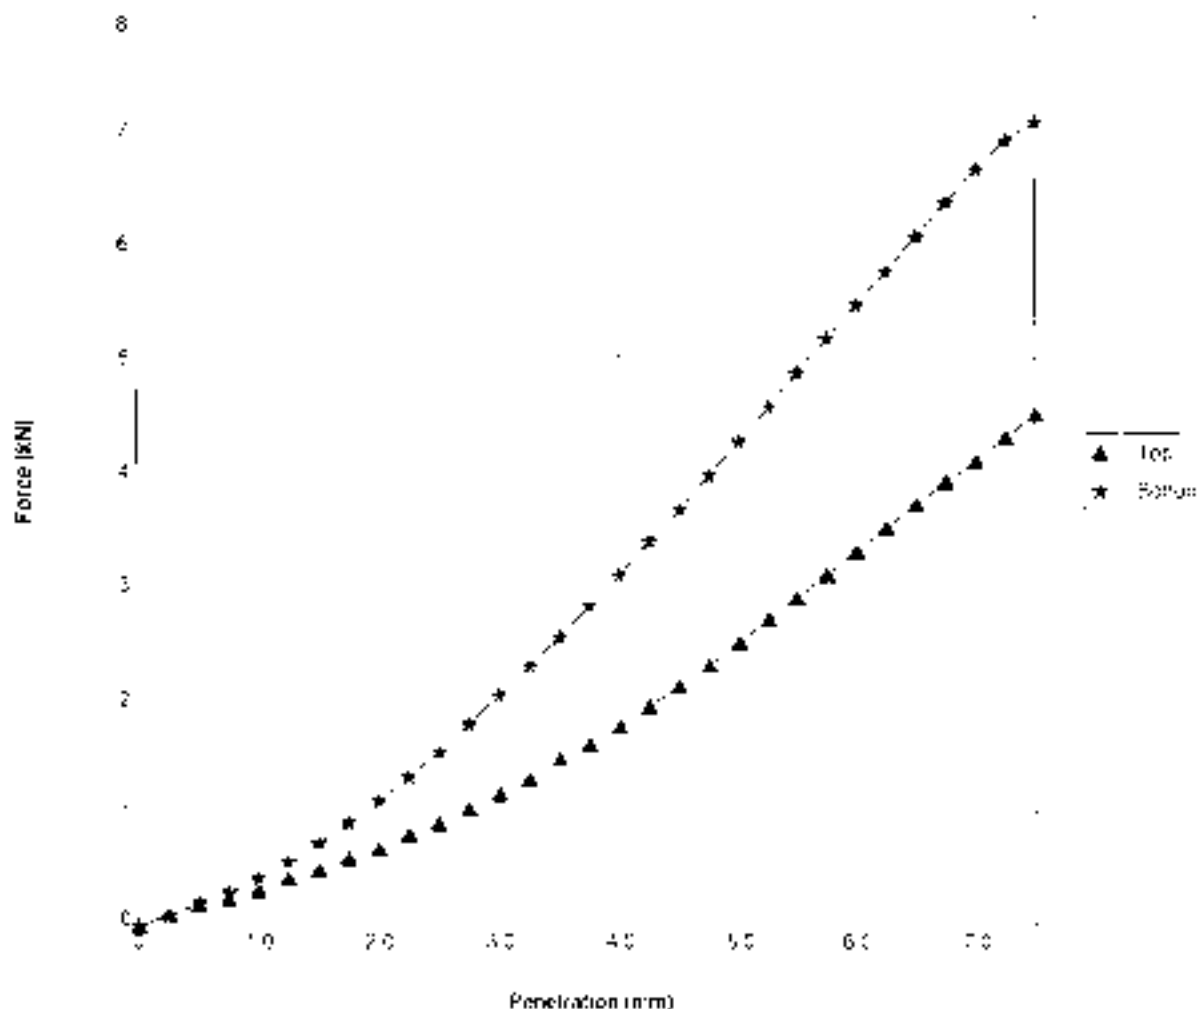

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title

Prairie Site Ground Investigation Works

Client

Sixth Tees Development Corporation



Signed

M. S. ...

Name

Page 1 of 1

Date of Issue

02/10/2020

Drawn by

CBR 401 PRAIRIE_AUK_TP146C (B6) (1)

Test Reference

4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

REGISTERED IN ENGLAND AND WALES COMPANY NO. 02042888
 REGISTERED OFFICE: 100, WILSON ROAD, SOUTH TREES, LEEDS, WEST YORKSHIRE, LS16 7JG


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No. **PRAIRIE AUK TP146C** Sample No. - **B8**

Depth (m): **2.30**

"As Received" Moisture Content (%)		Surcharge (Kg)	6
Retained on 20mm (%)	0.0	Seating Load (Ni)	Top 50 / Bottom 50
Correction Needed	No	Test Moisture Content (%)	Top 23 / Bottom 23
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	2.30
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.63
Date Tested	01/10/2020	CBR Value (%)	Top 5.2 / Bottom 10
Preparation Method	2.5kg Compaction		
Remarks			

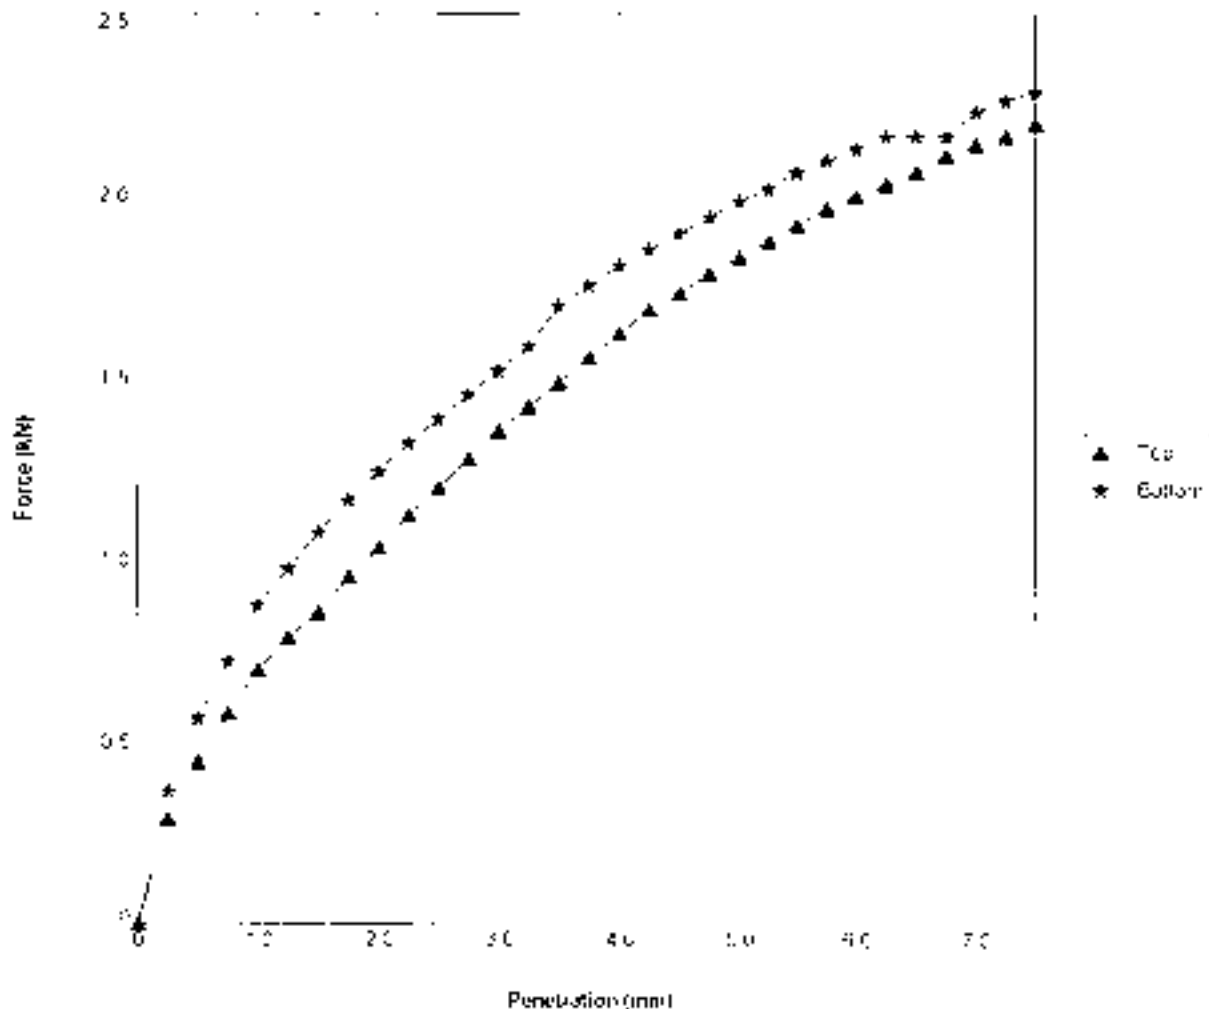

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title

Prairie Site Ground Investigation Works

South Trees Development Corporation



Report No.

Date of Issue

msore
 03/10/2020

Name

Contract No.

00740-146A-TP146C-SUB-0023

Page 1 of 1

Reference No.

4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25 Brinkley Industrial Estate, Farnley Park, Chester-le-Street, Co. Durham, DH8 2PL. Tel: 0191 261 4770 Fax: 0191 261 4743
Regional Office: Unit 21, Blundell Development Centre, Easing Wharf, Ewelham, West Yorkshire, WF1 5BL. Tel: 01752 735 300 Fax: 01752 735 288


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 : Part 4 : 1990 and Part 2 : Clause 3.2 : 1990

Exploratory Hole No. - PRAIRIE_AUK_TP149 Sample No. - B5

Depth (m) - 2.20

"As Received" Moisture Content (%) :		Surcharge (Kg) :	6
Retained on 20mm (%) :	0.0	Seating Load (N) :	Top 10 / Bottom 10
Correction Needed :	No	Test Moisture Content (%) :	Top 29 / Bottom 30
Soaking Time (Days) :	N/A	Bulk Density (Mg/m ³) :	1.92
Swelling (mm) :	N/A	Dry Density (Mg/m ³) :	1.49
Date Tested :	16/10/2020	CBR Value (%) :	Top 2.9 / Bottom 2.6
Preparation Method :	2.5kg Compaction		
Remarks :			

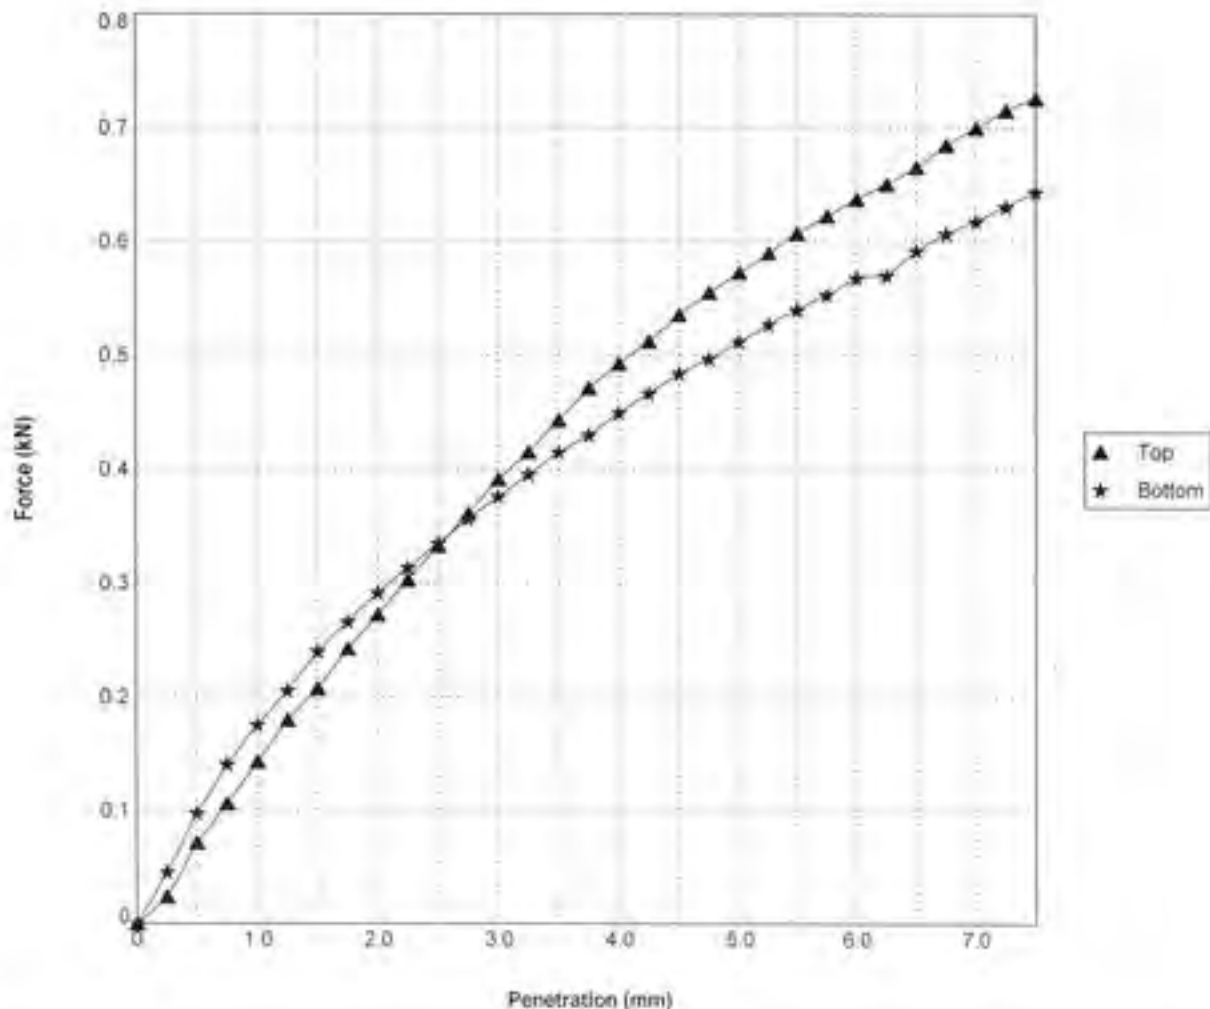

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works

Client :- South Tees Development Corporation



Signed :- *msere*

Name :-

Page 1 of 1

Date of issue :- 30/10/2020

Certificate No. :- CBR/4251/PRAIRIE_AUK_TP149/B5/2.20/1

AEG Contract No. :- 4251




ALLIED EXPLORATION & GEOTECHNICS LIMITED

DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 12: 1990

Exploratory Hole No - PRAIRIE_ADK_TP152 Sample No - B6 Depth (m) - 2.50

"As Received" Moisture Content (%)		Surcharge (Kg)	5
Retained on 20mm (%)	0.0	Sealing Load (N)	Top 10 / Bottom 10
Correction Needed	No	Test Moisture Content (%)	Top 31 / Bottom 30
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.90
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.45
Date Tested	29/09/2020	CBR Value (%)	Top 1.8 / Bottom 1.8
Preparation Method	2.5kg Compaction		
Remarks			

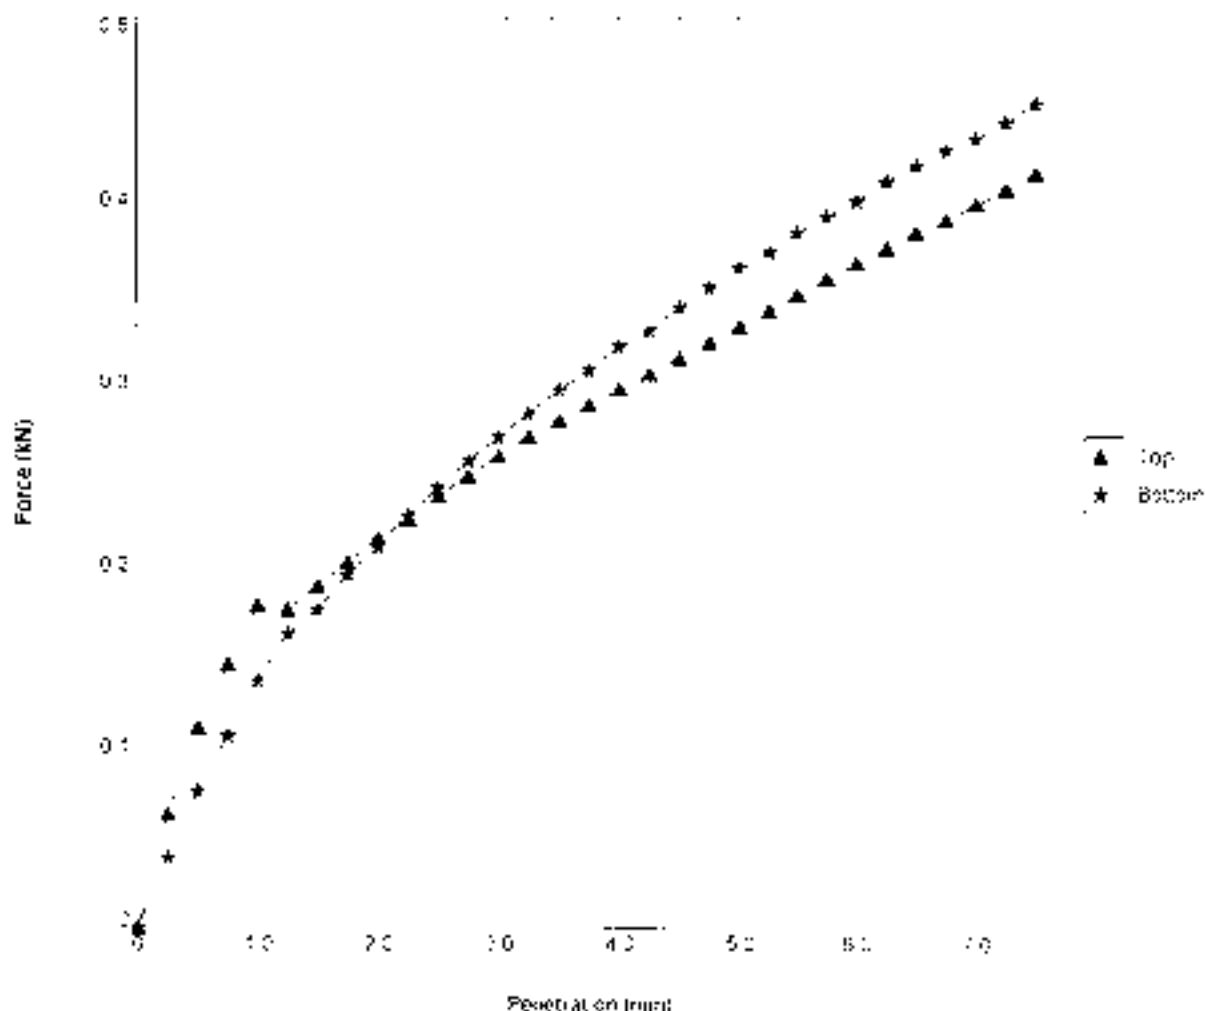

For description of symbols and procedure refer to the Laboratory Sample Description Sheet

Contract Title -

Prairie Site Ground Investigation Works

Client -

Southern Cross Development Corporation



Supervisor

M. Moore

Date of Issue -

09/10/2020

Tester

Certificate No -

JBR 4251 PRAIRIE_ADK_TP152_B6

Tester

Lab. Reference No -

4251

Page 2 of 2



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Registered Office: 100, Victoria Road, South Shields, Tyne and Wear, NE33 1JF, UK


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No - PRAIRIE_AUK_TP163 Sample No - B2

Depth (m) - 0.80

"As Received" Moisture Content (%)		Surcharge (Kg)	5
Retained on 20mm (%)	14.0	Sealing Load (N)	Top 50 / Bottom 50
Correction Needed	No	Test Moisture Content (%)	Top 14 / Bottom 14
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.37
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.20
Date Tested	05/10/2020	CBR Value (%)	Top 39 / Bottom 64
Preparation Method	2.5kg Compaction		
Remarks			

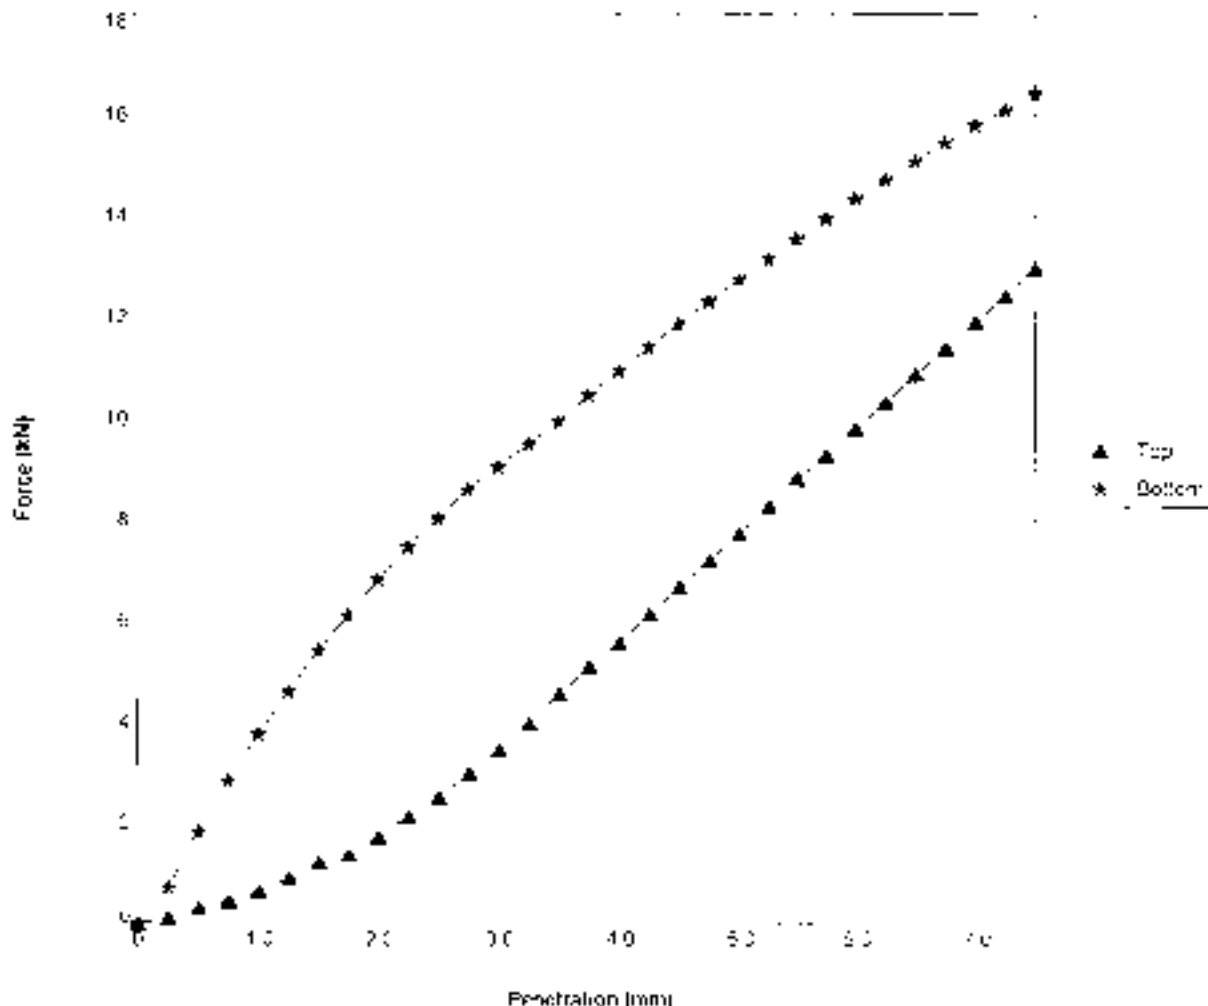

For full description of sample please refer to the Laboratory Sample Description sheet.

Contract Title:

Prairie Site Ground Investigation Works

Client:

South Tees Development Corporation



Signed:

msaw

Name:

Page 1 of 1

Date Issued:

04/10/2020

Certificate No.:

CBR4201/PRAIRIE_AUK_TP163/B2/0201

AEG Certificate No.

4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED


Registered in England, No. 02062012, Limited by Guarantee, Registered Office: 10, The Quadrant, Southport, Merseyside, L35 9DF

DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No - PRAIRIE_AUK_TP163 Sample No - B5 Depth (m)- 1.70

As Received Moisture Content (%)		Surcharge (Kg)	5
Retained on 20mm (%)	0.0	Sealing Load (N)	Top 10 / Bottom 10
Correction Needed	No	Test Moisture Content (%)	Top 27 / Bottom 27
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.99
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.57
Date Tested	01/10/2020	CBR Value (%)	Top 1.9 / Bottom 1.8
Preparation Method	2.5kg Compaction		
Remarks			

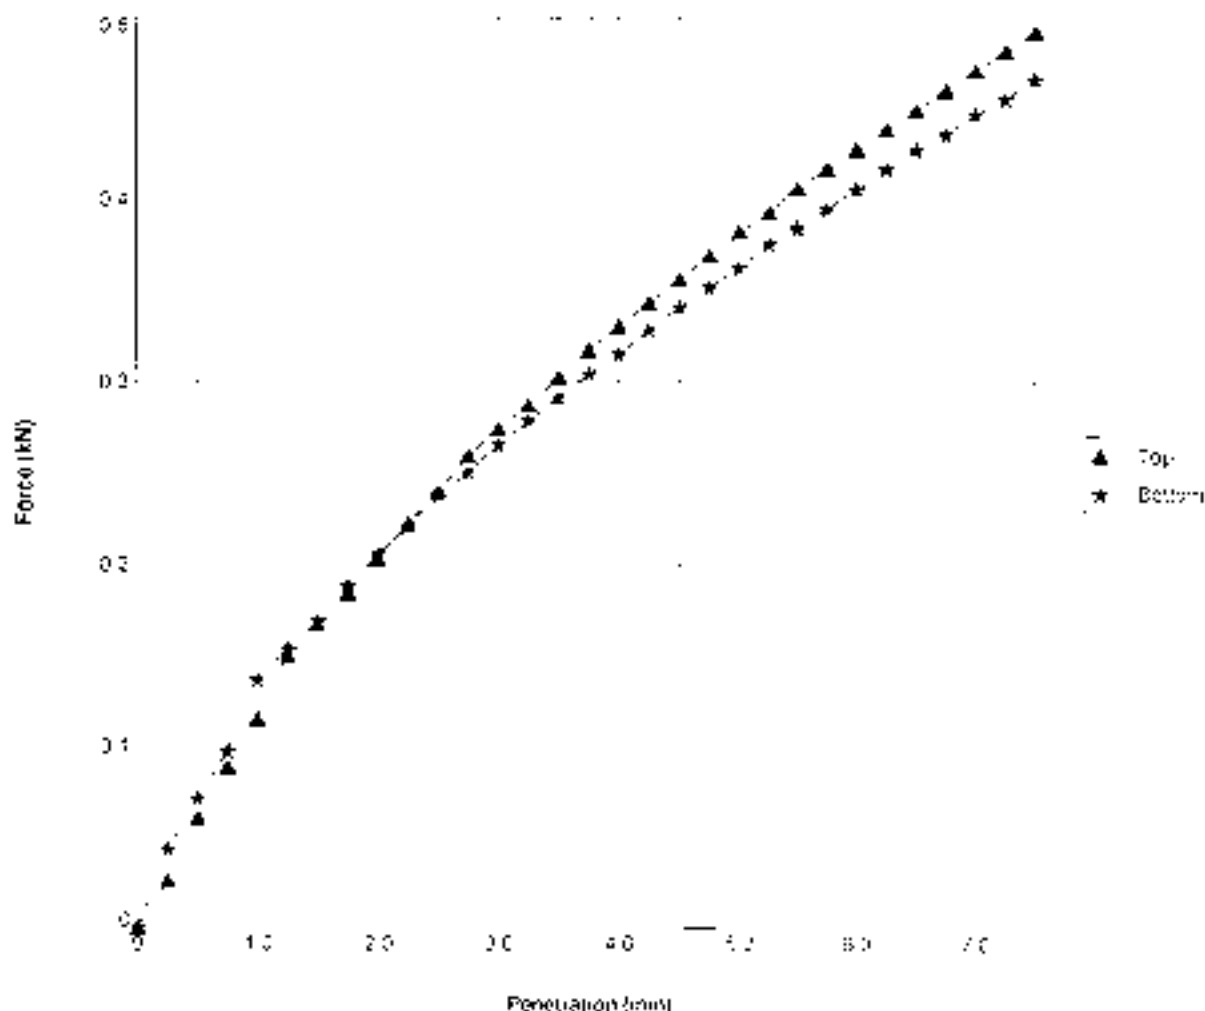

For determination of sample results refer to the Laboratory Report Description Sheet

Manufacturer:

Frame Site Ground Investigation Works

Client:

South Tees Development Corporation



Signed:

Date Tested:

01/10/2020

msgro

Name:

Geotechnical

CPN 4251 PRAIRIE_AUK_TP163 B5 1.70

Report No.:

AEG Report No.:

4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.7: 1990

Exploratory Hole No - PRAIRIE_AUK_TP168 Sample No - B7

Depth (m) - 1.60

As Received Moisture Content (%)		Surcharge (Kg)	8
Retained on 20mm (%)	0.0	Sealing Load (N)	Top 10 / Bottom 10
Correction Needed	No	Test Moisture Content (%)	Top 29 / Bottom 33
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.92
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.48
Date Tested	30/09/2020	CBR Value (%)	Top 2.7 / Bottom 2.3
Preparation Method	2.5kg Compaction		
Remarks			

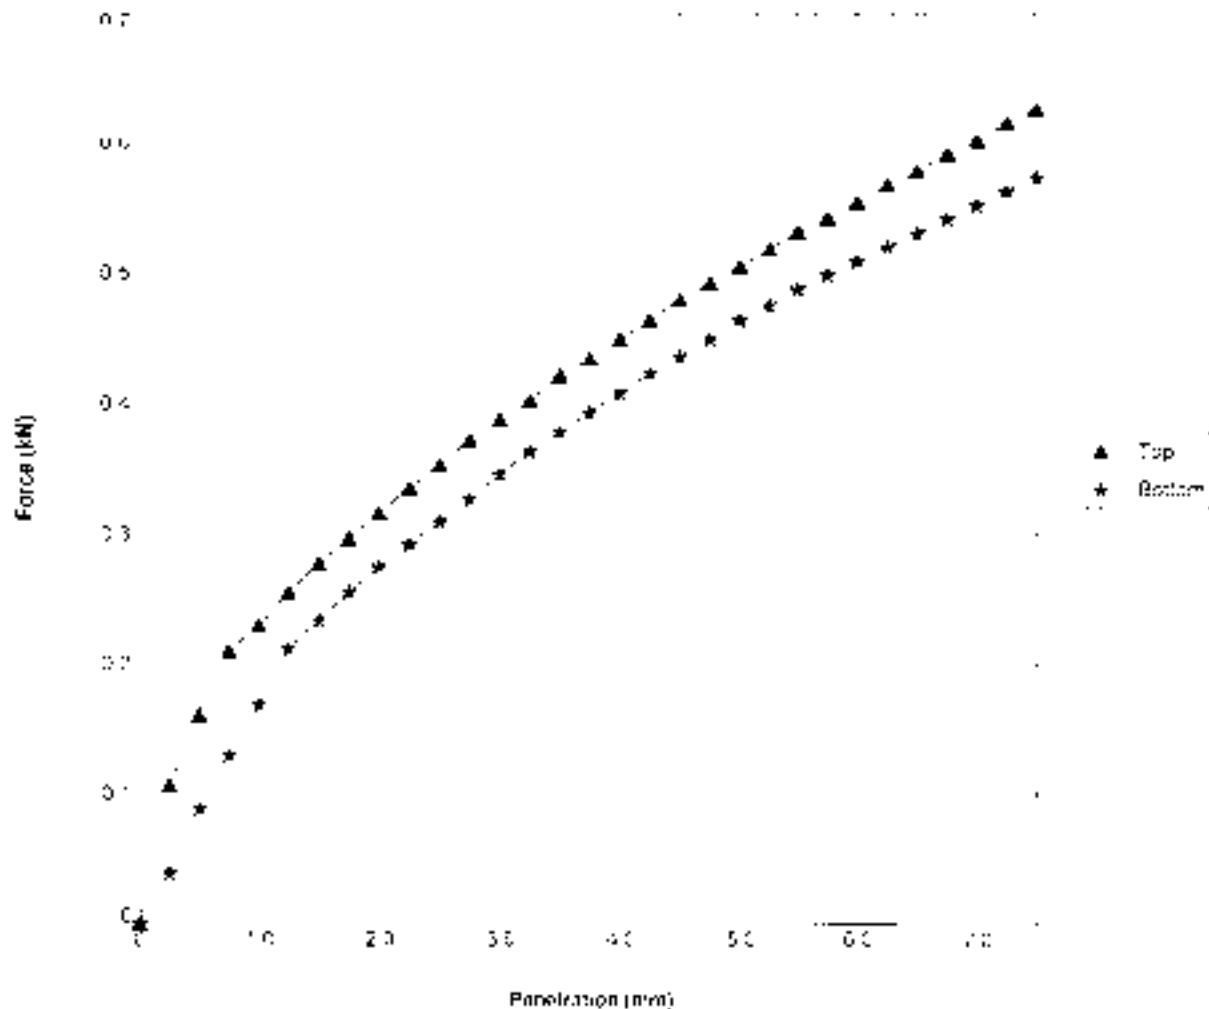

For description of sample please refer to the Laboratory Sample Description sheet

Company Name -

Prairie Site Ground Investigation Works

Client

South Tees Development Corporation



Signed *msoane*
 Date of Issue 30/09/2020

Name
 Location File
 PRAIRIE_AUK_TP168_B7_168

Project No
 AEG Control No
 4251




1367

DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.7: 1990

Exploratory Hole No - **PRAIRIE AUX TP173** Sample No - **B2** Depth (m) - **0.80**

"As Received" Moisture Content (%)		Surcharge (Kg)	6
Retained on 20mm (%)	22.0	Sealing Load (N)	Top 250 / Bottom 250
Correction Needed	No	Test Moisture Content (%)	Top 20 / Bottom 20
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.77
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.48
Date Tested :	30/09/2020	CBR Value (%)	Top 38 / Bottom 33
Preparation Method	2.5kg Compaction		
Remarks			

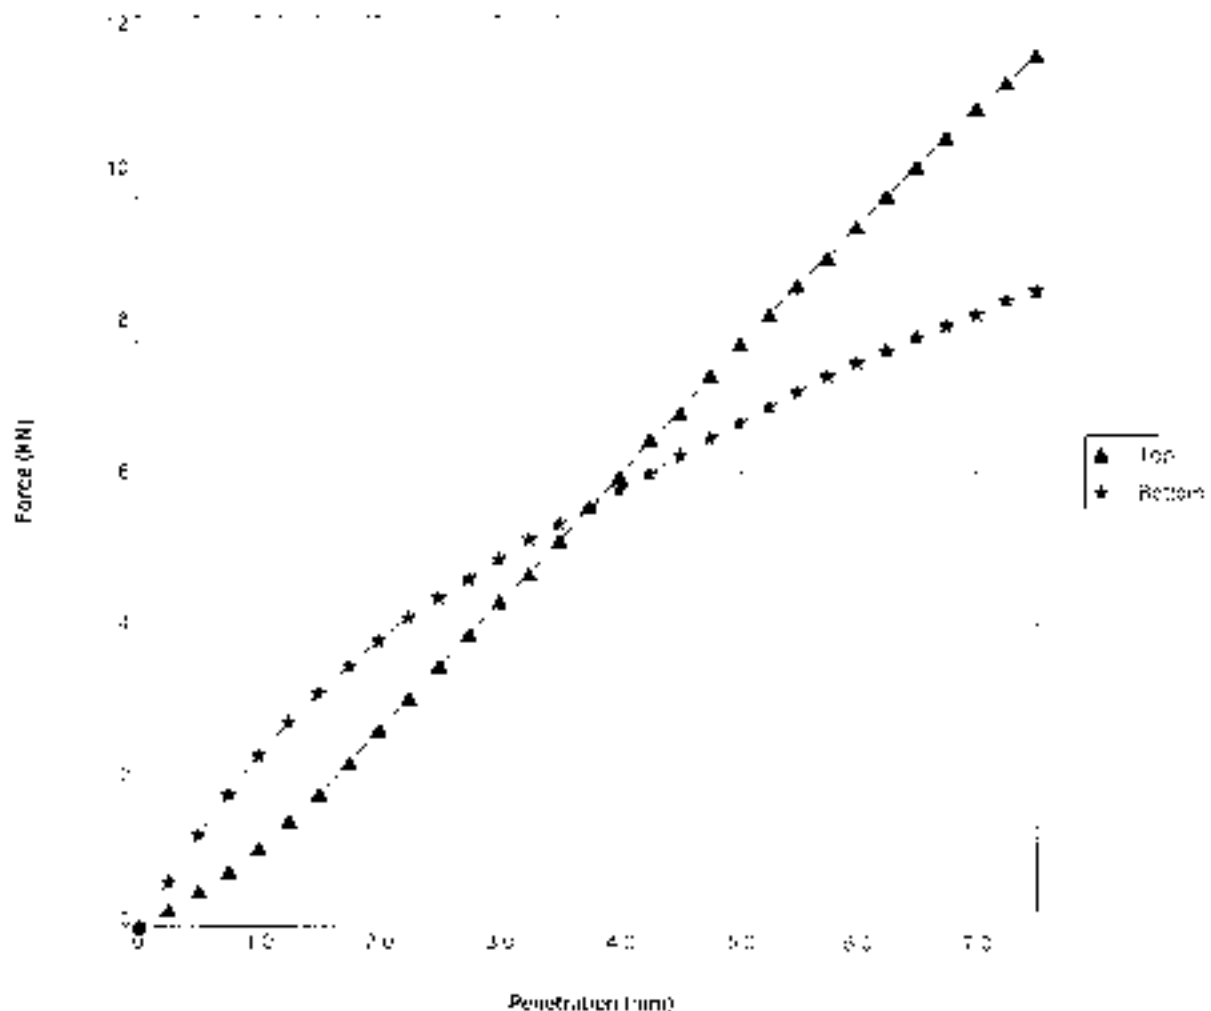

For verification of sample phase refer to the Laboratory Sample Description Sheet

Contract Title: **Prairie Site Ground Investigation Works** Location: **South Tees Development Corporation**



Signature: *[Handwritten Signature]*
 Date of Issue: **30/10/2020**

Name: **CBR 4251**
 Description: **CBR 4251 PRAIRIE AUX TP173 B2**

Page: **1 of 1**
 Job Reference: **4251**



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Method: BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1990


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No - PRAIRIE_AUK_TP176 Sample No - B5

Depth (m) - 2.00

"As Received" Moisture Content (%)		Surcharge (Kg)	8
Retained on 20mm (%)	0.0	Sealing Load (N)	Top 10 / Bottom 10
Correction Needed	No	Test Moisture Content (%)	Top 26 / Bottom 25
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.97
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.55
Date Tested	29/09/2020	CBR Value (%)	Top 1.7 / Bottom 1.6
Preparation Method	2.5kg Compaction		
Remarks			

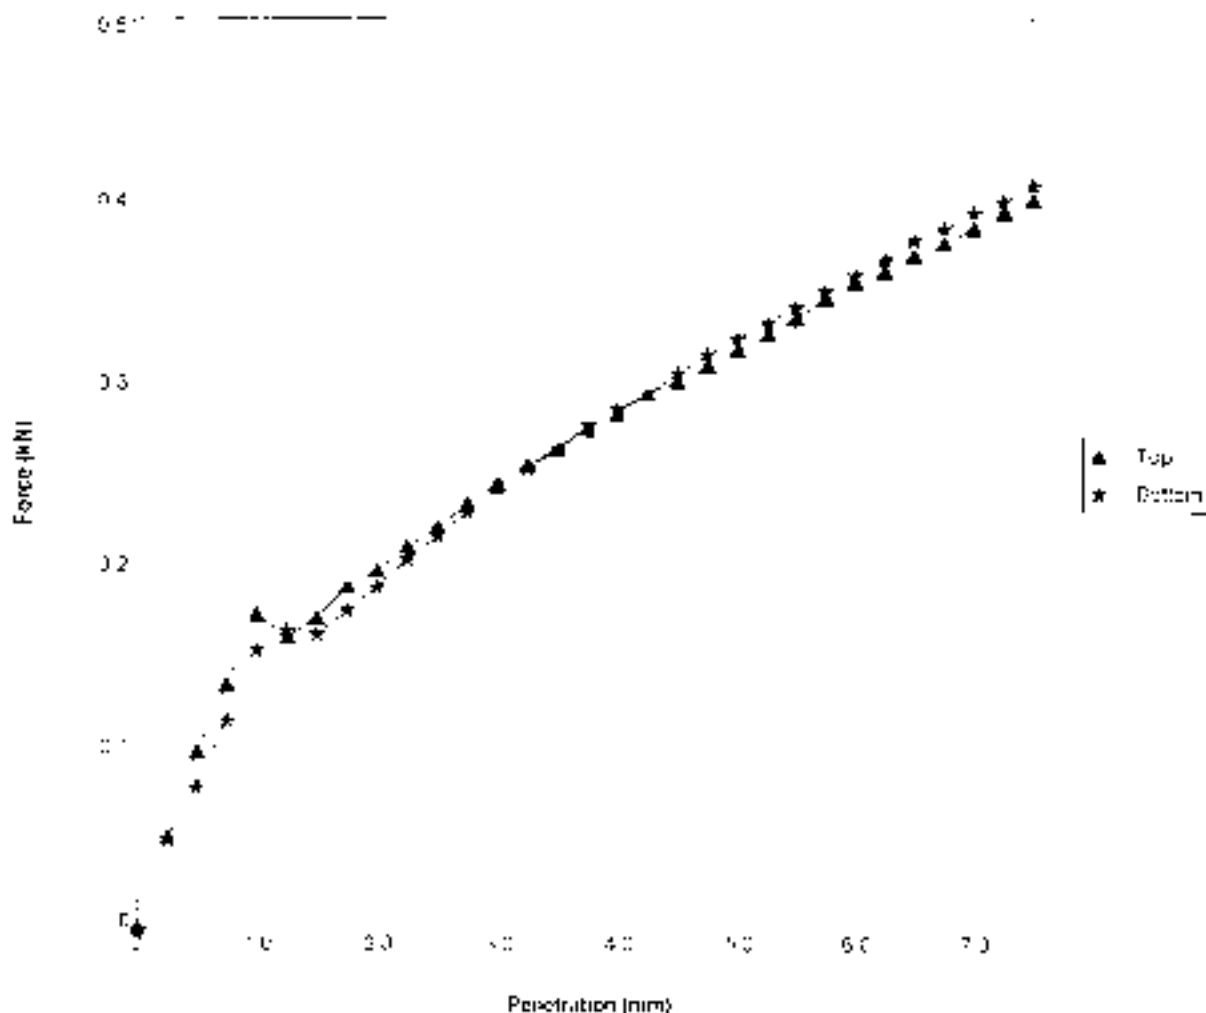

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title

Prairie Site Ground Investigation Works

Client

South Tynes Development Corporation



Author

msene

Name

Page 1 of 1

Date of Issue

23/10/2020

Client Ref No

Contract Ref: PRAIRIE_AUK_TP176-05-02

Associated File No

4251



1357

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Registered in England and Wales, No. 02052987, Registered Office: 100, Victoria Road, Bournemouth, Dorset, BH1 1JF


DÉTERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.7: 1990

Exploratory Hole No - **PRAIRIE_AUK_TP178** Sample No - **82**

Depth (m) - **0.60**

"As Received" Moisture Content (%)		Surcharge (Kg)	6
Retained on 20mm (%)	11.0	Seating Load (N)	Top 250 / Bottom 250
Correction Needed	No	Test Moisture Content (%)	Top 33 / Bottom 34
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.57
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.22
Date Tested	05/10/2020	CBR Value (%)	Top 30 / Bottom 35
Preparation Method	2.5kg Compaction		
Remarks			

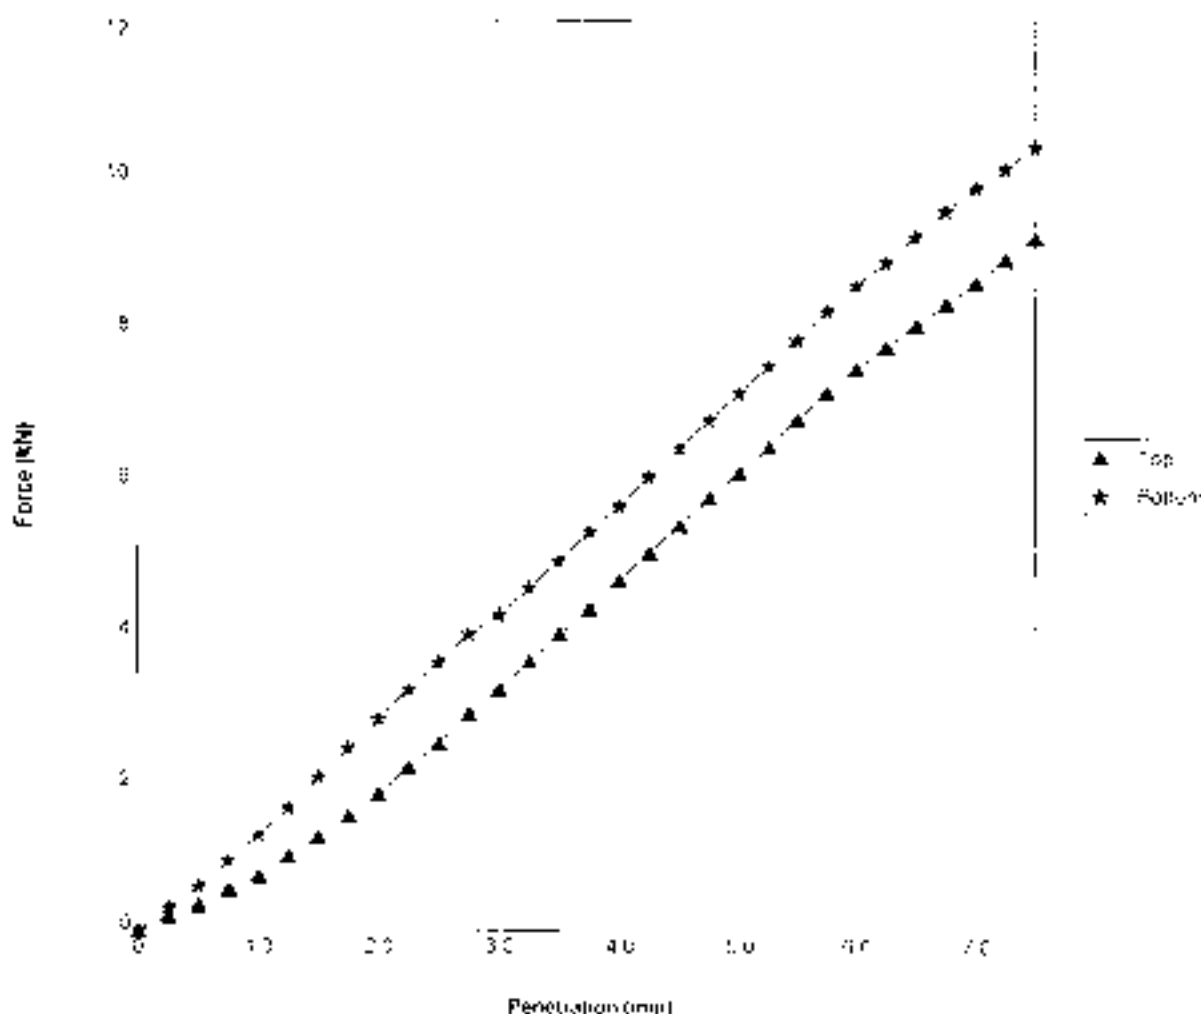

For description of sample please refer to the Laboratory Sample Description Sheet.

Contract Title -

Prairie Site Ground Investigation Works

South Fore Development Corporation



Signed

msere

Level 1

Supervisor

Date of Issue

05/10/2020

Certificate No.

0014001004-00-AUK-TP178-00-001

Accreditation No.

4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED


Method: BS 1377 Part 4: 1990 and Part 2: Clause 3.7: 1990

DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.7: 1990

Exploratory Hole No - PRAIRIE_AUK_TP181 Sample No **B2** Depth (m) - 0.50

"As Received" Moisture Content (%)		Surcharge (Kg)	6
Retained on 20mm (%)	25.0	Seating Load (N)	Top 250 / Bottom 250
Correction Needed	No	Test Moisture Content (%)	Top 15 / Bottom 15
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.75
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.52
Date Tested	02/10/2020	CBR Value (%)	Top 44 / Bottom 80
Preparation Method	2.5kg Compaction		
Remarks			

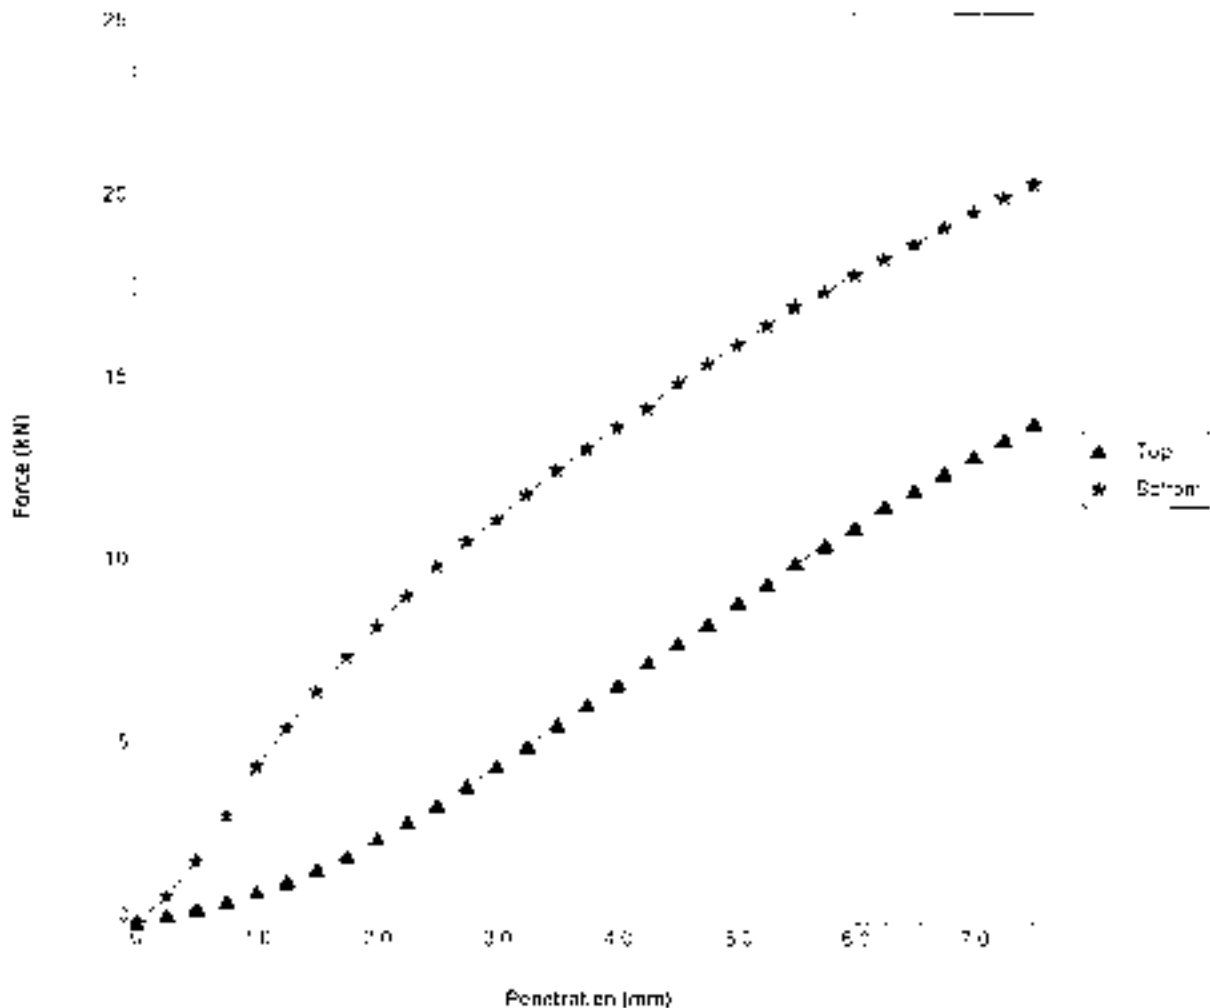

For identification of samples please refer to the Laboratory Sample Description Sheet

Contract Ref:

Prairie Site Ground Investigation Works

Client:

South Tees Development Corporation



Series:

ms20

Name:

Date Issued:

Date of Issue:

02/10/2020

Lab Reference No.:

100404/PRAIRIE_AUK_TP181/B2/0501

Project Reference No.:

4251



1167

ALLIED EXPLORATION & GEOTECHNICS LIMITED

100, 201st Street, Scarborough, Ontario M1B 2Y7, Canada


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 7: Clause 3.2: 1990

Exploratory Hole No - PRAIRIE_AUK_TP181 Sample No - B6

Depth (m) - 2.00

"As Received" Moisture Content (%)		Surcharge (Kg)	3
Retained on 20mm (%)	0.0	Sealing Load (kN)	Top 50 / Bottom 50
Correction Needed	No	Test Moisture Content (%)	Top 23 / Bottom 23
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	2.04
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.65
Date Tested	02/10/2020	GBR Value (%)	Top 3.2 / Bottom 4.0
Preparation Method	2.5kg Compaction		
Remarks			

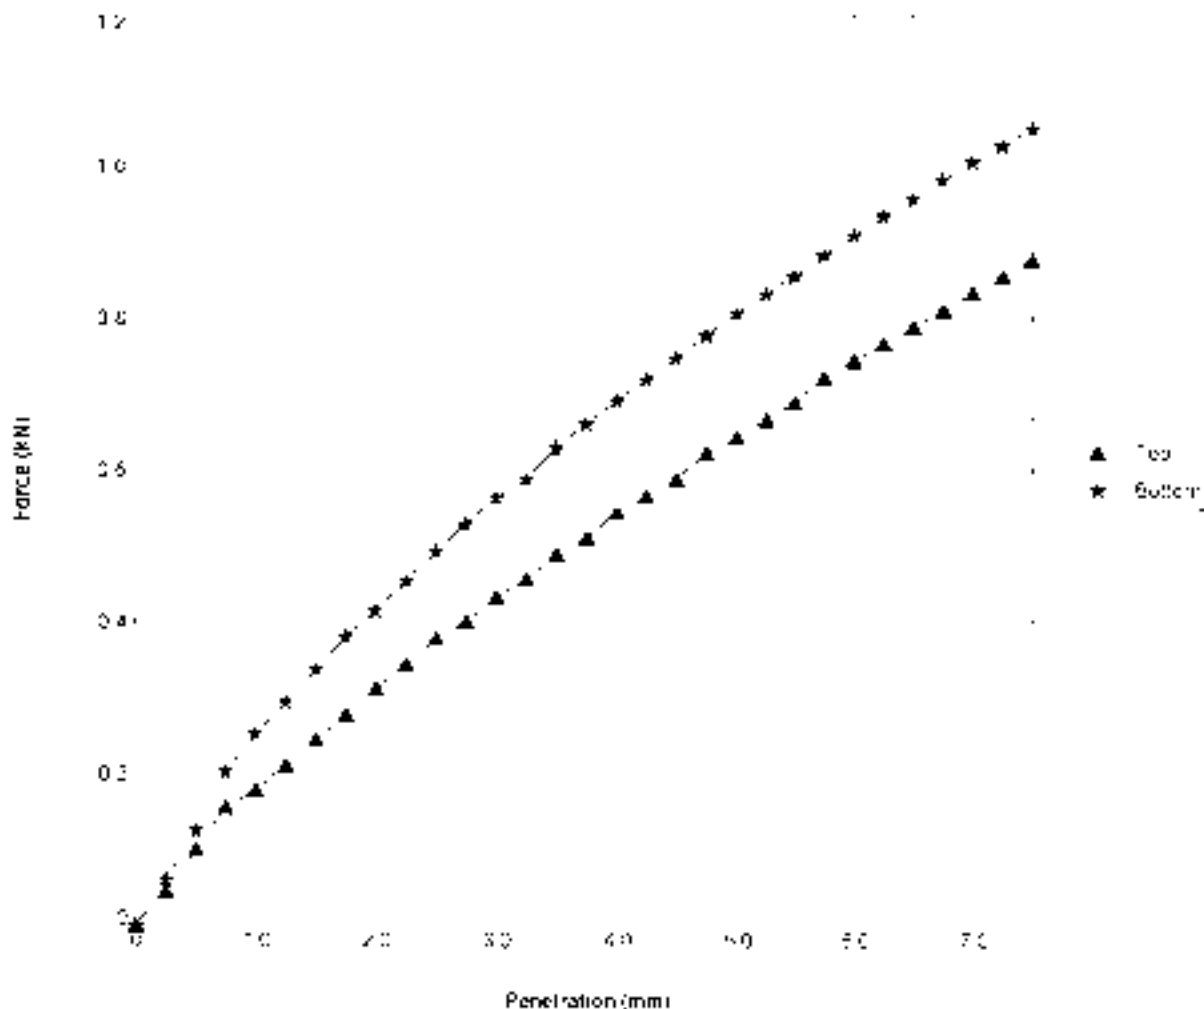

Each sample of soil used is referred to the Laboratory Sample Description Sheet

Contract No:

Prairie Site Ground Investigation Works

Client:

South Tees Development Corporation



By:

District Engineer

02/10/2020

For:

Compaction Test

GBR 4251 PRAIRIE_AUK_TP181 B6

By:

AEG Contract No:

4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Registered Office: 10, The Quadrant, South Tees, Sunderland, Tyne and Wear, England, S15 2NU


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No - PRAIRIE_AUK_TP182 Sample No - B2

Depth (m) - 0.60

"As Received" Moisture Content (%)		Surcharge (Kg)	10
Retained on 20mm (%)	17.0	Seating Load (N)	Top 250 / Bottom 250
Correction Needed	Yes	Test Moisture Content (%)	Top 16 / Bottom 16
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.48
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.28
Date Tested	25/09/2020	CBR Value (%)	Top 40 / Bottom 42
Preparation Method	2.5kg Compaction		
Remarks			

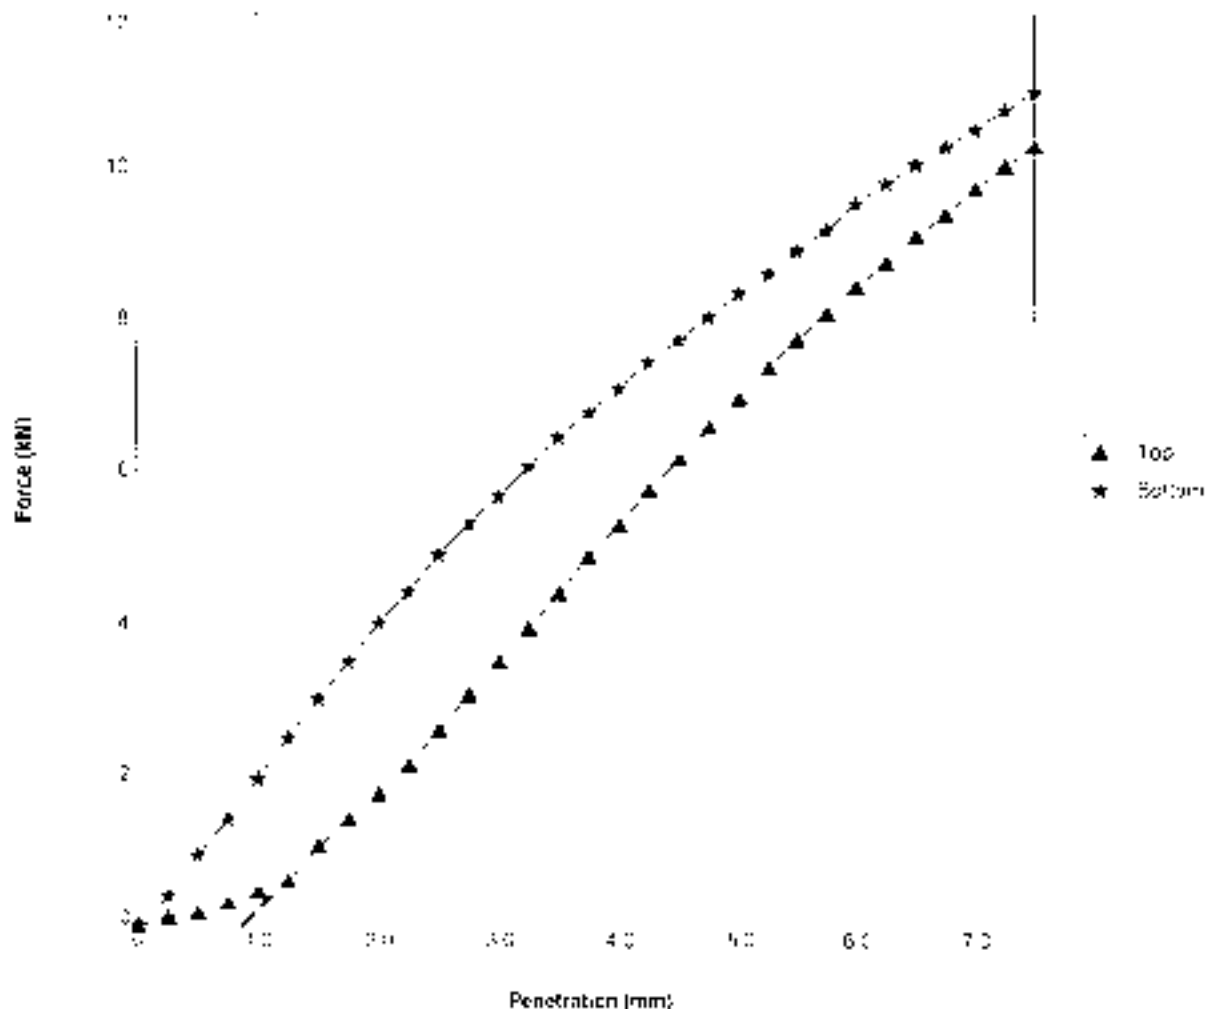

For identification of sample, please refer to the Laboratory Sample Description Sheet

Contract Title -

Prairie Site Ground Investigation Works

Client -

South Tees Development Corporation



Drawn by

msere

Checked by

25/09/2020

Title -

Contract No

025/ADN/PRAIRIE_AUK_TP182/B2/B2

Page 1 of 1

APD Control No -

4251



1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

100/1000, 100/1000, 100/1000, 100/1000, 100/1000, 100/1000, 100/1000, 100/1000, 100/1000, 100/1000


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No - PRAIRIE_AUK_TP182 Sample No - B5

Depth (m) - 1.60

"As Received" Moisture Content (%)		Surcharge (Kg)	6
Retained on 20mm (%)	0.0	Sealing Load (N)	Top 10 / Bottom 50
Correction Needed	Yes	Test Moisture Content (%)	Top 28 / Bottom 27
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	1.94
Swelling (mm)	N/A	Dry Density (Mg/m ³)	1.52
Date Tested	16/10/2020	CBR Value (%)	Top 4.6 / Bottom 4.8
Preparation Method	2.5kg Compaction		
Remarks			

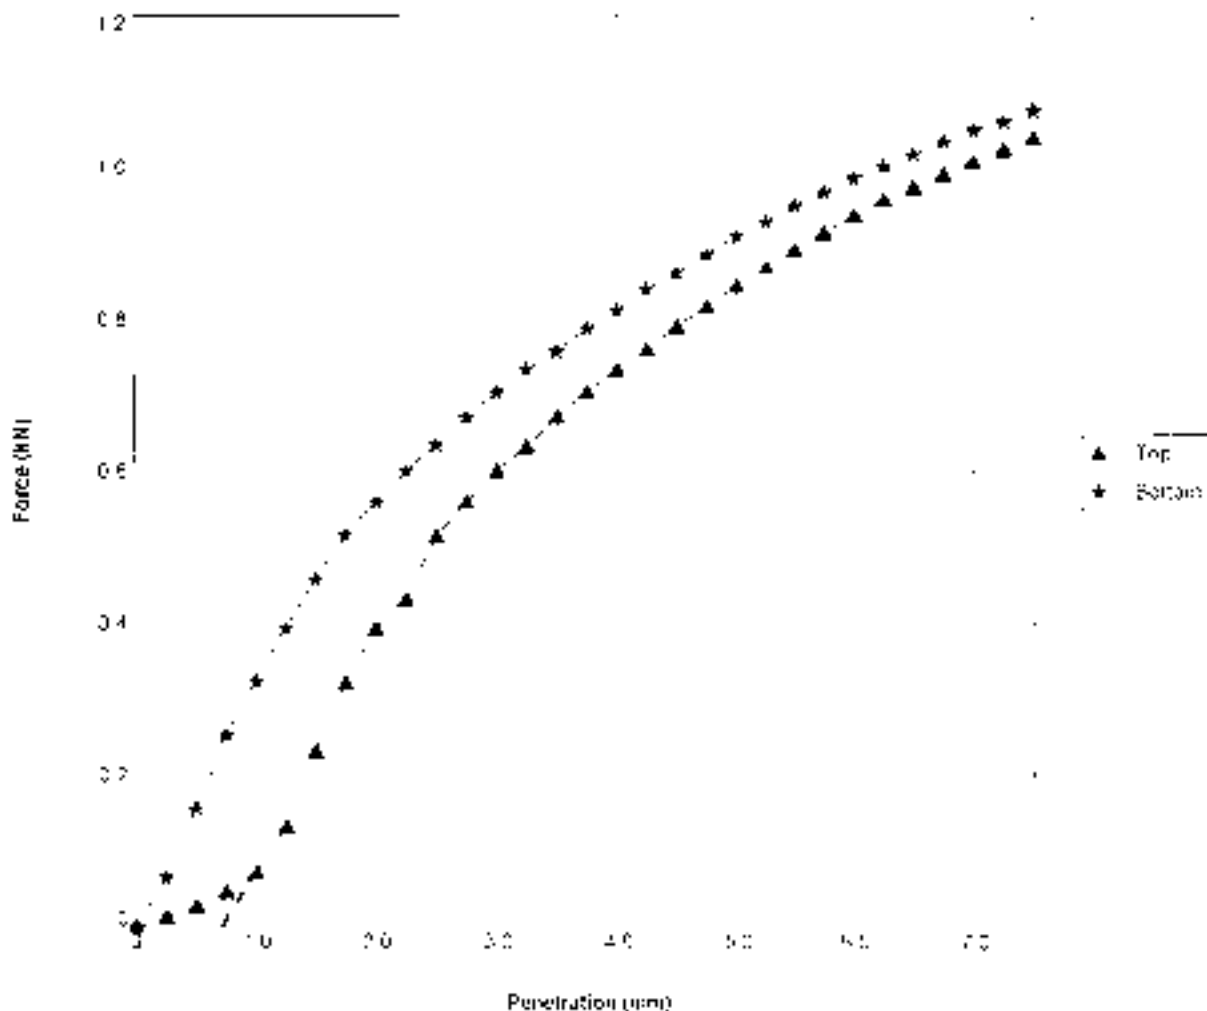

For next class of sample please refer to the Laboratory of 100/1000, 100/1000, 100/1000, 100/1000, 100/1000, 100/1000, 100/1000, 100/1000, 100/1000, 100/1000

Contract Title

Prairie Site Ground Investigation Works

Client

South Trees Development Corporation



Prepared by: *msoar*
 Date of Issue: 16/10/2020

Name: _____
 Checked by: _____
 Date: 16/10/2020

Project No: _____
 All Quantities: 4251



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 12, The Quadrant, South Shields, Tyne and Wear, NE33 1JF
 Telephone: 0191 275 4444 Fax: 0191 275 4445 E-mail: sales@allied-eg.co.uk


DETERMINATION OF THE CALIFORNIA BEARING RATIO

BS 1377 Part 4: 1990 and Part 2: Clause 3.2: 1990

Exploratory Hole No - PRAIRIE_AUK_TP189 Sample No - 82

Depth (m) 0.50

"As Received" Moisture Content (%)		Surcharge (Kg)	0
Retained on 20mm (%)	6.0	Sealing Load (N)	Top 250 / Bottom 250
Correction Needed	No	Test Moisture Content (%)	Top 17 / Bottom 17
Soaking Time (Days)	N/A	Bulk Density (Mg/m ³)	2.55
Swelling (mm)	N/A	Dry Density (Mg/m ³)	2.18
Date Tested	01/10/2020	CBR Value (%)	Top 38 / Bottom 45
Preparation Method	2.5kg Compaction		
Remarks			

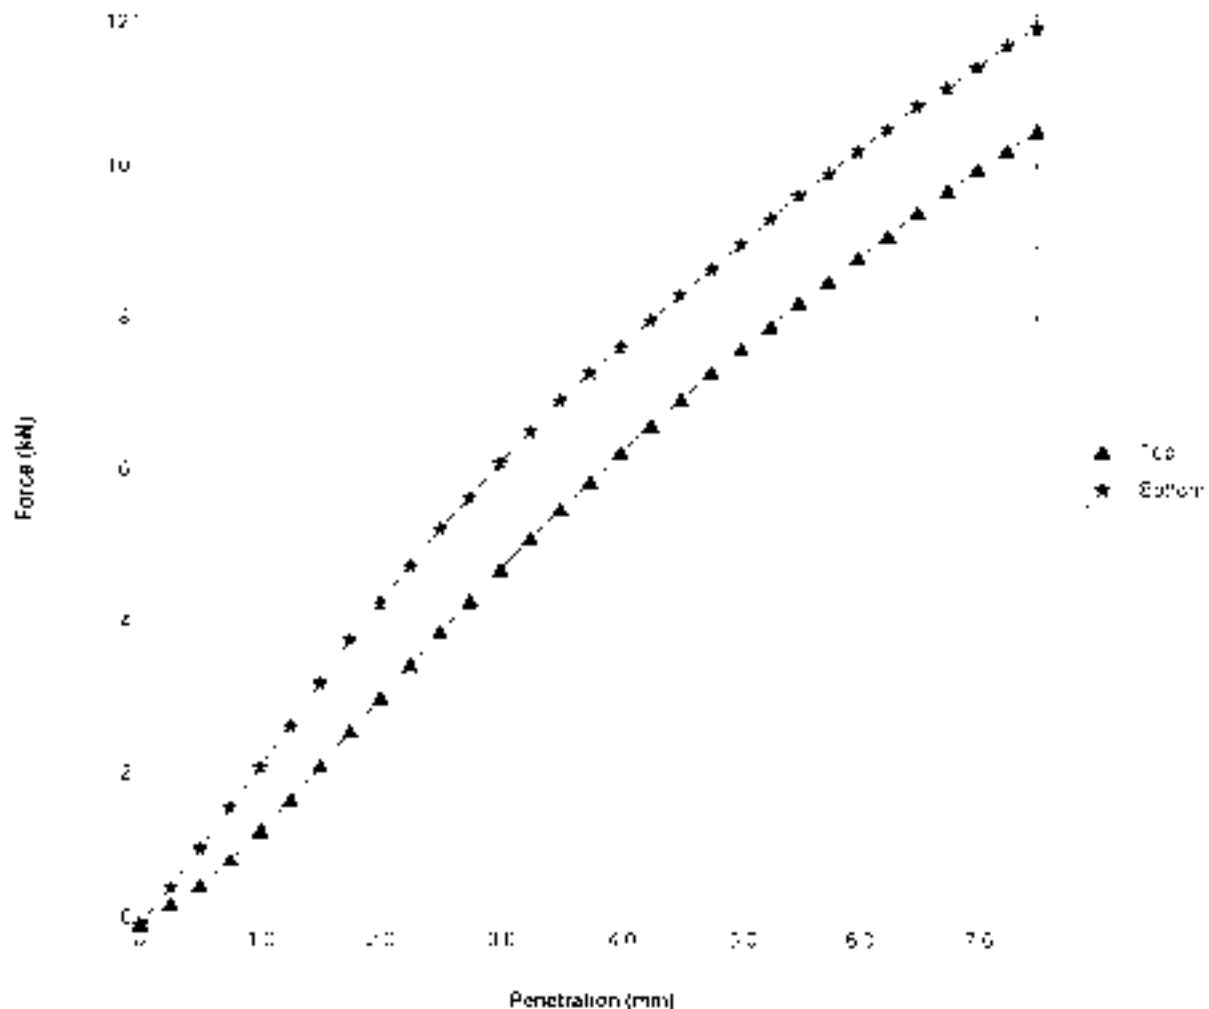

Please refer to the Laboratory Sample Description Sheet for a full description of sample(s) used in this test.

Contract Ref:

Prairie Site Ground Investigation Works

Client:

South Tees Development Corporation



Signed: *msore*
 Job: Client:
 28/10/2020

Name:
 Job Title: *Lab*
 CBR401 PRAIRIE_AUK_TP189_02020

Page: 1 of 1
 All Good To Go
 4251



Determination of One Dimensional Consolidation Properties



ALLIED EXPLORATION & GEOTECHNICS LIMITED

(INCORPORATED IN ENGLAND) (REGISTERED NO. 1274297)



ONE DIMENSIONAL CONSOLIDATION PROPERTIES

BS 1377 : PART 5 : 1990 : CLAUSE 3

Exploratory Hole No	PRAIRIE_AUK_BH103	Sample	U2	Depth (m)	2.50m
Specimen Type	Undisturbed	Orientation	Vertical	Specific Depth (m)	2.55m
	INITIAL	FINAL			
Height:	18.7	16.4	mm	Particle Density (Assumed):	2.70
Diameter:	74.74	74.74	mm	Degree of Saturation (%)	98.2
Moisture Content:	30.0	25.6	%	Test Duration (Days)	6
Wet Density	1.92	2.07	Mg/m ³	Date Tested	07/10/2009
Dry Density	1.43	1.65	Mg/m ³		

Square Root of Time Fitting Method				
Pressure Range kN/m ²	M _v m ² /MN	C _v m ² /yr	Temp C	Voids Ratio
Initial				0.825
0 - 50	0.828	.	21	0.749
50 - 100	0.438	2.25	21	0.711
100 - 50	0.056	Swelling	20	0.716
50 - 100	0.056	3.34	20	0.710
100 - 200	0.289	2.13	20	0.661
200 - 400	0.191	1.67	20	0.592

For sample description please refer to the Laboratory Sample Description Sheet


Contract Title Prairie Site Ground Investigation Works		Client South Tees Development Corporation	
	Signed 	Name M. SELKIRK	Page 1 of 2
	Date of Issue 18/11/2009	Certificate No. 4251:A	REG. CONTROL No. 4251

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Allied Geotech Ltd 25 South Shields Road, South Shields, Tyne and Wear, NE33 1JG, UK
 Registered Office: 25 South Shields Road, South Shields, Tyne and Wear, NE33 1JG, UK
 Registered in England No. 07558888

ONE DIMENSIONAL CONSOLIDATION PROPERTIES BS 1377 : PART 5 : 1990 : CLAUSE 3

Exploratory Hole No	PRAIRIE_AUK_BH103	Sample	U2	Depth (m)	2.50m
Specimen Type	Undisturbed	Orientation	Vertical	Specific Depth (m)	2.55m

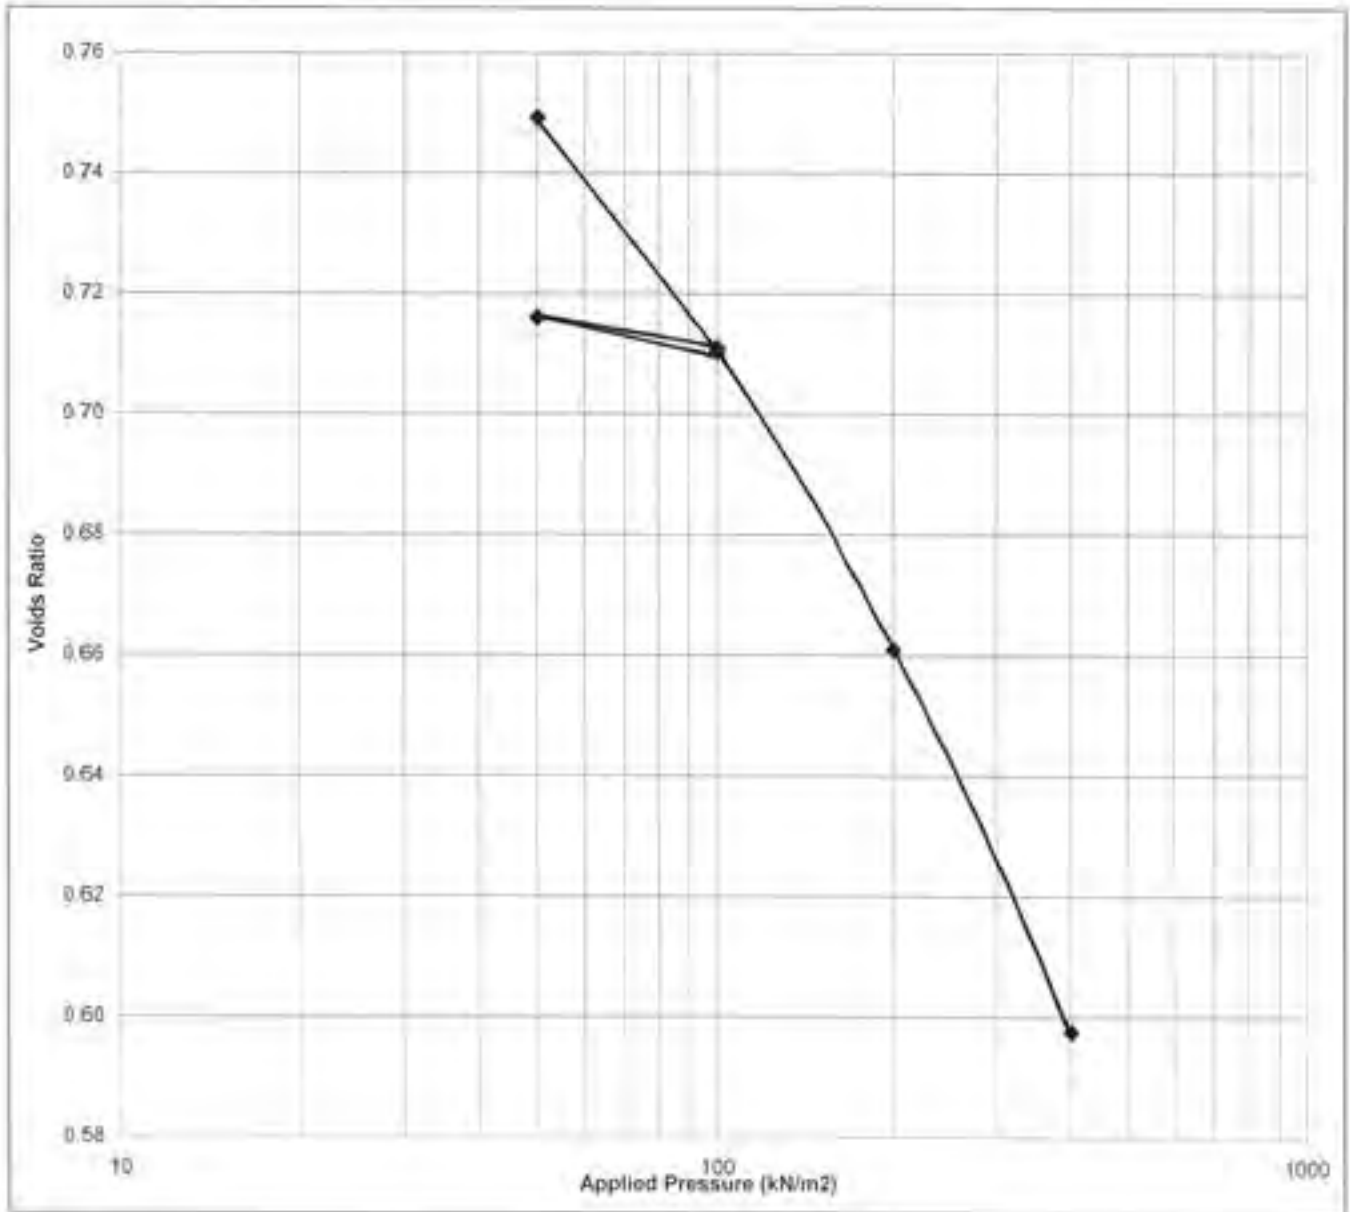

Contract Title: Prairie Site Ground Investigation Works	Client: South Tees Development Corporation
--	---

	Signed: <i>M. Selkirk</i>	Name: M. SELKIRK	Page 2 of 2	
	Date of Issue: 18/10/2020	Certificate No: 4251/A	AEG Contract No: 4251	

ALLIED EXPLORATION & GEOTECHNICS LIMITED

100, The Quadrant, South Shields, Tyne and Wear, NE33 1JG, UK
 Tel: 0191 276 6000 Fax: 0191 276 6001 Email: sales@allied-eg.co.uk

ONE DIMENSIONAL CONSOLIDATION PROPERTIES

BS 1377 : PART 5 : 1990 : CLAUSE 3

Exploratory Hole No	PRAIRIE_AUK_BH106	Sample	U2	Depth (m)	5.50m
Specimen Type	Undisturbed	Orientation	Vertical	Specific Depth (m)	5.50m
	INITIAL	FINAL			
Height:	18.6	16.7	mm	Particle Density (Assumed)	2.70
Diameter:	74.91	74.91	mm	Degree of Saturation (%)	99.5
Moisture Content	22.4	18.5	%	Test Duration (Days)	6
Wet Density	2.06	2.24	Mg/m ³	Date Tested	07/10/2020
Dry Density	1.68	1.89	Mg/m ³		

Square Root of Time Fitting Method				
Pressure Range kN/m ²	M _v m ² /MN	C _v m ² /yr	Temp C	Voids Ratio
Initial				0.603
0 - 100	0.374	.	21	0.548
100 - 200	0.120	7.80	21	0.520
200 - 100	0.012	Swelling	20	0.522
100 - 200	0.018	13.47	20	0.519
200 - 400	0.119	6.40	20	0.483
400 - 800	0.070	8.83	20	0.441

For sample description please refer to the Laboratory Sample Description Sheet

Contract Title

Prairie Site Ground Investigation Works

Client

South Tees Development Corporation



Signed

msene

Name

M SELKIRK

Page 1 of 2

Date of Issue

10/10/2020

Contract No.

4251-B

ACG Contract No.

4251




1367

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 25, 26 & 27, The Old Mill, Station Road, South Shields, Tyne and Wear, NE3 2UP. Tel: 0191 275 4700 Fax: 0191 275 4701
Regional Offices: 100, 101 & 102, The Old Mill, Station Road, South Shields, NE3 2UP. Tel: 0191 275 4700 Fax: 0191 275 4701

ONE DIMENSIONAL CONSOLIDATION PROPERTIES BS 1377 : PART 5 : 1990 : CLAUSE 3

Exploratory Hole No	PRAIRIE_AUK_BH106	Sample	U2	Depth (m)	5.50m
Specimen Type	Undisturbed	Orientation	Vertical	Specific Depth (m)	5.50m

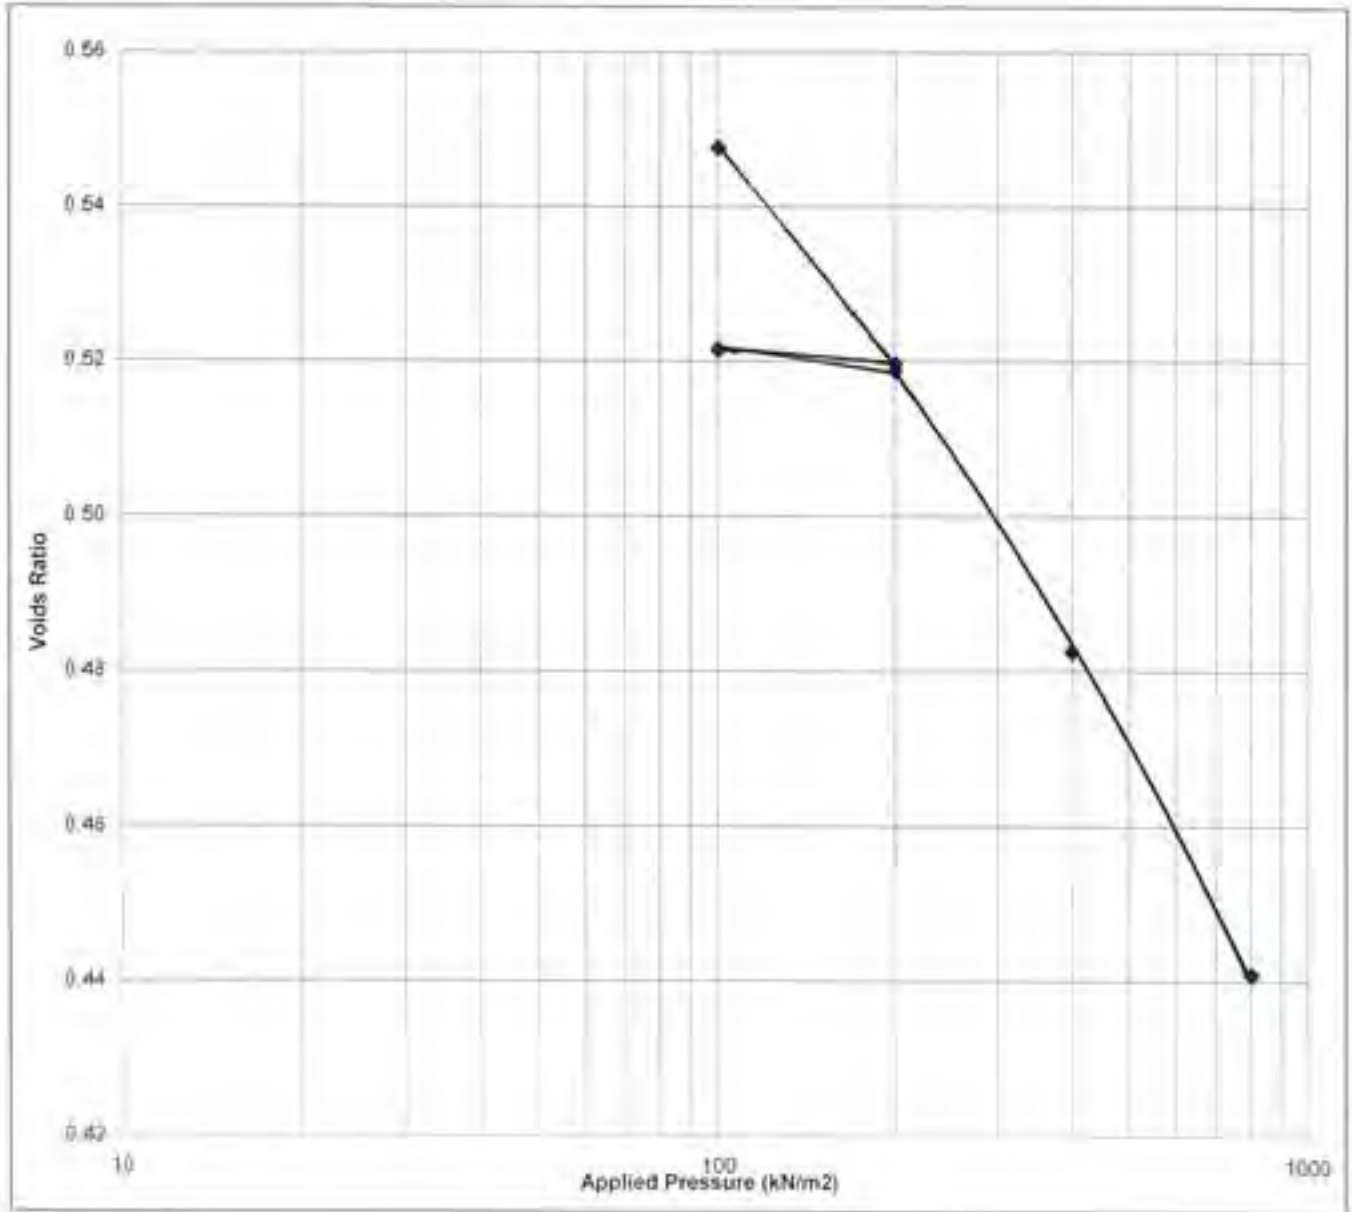

Contract Title: Prairie Site Ground Investigation Works	Client: South Tees Development Corporation
---	--

	Signed: <i>M. Selkirk</i>	Name: M. SELKIRK	Page 2 of 2	
	Date of Issue: 18/10/2020	Certificate No: 4251/B	AEG Contract No: 4251	

Shear Strength by Hand Vane



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 15, Bayside Industrial Estate, 1000 Park Road, Bayside, Christchurch 8013. Tel: 03 732 1111 Fax: 03 732 1112
Regional Office: Unit 21, Commerce Development Centre, Lower Moor, Christchurch 8013. Tel: 03 732 1111 Fax: 03 732 1112

DETERMINATION OF SHEAR STRENGTH BY HAND VANE

Exploratory Hole No.	Sample Depth (m)	Sample ID	Specific Depth (m)	Vane Shear Strength (kPa)	Remarks
PRAIRIE_AJK_BH104	8.50	U8	8.50	>130	Reading exceeded apparatus limits
PRAIRIE_AJK_BH104	8.50	U8	8.95	>130	Reading exceeded apparatus limits
PRAIRIE_AJK_BH103	2.50	U2	2.50	109	
PRAIRIE_AJK_BH103	2.50	U2	2.95	94	
PRAIRIE_AJK_BH103	4.50	U7	4.50	65	
PRAIRIE_AJK_BH103	4.50	U7	4.95	87	
PRAIRIE_AJK_BH103	1.20	U6	1.20	41	
PRAIRIE_AJK_BH103	1.20	U6	1.65	>130	Reading exceeded apparatus limits
PRAIRIE_AJK_BH103	5.00	U19	5.00	42	
PRAIRIE_AJK_BH103	5.00	U19	5.45	62	

For description of sample please refer to the Laboratory Sample Description Sheet

Contract Title :- Prairie Site Ground Investigation Works	Client :- South Tees Development Corporation
---	--

	Signed :- <i>msene</i>	Name :-	Page 1 of 1	
	Date of issue :- 03/11/2020	Certificate No :- HSY/4251/1	AEG Contract No :- 4251	

**Undrained Shear Strength in Triaxial Cell
without Pore Water Pressure Measurement**



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: 04333 Bury Gate, Middlesbrough, Teesside, North Yorkshire, YO21 2JY, Tel: 01709 361400 Fax: 01709 361415
Regional Offices: 100-125 Industrial Development Centre, Darlington, North Yorkshire, YO19 7JW, Tel: 01709 756100 Fax: 01709 756101

UNDRAINED SHEAR STRENGTH IN TRIAXIAL COMPRESSION WITHOUT MEASUREMENT OF PORE PRESSURE

BS 1377 - Part 7, Clauses 8 & 9 : 1990 Part 2 Clause 3.2

Exploratory Hole	Sample ID Depth (m)	Sample Type	Specific Depth (m)	Diameter (mm)	Length (mm)	Prep Method	Stage No.	Initial Moisture Content (%)	Bulk Density (Mg/m ³)	Dry Density (Mg/m ³)	Membrane Thickness (mm)	Membrane Correction (kPa)	Cell Pressure (kPa)	Corrected Deviator Stress (kPa)	Failure Strain (%)	Mode of Failure	Cu (kPa)	Date Tested
PRAIRIE_AUK_BH101	3.00	U2	3.02	103.6	209.5	UNDISTURBED	1	32.7	1.95	1.47	0.3	1.10	60	52	20.0	F	26	17/06/2020
PRAIRIE_AUK_BH101	5.00	U1	5.18	104.0	211.0	UNDISTURBED	1	32.9	1.93	1.46	0.3	0.79	80	83	13.0	F	32	17/06/2020
PRAIRIE_AUK_BH101	8.00	U12	8.01	103.0	210.0	UNDISTURBED	1	27.3	1.98	1.55	0.4	0.94	110	97	11.0	BR	43	17/06/2020
PRAIRIE_AUK_BH101	11.00	U16	11.01	104.7	210.7	UNDISTURBED	1	16.1	2.19	1.89	0.9	0.85	140	251	14.5	F	125	17/06/2020
PRAIRIE_AUK_BH103	3.50	U2	2.80	103.5	210.4	UNDISTURBED	1	31.1	1.94	1.48	0.3	1.10	50	94	20.0	F	42	06/10/2020
PRAIRIE_AUK_BH103	4.50	U5	4.56	103.7	211.0	UNDISTURBED	1	25.4	1.97	1.56	0.4	0.88	100	147	10.0	C	74	06/10/2020
PRAIRIE_AUK_BH100	7.00	U14	7.02	102.9	210.8	UNDISTURBED	1	27.4	1.97	1.55	0.3	0.43	150	106	8.0	BR	53	06/10/2020
PRAIRIE_AUK_BH103	18.00	U21	10.25	103.5	211.7	UNDISTURBED	1	17.2	2.07	1.77	0.3	0.92	200	185	16.0	C	93	06/10/2020
PRAIRIE_AUK_BH104	5.60	U2	5.53	101.8	211.5	UNDISTURBED	1	25.8	1.92	1.53	0.4	0.58	110	230	8.0	BR	115	06/10/2020
PRAIRIE_AUK_BH100	5.50	U2	5.57	103.3	210.1	UNDISTURBED	1	23.0	2.06	1.68	0.3	1.08	110	136	19.5	C	68	06/10/2020
PRAIRIE_AUK_BH100	6.50	U6	8.60	104.6	211.2	UNDISTURBED	1	14.3	2.25	1.97	0.4	1.24	175	502	15.5	C	251	06/10/2020
PRAIRIE_AUK_BH101	3.30	U2	3.00	102.6	212.7	UNDISTURBED	1	29.9	1.95	1.50	0.4	1.36	60	51	18.0	F	25	10/07/2020
PRAIRIE_AUK_BH107	5.00	U7	5.06	103.4	211.1	UNDISTURBED	1	23.6	2.05	1.66	0.3	1.01	100	134	18.0	BR	67	13/07/2020
PRAIRIE_AUK_BH109	3.80	U13	5.05	103.2	211.2	UNDISTURBED	1	23.6	2.04	1.65	0.3	0.82	60	142	13.5	BR	71	13/07/2020
PRAIRIE_AUK_BH110	4.80	U2	3.03	103.1	211.1	UNDISTURBED	1	30.4	1.91	1.47	0.3	0.85	60	71	10.0	BR	36	13/07/2020

For description of sample please refer to the Laboratory Sample Description Sheet. Please note the rate of strain was 2% per minute and the orientation of the test specimen was vertical. Latex membrane used.

	Date of Issue - 23/10/2020	Certificate No - TXL/4251/1	Signed - <i>MSOR</i>	Name -	Page 1 of 2
	Client - South Tees Development Corporation	Contract Title -	Prairie Site Ground Investigation Works		



ALLIED EXPLORATION & GEOTECHNICS LIMITED

Registered Office: 100, The Quadrant, London, W1 1AA, United Kingdom. Tel: 020 7591 2000. Fax: 020 7591 2001. Email: sales@allied-geotech.co.uk

UNDRAINED SHEAR STRENGTH IN TRIAXIAL COMPRESSION WITHOUT MEASUREMENT OF PORE PRESSURE

BS 1377 Part 2: Clauses 8.8, 8.9, 1989 Part 2 Clause 3.2

Experiment No.	Sample ID	Specimen Depth (mm)	Diameter (mm)	Length (mm)	Prep Method	Slope (%)	Moisture Content (%)	Soil Description	Bulk Density (kg/m ³)	Ring Density (kg/m ³)	Dr. Density (kg/m ³)	Membrane Thickness (mm)	Membrane Correction (%)	Cell Pressure (kPa)	Corrected Deviator Stress (kPa)	Failure Strain (%)	Mode of Failure	Failure Angle (°)	Date Tested
1	1001	840	100.7	210.6	100.0	1	64.2	2.06	2.06	1.54	0.3	0.60	100	105	12.5	C	52	10/07/2020	
2	1002	805	100.6	212.2	100.0	1	39.1	2.15	2.15	1.79	0.2	1.09	160	144	19.5	C	72	10/07/2020	
3	1003	1120	100.9	211.0	100.0	1	10.4	2.23	2.23	2.29	0.7	2.54	220	78.2	20.0	C	39	10/07/2020	

Note: For a full description of sample preparation refer to the Laboratory Sample Description Sheet. Please note the rate of strain was 2% per minute and the orientation of the test specimen was vertical. Later than the time and


10/07/2020

Site Code No.

Sample No.

Name

Page 2 of 2



Contract No.

Contract Title

Praxis Site Ground Investigation Works

REC Contract No.

4251

1367

Determination of Point Load Index

ALLIED EXPLORATION & GEOTECHNICS LIMITED

Head Office: Unit 21, West of Alton Road, Alton, Hampshire, GU34 5LJ. Tel: 01493 507400 Fax: 01493 507401
 Regional Offices: Unit 25, Bicknham Industrial Estate, Bicknham, Southampton, SO1 1BB. Tel: 01703 503888 Fax: 01703 503889

POINT LOAD STRENGTH INDEX

ISRM : 1985

Exploratory Hole No	Depth (m)	Type/Orientation	Width (mm)	Platen Separation (mm)+	Failure Load (kN)*	De ² (mm ²)	Point Load (IS) (MPa)	Size Factor	Point Load Index (IS50) (MPa)	Type	Date Tested
WPA01E_A(BC_04110)	7.70	Vertical	65.5	58.4	0.4	8365.0	0.06	1.23	0.078	Sandstone	17/05/2020

NOTES: - *Tested specimen measured using calibrated vernier calipers - # Invalid Failure (Did not pass through both points) !:-Top soft to register a reading

Date of issue :-

25/05/2020

Certificate No :-

PL425111

Signed :-

msae

Name :-

Prattis Site Ground Investigation Works

Page 1 of 1

AEG Contract No :-

4251

Client :-

South Tees Development Corporation

Contract Title :-

Prattis Site Ground Investigation Works



**Determination of Unconfined Compressive Strength
(Tested Externally)**



LABORATORY TEST CERTIFICATE

Certificate No : 20/504 - 01
To : Michelle Selkirk
Client : **Allied Exploration & Geotechnics Ltd.**
Unit 25 Stella Gill Industrial Estate
Pelton Fell
Chester-le-Street
County Durham
DH2 2RG

Dear Sirs,

LABORATORY TESTING OF ROCK

Introduction

We refer to samples taken from Prairie Site Ground Investigation Works and delivered to our laboratory on 18th June 2020.

Material & Source

Sample Reference : See Report Plate
Sampled By : Client
Sampling Certificate : Not Supplied
Location : See Report Plate
Description : Rock Cores
Date Sampled : Not Supplied
Date Tested : 18th June 2020 Onwards
Source : 4251 - Prairie Site Ground Investigation Works

Test Results;


As Detailed On Page 2

Comments;

Opinions and interpretations expressed herein are outside the scope of UKAS accreditation
This report should not be reproduced except in full without the written approval of the laboratory
All remaining samples for this project will be disposed of 28 days after issue of this test certificate

Remarks;

Approved for Issue




T McLelland (Director)


Date 10/11/2020




BOREHOLE	PRAIRIE_AUK_BH109	
SAMPLE	C	
DEPTH	m	9.00
SAMPLE DIAMETER	mm	81.64
SAMPLE HEIGHT	mm	169.33
TEST CONDITION	As Received	
RATE OF LOADING	kN/s	0.4
TEST DURATION	min.sec	4.37
DATE OF TESTING	22/06/2020	
LOAD FRAME USED	2000kN	
LOAD DIRECTION WITH RESPECT TO LITHOLOGY	Unknown	
FAILURE LOAD	kN	105.9
UNCONFINED COMPRESSIVE STRENGTH	MPa	20.2
WATER CONTENT (ISRM Suggested Methods)	%	3.5
BULK DENSITY (ISRM Suggested Methods)	Mg/m ³	2.60
DRY DENSITY (ISRM Suggested Methods)	Mg/m ³	2.51

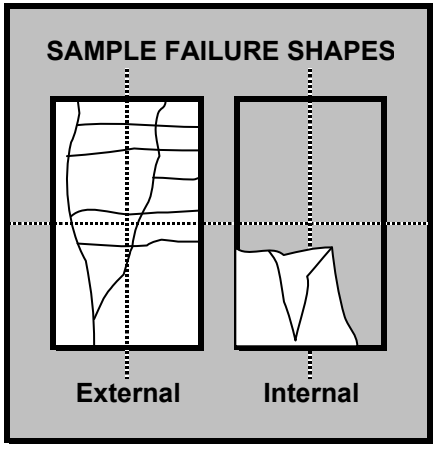

BOREHOLE	PRAIRIE_AUK_BH109	
SAMPLE	C	
DEPTH	m	11.30
SAMPLE DIAMETER	mm	83.10
SAMPLE HEIGHT	mm	186.89
TEST CONDITION	As Received	
RATE OF LOADING	kN/s	0.7
TEST DURATION	min.sec	3.28
DATE OF TESTING	22/06/2020	
LOAD FRAME USED	2000kN	
LOAD DIRECTION WITH RESPECT TO LITHOLOGY	Unknown	
FAILURE LOAD	kN	132.2
UNCONFINED COMPRESSIVE STRENGTH	MPa	24.4
WATER CONTENT (ISRM Suggested Methods)	%	1.7
BULK DENSITY (ISRM Suggested Methods)	Mg/m ³	2.58
DRY DENSITY (ISRM Suggested Methods)	Mg/m ³	2.54

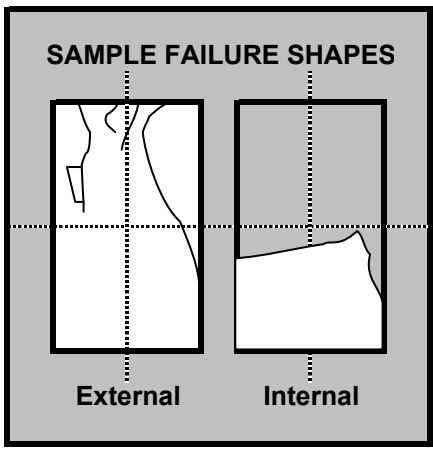

BOREHOLE		
SAMPLE		
DEPTH	m	
SAMPLE DIAMETER	mm	
SAMPLE HEIGHT	mm	
TEST CONDITION		
RATE OF LOADING	kN/s	
TEST DURATION	min.sec	
DATE OF TESTING		
LOAD FRAME USED		
LOAD DIRECTION WITH RESPECT TO LITHOLOGY		
FAILURE LOAD	kN	
UNCONFINED COMPRESSIVE STRENGTH	MPa	
WATER CONTENT (ISRM Suggested Methods)	%	
BULK DENSITY (ISRM Suggested Methods)	Mg/m ³	
DRY DENSITY (ISRM Suggested Methods)	Mg/m ³	

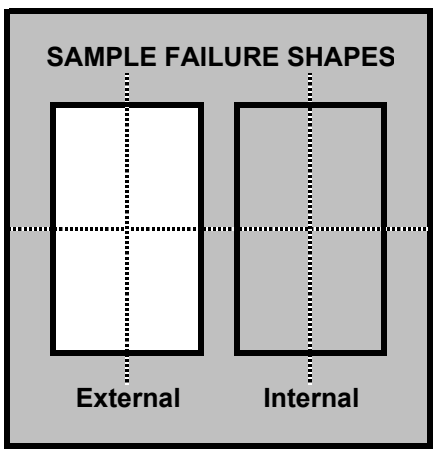

Tested in accordance with ASTM D7012 - 14

SUMMARY OF UNCONFINED COMPRESSIVE STRENGTH

**Slag Analysis
(Tested Externally)**



TRS REPORT

Report Ref: BG0E-F/AEG/PSR/TRS/07/20/RP2
Date Issued: 31 July 2020
TRS Sample Refs: BG0E01-04/BG0F01-02
Order No: LA2343

**EXAMINATION OF SIX SAMPLES
FROM
4251 PRAIRIE SITE GROUND INVESTIGATION
WORKS, REDCAR
FOR
ALLIED EXPLORATION & GEOTECHNICS LTD**



Thomas Research Services Ltd.

Tel: +44 (0) 1469 532 929

www.slagtest.co.uk

Unit 7, Tittershall Castle Court, Morgan Way, New Holland,

North Lincolnshire, DN19 7PZ, United Kingdom

A Limited Company registered in England. Company Registration No: 2518421

**EXAMINATION OF SIX SAMPLES
FROM
4251 PRAIRIE SITE GROUND INVESTIGATION
WORKS, REDCAR
FOR
ALLIED EXPLORATION & GEOTECHNICS LTD**

1. BACKGROUND

Four bulk samples were received from the above site on 11th May 2020, with a further two samples arriving on 16th June 2020. Each sample was weighed and allocated a unique TRS reference number, the details of which are recorded below:-

TRS Ref	Site Ref	Depth/m	Mass/kg
BG0E01	TP109 B2	1.0	11.8
BG0E02	TP116 B2	1.0	12.3
BG0E03	TP117 B2	1.0	16.3
BG0E04	TP121 B5	1.8	12.1
BG0F01	TP131 B4	1.5	10.0
BG0F02	TP132 B3	1.0	9.8

There was a delay in processing these samples due to the Coronavirus lockdown.

The purpose of the exercise was to identify the range and relative concentrations of any iron and steelmaking slags present in the samples, and whether there was any potential for volumetric instability from the materials.

2. SAMPLE PREPARATION & PROGRAMME OF ANALYSIS

The samples were primary crushed to reduce particle size down to <50mm, portions then being selected and dried at low temperature to constant weight. The dried material was subjected to a regime of stage crushing and quartering to further reduce particle size down to <5mm. Portions of this <5mm material were made up into resin bound blocks, one face of which was ground flat and polished using diamond pastes. Further portions of the <5mm material were milled to a fine powder. Fractions of material were extracted throughout the preparation procedure to provide the materials necessary for the further tests and analyses required in the programme.

A petrological examination was made of the polished blocks using reflected light microscopy, the complete findings of which are recorded in appendix A. The results of this examination were discussed in our report of 10th July 2020. On the basis of that report, the following tests and analyses were carried out on the samples:-

Samples BG0E01-02 were subjected to the following tests & analyses to assess the potential for expansion of the blast furnace slag.

- Water soluble sulphate (table 1)
- Acid soluble sulphate (table 1)
- Total sulphur (table 1)
- Thermal analysis (table 3)
- TRS accelerated expansion test (table 4)

Samples BG0E04 & BG0F01-02 were subjected to the following tests & analyses to assess the potential for expansion of the basic steel slag.

- Free CaO (table 2)
- Free MgO (table 2)
- Thermal analysis (table 3)
- TRS accelerated expansion test (table 4)

Sample BG0E03 were subjected to the following tests & analyses to assess the potential for expansion of the mixed slag.

- Water soluble sulphate (table 1)
- Acid soluble sulphate (table 1)
- Total sulphur (table 1)
- Free CaO (table 2)
- Free MgO (table 2)
- Thermal analysis (table 3)
- TRS accelerated expansion test (table 4)

3. DISCUSSION OF RESULTS

3.1 Petrology

A petrological examination was made of the six samples using reflected light microscopy. The complete findings of this examination are recorded in appendices A and B.

Blast furnace slag was present in all six samples, with substantial quantities present in samples BG0E01-03 and small amounts in samples BG0E04 & BG0F01-02. The blast furnace slag was predominantly crystalline with only minor amounts of glassy material seen. Secondary alteration due to weathering was moderate, consisting mainly of pore infill and surface rinds. Products of alteration included calcite, with other products being difficult to identify specifically under the microscope. Old weathered blast furnace slag may occasionally contain pockets of potentially expansive material (see appendix C). This potential can only be assessed by direct expansion testing (see sections 3.2-3.5). The unaltered slag consisted predominantly of melilite, along with more minor amounts of larnite, bredigite, spinel, metallic iron and sulphides.

Basic steel slag was present in all six samples. Samples BG0E01-02 contained minor amounts (small/very small), sample BG0E03 contained a medium amount, but samples BG0E04 & BG0F01-02 comprised predominantly of basic steel slag. The slag was extensively altered due to weathering, the secondary phases being difficult to identify specifically under the microscope. The unaltered basic steel slag consisted largely of dicalcium silicate, along with more minor amounts of FeO

& R₂O₃ phase, CaF phase, tricalcium silicate, lime phase and periclase. The mineralogy of the basic steel slag would suggest that it may have significant potential for expansion (see appendix C). This potential can only be assessed by direct expansion testing (see sections 3.2-3.5).

Minor amounts (small / very small) of basic refractory material were seen in four of the samples. This material, even in minor amounts, can have significant potential for expansion (see appendix C).

Other constituents seen in the samples in minor concentrations included alumina-silicate brick, quartz, limestone, iron ore, iron ore sinter, cinder, metal, coal, coke and fume. A cementitious material often bound the smaller particles together. This material appeared similar to the slag alteration products.

3.2 Sulphur Species

The following range of analyses were performed on samples BG0E01-03 (These samples contained significant amounts of blast furnace slag). The results are recorded in table 1:-

- Water soluble sulphate
- Acid soluble sulphate
- Total sulphur

Total sulphur values were in the range 0.62 to 1.07 percent. Acid soluble sulphates were in the range 0.30 to 0.87 percent, with corresponding water soluble sulphates of 0.17 to 0.35 g/l. These sulphate and sulphur values were fairly typical for blast furnace slag. However, care should be taken when specifying concrete that may come into contact with the slag. Calculations show that between 19 and 33 percent of the available sulphur is present as sulphate.

3.3 Thermal Analysis

Simultaneous differential thermal analysis (DTA) and thermo-gravimetric analysis (TGA) were performed on all six samples. The results are recorded in table three.

Ettringite was seen in three of the samples examined, at trace levels only. Gypsum was seen in all but one of the samples, at between trace and 3.7 percent. On comparing the gypsum values with the acid soluble sulphates, some of the gypsum values were overstated. This is common in old weathered blast furnace slag, and is usually an indicator of the presence of thaumasite. The presence of ettringite and possibly thaumasite would suggest some past expansion has occurred in the blast furnace slag.

Calcium hydroxide was recorded in four of the samples, at between 0.5 and 2.5 percent. Magnesium hydroxide was measured in three of the samples, at between 0.5 and 1.0 percent. These values were used to correct the free CaO and free MgO analyses recorded in Table 2.

Calcite was present in all of the samples examined at between 2.4 and 5.6 percent. This product is an indicator as to the weathered state of the slag.

3.4 Free CaO & Free MgO

Free CaO & free MgO analyses were carried out on samples BG0E03-04 & BG0F01-02 (These samples contained medium or more mounts of basic steel slag). The results are recorded in table 2. Both original and corrected values are recorded. The original values include both the oxide (CaO and MgO) and the hydroxide ((Ca(OH)₂ and Mg(OH)₂)) contents. The corrected values report only the oxide content (CaO and MgO) after correction using the hydroxide values

from the thermal analyses. These corrected values are the more significant, as it is only the oxides that are still free to hydrate, i.e. expand.

Free lime was recorded in the samples at between 1.5 and 5.2 percent. Free magnesia was recorded at between 0.3 and 3.3 percent. These corrected free lime and free magnesia levels record oxides that are potentially still free to hydrate (i.e. expand).

3.5 TRS Accelerated Expansion Test

The TRS accelerated expansion test was performed on all six samples. The results are recorded in table four. Note that the test measures potential for future expansion, and is not a measure of expansion that may have taken place in the past.

Samples consisting predominantly of blast furnace slag, with only minor amounts of basic steel slag recorded expansion results of between 0.22 and 0.25 percent. The sample containing mixed blast furnace slag and basic steel slag recorded an expansion result of between 0.50 percent. Samples consisting predominantly of basic steel slag recorded expansion results of between 2.56 and 3.11 percent.

4. CONCLUSIONS & RECOMMENDATIONS

The following conclusions can be drawn:-

- Blast furnace slag was a dominant constituent in three of the samples (BG0E01-03) and a minor constituent in the remaining three. The slag was mainly crystalline although minor amounts of glassy material were seen. The slag showed some alteration due to weathering. Old weathered blast furnace slag may occasionally contain pockets of potentially expansive material. Potential for expansion can only be assessed with direct expansion testing.
- Further testing of samples consisting predominantly of blast furnace slag (with up to medium amounts of basic steel slag) recorded expansion results of between 0.22 and 0.50 percent. Thermal analysis indicated some evidence of past expansion of the blast furnace slag (presence of ettringite and possibly thaumasite). The sulphate values should be taken into consideration when specifying concrete that may come into contact with the slag.
- Basic steel slag was the dominant constituent in samples BG0E04 and BG0F01-02. It was also present in more minor amounts (vs to m) in the remaining three samples. This material is likely to present a significant risk of expansion. Potential for expansion can only be assessed with direct expansion testing.
- Expansion testing of the samples consisting mainly of basic steel slag (BG0E04 & BG0F01-02) recorded expansion results of between 2.56 and 3.11 percent.
- Minor amounts of basic refractory material were seen in four of the six samples examined. This product can be a significant source of expansion, even when present in relatively small amounts.

- Other products were seen in the samples in minor amounts including alumino-silicate brick, quartz, limestone, iron ore, iron ore sinter, cinder, metal, coal, coke and fume.

Note

These conclusions apply only to the samples tested and may not represent the bulk of the material on the site from which they were taken.

Ian D. Thomas

Ian D Thomas BSc(Hons)

31 July 2020

TABLE 1 **SULPHUR SPECIES ANALYSES**

TRS Ref	Site Ref	Water Sol. SO ₄ (g/l)	Acid Sol. SO ₄ (%)	Total S (%)
BG0E01	TP109	0.19	0.87	1.07
BG0E02	TP116	0.17	0.70	0.86
BG0E03	TP117	0.35	0.7	0.62
BG0E04	TP121	-	-	-
BG0F01	TP131	-	-	-
BG0F02	TP131	-	-	-

TABLE 2 **ANALYSIS FOR FREE CaO AND FREE MgO**

TRS Ref	Site Ref	Free CaO Original (%)	Free CaO Corrected (%)	Free MgO Original (%)	Free MgO Corrected (%)
BG0E01	TP109	-	-	-	-
BG0E02	TP116	-	-	-	-
BG0E03	TP117	2	1.5	1.7	1.7
BG0E04	TP121	7.1	5.7	1.1	0.2
BG0F01	TP131	4.9	3.3	1.7	3.3
BG0F02	TP131	5.5	4.6	1.0	0.3

TABLE 3 **RESULTS FROM THERMAL ANALYSIS**

TRS Ref	Site Ref	Mass % by Thermal Analysis						
		L.O.I.	Etringite	Gypsum	Calcite	Ca(OH) ₂	Mg(OH) ₂	Others
BG0E01	TP109	0.29	0.00	1.7	2.4	0.0	0.0	-
BG0E02	TP116	5.35	0.00	1.2	4.4	0.0	0.0	clay?
BG0E03	TP117	5.60	0.0	0.00	5.4	0.5	0.0	clay?
BG0E04	TP121	7.05	0.00	0.00	2.0	2.5	0.5	-
BG0F01	TP131	6.85	0.0	0.00	5.0	0.8	0.5	clay?
BG0F02	TP131	3.07	0.0	0.5	4.4	1.3	1.0	-

TABLE 4 **TRS ACCELERATED EXPANSION TEST**

TRS Ref	Site Ref	7 day (%)	14 day (%)	21 day (%)	28 day (%)
BG0E01	TP109	0.15	0.27	-	-
BG0E02	TP116	1.75	0.25	-	-
BG0E03	TP117	1.30	0.45	0.48	0.70
BG0E04	TP121	0.31	1.50	2.11	2.56
BG0F01	TP131	1.51	2.75	3.05	4.11
BG0F02	TP131	1.25	1.91	2.60	2.85

APPENDIX A

PETROLOGICAL REPORT ON SAMPLES BG0E 01-04

A petrological examination has been carried out of four samples BG0E 01 to 04.

Polished blocks were prepared using particulate material crushed to a nominal size of -5mm . Representative material was made up into resin-bonded blocks. One face of each of these was ground flat and polished using diamond pastes. In addition, the surfaces were selectively etched with water and 0.1%N HCl in order to help with the phase identification.

The detailed results are given in the accompanying Table.

Samples 01, 02 and 03 consist largely of blast furnace slag and its alteration products.

Sample 04 is mainly basic steel slag whilst samples 01, 02 and 03 have very small, small and medium amounts respectively. Very little basic refractory material was seen.

Blast furnace slag

The unaltered blast furnace slag consists mainly of melilite (Ca,Mg,Al silicate). It is crystalline with crystals varying up to about 1mm in size. The matrix, the space between the melilite crystals, is partly occupied by silicate glass and partly with other silicates such as larnite ($\beta\text{-Ca}_2\text{SiO}_4$) and bredigite (Ca_2SiO_4 with some Mg in solid solution). Also, some spinel (MgAl_2O_4) occurs as a primary phase. The slag contains minor amounts of iron metal occurring as tiny globules and prills and, also, dendritic crystals of Ca,Mn sulphide. Secondary alteration is moderate. It is mainly restricted to pore infill and the formation of thin rinds and to the replacement of the matrix phases, especially the larnite. The secondary products are mostly finely granular and are difficult to identify specifically under the microscope. Some calcite (CaCO_3) is present but no well-crystallised gypsum ($\text{CaSO}_4 \cdot 2\text{H}_2\text{O}$) was seen.

Basic steel slag

The unaltered basic steel slag consists mainly of dicalcium silicate, tricalcium silicate, PO and R_2O_3 phases (FeO and Fe_2O_3 with some Al, Mn, Mg and Ca in solid solution) and CaF phases (complex Ca aluminoferrites). Individual particles vary considerably in composition. Lime phase (CaO with some Fe, Mn and Mg in solid solution) is present in substantial amounts. It occurs mainly as granular particles up to about 0.1 mm in size that are often packed together as macro-inclusions. Periclase (MgO with some Fe in solid solution) is uncommon. Some

metal is present as prills. The slag is extensively altered to secondary products that are difficult to identify specifically and are, probably, mainly hydrated silicates but also include some calcite (CaCO_3) and, probably, portlandite (Ca(OH)_2).

Other constituents

These include rare acid (silicic) slag, quartz, limestone, iron ore, iron ore sinter, metal and associated red (goethitic) rust, coke and fume. The particles are bonded together by cementitious material that is similar to the slag alteration products but probably also includes some clay. It consists mostly of complex hydrates difficult to identify under the optical microscope.

TRIS SAMPLES BGQE 01-04

	1	2	3	4
BLAST FURNACE SLAG				
<i>Amount</i>	L	L	L	S
<i>Phases present:-</i>				
Metallic	L	L	L	L
Lime & periclase	vs	vs	vs	
Matrix & other silicates	S	S	S	-
Ca & Fe sulphides	vs	vs	vs	-
Meta-iron	vs	vs	S	-
Spinel	S	S	S	-
Glassy slag	-	vs	S	-
Alteration products	m	m	L	m
Calcite	S	S	-	-
BASIC STEEL SLAG				
<i>Amount</i>	vs	S	m	L
<i>Phases present:-</i>				
Dicalcium silicate	-	m	m	m
Tricalcium silicate	-	-	S	-
R0 phase	vs	m	m	m
CaF phase	-	S	S	S
R3O4 phase	-	S	S	S
Metal & rust	-	S	S	vs
Lime phase	-	S	S	m
Periclase	vs	S	S	S
Alteration products	L	L		L
BASIC REFRACTORIES				
<i>Amount</i>	vs	vs	-	-
OTHER CONSTITUENTS				
Quartz, etc	S	vs	S	S
Acid (silicic) slag	vs	-	-	-
Metal, rust, scale, etc	S	S	S	S
Limestone & dolomite	-	vs	S	-
Iron ore, nonstone, etc	vs	vs	-	-
Coke	vs	vs	vs	vs
Cementitious alteration products	S	S	S	S

L = very large, l = large, m = medium, s = small and vs = very small amounts

GENERAL EXPLANATION

L = very large, l = large, m = medium, s = small and vs = very small amounts.

Blast furnace slag. When present this consists mainly of melite (Ca,Mg,Al silicate ranging in composition between $\text{Ca}_2\text{Al}_2\text{SiO}_7$ and $\text{Ca}_2\text{Mg}_2\text{SiO}_7$). Other common phases are merwinite ($\text{Ca}_2\text{MgSi}_2\text{O}_7$). The matrix often consists of some of the above phases, especially melite, but may also contain other phases such as wollastonite (CaSiO_3), anorthite ($\text{CaAl}_2\text{Si}_2\text{O}_7$) and pyroxene (CaMgSiO_3). Spinel (MgAl_2O_4) may be present. Sulphides and metal usually occur and are mostly finely dispersed, but the metal sometimes occurs as pits and may contain some graphite and Ti carbide (TiC). Material reported as ceramic in appearance is very finely crystalline. The alteration products often include talc and gypsum but are mostly silicate and/or sulphate hydrates that are difficult to identify specifically under the microscope.

Basic steel slag. When present this consists mainly of dicalcium silicate, mostly the β -form (larnite) but sometimes the α form. Phosphoric slags may contain nepselchinitite (Ca_2SiO_4 with $\text{Ca}_3\text{P}_2\text{O}_7$ in solid solution). Other silicate often present in small amounts, melted by H_2O , is probably melite. RO , R_2O and R_3O phases are typically present and are mainly FeO and Fe_2O_3 with some Mg, Mn, Cu, etc. in solid solution and complex Ca aluminoferrites. There may also be some Fe_3O_4 and spinel ($\text{Mg,FeAl}_2\text{O}_4$). The slag typically carries minor amounts of periclase (MgO with some Fe in solid solution) and lime phase (CaO with some Fe, Mn & Mg in solid solution). Other possible minor constituents include fluore (CaF_2) and apatite (Ca fluorophosphate), the last present in phosphoric slags. The alteration products are, again, difficult to identify specifically but are probably, mainly, hydrated silicates. Portlandite ($\text{Ca}(\text{OH})_2$) may be present.

Basic refractory material. When present, this is mainly magnesian and consists of granular periclase (MgO) with interstitial silicates. Sometimes samples contain chromite-magnesia material with chromite present in addition to the other phases. Hot face material (from close to the furnace) may also occur. The periclase and interstitial silicates show secondary alteration similar to that of the basic steel slag. Brucite ($\text{Mg}(\text{OH})_2$) is likely.

Acid steel slag. When present this consists mainly of fayalite ($\text{Fe,Mn}_2\text{SiO}_4$), Fe,Mn oxides and cristobalite (high temperature SiO_2).

Other slags. The 'intermediate slag' (probably primary flush slags from steel furnaces) has a variable phase assemblage, being mainly formed of silicates, particularly dicalcium silicate, melite, merwinite and a complex olivine phase together with corundum and wustite (FeO). Sometimes it contains significant amounts of periclase, well embedded in the slag. The 'ferrous slag' (probably from ladling operations) has similar silicates but much more substantial content of iron oxides, usually wustite. It is often associated with scale (iron oxides formed on the surface of steel during reheating/cooling). When present, the 'ferrous slag' consists of various silicates and silicate glass with Fe oxides, brucite ($\text{Fe}(\text{OH})_2$) and, sometimes, corundum (Al_2O_3). It is usually derived from heating furnaces and is often associated with burnt shale. When present, the 'silicious driver' is similar but devoid of iron oxides.

Other constituents The aluminosilicate brick includes a range of refractory firebrick, common brick and diamond-refractories. The quartz sandstone, etc. may include used silica refractory material consisting of quartz and high temperature forms. Sometimes there is a distinct granular texture and this is derived from silicate, a kind of chert. Generally this material may coat the finer particles together. It is similar to the other alteration products consisting mainly of amorphous hydrates difficult to identify under the microscope. Sometimes some is used Portland cement recognised by the total texture of the binder and the embedded quartz sand.

APPENDIX B

PETROLOGICAL REPORT ON SAMPLES BG0F 01 & 02

A petrological examination has been carried out of two samples BG0F 01 and 02.

Polished blocks were prepared using particulate material crushed to a nominal size of $\sim 5\text{mm}$. Representative material was made up into resin-bonded blocks. One face of each of these was ground flat and polished using diamond pastes. In addition, the surfaces were selectively etched with water and 0.1%N HCl in order to help with the phase identification.

The detailed results are given in the accompanying Table.

Both samples consist mainly of basic steel slag with small but significant amounts of basic refractory material.

There are small amounts of blast furnace slag and its alteration products.

Blast furnace slag

The unaltered blast furnace slag consists mainly of melilite (Ca,Mg,Al silicate). It is crystalline with crystals varying up to about 1mm in size. The matrix, the space between the melilite crystals, is partly occupied by silicate glass and partly with other silicates. Also, some spinel (MgAl_2O_4) occurs as a primary phase. The slag contains minor amounts of iron metal. Secondary alteration is moderate. It is mainly restricted to pore infill and the formation of thin rinds. The secondary products are mostly finely granular and are difficult to identify specifically under the microscope. Some calcite (CaCO_3) is present but no well-crystallised gypsum ($\text{CaSO}_4 \cdot 2\text{H}_2\text{O}$) was seen.

Basic steel slag

Although the individual particles vary considerably in composition the two samples are broadly similar to one another.

The unaltered basic steel slag consists mainly of dicalcium silicate, tricalcium silicate, RO, R_2O_3 and R \cdot O \cdot phases (FeO , Fe_2O_3 and Fe_3O_4 with some Al, Mn, Mg and Ca in solid solution), and CaF phases (complex Ca aluminoferrites). Lime phase (CaO with some Fe, Mn and Mg in solid solution) is present in substantial amounts and is widespread. It occurs mainly as granular particles up to about 0.1 mm in size that tends to be packed together as macro-inclusions. Periclase (MgO with some Fe in solid solution) is present in small amounts and like lime phase is widespread. It tends to be present in the grain cores protected by marginal RO phase that is more iron rich. Some metal is present as small prills partly rusted. The slag is extensively altered to secondary products that are

difficult to identify specifically and are, probably, mainly hydrated silicates but also include some calcite (CaCO_3).

Basic refractory material

This is mainly magnesian and consists of two types: (a) coarsely crystalline granular periclase (MgO) with bonding by magnesian silicates and (b) finely crystalline material probably seawater magnesia.

Other constituents

These include quartz, aluminosilicate brick, cinder, metal with associated red (goethitic) rust, coke, coal and fume. The particles are bonded together by cementitious material that is similar to the slag alteration products but probably also includes some clay. It consists mostly of complex hydrates difficult to identify under the optical microscope.

TRS SAMPLES BG0F 01 & 02

	1	2
BLAST FURNACE SLAG		
Amount	s	s
Phases present:-		
Melite	l	l
Matrix & other silicates	s	m
Metallic iron	-	vs
Spinel	-	s
Glassy slag	s	s
Alteration products	m	m
Cacite	-	s
BASIC STEEL SLAG		
Amount	l	l
Phases present:-		
Dicalcium silicate	l	m
Tricalcium silicate	-	s
Unclched silicate	-	s
RO phase	m	m
CaF phase	s	s
R3O4 & R2O3 phases	s	s
Metal & rust	s	s
Lime phase	s	s
Periclase	s	s
Alteration products	m	m
BASIC REFRACTORIES		
Amount	s	s
OTHER CONSTITUENTS		
Aluminosilicate brick	s	vs
Quartz etc	s	s
Cindery slag	vs	-
Fume	vs	vs
Metal rust scale etc	s	s
Coke	s	vs
Coal & char	s	-
Continuous alteration products	s	s

L = very large, l = large, m = medium, s = small and vs = very small amounts

GENERAL EXPLANATION

L = very large, l = large, m = medium, s = small and vs = very small amounts.

Blast furnace slag. When present this consists mainly of melilite (Ca/Mg,Al silicate ranging in composition between $\text{Ca}_2\text{Al}_2\text{Si}_2\text{O}_7$ and $\text{Ca}_2\text{MgSi}_2\text{O}_7$). Other common phases are merwinite ($\text{Ca}_2\text{Mg}_2\text{Si}_2\text{O}_7$). The matrix often consists of some of the above phases, especially melilite, but may also contain other phases such as wollastonite (CaSiO_3), anorthite ($\text{CaAl}_2\text{Si}_2\text{O}_7$) and pyroxene ($(\text{Ca/Mg})\text{SiO}_3$). Spinel (MgAl_2O_4) may be present. Sulphides and metal usually occur and are mostly finely dispersed, but the metal sometimes occurs as prills and may contain some graphite and Fe-carbo-nitride (FeCN). Material reported as ceramic in appearance is very finely crystalline. The alteration products often include talc and gypsum but are mostly silicate and/or sulpho-aluminate hydrates that are difficult to identify specifically under the microscope.

Basic steel slag. When present this consists mainly of dicalcium silicate, mostly the β -form (ferrite) but sometimes the α form. Phosphoric slags may contain nagelschmidite (Ca_2SiO_4 with $\text{Ca}_3\text{P}_2\text{O}_8$ in solid solution). Other silicates often present in small amounts, unetched by dilute HCl, is probably melilite, RO, R₂O, and RF phases and typically present and are mainly FeO and Fe₂O₃ with some Mg, Mn, Ca, etc. in solid solution and complex Ca aluminoferrites. There may also be some Fe₂O₃ and spinel ($(\text{Mg,Fe})\text{Al}_2\text{O}_4$). The slag typically carries minor amounts of pentase (MgO with some Fe in solid solution) and lime phase (CaO with some Fe, Mn & Mg in solid solution). Other possible minor constituents include fluoroite (CaF_2) and apatite (Ca fluorophosphate), the last present in phosphoric slags. The alteration products are, again, difficult to identify specifically but are probably, mainly, hydrated silicates. Portlandite ($\text{Ca}(\text{OH})_2$) may be present.

Basic refractory material. When present, this is mainly monocrystalline and consists of granular periclase (MgO) with interstitial silicates. Sometimes samples contain chromite-magnesia material with chromite present in addition to the other phases. Hot face material (from down to the hearth) may also occur. The periclase and interstitial silicates show secondary alteration similar to that of the basic steel slag. Brucite ($\text{Mg}(\text{OH})_2$) is likely.

Acid steel slag. When present this consists mainly of fayalite ($(\text{Fe,Mn})_2\text{SiO}_4$), Fe,Mn oxides and cristobalite (high temperature SiO_2).

Other slags. The 'intermediate slag' (probably primary flush slags from steel furnaces) has a variable phase assemblage, being mainly formed of silicates, particularly dicalcium silicate, melilite, merwinite and a complex olivine phase together with spinel and wustite (FeO). Sometimes it contains significant amounts of periclase, with embedded in the slag. The 'ferrous slag' (probably from foundry operations) has similar silicates but much more substantial content of iron oxides, usually wustite. It is often associated with scale (iron oxides formed on the surface of steel during reheating/cooking). When present, the 'foundry slag' consists of various silicates and silicate glass with Fe oxides, Fe₂SiO₄ (Fe₂Al₂O₇) and, sometimes, corundum (Al_2O_3). It is usually derived from heating furnaces and is often associated with burnt shale. When present, the 'siliceous comb' is similar but devoid of iron oxides.

Other constituents The starting silicate brick includes a range of refractory linings, commonly brick and some acid refractories. The quartz, sandstone, etc. may include used silica refractory material consisting of quartz and its high temperature forms. Sometimes there is a distinct quartz breccia and it is derived from siliceous sand of chert. Cementitious material may bind the brick particles together. This similar to the other alteration products consisting mostly of complex hydrates difficult to identify under the microscope but may include Portland cement, recognised by the typical features of the clinker and the embedded quartz sand.

APPENDIX C

MECHANISMS OF VOLUMETRIC INSTABILITY IN IRON AND STEEL INDUSTRY SLAGS

Volumetric change with time can occur in some types of iron and steel industry slags. These mechanisms are briefly described in this section.

Blast Furnace Slags

Fresh-make air-cooled, i.e. crystalline, blast furnace slags are almost always volumetrically stable after cooling. The two mechanisms for volumetric instability listed in BS1047:1983 – "Air Cooled Blast furnace Slag for use in Construction" are:-

- a) Beta to gamma inversion of dicalcium silicate.**
- b) Iron unsoundness.**

a) Research by G. H. Thomas on this phase transformation has shown the transformation to be athermal rather than isothermal. In practical terms this means that inversion, and the expansion associated with it, can only occur during the cooling cycle. In fully cooled material there would appear to be no further risk of instability from this mechanism.

b) Iron unsoundness is a very rare form of instability frequently associated with operating problems in the blast furnace. TRS know of only one instance in over 40 years. The mechanism, which is a hydrolysis reaction, is immediately triggered off by the presence of water. Once water has initiated the reaction, the mechanism proceeds to completion. It is impossible to arrest the process once started; at least by methods operating in normal ambient conditions.

It follows that the risk of late expansion from either of these mechanisms in blast furnace slag is remote.

c) Sulphoaluminate Type Activity

Some years ago, G. H. Thomas discovered a third mechanism that may give rise to volumetric instability. The process is possible only in some old blast furnace slag altered by weathering. When the sulphide sulphur in the blast furnace slag is oxidised during

weathering to sulphate, under some circumstances reactions can take place within the slag to produce an 'ettringite' type product. The process is somewhat analogous to sulphatic attack on concrete and has a similar result - expansion of the mass and associated disruption.

For the mechanism to have any significance, the slag needs to have residual potential for this reaction. Evidence of past activity does not necessarily indicate further reaction is possible.

The TRS accelerated expansion test is, we believe, uniquely capable of identifying such slags, as well as instability attributable to free CaO and free MgO in steel slag & etc.

Basic Steel Slags

Basic steel slags commonly contain significant quantities of free CaO and free MgO. These free oxides are well known for the massive expansion associated with their hydration. In practical terms, it is impossible to forecast when hydration will take place, but it can be up to decades after the material was cooled - or placed. The reasons are complex, but include the varying density of the oxides, due to the variation in temperatures at which the products have been held in the furnace. Other factors influencing rate of hydration include:-

- the protection of slags by a reaction product at the oxide interface with the slag,
- the presence of the oxides as lime or magnesia rich solid solutions instead of the pure oxide.

The result is potential future volumetric instability but at an unforeseeable date. Periclase, i.e. free MgO, is relatively much slower than free CaO to hydrate.

Scrap High Magnesia Refractories

These are particularly undesirable components in fill as they commonly result in high concentrations of free MgO. The problems associated with these concentrations are similar to those where periclase is found in basic steel slag.

**Specialist Chemical Testing
(Tested Externally)**



DETS

Certificate of Analysis

Certificate Number Combined 4251 Prairie

10-Nov-20

Client Allied Exploration & Geotechnics Limited
Unit 25
Stella Gill Industrial Estate
Pelton Fell
DH2 2RG

Our Reference Combined 4251 Prairie

Client Reference 4251

Order No (not supplied)

Contract Title Prairie Site Ground Investigation Works

Description 120 Soil samples, 24 Leachate samples, 42 Water samples.

Date Received 06-Apr-20

Date Started 06-Apr-20

Date Completed 10-Nov-20

Test Procedures Identified by prefix DETSn (details on request).

Notes Opinions and interpretations are outside the laboratory's scope of ISO 17025 accreditation. This certificate is issued in accordance with the accreditation requirements of the United Kingdom Accreditation Service. The results reported herein relate only to the material supplied to the laboratory. This certificate shall not be reproduced except in full, without the prior written approval of the laboratory.

Approved By



Adam Fenwick
Contracts Manager





Summary of Chemical Analysis

Matrix Descriptions

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Sample ID	Other ID	Depth	Lab No	Completed	Matrix Description
PRAIRIE_AUK_TP13 2	4	1.3	1663605	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP13 1	5	1.8	1663606	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP10 1	5	1	1663734	05/08/2020	Dark brown gravelly SAND (Possible made ground - brick)
PRAIRIE_AUK_TP10 1	9	2.2	1663735	05/08/2020	Dark brown sandy, clayey GRAVEL (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP10 4	5	1.5	1663736	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP10 5	11	2.5	1663737	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_BH10 4	1	5.5	1663978	05/08/2020	Dark brown gravelly, sandy CLAY
PRAIRIE_AUK_TP17 2	3	0.8	1665133	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP17 5	3	0.8	1665134	05/08/2020	Dark brown sandy GRAVEL (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP17 5	6	1.8	1665135	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP17 8	3	0.8	1665136	05/08/2020	Dark brown sandy GRAVEL (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_BH10 6	1	5.5	1665137	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP10 7	6	1.8	1665138	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP10 7	11	0.8	1665139	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP10 8	5	1	1665140	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP10 8	8	2	1665141	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP11 3	5	1.3	1665142	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_BH10 3	1	2.5	1665286	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP11 5	6	1.9	1665288	05/08/2020	Dark grey sandy GRAVEL (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP12 2	3	1	1665290	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP12 3	3	0.6	1665291	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_TP18 5	5	4.3	1665292	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP18 6	3	0.5	1665293	05/08/2020	Dark brown gravelly, sandy CLAY (Possible made ground - brick)
PRAIRIE_AUK_TP18 8	3	1	1665295	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP12 1	4	1.5	1665450	05/08/2020	Dark brown sandy, clayey GRAVEL (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP13 8	3	1.2	1665451	05/08/2020	Dark brown gravelly SAND (Possible made ground - brick)
PRAIRIE_AUK_TP14 9	3	1.3	1665452	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_TP16 8	1	0.05	1665453	05/08/2020	Dark brown gravelly, clayey SAND



Summary of Chemical Analysis

Matrix Descriptions

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Sample ID	Other ID	Depth	Lab No	Completed	Matrix Description
PRAIRIE_AUK_TP17 3	3	0.9	1665454	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_SURF ACE1	1	0	1665455	05/08/2020	Cream, gravelly, sandy and CLAY
PRAIRIE_AUK_TP11 4	6	0.9	1665588	05/08/2020	U/S (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP12 4	5	1.5	1665589	05/08/2020	Dark brown gravelly, very sandy CLAY
PRAIRIE_AUK_TP17 4	3	0.8	1665590	05/08/2020	Dark brown gravelly, very sandy CLAY
PRAIRIE_AUK_TP17 4	6	1.6	1665591	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP17 6	3	0.9	1665592	05/08/2020	Dark brown gravelly, very sandy CLAY
PRAIRIE_AUK_TP17 7	2	0.6	1665593	05/08/2020	Dark brown gravelly, very sandy CLAY
PRAIRIE_AUK_TP18 9	7	3	1665594	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP17 9	4	1.4	1665610	05/08/2020	U/S (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP17 9	7	2	1665611	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP18 1	3	0.6	1665612	05/08/2020	Dark brown gravelly, very, sandy CLAY
PRAIRIE_AUK_TP18 2	3	0.9	1665613	05/08/2020	U/S (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP14 5	4	1.6	1665990	05/08/2020	Dark brown gravelly, sandy CLAY
PRAIRIE_AUK_TP14 6C	5	1.3	1665991	05/08/2020	Dark brown gravelly, sandy CLAY
PRAIRIE_AUK_TP15 6A	2	0.3	1665992	05/08/2020	Dark brown gravelly, very sandy CLAY
PRAIRIE_AUK_TP16 2	3A	1.7	1665993	05/08/2020	Dark brown gravelly, very sandy CLAY including some rootlets
PRAIRIE_AUK_TP18 0	3	0.3	1665994	05/08/2020	Dark brown gravelly, very sandy CLAY including some rootlets
PRAIRIE_AUK_TP16 3	3	1.2	1665995	05/08/2020	U/S (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP13 5	5	1.3	1666343	05/08/2020	Dark brown clayey, sandy GRAVEL (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP13 6	3	0.8	1666344	05/08/2020	Dark brown sandy, clayey GRAVEL (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP13 6	10	2.9	1666345	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP16 5	3	1	1666346	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_TP16 7	6	2.5	1666347	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_TP16 9	3	1.5	1666348	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_BH10 8	1	2.5	1666610	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP13 9B	3	0.3	1666611	05/08/2020	Dark brown very sandy GRAVEL (Possible made ground - brick) (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP13 9B	6	3.3	1666612	05/08/2020	Dark brown sandy CLAY



Summary of Chemical Analysis

Matrix Descriptions

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Sample ID	Other ID	Depth	Lab No	Completed	Matrix Description
PRAIRIE_AUK_TP148A	5	1.4	1666613	05/08/2020	Dark brown very sandy GRAVEL (Possible made ground - brick) (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP150	3	1.5	1666614	05/08/2020	Dark brown very sandy GRAVEL (Possible made ground - brick) (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP159	3	0.6	1666615	05/08/2020	Dark brown very sandy GRAVEL (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP190A	3	1.1	1666616	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_BH105	1	3	1667231	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP126	5	2.6	1667232	05/08/2020	Dark brown gravelly, sandy CLAY
PRAIRIE_AUK_TP128	3	0.9	1667233	05/08/2020	U/S (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP129	4A	2.1	1667234	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP130	4A	1	1667235	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_TP147	4	1.5	1667236	05/08/2020	Dark brown gravelly, sandy CLAY
PRAIRIE_AUK_TP158	3	1.3	1667237	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_TP157	2	0.8	1667238	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_TP120A	3	1	1667501	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP134	3	1	1667502	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP134	6	2	1667503	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP161	3	1	1667504	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP166	3	0.45	1667505	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP166	8	1.2	1667506	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP171	3	0.75	1667507	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP187	3	0.7	1667508	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_BH110	1	3	1668118	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP102	4	1	1668119	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP102	11	3	1668120	05/08/2020	Dark brown gravelly, sandy CLAY
PRAIRIE_AUK_TP103	3	1	1668121	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP109	3	1	1668122	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP110	3	1	1668123	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP110	7	2	1668124	05/08/2020	Dark brown gravelly, sandy CLAY
PRAIRIE_AUK_TP111	4	1.5	1668125	05/08/2020	Dark brown gravelly SAND



Summary of Chemical Analysis

Matrix Descriptions

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Sample ID	Other ID	Depth	Lab No	Completed	Matrix Description
PRAIRIE_AUK_TP112	4	1.5	1668126	05/08/2020	Dark brown gravelly SAND (Possible made ground - brick)
PRAIRIE_AUK_TP119	3	1.5	1668127	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP119	7	2.5	1668128	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP133	2	0.5	1668129	05/08/2020	Dark brown, gravelly SAND
PRAIRIE_AUK_TP152	6	2	1668130	05/08/2020	Dark brown gravelly, very sandy CLAY
PRAIRIE_AUK_TP153	4	1.1	1668131	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP154	3	0.85	1668132	05/08/2020	Dark brown very gravelly SAND
PRAIRIE_AUK_TP155	3	0.7	1668133	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP160	4	0.75	1668134	05/08/2020	Dark brown gravelly SAND (Possible made ground - brick)
PRAIRIE_AUK_TP170	4	1	1668135	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_TP164	3	0.7	1668557	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP164	5	1.3	1668558	05/08/2020	Dark brown gravelly, slightly clayey SAND
PRAIRIE_AUK_TP184	2	0.3	1668559	05/08/2020	Dark brown sandy GRAVEL including odd rootlets (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP106	3	1	1668560	05/08/2020	Dark brown gravelly, sandy CLAY
PRAIRIE_AUK_TP116	3	1.3	1668561	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_TP117	8	3	1668562	05/08/2020	Dark brown sandy, clayey GRAVEL (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP118	3	1.2	1668563	05/08/2020	Dark brown gravelly SAND
PRAIRIE_AUK_TP127	3	0.3	1668564	05/08/2020	Dark brown gravelly SAND (Possible made ground - brick)
PRAIRIE_AUK_TP127A	3	2.8	1668565	05/08/2020	Brown sandy CLAY
PRAIRIE_AUK_TP140	3	1	1668566	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_TP141	4	2	1668567	05/08/2020	U/S (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP142	3	0.9	1668568	05/08/2020	U/S (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP142	4	1.5	1668569	05/08/2020	U/S (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP143	3	0.8	1668570	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_TP143	6	1.6	1668571	05/08/2020	Dark brown gravelly, sandy CLAY
PRAIRIE_AUK_TP151	5	1.2	1668572	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_TP139	4	1.1	1668657	05/08/2020	Dark brown very gravelly, sandy CLAY
PRAIRIE_AUK_TP144	3	0.8	1668869	05/08/2020	Dark brown very sandy, clayey GRAVEL (sample matrix outside MCERTS scope of accreditation)



Summary of Chemical Analysis

Matrix Descriptions

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Sample ID	Other ID	Depth	Lab No	Completed	Matrix Description
PRAIRIE_AUK_TP11 2	7	2.1	1669251	05/08/2020	Dark brown sandy GRAVEL (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP19 4A	1	1.4	1670142	05/08/2020	U/S (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP19 6A	1	1.4	1670143	05/08/2020	U/S (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_TP20 1	1	3.6	1670144	05/08/2020	Dark brown gravelly, clayey SAND
PRAIRIE_AUK_TP19 3	1	0.8	1670502	05/08/2020	U/S (sample matrix outside MCERTS scope of accreditation)
PRAIRIE_AUK_BH10 1	1	3	1675450	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_BH10 7	1	3	1675451	05/08/2020	Dark brown sandy CLAY
PRAIRIE_AUK_SW4	1	0	1700277	05/08/2020	Dark grey very gravelly SAND



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1663605	1663606	1663734	1663735	1663736
Sample ID	PRAIRIE_AUK_TP132	PRAIRIE_AUK_TP131	PRAIRIE_AUK_TP101	PRAIRIE_AUK_TP101	PRAIRIE_AUK_TP104
Depth	1.30	1.80	1.00	2.20	1.50
Other ID	4	5	5	9	5
Sample Type	ES	ES	ES	ES	ES
Sampling Date	02/04/2020	02/04/2020	01/04/2020	01/04/2020	01/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Asbestos Quantification	DETSC 1102	0.001	%			0.001		
Metals								
Aluminium	DETSC 2301*	1	mg/kg	12000	15000	36000	32000	31000
Antimony	DETSC 2301*	1	mg/kg	7.7	9.1	1.4	1.5	3.4
Arsenic	DETSC 2301#	0.2	mg/kg	5.2	13	13	18	23
Barium	DETSC 2301#	1.5	mg/kg	220	1300	390	280	390
Beryllium	DETSC 2301#	0.2	mg/kg	0.7	1.4	4.4	4.0	3.5
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	5.4	1.3	3.1	4.3	3.4
Cadmium	DETSC 2301#	0.1	mg/kg	0.4	0.3	0.4	0.5	0.5
Chromium	DETSC 2301#	0.15	mg/kg	410	620	30	39	120
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	36	100	55	54	61
Iron	DETSC 2301	25	mg/kg	140000	99000	18000	31000	56000
Lead	DETSC 2301#	0.3	mg/kg	88	46	330	89	110
Magnesium	DETSC 2301*	1	mg/kg	41000	33000	23000	14000	25000
Manganese	DETSC 2301#	20	mg/kg	18000	17000	2900	1500	7700
Mercury	DETSC 2325#	0.05	mg/kg	< 0.05	0.07	0.25	0.24	0.34
Molybdenum	DETSC 2301#	0.4	mg/kg	3.9	1.5	1.0	1.6	1.4
Nickel	DETSC 2301#	1	mg/kg	17	12	9.7	23	21
Silicon	DETSC 2301*	10	mg/kg	42000	46000	67000	120000	64000
Vanadium	DETSC 2301#	0.8	mg/kg	430	3300	74	91	290
Zinc	DETSC 2301#	1	mg/kg	130	56	170	200	180
Inorganics								
Loss on Ignition at 440oC	DETSC 2003#	0.01	%					
pH	DETSC 2008#		pH	12.2	12.1	10.0	10.1	10.9
Calorific Value	DETSC 5008	1	MJ/kg					
Cyanide, Total	DETSC 2130#	0.1	mg/kg	0.7	0.4	0.6	0.2	0.3
Cyanide, Free	DETSC 2130#	0.1	mg/kg	< 0.1	< 0.1	< 0.1	< 0.1	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	< 0.6	< 0.6	2.4	0.7	< 0.6
Organic matter	DETSC 2002#	0.1	%	1.0	1.6	4.5	2.8	2.4
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	17	24	850	590	490
Sulphur (free)	DETSC 3049#	0.75	mg/kg	< 0.75	1.9	120	16	5.0



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1663605	1663606	1663734	1663735	1663736
Sample ID	PRAIRIE_AUK_ TP132	PRAIRIE_AUK_ TP131	PRAIRIE_AUK_ TP101	PRAIRIE_AUK_ TP101	PRAIRIE_AUK_ TP104
Depth	1.30	1.80	1.00	2.20	1.50
Other ID	4	5	5	9	5
Sample Type	ES	ES	ES	ES	ES
Sampling Date	02/04/2020	02/04/2020	01/04/2020	01/04/2020	01/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Petroleum Hydrocarbons								
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	2.7	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	4.9	< 1.5	< 1.5	3.6	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	43	11	< 3.4	20	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	48	12	< 10	27	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	1.1	< 0.9	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	1.1	< 0.5	0.5	< 0.5	< 0.5
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	1.9	< 0.6	19	1.5	< 0.6
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	7.7	< 1.4	38	16	< 1.4
Aromatic C5-C35	DETSC 3072*	10	mg/kg	12	< 10	58	18	< 10
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	60	12	58	45	< 10
EPH (C10-C40)	DETSC 3311#	10	mg/kg	290	68	1100	110	120
PAHs								
Naphthalene	DETSC 3303#	0.03	mg/kg	0.08	< 0.03	0.09	0.08	< 0.03
Acenaphthylene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	0.05	< 0.03	< 0.03
Acenaphthene	DETSC 3303#	0.03	mg/kg	0.09	< 0.03	1.4	0.15	0.05
Fluorene	DETSC 3303	0.03	mg/kg	< 0.03	< 0.03	1.4	0.11	0.06
Phenanthrene	DETSC 3303#	0.03	mg/kg	1.6	0.42	22	1.1	1.1
Anthracene	DETSC 3303	0.03	mg/kg	0.08	0.08	2.7	0.21	0.14
Fluoranthene	DETSC 3303#	0.03	mg/kg	1.4	0.97	37	1.4	1.9
Pyrene	DETSC 3303#	0.03	mg/kg	0.91	0.74	31	1.0	1.6
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	0.24	0.33	7.8	0.39	0.66
Chrysene	DETSC 3303	0.03	mg/kg	0.44	0.40	7.1	0.49	0.79
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	0.44	0.45	6.7	0.36	0.75
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.18	0.18	2.6	0.15	0.31
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	0.14	0.22	3.7	0.23	0.43
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.14	0.13	2.0	0.10	0.20
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	0.04	0.04	0.55	0.03	0.06
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	0.19	0.16	2.3	0.11	0.27
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	6.0	4.1	130	5.9	8.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1663605	1663606	1663734	1663735	1663736
PRAIRIE_AUK_	PRAIRIE_AUK_	PRAIRIE_AUK_	PRAIRIE_AUK_	PRAIRIE_AUK_	PRAIRIE_AUK_
Sample ID	TP132	TP131	TP101	TP101	TP104
Depth	1.30	1.80	1.00	2.20	1.50
Other ID	4	5	5	9	5
Sample Type	ES	ES	ES	ES	ES
Sampling Date	02/04/2020	02/04/2020	01/04/2020	01/04/2020	01/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units						
PCBs									
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg						
PCB 52	DETSC 3401#	0.01	mg/kg						
PCB 101	DETSC 3401#	0.01	mg/kg						
PCB 118	DETSC 3401#	0.01	mg/kg						
PCB 153	DETSC 3401#	0.01	mg/kg						
PCB 138	DETSC 3401#	0.01	mg/kg						
PCB 180	DETSC 3401#	0.01	mg/kg						
PCB 7 Total	DETSC 3401#	0.01	mg/kg						
Phenols									
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	0.4	0.3	0.4	< 0.3	< 0.3	



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1663737	1663978	1665133	1665134
Sample ID	PRAIRIE_AUK_TP105	PRAIRIE_AUK_BH104	PRAIRIE_AUK_TP172	PRAIRIE_AUK_TP175
Depth	2.50	5.50	0.80	0.80
Other ID	11	1	3	3
Sample Type	ES	ES	ES	ES
Sampling Date	01/04/2020	03/04/2020	06/04/2020	06/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Asbestos Quantification	DETSC 1102	0.001	%			0.001	
Metals							
Aluminium	DETSC 2301*	1	mg/kg	16000	9700	12000	18000
Antimony	DETSC 2301*	1	mg/kg	2.0	< 1.0	1.9	3.7
Arsenic	DETSC 2301#	0.2	mg/kg	14	5.9	20	13
Barium	DETSC 2301#	1.5	mg/kg	400	120	650	350
Beryllium	DETSC 2301#	0.2	mg/kg	1.7	0.7	1.5	2.8
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	2.2	1.1	7.7	3.3
Cadmium	DETSC 2301#	0.1	mg/kg	0.4	0.1	1.4	0.6
Chromium	DETSC 2301#	0.15	mg/kg	38	20	19	130
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	44	19	95	54
Iron	DETSC 2301	25	mg/kg	46000	24000	34000	57000
Lead	DETSC 2301#	0.3	mg/kg	45	11	120	1500
Magnesium	DETSC 2301*	1	mg/kg	7900	11000	8800	12000
Manganese	DETSC 2301#	20	mg/kg	1100	450	38000	8400
Mercury	DETSC 2325#	0.05	mg/kg	0.09	< 0.05	4.1	0.37
Molybdenum	DETSC 2301#	0.4	mg/kg	1.1	0.8	2.7	1.8
Nickel	DETSC 2301#	1	mg/kg	38	23	25	18
Silicon	DETSC 2301*	10	mg/kg	180000	120000	80000	79000
Vanadium	DETSC 2301#	0.8	mg/kg	48	28	39	280
Zinc	DETSC 2301#	1	mg/kg	160	48	280	170
Inorganics							
Loss on Ignition at 440oC	DETSC 2003#	0.01	%				
pH	DETSC 2008#		pH	9.1	8.1	10.0	10.4
Calorific Value	DETSC 5008	1	MJ/kg				
Cyanide, Total	DETSC 2130#	0.1	mg/kg	< 0.1	< 0.1	52	6.7
Cyanide, Free	DETSC 2130#	0.1	mg/kg	< 0.1	< 0.1	0.5	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	0.6	< 0.6	3.6	0.9
Organic matter	DETSC 2002#	0.1	%	1.4	1.0	4.4	3.1
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	770	100	450	390
Sulphur (free)	DETSC 3049#	0.75	mg/kg	8.0	< 0.75	15	1000



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1663737	1663978	1665133	1665134
Sample ID	PRAIRIE_AUK_TP105	PRAIRIE_AUK_BH104	PRAIRIE_AUK_TP172	PRAIRIE_AUK_TP175
Depth	2.50	5.50	0.80	0.80
Other ID	11	1	3	3
Sample Type	ES	ES	ES	ES
Sampling Date	01/04/2020	03/04/2020	06/04/2020	06/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Petroleum Hydrocarbons							
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	0.13
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	2.1
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	93
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	350
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	< 3.4	< 3.4	67
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	510
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	0.15
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	0.22
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	1.3
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	2.1	< 0.9	< 0.9	250
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	3.1	< 0.5	2.3	2100
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	7.6	< 0.6	21	830
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	9.7	< 1.4	33	210
Aromatic C5-C35	DETSC 3072*	10	mg/kg	23	< 10	57	3400
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	23	< 10	57	3900
EPH (C10-C40)	DETSC 3311#	10	mg/kg	78	< 10	360	10000
PAHs							
Naphthalene	DETSC 3303#	0.03	mg/kg	0.06	< 0.03	0.35	24
Acenaphthylene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	0.92	19
Acenaphthene	DETSC 3303#	0.03	mg/kg	0.62	< 0.03	0.99	98
Fluorene	DETSC 3303	0.03	mg/kg	0.57	< 0.03	1.6	74
Phenanthrene	DETSC 3303#	0.03	mg/kg	3.1	< 0.03	8.0	98
Anthracene	DETSC 3303	0.03	mg/kg	0.53	< 0.03	8.0	30
Fluoranthene	DETSC 3303#	0.03	mg/kg	3.0	< 0.03	12	41
Pyrene	DETSC 3303#	0.03	mg/kg	2.3	< 0.03	11	30
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	0.74	< 0.03	6.5	13
Chrysene	DETSC 3303	0.03	mg/kg	0.85	< 0.03	4.8	12
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	0.92	< 0.03	5.6	12
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.30	< 0.03	2.8	59
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	0.55	< 0.03	3.9	120
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.28	< 0.03	2.4	53
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	0.08	< 0.03	0.61	15
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	0.35	< 0.03	2.9	64
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	14	< 0.10	72	760



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1663737	1663978	1665133	1665134
Sample ID	PRAIRIE_AUK_TP105	PRAIRIE_AUK_BH104	PRAIRIE_AUK_TP172	PRAIRIE_AUK_TP175
Depth	2.50	5.50	0.80	0.80
Other ID	11	1	3	3
Sample Type	ES	ES	ES	ES
Sampling Date	01/04/2020	03/04/2020	06/04/2020	06/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
PCBs							
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg				
PCB 52	DETSC 3401#	0.01	mg/kg				
PCB 101	DETSC 3401#	0.01	mg/kg				
PCB 118	DETSC 3401#	0.01	mg/kg				
PCB 153	DETSC 3401#	0.01	mg/kg				
PCB 138	DETSC 3401#	0.01	mg/kg				
PCB 180	DETSC 3401#	0.01	mg/kg				
PCB 7 Total	DETSC 3401#	0.01	mg/kg				
Phenols							
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	< 0.3	1.4	< 0.3	5.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665135	1665136	1665137	1665138
Sample ID	PRAIRIE_AUK_ TP175	PRAIRIE_AUK_ TP178	PRAIRIE_AUK_ BH106	PRAIRIE_AUK_ TP107
Depth	1.80	0.80	5.50	1.80
Other ID	6	3	1	6
Sample Type	ES	ES	ES	ES
Sampling Date	06/04/2020	06/04/2020	06/04/2020	06/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Asbestos Quantification	DETSC 1102	0.001	%				
Metals							
Aluminium	DETSC 2301*	1	mg/kg	14000	16000	15000	12000
Antimony	DETSC 2301*	1	mg/kg	1.2	2.4	1.5	4.8
Arsenic	DETSC 2301#	0.2	mg/kg	8.4	18	6.4	33
Barium	DETSC 2301#	1.5	mg/kg	340	250	160	270
Beryllium	DETSC 2301#	0.2	mg/kg	1.2	2.2	1.2	2.6
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	0.8	1.5	1.1	2.3
Cadmium	DETSC 2301#	0.1	mg/kg	0.2	0.4	0.2	1.4
Chromium	DETSC 2301#	0.15	mg/kg	28	18	52	90
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	31	91	32	120
Iron	DETSC 2301	25	mg/kg	35000	70000	32000	87000
Lead	DETSC 2301#	0.3	mg/kg	30	70	20	120
Magnesium	DETSC 2301*	1	mg/kg	6000	5900	14000	7400
Manganese	DETSC 2301#	20	mg/kg	900	670	1200	3200
Mercury	DETSC 2325#	0.05	mg/kg	0.19	0.13	0.78	0.07
Molybdenum	DETSC 2301#	0.4	mg/kg	< 0.4	3.6	0.6	4.0
Nickel	DETSC 2301#	1	mg/kg	34	41	25	58
Silicon	DETSC 2301*	10	mg/kg	180000	66000	140000	50000
Vanadium	DETSC 2301#	0.8	mg/kg	33	96	150	280
Zinc	DETSC 2301#	1	mg/kg	83	160	69	350
Inorganics							
Loss on Ignition at 440oC	DETSC 2003#	0.01	%		26		
pH	DETSC 2008#		pH	8.4	8.0	11.1	9.7
Calorific Value	DETSC 5008	1	MJ/kg		13.5		
Cyanide, Total	DETSC 2130#	0.1	mg/kg	2.0	2.5	0.2	1.6
Cyanide, Free	DETSC 2130#	0.1	mg/kg	< 0.1	< 0.1	< 0.1	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	< 0.6	< 0.6	< 0.6	< 0.6
Organic matter	DETSC 2002#	0.1	%	3.2	12	1.9	13
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	35	61	310	200
Sulphur (free)	DETSC 3049#	0.75	mg/kg	< 0.75	< 0.75	0.92	< 0.75



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665135	1665136	1665137	1665138
Sample ID	PRAIRIE_AUK_ TP175	PRAIRIE_AUK_ TP178	PRAIRIE_AUK_ BH106	PRAIRIE_AUK_ TP107
Depth	1.80	0.80	5.50	1.80
Other ID	6	3	1	6
Sample Type	ES	ES	ES	ES
Sampling Date	06/04/2020	06/04/2020	06/04/2020	06/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Petroleum Hydrocarbons							
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	0.37	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	7.2	< 1.2	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	31	< 1.5	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	< 3.4	< 3.4	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	39	< 10	< 10	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	0.48	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	0.24	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	0.64	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	85	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	310	< 0.5	< 0.5	< 0.5
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	160	< 0.6	< 0.6	< 0.6
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	96	< 1.4	< 1.4	< 1.4
Aromatic C5-C35	DETSC 3072*	10	mg/kg	650	< 10	< 10	< 10
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	690	< 10	< 10	< 10
EPH (C10-C40)	DETSC 3311#	10	mg/kg	1200	< 10	< 10	< 10
PAHs							
Naphthalene	DETSC 3303#	0.03	mg/kg	440	0.06	0.11	0.06
Acenaphthylene	DETSC 3303#	0.03	mg/kg	31	0.03	< 0.03	0.04
Acenaphthene	DETSC 3303#	0.03	mg/kg	340	0.09	0.13	0.07
Fluorene	DETSC 3303	0.03	mg/kg	220	0.09	0.12	0.06
Phenanthrene	DETSC 3303#	0.03	mg/kg	290	0.12	0.22	0.42
Anthracene	DETSC 3303	0.03	mg/kg	53	< 0.03	0.03	0.08
Fluoranthene	DETSC 3303#	0.03	mg/kg	87	0.11	0.13	1.2
Pyrene	DETSC 3303#	0.03	mg/kg	62	0.08	0.10	1.1
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	27	0.07	0.05	0.71
Chrysene	DETSC 3303	0.03	mg/kg	23	0.06	0.05	0.66
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	23	0.06	0.05	1.0
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	10	< 0.03	< 0.03	0.41
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	20	0.04	0.03	0.54
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	8.6	< 0.03	< 0.03	0.31
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	2.5	< 0.03	< 0.03	0.10
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	10	< 0.03	< 0.03	0.35
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	1700	0.76	0.97	7.1



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1665135	1665136	1665137	1665138
Sample ID	PRAIRIE_AUK_ TP175	PRAIRIE_AUK_ TP178	PRAIRIE_AUK_ BH106	PRAIRIE_AUK_ TP107
Depth	1.80	0.80	5.50	1.80
Other ID	6	3	1	6
Sample Type	ES	ES	ES	ES
Sampling Date	06/04/2020	06/04/2020	06/04/2020	06/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
PCBs							
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg				
PCB 52	DETSC 3401#	0.01	mg/kg				
PCB 101	DETSC 3401#	0.01	mg/kg				
PCB 118	DETSC 3401#	0.01	mg/kg				
PCB 153	DETSC 3401#	0.01	mg/kg				
PCB 138	DETSC 3401#	0.01	mg/kg				
PCB 180	DETSC 3401#	0.01	mg/kg				
PCB 7 Total	DETSC 3401#	0.01	mg/kg				
Phenols							
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	3.9	0.5	< 0.3	< 0.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665139	1665140	1665141	1665142
Sample ID	PRAIRIE_AUK_ TP107	PRAIRIE_AUK_ TP108	PRAIRIE_AUK_ TP108	PRAIRIE_AUK_ TP113
Depth	0.80	1.00	2.00	1.30
Other ID	11	5	8	5
Sample Type	ES	ES	ES	ES
Sampling Date	06/04/2020	06/04/2020	06/04/2020	06/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Asbestos Quantification	DETSC 1102	0.001	%		0.001	0.002	0.006
Metals							
Aluminium	DETSC 2301*	1	mg/kg	12000	23000	10000	21000
Antimony	DETSC 2301*	1	mg/kg	< 1.0	5.3	11	4.5
Arsenic	DETSC 2301#	0.2	mg/kg	9.2	11	31	18
Barium	DETSC 2301#	1.5	mg/kg	290	650	830	320
Beryllium	DETSC 2301#	0.2	mg/kg	1.2	2.3	1.0	2.7
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	2.6	1.5	1.9	4.3
Cadmium	DETSC 2301#	0.1	mg/kg	0.2	1.5	5.8	1.3
Chromium	DETSC 2301#	0.15	mg/kg	25	340	620	150
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	23	40	89	72
Iron	DETSC 2301	25	mg/kg	33000	57000	100000	75000
Lead	DETSC 2301#	0.3	mg/kg	36	120	320	140
Magnesium	DETSC 2301*	1	mg/kg	3800	21000	23000	18000
Manganese	DETSC 2301#	20	mg/kg	440	14000	16000	7800
Mercury	DETSC 2325#	0.05	mg/kg	< 0.05	0.06	0.06	0.08
Molybdenum	DETSC 2301#	0.4	mg/kg	0.7	3.5	6.7	2.3
Nickel	DETSC 2301#	1	mg/kg	30	16	40	24
Silicon	DETSC 2301*	10	mg/kg	190000	54000	49000	63000
Vanadium	DETSC 2301#	0.8	mg/kg	40	950	1600	280
Zinc	DETSC 2301#	1	mg/kg	98	230	520	280
Inorganics							
Loss on Ignition at 440oC	DETSC 2003#	0.01	%		8.1	4.8	
pH	DETSC 2008#		pH	8.6	11.7	11.9	11.3
Calorific Value	DETSC 5008	1	MJ/kg		< 1.0	< 1.0	
Cyanide, Total	DETSC 2130#	0.1	mg/kg	22	0.5	0.7	5.9
Cyanide, Free	DETSC 2130#	0.1	mg/kg	0.1	< 0.1	< 0.1	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	< 0.6	< 0.6	< 0.6	< 0.6
Organic matter	DETSC 2002#	0.1	%	1.2	1.4	1.9	4.0
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	270	330	160	320
Sulphur (free)	DETSC 3049#	0.75	mg/kg	< 0.75	5.3	3.5	2.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665139	1665140	1665141	1665142
Sample ID	PRAIRIE_AUK_ TP107	PRAIRIE_AUK_ TP108	PRAIRIE_AUK_ TP108	PRAIRIE_AUK_ TP113
Depth	0.80	1.00	2.00	1.30
Other ID	11	5	8	5
Sample Type	ES	ES	ES	ES
Sampling Date	06/04/2020	06/04/2020	06/04/2020	06/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Petroleum Hydrocarbons							
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	31	13	46
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	32	14	46
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	< 0.5	1.6	0.8
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	< 0.6	5.1	7.9	7.1
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	< 1.4	67	36	76
Aromatic C5-C35	DETSC 3072*	10	mg/kg	< 10	72	46	84
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	< 10	100	60	130
EPH (C10-C40)	DETSC 3311#	10	mg/kg	< 10	420	180	230
PAHs							
Naphthalene	DETSC 3303#	0.03	mg/kg	0.23	0.06	0.20	0.21
Acenaphthylene	DETSC 3303#	0.03	mg/kg	0.06	0.03	0.56	0.15
Acenaphthene	DETSC 3303#	0.03	mg/kg	0.14	0.15	0.48	0.13
Fluorene	DETSC 3303	0.03	mg/kg	0.17	0.13	0.94	0.23
Phenanthrene	DETSC 3303#	0.03	mg/kg	0.44	1.3	4.2	1.8
Anthracene	DETSC 3303	0.03	mg/kg	0.07	0.30	1.9	0.52
Fluoranthene	DETSC 3303#	0.03	mg/kg	0.57	4.1	9.7	5.0
Pyrene	DETSC 3303#	0.03	mg/kg	0.46	4.2	8.6	6.0
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	0.26	3.3	7.8	3.0
Chrysene	DETSC 3303	0.03	mg/kg	0.28	2.1	4.8	2.3
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	0.32	4.0	12	3.1
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.13	1.8	6.2	1.2
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	0.21	2.4	8.4	2.3
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.10	1.1	3.1	0.79
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	< 0.03	0.28	0.72	0.23
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	0.11	1.3	2.9	1.0
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	3.5	26	73	28



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1665139	1665140	1665141	1665142
Sample ID	PRAIRIE_AUK_ TP107	PRAIRIE_AUK_ TP108	PRAIRIE_AUK_ TP108	PRAIRIE_AUK_ TP113
Depth	0.80	1.00	2.00	1.30
Other ID	11	5	8	5
Sample Type	ES	ES	ES	ES
Sampling Date	06/04/2020	06/04/2020	06/04/2020	06/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
PCBs							
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg				
PCB 52	DETSC 3401#	0.01	mg/kg				
PCB 101	DETSC 3401#	0.01	mg/kg				
PCB 118	DETSC 3401#	0.01	mg/kg				
PCB 153	DETSC 3401#	0.01	mg/kg				
PCB 138	DETSC 3401#	0.01	mg/kg				
PCB 180	DETSC 3401#	0.01	mg/kg				
PCB 7 Total	DETSC 3401#	0.01	mg/kg				
Phenols							
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	< 0.3	< 0.3	< 0.3	< 0.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665286	1665288	1665290	1665291
Sample ID	PRAIRIE_AUK_ BH103	PRAIRIE_AUK_ TP115	PRAIRIE_AUK_ TP122	PRAIRIE_AUK_ TP123
Depth	2.50	1.90	1.00	0.60
Other ID	1	6	3	3
Sample Type	ES	ES	ES	ES
Sampling Date	08/04/2020	08/04/2020	08/04/2020	08/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Asbestos Quantification	DETSC 1102	0.001	%			0.002	
Metals							
Aluminium	DETSC 2301*	1	mg/kg	14000	35000	10000	16000
Antimony	DETSC 2301*	1	mg/kg	1.5	1.4	6.6	5.0
Arsenic	DETSC 2301#	0.2	mg/kg	11	4.2	10	14
Barium	DETSC 2301#	1.5	mg/kg	270	370	160	240
Beryllium	DETSC 2301#	0.2	mg/kg	1.4	3.9	1.2	1.2
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	1.7	4.4	2.0	3.7
Cadmium	DETSC 2301#	0.1	mg/kg	0.3	< 0.1	2.6	0.5
Chromium	DETSC 2301#	0.15	mg/kg	30	66	85	190
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	39	10	170	68
Iron	DETSC 2301	25	mg/kg	42000	14000	180000	86000
Lead	DETSC 2301#	0.3	mg/kg	50	4.6	91	56
Magnesium	DETSC 2301*	1	mg/kg	9500	33000	6000	16000
Manganese	DETSC 2301#	20	mg/kg	1200	4100	2400	9400
Mercury	DETSC 2325#	0.05	mg/kg	< 0.05	< 0.05	< 0.05	0.29
Molybdenum	DETSC 2301#	0.4	mg/kg	0.8	0.4	12	3.2
Nickel	DETSC 2301#	1	mg/kg	34	2.9	65	19
Silicon	DETSC 2301*	10	mg/kg	160000	77000	39000	95000
Vanadium	DETSC 2301#	0.8	mg/kg	47	230	71	360
Zinc	DETSC 2301#	1	mg/kg	130	33	3000	200
Inorganics							
Loss on Ignition at 440oC	DETSC 2003#	0.01	%			2.1	
pH	DETSC 2008#		pH	9.7	11.4	11.2	11.9
Calorific Value	DETSC 5008	1	MJ/kg			< 1.0	
Cyanide, Total	DETSC 2130#	0.1	mg/kg	0.5	1.6	9.5	29
Cyanide, Free	DETSC 2130#	0.1	mg/kg	< 0.1	< 0.1	< 0.1	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	< 0.6	0.8	< 0.6	6.3
Organic matter	DETSC 2002#	0.1	%	3.7	0.8	1.5	2.1
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	470	400	230	170
Sulphur (free)	DETSC 3049#	0.75	mg/kg	3.4	4.5	< 0.75	7.9



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1665286	1665288	1665290	1665291
Sample ID	PRAIRIE_AUK_ BH103	PRAIRIE_AUK_ TP115	PRAIRIE_AUK_ TP122	PRAIRIE_AUK_ TP123
Depth	2.50	1.90	1.00	0.60
Other ID	1	6	3	3
Sample Type	ES	ES	ES	ES
Sampling Date	08/04/2020	08/04/2020	08/04/2020	08/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Petroleum Hydrocarbons							
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	40
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	290
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	< 3.4	24	190
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	24	520
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	< 0.5	< 0.5	16
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	< 0.6	< 0.6	< 0.6	99
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	< 1.4	< 1.4	< 1.4	100
Aromatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	220
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	24	730
EPH (C10-C40)	DETSC 3311#	10	mg/kg	< 10	< 10	120	1500
PAHs							
Naphthalene	DETSC 3303#	0.03	mg/kg	0.29	< 0.03	< 0.03	< 0.30
Acenaphthylene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.30
Acenaphthene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.30
Fluorene	DETSC 3303	0.03	mg/kg	0.04	< 0.03	< 0.03	< 0.30
Phenanthrene	DETSC 3303#	0.03	mg/kg	0.12	0.05	0.08	0.48
Anthracene	DETSC 3303	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.30
Fluoranthene	DETSC 3303#	0.03	mg/kg	0.10	0.11	0.11	0.92
Pyrene	DETSC 3303#	0.03	mg/kg	0.07	0.09	0.09	0.72
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	0.03	0.05	0.04	0.56
Chrysene	DETSC 3303	0.03	mg/kg	0.04	0.05	0.06	0.50
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	< 0.03	0.05	0.06	0.53
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	0.03	< 0.30
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.30
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	0.03	0.36
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.30
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.30
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	0.62	0.39	0.44	< 3.37



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1665286	1665288	1665290	1665291
Sample ID	PRAIRIE_AUK_ BH103	PRAIRIE_AUK_ TP115	PRAIRIE_AUK_ TP122	PRAIRIE_AUK_ TP123
Depth	2.50	1.90	1.00	0.60
Other ID	1	6	3	3
Sample Type	ES	ES	ES	ES
Sampling Date	08/04/2020	08/04/2020	08/04/2020	08/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
PCBs							
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg		< 0.01		
PCB 52	DETSC 3401#	0.01	mg/kg		< 0.01		
PCB 101	DETSC 3401#	0.01	mg/kg		< 0.01		
PCB 118	DETSC 3401#	0.01	mg/kg		< 0.01		
PCB 153	DETSC 3401#	0.01	mg/kg		< 0.01		
PCB 138	DETSC 3401#	0.01	mg/kg		< 0.01		
PCB 180	DETSC 3401#	0.01	mg/kg		< 0.01		
PCB 7 Total	DETSC 3401#	0.01	mg/kg		< 0.01		
Phenols							
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	0.4	< 0.3	< 0.3	< 0.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665292	1665293	1665295	1665450
Sample ID	PRAIRIE_AUK_TP185	PRAIRIE_AUK_TP186	PRAIRIE_AUK_TP188	PRAIRIE_AUK_TP121
Depth	4.30	0.50	1.00	1.50
Other ID	5	3	3	4
Sample Type	ES	ES	ES	ES
Sampling Date	08/04/2020	07/04/2020	08/04/2020	09/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Asbestos Quantification	DETSC 1102	0.001	%				
Metals							
Aluminium	DETSC 2301*	1	mg/kg	11000	15000	11000	8100
Antimony	DETSC 2301*	1	mg/kg	1.3	4.7	3.9	11
Arsenic	DETSC 2301#	0.2	mg/kg	8.1	150	28	1.6
Barium	DETSC 2301#	1.5	mg/kg	220	340	270	210
Beryllium	DETSC 2301#	0.2	mg/kg	0.9	1.4	1.1	0.4
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	0.6	1.0	2.4	3.6
Cadmium	DETSC 2301#	0.1	mg/kg	0.3	3.7	0.2	0.2
Chromium	DETSC 2301#	0.15	mg/kg	23	55	69	750
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	32	100	53	21
Iron	DETSC 2301	25	mg/kg	42000	78000	60000	180000
Lead	DETSC 2301#	0.3	mg/kg	23	68	26	14
Magnesium	DETSC 2301*	1	mg/kg	7500	8400	7100	32000
Manganese	DETSC 2301#	20	mg/kg	490	75000	21000	37000
Mercury	DETSC 2325#	0.05	mg/kg	< 0.05	0.60	0.11	< 0.05
Molybdenum	DETSC 2301#	0.4	mg/kg	0.8	38	2.5	3.6
Nickel	DETSC 2301#	1	mg/kg	31	46	27	3.6
Silicon	DETSC 2301*	10	mg/kg	170000	14000	48000	38000
Vanadium	DETSC 2301#	0.8	mg/kg	28	240	150	1700
Zinc	DETSC 2301#	1	mg/kg	160	150	81	56
Inorganics							
Loss on Ignition at 440oC	DETSC 2003#	0.01	%	4.4		13	
pH	DETSC 2008#		pH	8.4	10.7	10.6	12.1
Calorific Value	DETSC 5008	1	MJ/kg	< 1.0		12.0	
Cyanide, Total	DETSC 2130#	0.1	mg/kg	0.5	19	2.6	23
Cyanide, Free	DETSC 2130#	0.1	mg/kg	< 0.1	0.5	< 0.1	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	< 0.6	< 0.6	< 0.6	1.2
Organic matter	DETSC 2002#	0.1	%	1.9	3.0	5.0	1.5
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	120	270	220	32
Sulphur (free)	DETSC 3049#	0.75	mg/kg	< 0.75	2.7	2.1	< 0.75



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1665292	1665293	1665295	1665450
Sample ID	PRAIRIE_AUK_TP185	PRAIRIE_AUK_TP186	PRAIRIE_AUK_TP188	PRAIRIE_AUK_TP121
Depth	4.30	0.50	1.00	1.50
Other ID	5	3	3	4
Sample Type	ES	ES	ES	ES
Sampling Date	08/04/2020	07/04/2020	08/04/2020	09/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Petroleum Hydrocarbons							
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	< 3.4	< 3.4	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	1.6	< 0.5	< 0.5
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	< 0.6	5.2	< 0.6	< 0.6
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	< 1.4	8.4	< 1.4	< 1.4
Aromatic C5-C35	DETSC 3072*	10	mg/kg	< 10	16	< 10	< 10
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	< 10	16	< 10	< 10
EPH (C10-C40)	DETSC 3311#	10	mg/kg	< 10	130	140	< 10
PAHs							
Naphthalene	DETSC 3303#	0.03	mg/kg	< 0.03	0.61	0.31	< 0.03
Acenaphthylene	DETSC 3303#	0.03	mg/kg	< 0.03	0.59	0.17	< 0.03
Acenaphthene	DETSC 3303#	0.03	mg/kg	< 0.03	0.40	0.13	< 0.03
Fluorene	DETSC 3303	0.03	mg/kg	< 0.03	0.42	0.20	< 0.03
Phenanthrene	DETSC 3303#	0.03	mg/kg	< 0.03	2.5	2.6	0.10
Anthracene	DETSC 3303	0.03	mg/kg	< 0.03	1.3	0.67	< 0.03
Fluoranthene	DETSC 3303#	0.03	mg/kg	< 0.03	6.5	4.2	0.39
Pyrene	DETSC 3303#	0.03	mg/kg	< 0.03	5.7	3.2	0.49
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	< 0.03	2.7	1.4	0.18
Chrysene	DETSC 3303	0.03	mg/kg	< 0.03	2.2	1.2	0.26
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	< 0.03	3.0	1.3	0.27
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	< 0.03	1.3	0.57	0.10
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	< 0.03	2.1	0.79	0.12
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	< 0.03	0.93	0.27	0.09
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	< 0.03	0.25	0.10	< 0.03
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	< 0.03	1.1	0.33	0.09
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	< 0.10	31	17	2.1



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1665292	1665293	1665295	1665450
Sample ID	PRAIRIE_AUK_ TP185	PRAIRIE_AUK_ TP186	PRAIRIE_AUK_ TP188	PRAIRIE_AUK_ TP121
Depth	4.30	0.50	1.00	1.50
Other ID	5	3	3	4
Sample Type	ES	ES	ES	ES
Sampling Date	08/04/2020	07/04/2020	08/04/2020	09/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
PCBs							
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg				
PCB 52	DETSC 3401#	0.01	mg/kg				
PCB 101	DETSC 3401#	0.01	mg/kg				
PCB 118	DETSC 3401#	0.01	mg/kg				
PCB 153	DETSC 3401#	0.01	mg/kg				
PCB 138	DETSC 3401#	0.01	mg/kg				
PCB 180	DETSC 3401#	0.01	mg/kg				
PCB 7 Total	DETSC 3401#	0.01	mg/kg				
Phenols							
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	< 0.3	< 0.3	< 0.3	< 0.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665451	1665452	1665453	1665454
Sample ID	PRAIRIE_AUK_ TP138	PRAIRIE_AUK_ TP149	PRAIRIE_AUK_ TP168	PRAIRIE_AUK_ TP173
Depth	1.20	1.30	0.05	0.90
Other ID	3	3	1	3
Sample Type	ES	ES	ES	ES
Sampling Date	09/04/2020	09/04/2020	09/04/2020	09/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Asbestos Quantification	DETSC 1102	0.001	%	0.020	< 0.001	< 0.001	< 0.001
Metals							
Aluminium	DETSC 2301*	1	mg/kg	12000	8600	19000	21000
Antimony	DETSC 2301*	1	mg/kg	3.2	2.5	3.9	6.1
Arsenic	DETSC 2301#	0.2	mg/kg	15	37	44	78
Barium	DETSC 2301#	1.5	mg/kg	200	1100	210	210
Beryllium	DETSC 2301#	0.2	mg/kg	0.8	1.1	2.1	2.5
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	2.1	2.5	1.5	3.1
Cadmium	DETSC 2301#	0.1	mg/kg	0.5	0.7	0.6	0.5
Chromium	DETSC 2301#	0.15	mg/kg	150	33	61	93
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	26	110	78	320
Iron	DETSC 2301	25	mg/kg	47000	48000	91000	150000
Lead	DETSC 2301#	0.3	mg/kg	53	180	93	70
Magnesium	DETSC 2301*	1	mg/kg	12000	8000	10000	7700
Manganese	DETSC 2301#	20	mg/kg	5100	2000	2100	4100
Mercury	DETSC 2325#	0.05	mg/kg	2.1	1.4	0.15	0.09
Molybdenum	DETSC 2301#	0.4	mg/kg	2.0	2.6	2.1	5.6
Nickel	DETSC 2301#	1	mg/kg	13	27	38	86
Silicon	DETSC 2301*	10	mg/kg	88000	46000	62000	48000
Vanadium	DETSC 2301#	0.8	mg/kg	140	90	200	230
Zinc	DETSC 2301#	1	mg/kg	160	350	330	380
Inorganics							
Loss on Ignition at 440oC	DETSC 2003#	0.01	%				
pH	DETSC 2008#		pH	11.5	10.3	9.0	8.7
Calorific Value	DETSC 5008	1	MJ/kg				
Cyanide, Total	DETSC 2130#	0.1	mg/kg	9.9	11	0.6	120
Cyanide, Free	DETSC 2130#	0.1	mg/kg	0.3	< 0.1	< 0.1	0.2
Thiocyanate	DETSC 2130#	0.6	mg/kg	0.7	< 0.6	< 0.6	1.8
Organic matter	DETSC 2002#	0.1	%	1.3	2.8	12	8.6
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	150	290	77	540
Sulphur (free)	DETSC 3049#	0.75	mg/kg	2.4	1.5	< 0.75	2.4



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665451	1665452	1665453	1665454
Sample ID	PRAIRIE_AUK_ TP138	PRAIRIE_AUK_ TP149	PRAIRIE_AUK_ TP168	PRAIRIE_AUK_ TP173
Depth	1.20	1.30	0.05	0.90
Other ID	3	3	1	3
Sample Type	ES	ES	ES	ES
Sampling Date	09/04/2020	09/04/2020	09/04/2020	09/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Petroleum Hydrocarbons							
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	11	12	7.4	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	13	13	< 10	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	< 0.5	< 0.5	< 0.5
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	7.9	< 0.6	< 0.6	< 0.6
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	30	< 1.4	< 1.4	< 1.4
Aromatic C5-C35	DETSC 3072*	10	mg/kg	38	< 10	< 10	< 10
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	51	13	< 10	< 10
EPH (C10-C40)	DETSC 3311#	10	mg/kg	280	96	< 10	< 10
PAHs							
Naphthalene	DETSC 3303#	0.03	mg/kg	0.04	< 0.03	0.06	2.0
Acenaphthylene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	0.09
Acenaphthene	DETSC 3303#	0.03	mg/kg	0.05	< 0.03	0.05	0.57
Fluorene	DETSC 3303	0.03	mg/kg	0.04	0.03	0.03	0.20
Phenanthrene	DETSC 3303#	0.03	mg/kg	0.44	0.35	0.28	0.37
Anthracene	DETSC 3303	0.03	mg/kg	0.08	0.06	0.04	0.05
Fluoranthene	DETSC 3303#	0.03	mg/kg	2.1	0.87	0.43	0.30
Pyrene	DETSC 3303#	0.03	mg/kg	2.1	0.70	0.37	0.23
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	1.4	0.36	0.18	0.09
Chrysene	DETSC 3303	0.03	mg/kg	1.2	0.35	0.25	0.14
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	1.8	0.32	0.24	0.11
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.78	0.14	0.10	0.05
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	1.2	0.18	0.12	0.05
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.58	0.09	0.08	0.04
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	0.20	0.03	< 0.03	< 0.03
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	1.0	0.09	0.09	0.04
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	13	3.5	2.3	4.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1665451	1665452	1665453	1665454
Sample ID	PRAIRIE_AUK_ TP138	PRAIRIE_AUK_ TP149	PRAIRIE_AUK_ TP168	PRAIRIE_AUK_ TP173
Depth	1.20	1.30	0.05	0.90
Other ID	3	3	1	3
Sample Type	ES	ES	ES	ES
Sampling Date	09/04/2020	09/04/2020	09/04/2020	09/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
PCBs							
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg	< 0.01			
PCB 52	DETSC 3401#	0.01	mg/kg	0.26			
PCB 101	DETSC 3401#	0.01	mg/kg	0.44			
PCB 118	DETSC 3401#	0.01	mg/kg	0.40			
PCB 153	DETSC 3401#	0.01	mg/kg	0.24			
PCB 138	DETSC 3401#	0.01	mg/kg	0.40			
PCB 180	DETSC 3401#	0.01	mg/kg	0.05			
PCB 7 Total	DETSC 3401#	0.01	mg/kg	1.8			
Phenols							
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	< 0.3	< 0.3	0.3	< 0.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665455	1665588	1665589	1665590
Sample ID	PRAIRIE_AUK_SU RFACE1	PRAIRIE_AUK_ TP114	PRAIRIE_AUK_ TP124	PRAIRIE_AUK_ TP174
Depth	0.00	0.90	1.50	0.80
Other ID	1	6	5	3
Sample Type	ES	ES	ES	ES
Sampling Date	09/04/2020	07/04/2020	08/04/2020	08/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Asbestos Quantification	DETSC 1102	0.001	%			0.002	
Metals							
Aluminium	DETSC 2301*	1	mg/kg	4800	12000	8300	9200
Antimony	DETSC 2301*	1	mg/kg	< 1.0	4.6	3.8	5.6
Arsenic	DETSC 2301#	0.2	mg/kg	1.8	51	40	58
Barium	DETSC 2301#	1.5	mg/kg	130	140	350	250
Beryllium	DETSC 2301#	0.2	mg/kg	0.5	1.3	0.8	0.9
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	1.9	0.8	7.2	1.4
Cadmium	DETSC 2301#	0.1	mg/kg	0.1	3.9	3.1	0.3
Chromium	DETSC 2301#	0.15	mg/kg	1.7	66	48	81
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	5.9	110	69	120
Iron	DETSC 2301	25	mg/kg	2700	69000	51000	120000
Lead	DETSC 2301#	0.3	mg/kg	10	330	90	110
Magnesium	DETSC 2301*	1	mg/kg	4700	3900	9900	8600
Manganese	DETSC 2301#	20	mg/kg	1500	2000	23000	99000
Mercury	DETSC 2325#	0.05	mg/kg	0.22	0.35	0.26	0.33
Molybdenum	DETSC 2301#	0.4	mg/kg	< 0.4	2.5	4.0	18
Nickel	DETSC 2301#	1	mg/kg	1.6	47	32	78
Silicon	DETSC 2301*	10	mg/kg	9500	U/S	100000	36000
Vanadium	DETSC 2301#	0.8	mg/kg	7.9	110	100	67
Zinc	DETSC 2301#	1	mg/kg	47	4200	340	160
Inorganics							
Loss on Ignition at 440oC	DETSC 2003#	0.01	%				6.5
pH	DETSC 2008#		pH	10.8	8.3	9.7	8.4
Calorific Value	DETSC 5008	1	MJ/kg				2.5
Cyanide, Total	DETSC 2130#	0.1	mg/kg	21	0.6	41	5.5
Cyanide, Free	DETSC 2130#	0.1	mg/kg	0.5	< 0.1	0.2	0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	6.6	2.2	1.7	1.3
Organic matter	DETSC 2002#	0.1	%	1.3	2.5	1.6	2.4
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	670	44	130	110
Sulphur (free)	DETSC 3049#	0.75	mg/kg	< 0.75	13	< 0.75	< 0.75



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665455	1665588	1665589	1665590
Sample ID	PRAIRIE_AUK_SU RFACE1	PRAIRIE_AUK_ TP114	PRAIRIE_AUK_ TP124	PRAIRIE_AUK_ TP174
Depth	0.00	0.90	1.50	0.80
Other ID	1	6	5	3
Sample Type	ES	ES	ES	ES
Sampling Date	09/04/2020	07/04/2020	08/04/2020	08/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Petroleum Hydrocarbons							
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 1.00	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 1.00	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	1.5	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	< 3.4	< 3.4	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 763.0	< 10	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	6.0	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	5.6	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	15	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	130	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	97	< 0.5	< 0.5
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	< 0.6	150	< 0.6	< 0.6
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	< 1.4	83	< 1.4	< 1.4
Aromatic C5-C35	DETSC 3072*	10	mg/kg	< 10	490	< 10	< 10
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	< 10	1300	< 10	< 10
EPH (C10-C40)	DETSC 3311#	10	mg/kg	< 10			
PAHs							
Naphthalene	DETSC 3303#	0.03	mg/kg	< 0.03	37000	0.05	0.11
Acenaphthylene	DETSC 3303#	0.03	mg/kg	< 0.03	5600	0.07	0.27
Acenaphthene	DETSC 3303#	0.03	mg/kg	< 0.03	41	< 0.03	0.17
Fluorene	DETSC 3303	0.03	mg/kg	< 0.03	6200	< 0.03	0.23
Phenanthrene	DETSC 3303#	0.03	mg/kg	< 0.03	22000	1.2	1.7
Anthracene	DETSC 3303	0.03	mg/kg	< 0.03	5700	0.22	0.43
Fluoranthene	DETSC 3303#	0.03	mg/kg	< 0.03	11000	4.4	3.2
Pyrene	DETSC 3303#	0.03	mg/kg	< 0.03	9700	3.8	2.6
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	< 0.03	4600	1.6	0.96
Chrysene	DETSC 3303	0.03	mg/kg	< 0.03	3600	1.8	0.93
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	< 0.03	91	1.7	0.92
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	< 0.03	49	0.86	0.39
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	< 0.03	92	0.66	0.60
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	< 0.03	31	0.62	0.30
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	< 0.03	8.4	0.21	0.09
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	< 0.03	29	0.72	0.35
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	< 0.10	110000	18	13



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665455	1665588	1665589	1665590
Sample ID	PRAIRIE_AUK_SU RFACE1	PRAIRIE_AUK_ TP114	PRAIRIE_AUK_ TP124	PRAIRIE_AUK_ TP174
Depth	0.00	0.90	1.50	0.80
Other ID	1	6	5	3
Sample Type	ES	ES	ES	ES
Sampling Date	09/04/2020	07/04/2020	08/04/2020	08/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
PCBs							
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg		< 0.05		
PCB 52	DETSC 3401#	0.01	mg/kg		< 0.05		
PCB 101	DETSC 3401#	0.01	mg/kg		< 0.05		
PCB 118	DETSC 3401#	0.01	mg/kg		< 0.05		
PCB 153	DETSC 3401#	0.01	mg/kg		< 0.05		
PCB 138	DETSC 3401#	0.01	mg/kg		< 0.05		
PCB 180	DETSC 3401#	0.01	mg/kg		< 0.05		
PCB 7 Total	DETSC 3401#	0.01	mg/kg		< 0.01		
Phenols							
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	< 0.3	210	< 0.3	< 0.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665591	1665592	1665593	1665594
Sample ID	PRAIRIE_AUK_TP174	PRAIRIE_AUK_TP176	PRAIRIE_AUK_TP177	PRAIRIE_AUK_TP189
Depth	1.60	0.90	0.60	3.00
Other ID	6	3	2	7
Sample Type	ES	ES	ES	ES
Sampling Date	08/04/2020	07/04/2020	07/04/2020	07/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Asbestos Quantification	DETSC 1102	0.001	%				
Metals							
Aluminium	DETSC 2301*	1	mg/kg	12000	30000	31000	19000
Antimony	DETSC 2301*	1	mg/kg	< 1.0	3.0	2.8	1.3
Arsenic	DETSC 2301#	0.2	mg/kg	6.2	83	37	9.9
Barium	DETSC 2301#	1.5	mg/kg	84	260	120	260
Beryllium	DETSC 2301#	0.2	mg/kg	0.6	3.7	4.0	1.5
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	1.2	4.2	2.9	1.0
Cadmium	DETSC 2301#	0.1	mg/kg	< 0.1	0.4	0.2	0.2
Chromium	DETSC 2301#	0.15	mg/kg	20	58	110	33
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	17	80	26	30
Iron	DETSC 2301	25	mg/kg	32000	100000	80000	46000
Lead	DETSC 2301#	0.3	mg/kg	23	61	29	27
Magnesium	DETSC 2301*	1	mg/kg	2300	13000	11000	13000
Manganese	DETSC 2301#	20	mg/kg	370	1600	1600	830
Mercury	DETSC 2325#	0.05	mg/kg	0.06	0.08	< 0.05	0.08
Molybdenum	DETSC 2301#	0.4	mg/kg	0.6	3.2	1.2	0.6
Nickel	DETSC 2301#	1	mg/kg	11	65	32	42
Silicon	DETSC 2301*	10	mg/kg	190000	71000	61000	140000
Vanadium	DETSC 2301#	0.8	mg/kg	27	190	450	42
Zinc	DETSC 2301#	1	mg/kg	58	360	260	94
Inorganics							
Loss on Ignition at 440oC	DETSC 2003#	0.01	%		12		
pH	DETSC 2008#		pH	7.2	8.4	8.7	7.9
Calorific Value	DETSC 5008	1	MJ/kg		5.0		
Cyanide, Total	DETSC 2130#	0.1	mg/kg	1.0	0.2	0.4	< 0.1
Cyanide, Free	DETSC 2130#	0.1	mg/kg	< 0.1	< 0.1	< 0.1	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	1.2	0.8	0.8	< 0.6
Organic matter	DETSC 2002#	0.1	%	0.7	3.2	2.9	0.8
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	190	170	83	350
Sulphur (free)	DETSC 3049#	0.75	mg/kg	6.8	< 0.75	< 0.75	< 0.75



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1665591	1665592	1665593	1665594
Sample ID	PRAIRIE_AUK_TP174	PRAIRIE_AUK_TP176	PRAIRIE_AUK_TP177	PRAIRIE_AUK_TP189
Depth	1.60	0.90	0.60	3.00
Other ID	6	3	2	7
Sample Type	ES	ES	ES	ES
Sampling Date	08/04/2020	07/04/2020	07/04/2020	07/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Petroleum Hydrocarbons							
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	7.3	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	< 3.4	< 3.4	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	< 0.5	< 0.5	< 0.5
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	< 0.6	< 0.6	< 0.6	< 0.6
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	< 1.4	< 1.4	< 1.4	< 1.4
Aromatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	< 10
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	< 10
EPH (C10-C40)	DETSC 3311#	10	mg/kg				
PAHs							
Naphthalene	DETSC 3303#	0.03	mg/kg	< 0.03	0.04	< 0.03	< 0.03
Acenaphthylene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03
Acenaphthene	DETSC 3303#	0.03	mg/kg	< 0.03	0.05	< 0.03	< 0.03
Fluorene	DETSC 3303	0.03	mg/kg	< 0.03	0.04	< 0.03	< 0.03
Phenanthrene	DETSC 3303#	0.03	mg/kg	< 0.03	0.17	0.06	< 0.03
Anthracene	DETSC 3303	0.03	mg/kg	< 0.03	0.06	< 0.03	< 0.03
Fluoranthene	DETSC 3303#	0.03	mg/kg	0.05	0.67	0.14	< 0.03
Pyrene	DETSC 3303#	0.03	mg/kg	0.04	0.62	0.16	< 0.03
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	0.03	0.10	0.05	< 0.03
Chrysene	DETSC 3303	0.03	mg/kg	< 0.03	0.15	0.08	< 0.03
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	< 0.03	0.06	0.05	< 0.03
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	< 0.03	0.03	< 0.03	< 0.03
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	< 0.10	2.0	0.53	< 0.10



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1665591	1665592	1665593	1665594
Sample ID	PRAIRIE_AUK_TP174	PRAIRIE_AUK_TP176	PRAIRIE_AUK_TP177	PRAIRIE_AUK_TP189
Depth	1.60	0.90	0.60	3.00
Other ID	6	3	2	7
Sample Type	ES	ES	ES	ES
Sampling Date	08/04/2020	07/04/2020	07/04/2020	07/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
PCBs							
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg				
PCB 52	DETSC 3401#	0.01	mg/kg				
PCB 101	DETSC 3401#	0.01	mg/kg				
PCB 118	DETSC 3401#	0.01	mg/kg				
PCB 153	DETSC 3401#	0.01	mg/kg				
PCB 138	DETSC 3401#	0.01	mg/kg				
PCB 180	DETSC 3401#	0.01	mg/kg				
PCB 7 Total	DETSC 3401#	0.01	mg/kg				
Phenols							
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	< 0.3	0.8	0.9	< 0.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665610	1665611	1665612	1665613
Sample ID	PRAIRIE_AUK_ TP179	PRAIRIE_AUK_ TP179	PRAIRIE_AUK_ TP181	PRAIRIE_AUK_ TP182
Depth	1.40	2.00	0.60	0.90
Other ID	4	7	3	3
Sample Type	ES	ES	ES	ES
Sampling Date	09/04/2020	09/04/2020	09/04/2020	09/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Asbestos Quantification	DETSC 1102	0.001	%				
Metals							
Aluminium	DETSC 2301*	1	mg/kg	39000	15000	18000	21000
Antimony	DETSC 2301*	1	mg/kg	4.6	1.3	4.7	2.5
Arsenic	DETSC 2301#	0.2	mg/kg	88	9.3	45	33
Barium	DETSC 2301#	1.5	mg/kg	79	190	280	82
Beryllium	DETSC 2301#	0.2	mg/kg	4.0	1.7	2.5	3.0
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	2.3	1.5	1.5	2.4
Cadmium	DETSC 2301#	0.1	mg/kg	0.2	0.1	0.5	0.2
Chromium	DETSC 2301#	0.15	mg/kg	120	29	23	51
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	32	29	130	23
Iron	DETSC 2301	25	mg/kg	160000	39000	41000	87000
Lead	DETSC 2301#	0.3	mg/kg	27	34	380	23
Magnesium	DETSC 2301*	1	mg/kg	11000	4000	6400	7000
Manganese	DETSC 2301#	20	mg/kg	1200	320	12000	1000
Mercury	DETSC 2325#	0.05	mg/kg	0.32	0.05	0.10	0.75
Molybdenum	DETSC 2301#	0.4	mg/kg	2.1	0.5	2.6	0.8
Nickel	DETSC 2301#	1	mg/kg	98	30	23	28
Silicon	DETSC 2301*	10	mg/kg	100000	190000	56000	73000
Vanadium	DETSC 2301#	0.8	mg/kg	360	33	83	150
Zinc	DETSC 2301#	1	mg/kg	200	99	210	130
Inorganics							
Loss on Ignition at 440oC	DETSC 2003#	0.01	%				
pH	DETSC 2008#		pH	7.5	7.6	8.6	8.0
Calorific Value	DETSC 5008	1	MJ/kg				
Cyanide, Total	DETSC 2130#	0.1	mg/kg	120	4.8	20	3300
Cyanide, Free	DETSC 2130#	0.1	mg/kg	0.3	< 0.1	< 0.1	4.5
Thiocyanate	DETSC 2130#	0.6	mg/kg	2.1	< 0.6	0.9	69
Organic matter	DETSC 2002#	0.1	%	4.4	1.8	6.1	7.0
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	900	490	220	650
Sulphur (free)	DETSC 3049#	0.75	mg/kg	< 0.75	< 0.75	60	26



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665610	1665611	1665612	1665613
Sample ID	PRAIRIE_AUK_ TP179	PRAIRIE_AUK_ TP179	PRAIRIE_AUK_ TP181	PRAIRIE_AUK_ TP182
Depth	1.40	2.00	0.60	0.90
Other ID	4	7	3	3
Sample Type	ES	ES	ES	ES
Sampling Date	09/04/2020	09/04/2020	09/04/2020	09/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Petroleum Hydrocarbons							
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	0.25
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	6.3
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	42
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	49
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	< 3.4	< 3.4	3.6
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	100
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	0.04
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	0.03	< 0.01	< 0.01	0.31
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	0.71	< 0.01	< 0.01	13
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	27	< 0.9	< 0.9	1700
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	150	< 0.5	< 0.5	2500
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	31	< 0.6	< 0.6	370
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	9.7	< 1.4	< 1.4	82
Aromatic C5-C35	DETSC 3072*	10	mg/kg	220	< 10	< 10	4600
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	220	< 10	< 10	4700
EPH (C10-C40)	DETSC 3311#	10	mg/kg				
PAHs							
Naphthalene	DETSC 3303#	0.03	mg/kg	190	2.5	0.27	3500
Acenaphthylene	DETSC 3303#	0.03	mg/kg	13	0.07	0.23	1300
Acenaphthene	DETSC 3303#	0.03	mg/kg	200	1.0	1.5	1300
Fluorene	DETSC 3303	0.03	mg/kg	100	0.47	1.1	730
Phenanthrene	DETSC 3303#	0.03	mg/kg	65	0.33	1.2	500
Anthracene	DETSC 3303	0.03	mg/kg	18	0.09	0.31	130
Fluoranthene	DETSC 3303#	0.03	mg/kg	12	0.08	0.56	120
Pyrene	DETSC 3303#	0.03	mg/kg	8.2	0.05	0.42	80
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	1.7	< 0.03	0.12	6.9
Chrysene	DETSC 3303	0.03	mg/kg	1.5	< 0.03	0.16	5.2
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	0.74	< 0.03	0.13	3.1
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.31	< 0.03	0.06	1.6
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	0.59	< 0.03	0.07	2.1
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.17	< 0.03	0.06	0.66
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	0.05	< 0.03	< 0.03	0.20
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	0.19	< 0.03	0.06	0.71
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	610	4.6	6.2	7700



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1665610	1665611	1665612	1665613
Sample ID	PRAIRIE_AUK_ TP179	PRAIRIE_AUK_ TP179	PRAIRIE_AUK_ TP181	PRAIRIE_AUK_ TP182
Depth	1.40	2.00	0.60	0.90
Other ID	4	7	3	3
Sample Type	ES	ES	ES	ES
Sampling Date	09/04/2020	09/04/2020	09/04/2020	09/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
PCBs							
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg				
PCB 52	DETSC 3401#	0.01	mg/kg				
PCB 101	DETSC 3401#	0.01	mg/kg				
PCB 118	DETSC 3401#	0.01	mg/kg				
PCB 153	DETSC 3401#	0.01	mg/kg				
PCB 138	DETSC 3401#	0.01	mg/kg				
PCB 180	DETSC 3401#	0.01	mg/kg				
PCB 7 Total	DETSC 3401#	0.01	mg/kg				
Phenols							
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	1.6	0.6	1.0	9.0



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665990	1665991	1665992	1665993	1665994
Sample ID	PRAIRIE_AUK_TP145	PRAIRIE_AUK_TP146C	PRAIRIE_AUK_TP156A	PRAIRIE_AUK_TP162	PRAIRIE_AUK_TP180
Depth	1.60	1.30	0.30	1.70	0.30
Other ID	4	5	2	3A	3
Sample Type	ES	ES	ES	ES	ES
Sampling Date	14/04/2020	14/04/2020	14/04/2020	14/04/2020	14/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Asbestos Quantification	DETSC 1102	0.001	%			0.001		
Metals								
Aluminium	DETSC 2301*	1	mg/kg	11000	16000	26000	16000	15000
Antimony	DETSC 2301*	1	mg/kg	69	9.5	6.5	18	5.6
Arsenic	DETSC 2301#	0.2	mg/kg	64	14	31	2100	12
Barium	DETSC 2301#	1.5	mg/kg	560	250	540	320	270
Beryllium	DETSC 2301#	0.2	mg/kg	1.9	1.9	2.6	2.3	1.5
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	2.5	3.2	2.5	2.2	2.4
Cadmium	DETSC 2301#	0.1	mg/kg	0.8	1.0	0.7	1.7	0.7
Chromium	DETSC 2301#	0.15	mg/kg	120	19	170	100	310
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	20000	420	110	190	31
Iron	DETSC 2301	25	mg/kg	45000	35000	140000	360000	99000
Lead	DETSC 2301#	0.3	mg/kg	1200	210	110	870	94
Magnesium	DETSC 2301*	1	mg/kg	11000	9000	17000	3500	23000
Manganese	DETSC 2301#	20	mg/kg	4900	1700	6100	2800	28000
Mercury	DETSC 2325#	0.05	mg/kg	0.19	0.17	0.69	0.73	0.47
Molybdenum	DETSC 2301#	0.4	mg/kg	2.9	1.0	2.2	73	2.8
Nickel	DETSC 2301#	1	mg/kg	41	17	40	160	16
Silicon	DETSC 2301*	10	mg/kg	23000	69000	43000	53000	67000
Vanadium	DETSC 2301#	0.8	mg/kg	240	57	700	310	1200
Zinc	DETSC 2301#	1	mg/kg	1500	350	310	630	270
Inorganics								
Loss on Ignition at 440oC	DETSC 2003#	0.01	%					
pH	DETSC 2008#		pH	11.2	9.6	10.6	8.2	11.5
Calorific Value	DETSC 5008	1	MJ/kg					
Cyanide, Total	DETSC 2130#	0.1	mg/kg	1.3	13	12	3.6	2.3
Cyanide, Free	DETSC 2130#	0.1	mg/kg	< 0.1	< 0.1	< 0.1	< 0.1	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	< 0.6	0.7	< 0.6	< 0.6	< 0.6
Organic matter	DETSC 2002#	0.1	%	2.8	5.8	3.2	3.4	3.3
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	200	590	280	110	110
Sulphur (free)	DETSC 3049#	0.75	mg/kg	< 0.75	5.2	1.2	< 0.75	1.4



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665990	1665991	1665992	1665993	1665994
Sample ID	PRAIRIE_AUK_TP145	PRAIRIE_AUK_TP146C	PRAIRIE_AUK_TP156A	PRAIRIE_AUK_TP162	PRAIRIE_AUK_TP180
Depth	1.60	1.30	0.30	1.70	0.30
Other ID	4	5	2	3A	3
Sample Type	ES	ES	ES	ES	ES
Sampling Date	14/04/2020	14/04/2020	14/04/2020	14/04/2020	14/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Petroleum Hydrocarbons								
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	6.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	16	< 1.2	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	45	< 1.5	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	99	< 3.4	< 3.4	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	170	< 10	< 10	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	1.3	< 0.9	4.2	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	1.6	< 0.5	5.1	< 0.5
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	< 0.6	13	< 0.6	0.7	< 0.6
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	< 1.4	55	< 1.4	< 1.4	< 1.4
Aromatic C5-C35	DETSC 3072*	10	mg/kg	< 10	71	< 10	10	< 10
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	< 10	240	< 10	10	< 10
EPH (C10-C40)	DETSC 3311#	10	mg/kg					
PAHs								
Naphthalene	DETSC 3303#	0.03	mg/kg	0.06	0.03	0.05	< 0.03	0.24
Acenaphthylene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	0.03	< 0.03	0.06
Acenaphthene	DETSC 3303#	0.03	mg/kg	0.04	< 0.03	< 0.03	< 0.03	0.11
Fluorene	DETSC 3303	0.03	mg/kg	0.03	< 0.03	0.03	< 0.03	0.09
Phenanthrene	DETSC 3303#	0.03	mg/kg	0.37	0.32	0.63	< 0.03	1.8
Anthracene	DETSC 3303	0.03	mg/kg	0.09	0.07	0.17	< 0.03	0.79
Fluoranthene	DETSC 3303#	0.03	mg/kg	1.5	1.0	3.0	0.03	2.2
Pyrene	DETSC 3303#	0.03	mg/kg	1.4	0.91	3.0	0.03	2.0
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	0.61	0.43	1.6	0.03	0.82
Chrysene	DETSC 3303	0.03	mg/kg	0.61	0.40	1.3	< 0.03	0.90
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	0.92	0.44	2.0	< 0.03	0.86
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.30	0.19	0.79	< 0.03	0.37
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	0.47	0.30	1.2	< 0.03	0.43
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.21	0.12	0.58	< 0.03	0.19
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	0.06	0.03	0.15	< 0.03	0.06
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	0.30	0.16	0.77	< 0.03	0.27
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	7.0	4.3	15	< 0.10	11



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1665990	1665991	1665992	1665993	1665994
Sample ID	PRAIRIE_AUK_TP145	PRAIRIE_AUK_TP146C	PRAIRIE_AUK_TP156A	PRAIRIE_AUK_TP162	PRAIRIE_AUK_TP180
Depth	1.60	1.30	0.30	1.70	0.30
Other ID	4	5	2	3A	3
Sample Type	ES	ES	ES	ES	ES
Sampling Date	14/04/2020	14/04/2020	14/04/2020	14/04/2020	14/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
PCBs								
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 52	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 101	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 118	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 153	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 138	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 180	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 7 Total	DETSC 3401#	0.01	mg/kg		< 0.01			
Phenols								
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	< 0.3	< 0.3	< 0.3	< 0.3	< 0.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665995	1666343	1666344	1666345	1666346
Sample ID	PRAIRIE_AUK_TP163	PRAIRIE_AUK_TP135	PRAIRIE_AUK_TP136	PRAIRIE_AUK_TP136	PRAIRIE_AUK_TP165
Depth	1.20	1.30	0.80	2.90	1.00
Other ID	3	5	3	10	3
Sample Type	ES	ES	ES	ES	ES
Sampling Date	14/04/2020	15/04/2020	15/04/2020	15/04/2020	15/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Asbestos Quantification	DETSC 1102	0.001	%	< 0.001	< 0.001			
Metals								
Aluminium	DETSC 2301*	1	mg/kg	53000	25000	38000	15000	5900
Antimony	DETSC 2301*	1	mg/kg	< 1.0	4.5	< 1.0	1.2	2.5
Arsenic	DETSC 2301#	0.2	mg/kg	12	61	7.0	9.3	23
Barium	DETSC 2301#	1.5	mg/kg	170	500	160	310	150
Beryllium	DETSC 2301#	0.2	mg/kg	7.0	3.3	5.3	1.3	0.4
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	1.5	2.6	1.4	0.9	1.4
Cadmium	DETSC 2301#	0.1	mg/kg	0.1	0.8	0.2	0.2	0.4
Chromium	DETSC 2301#	0.15	mg/kg	12	52	9.1	26	120
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	40	100	15	29	28
Iron	DETSC 2301	25	mg/kg	6800	3200	8900	40000	41000
Lead	DETSC 2301#	0.3	mg/kg	15	220	5.0	35	43
Magnesium	DETSC 2301*	1	mg/kg	16000	15000	17000	6200	10000
Manganese	DETSC 2301#	20	mg/kg	1200	5300	870	700	18000
Mercury	DETSC 2325#	0.05	mg/kg	0.07	0.37	< 0.05	< 0.05	0.11
Molybdenum	DETSC 2301#	0.4	mg/kg	0.5	5.4	0.5	0.4	1.6
Nickel	DETSC 2301#	1	mg/kg	2.5	33	5.9	37	15
Silicon	DETSC 2301*	10	mg/kg	63000	64000	64000	170000	53000
Vanadium	DETSC 2301#	0.8	mg/kg	41	120	31	31	470
Zinc	DETSC 2301#	1	mg/kg	39	270	54	100	120
Inorganics								
Loss on Ignition at 440oC	DETSC 2003#	0.01	%					
pH	DETSC 2008#		pH	10.4	10.3	11.4	8.6	11.4
Calorific Value	DETSC 5008	1	MJ/kg					
Cyanide, Total	DETSC 2130#	0.1	mg/kg	1300	0.4	0.6	0.3	1.0
Cyanide, Free	DETSC 2130#	0.1	mg/kg	0.4	< 0.1	< 0.1	< 0.1	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	8.9	0.6	< 0.6	< 0.6	0.6
Organic matter	DETSC 2002#	0.1	%	1.1	3.3	0.5	2.6	13
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	480	400	840	120	170
Sulphur (free)	DETSC 3049#	0.75	mg/kg	< 0.75	0.83	2.2	< 0.75	1.4



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1665995	1666343	1666344	1666345	1666346
Sample ID	PRAIRIE_AUK_TP163	PRAIRIE_AUK_TP135	PRAIRIE_AUK_TP136	PRAIRIE_AUK_TP136	PRAIRIE_AUK_TP165
Depth	1.20	1.30	0.80	2.90	1.00
Other ID	3	5	3	10	3
Sample Type	ES	ES	ES	ES	ES
Sampling Date	14/04/2020	15/04/2020	15/04/2020	15/04/2020	15/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Petroleum Hydrocarbons								
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	< 3.4	< 3.4	< 3.4	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	< 10	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	0.35	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	1.7	< 0.9	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	96	< 0.5	< 0.5	< 0.5	< 0.5
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	40	< 0.6	< 0.6	< 0.6	< 0.6
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	7.1	< 1.4	< 1.4	< 1.4	< 1.4
Aromatic C5-C35	DETSC 3072*	10	mg/kg	150	< 10	< 10	< 10	< 10
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	150	< 10	< 10	< 10	< 10
EPH (C10-C40)	DETSC 3311#	10	mg/kg					
PAHs								
Naphthalene	DETSC 3303#	0.03	mg/kg	0.85	0.03	< 0.03	< 0.03	0.42
Acenaphthylene	DETSC 3303#	0.03	mg/kg	4.1	< 0.03	< 0.03	< 0.03	0.06
Acenaphthene	DETSC 3303#	0.03	mg/kg	20	0.05	< 0.03	< 0.03	0.05
Fluorene	DETSC 3303	0.03	mg/kg	11	0.03	< 0.03	< 0.03	0.07
Phenanthrene	DETSC 3303#	0.03	mg/kg	7.8	0.57	< 0.03	< 0.03	0.91
Anthracene	DETSC 3303	0.03	mg/kg	11	0.18	< 0.03	< 0.03	0.26
Fluoranthene	DETSC 3303#	0.03	mg/kg	11	2.3	< 0.03	< 0.03	1.0
Pyrene	DETSC 3303#	0.03	mg/kg	7.5	3.4	< 0.03	< 0.03	0.83
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	1.6	1.1	< 0.03	< 0.03	0.40
Chrysene	DETSC 3303	0.03	mg/kg	1.4	1.2	< 0.03	< 0.03	0.51
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	0.70	1.3	< 0.03	< 0.03	0.49
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.30	0.53	< 0.03	< 0.03	0.18
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	0.53	0.87	< 0.03	< 0.03	0.26
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.13	0.37	< 0.03	< 0.03	0.15
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	0.04	0.10	< 0.03	< 0.03	0.05
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	0.14	0.47	< 0.03	< 0.03	0.19
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	78	12	< 0.10	< 0.10	5.8



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1665995	1666343	1666344	1666345	1666346
Sample ID	PRAIRIE_AUK_ TP163	PRAIRIE_AUK_ TP135	PRAIRIE_AUK_ TP136	PRAIRIE_AUK_ TP136	PRAIRIE_AUK_ TP165
Depth	1.20	1.30	0.80	2.90	1.00
Other ID	3	5	3	10	3
Sample Type	ES	ES	ES	ES	ES
Sampling Date	14/04/2020	15/04/2020	15/04/2020	15/04/2020	15/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
PCBs								
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg					
PCB 52	DETSC 3401#	0.01	mg/kg					
PCB 101	DETSC 3401#	0.01	mg/kg					
PCB 118	DETSC 3401#	0.01	mg/kg					
PCB 153	DETSC 3401#	0.01	mg/kg					
PCB 138	DETSC 3401#	0.01	mg/kg					
PCB 180	DETSC 3401#	0.01	mg/kg					
PCB 7 Total	DETSC 3401#	0.01	mg/kg					
Phenols								
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	1.1	< 0.3	< 0.3	< 0.3	< 0.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1666347	1666348	1666610	1666611	1666612
Sample ID	PRAIRIE_AUK_TP167	PRAIRIE_AUK_TP169	PRAIRIE_AUK_BH108	PRAIRIE_AUK_TP139B	PRAIRIE_AUK_TP139B
Depth	2.50	1.50	2.50	0.30	3.30
Other ID	6	3	1	3	6
Sample Type	ES	ES	ES	ES	ES
Sampling Date	15/04/2020	15/04/2020	15/04/2020	16/04/2020	16/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Asbestos Quantification	DETSC 1102	0.001	%		< 0.001		< 0.001	
Metals								
Aluminium	DETSC 2301*	1	mg/kg	11000	8600	17000	26000	14000
Antimony	DETSC 2301*	1	mg/kg	2.5	1.7	2.0	5.4	1.4
Arsenic	DETSC 2301#	0.2	mg/kg	5.8	7.3	10	43	7.8
Barium	DETSC 2301#	1.5	mg/kg	220	120	240	810	330
Beryllium	DETSC 2301#	0.2	mg/kg	0.9	0.5	1.6	3.1	1.0
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	2.7	1.2	1.4	6.6	0.5
Cadmium	DETSC 2301#	0.1	mg/kg	0.2	0.7	0.3	1.9	0.2
Chromium	DETSC 2301#	0.15	mg/kg	120	46	76	77	24
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	17	39	46	94	29
Iron	DETSC 2301	25	mg/kg	42000	27000	46000	84000	40000
Lead	DETSC 2301#	0.3	mg/kg	31	68	38	410	28
Magnesium	DETSC 2301*	1	mg/kg	17000	6300	12000	21000	8700
Manganese	DETSC 2301#	20	mg/kg	8400	2000	1800	16000	700
Mercury	DETSC 2325#	0.05	mg/kg	0.13	0.10	0.27	3.6	0.06
Molybdenum	DETSC 2301#	0.4	mg/kg	1.0	1.7	1.0	3.5	0.4
Nickel	DETSC 2301#	1	mg/kg	12	24	37	31	33
Silicon	DETSC 2301*	10	mg/kg	64000	110000	160000	47000	160000
Vanadium	DETSC 2301#	0.8	mg/kg	410	75	200	140	30
Zinc	DETSC 2301#	1	mg/kg	78	150	140	1200	99
Inorganics								
Loss on Ignition at 440oC	DETSC 2003#	0.01	%					
pH	DETSC 2008#		pH	11.3	9.8	10.0	11.0	8.1
Calorific Value	DETSC 5008	1	MJ/kg					
Cyanide, Total	DETSC 2130#	0.1	mg/kg	2.2	0.6	2.0	220	2.0
Cyanide, Free	DETSC 2130#	0.1	mg/kg	< 0.1	< 0.1	< 0.1	0.4	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	0.7	0.8	< 0.6	3.1	< 0.6
Organic matter	DETSC 2002#	0.1	%	1.6	13	2.6	2.1	3.4
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	220	110	180	740	320
Sulphur (free)	DETSC 3049#	0.75	mg/kg	1.9	1.1	< 0.75	2.4	< 0.75



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1666347	1666348	1666610	1666611	1666612
Sample ID	PRAIRIE_AUK_TP167	PRAIRIE_AUK_TP169	PRAIRIE_AUK_BH108	PRAIRIE_AUK_TP139B	PRAIRIE_AUK_TP139B
Depth	2.50	1.50	2.50	0.30	3.30
Other ID	6	3	1	3	6
Sample Type	ES	ES	ES	ES	ES
Sampling Date	15/04/2020	15/04/2020	15/04/2020	16/04/2020	16/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Petroleum Hydrocarbons								
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	< 3.4	< 3.4	< 3.4	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	< 10	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	< 0.9	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	< 0.5	< 0.5	< 0.5	< 0.5
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	< 0.6	< 0.6	< 0.6	< 0.6	< 0.6
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	< 1.4	< 1.4	< 1.4	< 1.4	< 1.4
Aromatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	< 10	< 10
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	< 10	< 10
EPH (C10-C40)	DETSC 3311#	10	mg/kg					
PAHs								
Naphthalene	DETSC 3303#	0.03	mg/kg	0.20	0.38	< 0.03	0.45	0.31
Acenaphthylene	DETSC 3303#	0.03	mg/kg	0.06	0.09	< 0.03	0.10	0.05
Acenaphthene	DETSC 3303#	0.03	mg/kg	0.09	< 0.03	< 0.03	0.60	0.36
Fluorene	DETSC 3303	0.03	mg/kg	0.12	0.13	< 0.03	0.55	0.27
Phenanthrene	DETSC 3303#	0.03	mg/kg	1.5	1.9	0.04	1.5	0.33
Anthracene	DETSC 3303	0.03	mg/kg	0.37	0.50	< 0.03	0.34	0.06
Fluoranthene	DETSC 3303#	0.03	mg/kg	1.8	2.1	0.08	1.6	0.11
Pyrene	DETSC 3303#	0.03	mg/kg	1.4	1.7	0.07	1.3	0.08
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	0.55	0.65	< 0.03	0.30	0.04
Chrysene	DETSC 3303	0.03	mg/kg	0.69	0.67	< 0.03	0.52	0.03
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	0.69	0.56	0.04	0.43	0.03
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.26	0.22	< 0.03	0.17	< 0.03
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	0.32	0.31	< 0.03	0.20	< 0.03
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.20	0.13	< 0.03	0.12	< 0.03
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	0.06	0.04	< 0.03	0.04	< 0.03
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	0.24	0.16	< 0.03	0.16	< 0.03
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	8.6	9.5	0.23	8.3	1.6



Summary of Chemical Analysis Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1666347	1666348	1666610	1666611	1666612
Sample ID	PRAIRIE_AUK_TP167	PRAIRIE_AUK_TP169	PRAIRIE_AUK_BH108	PRAIRIE_AUK_TP139B	PRAIRIE_AUK_TP139B
Depth	2.50	1.50	2.50	0.30	3.30
Other ID	6	3	1	3	6
Sample Type	ES	ES	ES	ES	ES
Sampling Date	15/04/2020	15/04/2020	15/04/2020	16/04/2020	16/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
PCBs								
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg					
PCB 52	DETSC 3401#	0.01	mg/kg					
PCB 101	DETSC 3401#	0.01	mg/kg					
PCB 118	DETSC 3401#	0.01	mg/kg					
PCB 153	DETSC 3401#	0.01	mg/kg					
PCB 138	DETSC 3401#	0.01	mg/kg					
PCB 180	DETSC 3401#	0.01	mg/kg					
PCB 7 Total	DETSC 3401#	0.01	mg/kg					
Phenols								
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	< 0.3	< 0.3	0.5	< 0.3	< 0.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1666613	1666614	1666615	1666616	1667231
Sample ID	PRAIRIE_AUK_TP148A	PRAIRIE_AUK_TP150	PRAIRIE_AUK_TP159	PRAIRIE_AUK_TP190A	PRAIRIE_AUK_BH105
Depth	1.40	1.50	0.60	1.10	3.00
Other ID	5	3	3	3	1
Sample Type	ES	ES	ES	ES	ES
Sampling Date	16/04/2020	16/04/2020	16/04/2020	16/04/2020	16/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Asbestos Quantification	DETSC 1102	0.001	%		0.009	0.002	0.003	
Metals								
Aluminium	DETSC 2301*	1	mg/kg	20000	7700	15000	15000	13000
Antimony	DETSC 2301*	1	mg/kg	2.7	7.6	< 1.0	1.6	2.0
Arsenic	DETSC 2301#	0.2	mg/kg	24	30	6.1	21	8.7
Barium	DETSC 2301#	1.5	mg/kg	330	400	340	560	170
Beryllium	DETSC 2301#	0.2	mg/kg	2.3	0.8	3.2	1.3	1.1
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	3.7	1.9	2.0	6.6	1.2
Cadmium	DETSC 2301#	0.1	mg/kg	1.0	1.3	0.1	1.5	0.2
Chromium	DETSC 2301#	0.15	mg/kg	69	75	53	24	34
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	39	130	14	54	40
Iron	DETSC 2301	25	mg/kg	53000	180000	18000	34000	41000
Lead	DETSC 2301#	0.3	mg/kg	65	420	13	160	40
Magnesium	DETSC 2301*	1	mg/kg	14000	8200	12000	8900	10000
Manganese	DETSC 2301#	20	mg/kg	16000	2400	4600	24000	730
Mercury	DETSC 2325#	0.05	mg/kg	1.3	2.6	0.13	1.8	0.07
Molybdenum	DETSC 2301#	0.4	mg/kg	2.9	5.8	0.7	3.6	1.0
Nickel	DETSC 2301#	1	mg/kg	23	54	5.8	24	37
Silicon	DETSC 2301*	10	mg/kg	51000	53000	59000	62000	160000
Vanadium	DETSC 2301#	0.8	mg/kg	110	110	160	49	41
Zinc	DETSC 2301#	1	mg/kg	200	830	65	630	140
Inorganics								
Loss on Ignition at 440oC	DETSC 2003#	0.01	%					
pH	DETSC 2008#		pH	11.3	10.1	10.7	10.8	8.5
Calorific Value	DETSC 5008	1	MJ/kg					
Cyanide, Total	DETSC 2130#	0.1	mg/kg	22	8.2	0.9	240	< 0.1
Cyanide, Free	DETSC 2130#	0.1	mg/kg	0.1	0.1	< 0.1	0.6	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	1.2	< 0.6	1.5	4.7	< 0.6
Organic matter	DETSC 2002#	0.1	%	2.7	2.1	2.0	2.6	2.1
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	630	350	550	530	220
Sulphur (free)	DETSC 3049#	0.75	mg/kg	63	3.5	12	1.1	< 0.75



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1666613	1666614	1666615	1666616	1667231
Sample ID	PRAIRIE_AUK_TP148A	PRAIRIE_AUK_TP150	PRAIRIE_AUK_TP159	PRAIRIE_AUK_TP190A	PRAIRIE_AUK_BH105
Depth	1.40	1.50	0.60	1.10	3.00
Other ID	5	3	3	3	1
Sample Type	ES	ES	ES	ES	ES
Sampling Date	16/04/2020	16/04/2020	16/04/2020	16/04/2020	16/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Petroleum Hydrocarbons								
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	< 3.4	< 3.4	< 3.4	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	< 10	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	< 0.9	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	< 0.5	< 0.5	< 0.5	< 0.5
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	< 0.6	< 0.6	< 0.6	< 0.6	< 0.6
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	< 1.4	< 1.4	18	< 1.4	< 1.4
Aromatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	18	< 10	< 10
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	18	< 10	< 10
EPH (C10-C40)	DETSC 3311#	10	mg/kg					
PAHs								
Naphthalene	DETSC 3303#	0.03	mg/kg	0.23	0.53	0.20	0.07	< 0.03
Acenaphthylene	DETSC 3303#	0.03	mg/kg	< 0.03	0.07	0.08	< 0.03	< 0.03
Acenaphthene	DETSC 3303#	0.03	mg/kg	0.27	0.67	0.23	0.16	< 0.03
Fluorene	DETSC 3303	0.03	mg/kg	0.21	0.49	0.16	0.09	< 0.03
Phenanthrene	DETSC 3303#	0.03	mg/kg	1.5	1.6	0.27	1.4	< 0.03
Anthracene	DETSC 3303	0.03	mg/kg	0.18	0.34	0.10	0.14	< 0.03
Fluoranthene	DETSC 3303#	0.03	mg/kg	2.2	2.1	1.1	3.0	0.04
Pyrene	DETSC 3303#	0.03	mg/kg	1.8	1.7	1.6	2.8	< 0.03
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	0.50	0.50	0.39	0.96	< 0.03
Chrysene	DETSC 3303	0.03	mg/kg	0.77	0.68	0.73	1.1	< 0.03
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	0.66	0.67	1.5	1.2	< 0.03
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.29	0.28	0.70	0.51	< 0.03
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	0.44	0.36	0.77	0.80	< 0.03
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.20	0.20	0.49	0.31	< 0.03
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	0.06	0.06	0.14	0.09	< 0.03
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	0.24	0.24	0.59	0.38	< 0.03
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	9.4	10	9.0	13	< 0.10



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1666613	1666614	1666615	1666616	1667231
Sample ID	PRAIRIE_AUK_TP148A	PRAIRIE_AUK_TP150	PRAIRIE_AUK_TP159	PRAIRIE_AUK_TP190A	PRAIRIE_AUK_BH105
Depth	1.40	1.50	0.60	1.10	3.00
Other ID	5	3	3	3	1
Sample Type	ES	ES	ES	ES	ES
Sampling Date	16/04/2020	16/04/2020	16/04/2020	16/04/2020	16/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
PCBs								
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg					
PCB 52	DETSC 3401#	0.01	mg/kg					
PCB 101	DETSC 3401#	0.01	mg/kg					
PCB 118	DETSC 3401#	0.01	mg/kg					
PCB 153	DETSC 3401#	0.01	mg/kg					
PCB 138	DETSC 3401#	0.01	mg/kg					
PCB 180	DETSC 3401#	0.01	mg/kg					
PCB 7 Total	DETSC 3401#	0.01	mg/kg					
Phenols								
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	0.3	< 0.3	< 0.3	< 0.3	< 0.3

Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1667232	1667233	1667234	1667235	1667236
Sample ID	PRAIRIE_AUK_TP126	PRAIRIE_AUK_TP128	PRAIRIE_AUK_TP129	PRAIRIE_AUK_TP130	PRAIRIE_AUK_TP147
Depth	2.60	0.90	2.10	1.00	1.50
Other ID	5	3	4A	4A	4
Sample Type	ES	ES	ES	ES	ES
Sampling Date	17/04/2020	17/04/2020	17/04/2020	17/04/2020	17/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Asbestos Quantification	DETSC 1102	0.001	%		< 0.001			< 0.001
Metals								
Aluminium	DETSC 2301*	1	mg/kg	9800	3300	11000	9200	19000
Antimony	DETSC 2301*	1	mg/kg	4.1	< 1.0	1.4	2.9	3.6
Arsenic	DETSC 2301#	0.2	mg/kg	13	5.4	8.2	34	14
Barium	DETSC 2301#	1.5	mg/kg	160	89	430	130	390
Beryllium	DETSC 2301#	0.2	mg/kg	1.1	0.8	1.0	1.6	1.9
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	5.2	1.3	1.8	1.6	3.2
Cadmium	DETSC 2301#	0.1	mg/kg	0.5	< 0.1	0.4	0.4	0.8
Chromium	DETSC 2301#	0.15	mg/kg	50	8.8	25	69	99
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	86	35	29	56	58
Iron	DETSC 2301	25	mg/kg	110000	4800	35000	60000	56000
Lead	DETSC 2301#	0.3	mg/kg	82	27	40	100	220
Magnesium	DETSC 2301*	1	mg/kg	7500	1500	4100	4400	14000
Manganese	DETSC 2301#	20	mg/kg	2200	61	1300	2200	4100
Mercury	DETSC 2325#	0.05	mg/kg	0.22	< 0.05	< 0.05	0.18	0.83
Molybdenum	DETSC 2301#	0.4	mg/kg	2.2	< 0.4	0.6	1.7	1.8
Nickel	DETSC 2301#	1	mg/kg	28	12	39	38	20
Silicon	DETSC 2301*	10	mg/kg	23000	140000	180000	93000	87000
Vanadium	DETSC 2301#	0.8	mg/kg	160	10	33	170	190
Zinc	DETSC 2301#	1	mg/kg	440	39	140	280	340
Inorganics								
Loss on Ignition at 440oC	DETSC 2003#	0.01	%					
pH	DETSC 2008#		pH	10.3	8.6	8.8	9.3	10.9
Calorific Value	DETSC 5008	1	MJ/kg					
Cyanide, Total	DETSC 2130#	0.1	mg/kg	7.9	0.6	0.5	3.0	29
Cyanide, Free	DETSC 2130#	0.1	mg/kg	< 0.1	< 0.1	< 0.1	< 0.1	0.5
Thiocyanate	DETSC 2130#	0.6	mg/kg	1.2	< 0.6	< 0.6	< 0.6	2.5
Organic matter	DETSC 2002#	0.1	%	12	3.6	2.1	5.3	2.4
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	1200	25	270	100	480
Sulphur (free)	DETSC 3049#	0.75	mg/kg	24	< 0.75	< 0.75	< 0.75	< 0.75



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1667232	1667233	1667234	1667235	1667236
Sample ID	PRAIRIE_AUK_TP126	PRAIRIE_AUK_TP128	PRAIRIE_AUK_TP129	PRAIRIE_AUK_TP130	PRAIRIE_AUK_TP147
Depth	2.60	0.90	2.10	1.00	1.50
Other ID	5	3	4A	4A	4
Sample Type	ES	ES	ES	ES	ES
Sampling Date	17/04/2020	17/04/2020	17/04/2020	17/04/2020	17/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Petroleum Hydrocarbons								
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	0.20	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	25	< 1.2	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	2.1	< 1.5	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	< 3.4	< 3.4	< 3.4	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	28	< 10	< 10	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	2.2	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	320	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	1400	< 0.5	< 0.5	1.3
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	< 0.6	6.4	< 0.6	< 0.6	4.8
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	< 1.4	< 1.4	< 1.4	< 1.4	23
Aromatic C5-C35	DETSC 3072*	10	mg/kg	< 10	1700	< 10	< 10	29
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	< 10	1700	< 10	< 10	29
EPH (C10-C40)	DETSC 3311#	10	mg/kg					
PAHs								
Naphthalene	DETSC 3303#	0.03	mg/kg	0.14	520	3.2	0.05	0.07
Acenaphthylene	DETSC 3303#	0.03	mg/kg	0.05	5.5	< 0.03	< 0.03	< 0.03
Acenaphthene	DETSC 3303#	0.03	mg/kg	0.30	520	3.6	0.16	0.09
Fluorene	DETSC 3303	0.03	mg/kg	0.29	100	0.66	0.04	0.05
Phenanthrene	DETSC 3303#	0.03	mg/kg	0.73	5.1	0.09	0.18	0.73
Anthracene	DETSC 3303	0.03	mg/kg	0.77	1.1	0.09	0.04	0.77
Fluoranthene	DETSC 3303#	0.03	mg/kg	0.56	0.34	< 0.03	0.24	2.0
Pyrene	DETSC 3303#	0.03	mg/kg	0.45	0.24	< 0.03	0.20	2.0
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	0.19	0.15	< 0.03	0.11	1.1
Chrysene	DETSC 3303	0.03	mg/kg	0.19	0.16	< 0.03	0.13	1.1
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	0.20	0.17	< 0.03	0.11	1.4
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.09	0.08	< 0.03	0.06	0.61
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	0.12	0.10	< 0.03	0.05	0.88
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.07	0.09	< 0.03	0.05	0.55
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03	0.17
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	0.07	0.08	< 0.03	0.04	0.65
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	4.2	1200	7.7	1.4	12



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1667232	1667233	1667234	1667235	1667236
Sample ID	PRAIRIE_AUK_TP126	PRAIRIE_AUK_TP128	PRAIRIE_AUK_TP129	PRAIRIE_AUK_TP130	PRAIRIE_AUK_TP147
Depth	2.60	0.90	2.10	1.00	1.50
Other ID	5	3	4A	4A	4
Sample Type	ES	ES	ES	ES	ES
Sampling Date	17/04/2020	17/04/2020	17/04/2020	17/04/2020	17/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
PCBs								
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg					
PCB 52	DETSC 3401#	0.01	mg/kg					
PCB 101	DETSC 3401#	0.01	mg/kg					
PCB 118	DETSC 3401#	0.01	mg/kg					
PCB 153	DETSC 3401#	0.01	mg/kg					
PCB 138	DETSC 3401#	0.01	mg/kg					
PCB 180	DETSC 3401#	0.01	mg/kg					
PCB 7 Total	DETSC 3401#	0.01	mg/kg					
Phenols								
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	< 0.3	< 0.3	< 0.3	< 0.3	< 0.3



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1667237	1667238	1667501	1667502	1667503
Sample ID	PRAIRIE_AUK_TP158	PRAIRIE_AUK_TP157	PRAIRIE_AUK_TP120A	PRAIRIE_AUK_TP134	PRAIRIE_AUK_TP134
Depth	1.30	0.80	1.00	1.00	2.00
Other ID	3	2	3	3	6
Sample Type	ES	ES	ES	ES	ES
Sampling Date	17/04/2020	17/04/2020	20/04/2020	20/04/2020	20/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Asbestos Quantification	DETSC 1102	0.001	%		< 0.001	0.001		
Metals								
Aluminium	DETSC 2301*	1	mg/kg	10000	9600	21000	8700	13000
Antimony	DETSC 2301*	1	mg/kg	1.8	4.3	4.0	18	1.5
Arsenic	DETSC 2301#	0.2	mg/kg	9.1	10	12	61	9.0
Barium	DETSC 2301#	1.5	mg/kg	390	200	330	200	300
Beryllium	DETSC 2301#	0.2	mg/kg	1.7	1.0	3.1	0.9	1.2
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	7.4	3.5	4.9	2.6	0.8
Cadmium	DETSC 2301#	0.1	mg/kg	0.6	0.8	0.8	0.6	0.3
Chromium	DETSC 2301#	0.15	mg/kg	24	200	190	240	29
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	94	40	56	100	29
Iron	DETSC 2301	25	mg/kg	32000	61000	58000	140000	43000
Lead	DETSC 2301#	0.3	mg/kg	130	140	89	160	30
Magnesium	DETSC 2301*	1	mg/kg	7700	14000	18000	15000	7300
Manganese	DETSC 2301#	20	mg/kg	1000	12000	8200	26000	850
Mercury	DETSC 2325#	0.05	mg/kg	0.56	2.2	0.19	0.09	< 0.05
Molybdenum	DETSC 2301#	0.4	mg/kg	1.2	2.6	5.8	4.6	0.5
Nickel	DETSC 2301#	1	mg/kg	13	11	19	29	38
Silicon	DETSC 2301*	10	mg/kg	95000	70000	72000	59000	170000
Vanadium	DETSC 2301#	0.8	mg/kg	37	410	360	680	36
Zinc	DETSC 2301#	1	mg/kg	710	470	190	180	99
Inorganics								
Loss on Ignition at 440oC	DETSC 2003#	0.01	%					
pH	DETSC 2008#		pH	9.9	12.0	11.3	11.3	8.7
Calorific Value	DETSC 5008	1	MJ/kg					
Cyanide, Total	DETSC 2130#	0.1	mg/kg	57	25	2.2	1.4	0.1
Cyanide, Free	DETSC 2130#	0.1	mg/kg	0.2	< 0.1	< 0.1	< 0.1	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	3.3	1.5	0.7	< 0.6	< 0.6
Organic matter	DETSC 2002#	0.1	%	2.7	2.4	2.9	2.5	2.3
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	620	65	250	130	78
Sulphur (free)	DETSC 3049#	0.75	mg/kg	14	1.9	33	6.0	< 0.75



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1667237	1667238	1667501	1667502	1667503
Sample ID	PRAIRIE_AUK_TP158	PRAIRIE_AUK_TP157	PRAIRIE_AUK_TP120A	PRAIRIE_AUK_TP134	PRAIRIE_AUK_TP134
Depth	1.30	0.80	1.00	1.00	2.00
Other ID	3	2	3	3	6
Sample Type	ES	ES	ES	ES	ES
Sampling Date	17/04/2020	17/04/2020	20/04/2020	20/04/2020	20/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Petroleum Hydrocarbons								
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	3.4	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	27	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	< 3.4	270	< 3.4	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	300	< 10	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	< 0.9	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	0.6	6.8	1.5	< 0.5
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	1.3	6.3	100	15	< 0.6
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	7.2	22	510	69	< 1.4
Aromatic C5-C35	DETSC 3072*	10	mg/kg	< 10	29	610	86	< 10
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	< 10	29	910	86	< 10
EPH (C10-C40)	DETSC 3311#	10	mg/kg					
PAHs								
Naphthalene	DETSC 3303#	0.03	mg/kg	0.47	0.16	0.04	< 0.03	< 0.03
Acenaphthylene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	0.03	< 0.03	< 0.03
Acenaphthene	DETSC 3303#	0.03	mg/kg	0.55	0.27	0.13	0.09	< 0.03
Fluorene	DETSC 3303	0.03	mg/kg	0.11	0.05	0.05	0.12	< 0.03
Phenanthrene	DETSC 3303#	0.03	mg/kg	0.44	0.49	1.4	0.93	< 0.03
Anthracene	DETSC 3303	0.03	mg/kg	0.08	0.04	0.39	0.48	< 0.03
Fluoranthene	DETSC 3303#	0.03	mg/kg	1.2	0.72	8.2	1.5	< 0.03
Pyrene	DETSC 3303#	0.03	mg/kg	1.1	0.63	12	1.2	< 0.03
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	0.55	0.54	6.6	0.62	< 0.03
Chrysene	DETSC 3303	0.03	mg/kg	0.57	0.72	4.8	0.47	< 0.03
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	0.66	0.64	7.3	0.66	< 0.03
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.31	0.26	2.9	0.29	< 0.03
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	0.39	0.29	5.8	0.52	< 0.03
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.28	0.14	1.9	0.21	< 0.03
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	0.05	0.03	0.53	0.06	< 0.03
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	0.34	0.15	2.4	0.25	< 0.03
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	7.1	5.1	54	7.4	< 0.10



Summary of Chemical Analysis Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1667237	1667238	1667501	1667502	1667503
Sample ID	PRAIRIE_AUK_ TP158	PRAIRIE_AUK_ TP157	PRAIRIE_AUK_ TP120A	PRAIRIE_AUK_ TP134	PRAIRIE_AUK_ TP134
Depth	1.30	0.80	1.00	1.00	2.00
Other ID	3	2	3	3	6
Sample Type	ES	ES	ES	ES	ES
Sampling Date	17/04/2020	17/04/2020	20/04/2020	20/04/2020	20/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
PCBs								
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 52	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 101	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 118	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 153	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 138	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 180	DETSC 3401#	0.01	mg/kg		< 0.01			
PCB 7 Total	DETSC 3401#	0.01	mg/kg		< 0.01			
Phenols								
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	< 0.3	< 0.3	< 0.3	< 0.3	< 0.3

Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1667504	1667505	1667506	1667507
Sample ID	PRAIRIE_AUK_ TP161	PRAIRIE_AUK_ TP166	PRAIRIE_AUK_ TP166	PRAIRIE_AUK_ TP171
Depth	1.00	0.45	1.20	0.75
Other ID	3	3	8	3
Sample Type	ES	ES	ES	ES
Sampling Date	20/04/2020	20/04/2020	20/04/2020	20/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Asbestos Quantification	DETSC 1102	0.001	%		0.001		
Metals							
Aluminium	DETSC 2301*	1	mg/kg	12000	28000	10000	18000
Antimony	DETSC 2301*	1	mg/kg	5.5	5.1	1.2	3.4
Arsenic	DETSC 2301#	0.2	mg/kg	8.1	22	7.6	30
Barium	DETSC 2301#	1.5	mg/kg	260	700	200	610
Beryllium	DETSC 2301#	0.2	mg/kg	1.9	3.4	1.0	3.2
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	1.8	2.2	0.5	1.9
Cadmium	DETSC 2301#	0.1	mg/kg	0.2	0.9	0.2	3.6
Chromium	DETSC 2301#	0.15	mg/kg	150	140	23	27
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	150	160	26	110
Iron	DETSC 2301	25	mg/kg	53000	91000	33000	63000
Lead	DETSC 2301#	0.3	mg/kg	59	190	23	310
Magnesium	DETSC 2301*	1	mg/kg	11000	21000	3500	5700
Manganese	DETSC 2301#	20	mg/kg	3400	6600	840	1600
Mercury	DETSC 2325#	0.05	mg/kg	0.08	0.28	< 0.05	0.06
Molybdenum	DETSC 2301#	0.4	mg/kg	1.8	5.7	< 0.4	4.2
Nickel	DETSC 2301#	1	mg/kg	15	53	40	46
Silicon	DETSC 2301*	10	mg/kg	80000	59000	180000	90000
Vanadium	DETSC 2301#	0.8	mg/kg	160	340	28	120
Zinc	DETSC 2301#	1	mg/kg	110	210	66	1500
Inorganics							
Loss on Ignition at 440oC	DETSC 2003#	0.01	%				
pH	DETSC 2008#		pH	11.4	10.0	7.9	8.5
Calorific Value	DETSC 5008	1	MJ/kg				
Cyanide, Total	DETSC 2130#	0.1	mg/kg	0.5	0.5	< 0.1	0.5
Cyanide, Free	DETSC 2130#	0.1	mg/kg	< 0.1	< 0.1	< 0.1	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	< 0.6	< 0.6	< 0.6	< 0.6
Organic matter	DETSC 2002#	0.1	%	1.6	2.5	1.8	5.8
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	100	260	84	120
Sulphur (free)	DETSC 3049#	0.75	mg/kg	< 0.75	3.9	< 0.75	< 0.75



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1667504	1667505	1667506	1667507
Sample ID	PRAIRIE_AUK_ TP161	PRAIRIE_AUK_ TP166	PRAIRIE_AUK_ TP166	PRAIRIE_AUK_ TP171
Depth	1.00	0.45	1.20	0.75
Other ID	3	3	8	3
Sample Type	ES	ES	ES	ES
Sampling Date	20/04/2020	20/04/2020	20/04/2020	20/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Petroleum Hydrocarbons							
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	30	9.9	< 3.4	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	31	11	< 10	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	0.7	< 0.5	< 0.5
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	4.4	19	< 0.6	< 0.6
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	29	65	< 1.4	< 1.4
Aromatic C5-C35	DETSC 3072*	10	mg/kg	33	84	< 10	< 10
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	64	95	< 10	< 10
EPH (C10-C40)	DETSC 3311#	10	mg/kg				
PAHs							
Naphthalene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03
Acenaphthylene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03
Acenaphthene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03
Fluorene	DETSC 3303	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03
Phenanthrene	DETSC 3303#	0.03	mg/kg	0.15	0.25	< 0.03	0.09
Anthracene	DETSC 3303	0.03	mg/kg	< 0.03	0.08	< 0.03	< 0.03
Fluoranthene	DETSC 3303#	0.03	mg/kg	0.32	1.2	< 0.03	0.20
Pyrene	DETSC 3303#	0.03	mg/kg	0.33	1.1	< 0.03	0.17
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	0.19	0.67	< 0.03	0.11
Chrysene	DETSC 3303	0.03	mg/kg	0.19	0.60	< 0.03	0.12
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	< 0.03	0.89	< 0.03	0.17
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.11	0.37	< 0.03	0.08
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	0.13	0.71	< 0.03	0.12
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.09	0.29	< 0.03	0.06
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	< 0.03	0.08	< 0.03	< 0.03
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	0.11	0.38	< 0.03	0.07
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	1.6	6.6	< 0.10	1.2



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie
 Client Ref 4251
 Contract Title Prairie Site Ground Investigation Works

Lab No	1667504	1667505	1667506	1667507
Sample ID	PRAIRIE_AUK_ TP161	PRAIRIE_AUK_ TP166	PRAIRIE_AUK_ TP166	PRAIRIE_AUK_ TP171
Depth	1.00	0.45	1.20	0.75
Other ID	3	3	8	3
Sample Type	ES	ES	ES	ES
Sampling Date	20/04/2020	20/04/2020	20/04/2020	20/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
PCBs							
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg				
PCB 52	DETSC 3401#	0.01	mg/kg				
PCB 101	DETSC 3401#	0.01	mg/kg				
PCB 118	DETSC 3401#	0.01	mg/kg				
PCB 153	DETSC 3401#	0.01	mg/kg				
PCB 138	DETSC 3401#	0.01	mg/kg				
PCB 180	DETSC 3401#	0.01	mg/kg				
PCB 7 Total	DETSC 3401#	0.01	mg/kg				
Phenols							
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	< 0.3	< 0.3	< 0.3	< 0.3

Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1667508	1668118	1668119	1668120	1668121
Sample ID	PRAIRIE_AUK_TP187	PRAIRIE_AUK_BH110	PRAIRIE_AUK_TP102	PRAIRIE_AUK_TP102	PRAIRIE_AUK_TP103
Depth	0.70	3.00	1.00	3.00	1.00
Other ID	3	1	4	11	3
Sample Type	ES	ES	ES	ES	ES
Sampling Date	20/04/2020	20/04/2020	21/04/2020	21/04/2020	21/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Asbestos Quantification	DETSC 1102	0.001	%				< 0.001	
Metals								
Aluminium	DETSC 2301*	1	mg/kg	14000	12000	49000	19000	45000
Antimony	DETSC 2301*	1	mg/kg	22	1.4	1.3	1.8	1.5
Arsenic	DETSC 2301#	0.2	mg/kg	46	7.5	11	21	8.1
Barium	DETSC 2301#	1.5	mg/kg	340	210	460	630	440
Beryllium	DETSC 2301#	0.2	mg/kg	3.2	1.1	8.9	2.0	5.7
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	1.1	0.6	1.8	2.4	2.4
Cadmium	DETSC 2301#	0.1	mg/kg	24	0.1	0.1	0.5	< 0.1
Chromium	DETSC 2301#	0.15	mg/kg	19	28	30	29	82
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	530	27	22	36	17
Iron	DETSC 2301	25	mg/kg	110000	31000	19000	36000	26000
Lead	DETSC 2301#	0.3	mg/kg	1800	24	20	98	14
Magnesium	DETSC 2301*	1	mg/kg	5200	9400	28000	7400	25000
Manganese	DETSC 2301#	20	mg/kg	4200	570	6700	1100	6200
Mercury	DETSC 2325#	0.05	mg/kg	0.13	< 0.05	0.06	0.08	< 0.05
Molybdenum	DETSC 2301#	0.4	mg/kg	6.4	0.7	0.6	0.7	0.6
Nickel	DETSC 2301#	1	mg/kg	55	37	7.2	25	11
Silicon	DETSC 2301*	10	mg/kg	96000	170000	72000	160000	68000
Vanadium	DETSC 2301#	0.8	mg/kg	81	31	100	65	110
Zinc	DETSC 2301#	1	mg/kg	3800	91	84	300	43
Inorganics								
Loss on Ignition at 440oC	DETSC 2003#	0.01	%					
pH	DETSC 2008#		pH	8.8	7.7	10.1	8.5	9.2
Calorific Value	DETSC 5008	1	MJ/kg					
Cyanide, Total	DETSC 2130#	0.1	mg/kg	11	< 0.1	0.2	0.2	0.2
Cyanide, Free	DETSC 2130#	0.1	mg/kg	< 0.1	< 0.1	< 0.1	< 0.1	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	< 0.6	< 0.6	< 0.6	0.7	< 0.6
Organic matter	DETSC 2002#	0.1	%	14	3.3	1.4	3.3	3.1
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	74	350	580	220	680
Sulphur (free)	DETSC 3049#	0.75	mg/kg	< 0.75	< 0.75	< 0.75	2.2	110



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1667508	1668118	1668119	1668120	1668121
Sample ID	PRAIRIE_AUK_ TP187	PRAIRIE_AUK_ BH110	PRAIRIE_AUK_ TP102	PRAIRIE_AUK_ TP102	PRAIRIE_AUK_ TP103
Depth	0.70	3.00	1.00	3.00	1.00
Other ID	3	1	4	11	3
Sample Type	ES	ES	ES	ES	ES
Sampling Date	20/04/2020	20/04/2020	21/04/2020	21/04/2020	21/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units	1667508	1668118	1668119	1668120	1668121
Petroleum Hydrocarbons								
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	11	3.1
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	< 1.2	< 1.2	29	13
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	33	14
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	< 3.4	< 3.4	29	17
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	100	47
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	< 0.9	< 0.9	1.8	0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	< 0.5	< 0.5	13	8.2
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	< 0.6	< 0.6	< 0.6	16	30
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	< 1.4	< 1.4	< 1.4	5.9	97
Aromatic C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	36	140
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	< 10	< 10	< 10	140	180
EPH (C10-C40)	DETSC 3311#	10	mg/kg					
PAHs								
Naphthalene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03	< 0.03
Acenaphthylene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03	0.10
Acenaphthene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03	0.12
Fluorene	DETSC 3303	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03	0.13
Phenanthrene	DETSC 3303#	0.03	mg/kg	0.06	< 0.03	< 0.03	0.11	2.6
Anthracene	DETSC 3303	0.03	mg/kg	< 0.03	0.05	< 0.03	< 0.03	0.81
Fluoranthene	DETSC 3303#	0.03	mg/kg	0.29	< 0.03	0.06	0.16	36
Pyrene	DETSC 3303#	0.03	mg/kg	0.28	< 0.03	0.06	0.13	29
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	0.15	0.06	0.04	0.05	15
Chrysene	DETSC 3303	0.03	mg/kg	0.16	< 0.03	0.05	0.05	11
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	0.24	< 0.03	0.07	< 0.03	14
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.10	< 0.03	< 0.03	< 0.03	7.1
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	0.18	< 0.03	< 0.03	< 0.03	11
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.09	< 0.03	0.04	< 0.03	4.1
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	< 0.03	< 0.03	< 0.03	< 0.03	1.2
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	0.11	< 0.03	0.04	< 0.03	5.0
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	1.7	0.11	0.36	0.49	140



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1667508	1668118	1668119	1668120	1668121
PRAIRIE_AUK_	PRAIRIE_AUK_	PRAIRIE_AUK_	PRAIRIE_AUK_	PRAIRIE_AUK_	PRAIRIE_AUK_
Sample ID	TP187	BH110	TP102	TP102	TP103
Depth	0.70	3.00	1.00	3.00	1.00
Other ID	3	1	4	11	3
Sample Type	ES	ES	ES	ES	ES
Sampling Date	20/04/2020	20/04/2020	21/04/2020	21/04/2020	21/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
PCBs								
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg			< 0.01		
PCB 52	DETSC 3401#	0.01	mg/kg			< 0.01		
PCB 101	DETSC 3401#	0.01	mg/kg			< 0.01		
PCB 118	DETSC 3401#	0.01	mg/kg			< 0.01		
PCB 153	DETSC 3401#	0.01	mg/kg			< 0.01		
PCB 138	DETSC 3401#	0.01	mg/kg			< 0.01		
PCB 180	DETSC 3401#	0.01	mg/kg			< 0.01		
PCB 7 Total	DETSC 3401#	0.01	mg/kg			< 0.01		
Phenols								
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	< 0.3	< 0.3	0.3	< 0.3	0.5



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1668122	1668123	1668124	1668125	1668126
Sample ID	PRAIRIE_AUK_TP109	PRAIRIE_AUK_TP110	PRAIRIE_AUK_TP110	PRAIRIE_AUK_TP111	PRAIRIE_AUK_TP112
Depth	1.00	1.00	2.00	1.50	1.50
Other ID	3	3	7	4	4
Sample Type	ES	ES	ES	ES	ES
Sampling Date	21/04/2020	21/04/2020	21/04/2020	22/04/2020	22/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Asbestos Quantification	DETSC 1102	0.001	%				0.002	
Metals								
Aluminium	DETSC 2301*	1	mg/kg	33000	31000	18000	18000	14000
Antimony	DETSC 2301*	1	mg/kg	2.1	1.8	2.9	8.9	4.5
Arsenic	DETSC 2301#	0.2	mg/kg	11	6.8	21	48	19
Barium	DETSC 2301#	1.5	mg/kg	350	490	380	600	540
Beryllium	DETSC 2301#	0.2	mg/kg	4.4	3.6	1.8	1.8	1.8
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	6.7	3.3	1.6	1.4	1.0
Cadmium	DETSC 2301#	0.1	mg/kg	0.2	0.2	0.4	0.9	0.9
Chromium	DETSC 2301#	0.15	mg/kg	110	72	78	390	210
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	71	110	60	76	68
Iron	DETSC 2301	25	mg/kg	35000	31000	60000	99000	65000
Lead	DETSC 2301#	0.3	mg/kg	33	31	94	120	60
Magnesium	DETSC 2301*	1	mg/kg	21000	24000	9500	29000	12000
Manganese	DETSC 2301#	20	mg/kg	8200	5100	1900	9100	4900
Mercury	DETSC 2325#	0.05	mg/kg	< 0.05	0.06	0.23	0.36	< 0.05
Molybdenum	DETSC 2301#	0.4	mg/kg	0.7	1.2	1.8	3.1	5.4
Nickel	DETSC 2301#	1	mg/kg	9.3	9.8	40	32	31
Silicon	DETSC 2301*	10	mg/kg	72000	68000	16000	67000	79000
Vanadium	DETSC 2301#	0.8	mg/kg	300	180	210	1100	690
Zinc	DETSC 2301#	1	mg/kg	68	140	260	290	580
Inorganics								
Loss on Ignition at 440oC	DETSC 2003#	0.01	%					
pH	DETSC 2008#		pH	10.2	11.2	10.4	11.6	11.3
Calorific Value	DETSC 5008	1	MJ/kg					
Cyanide, Total	DETSC 2130#	0.1	mg/kg	0.2	0.1	< 0.1	0.5	< 0.1
Cyanide, Free	DETSC 2130#	0.1	mg/kg	< 0.1	< 0.1	< 0.1	< 0.1	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	< 0.6	< 0.6	< 0.6	< 0.6	< 0.6
Organic matter	DETSC 2002#	0.1	%	1.1	2.3	2.7	2.7	2.0
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	400	260	230	87	140
Sulphur (free)	DETSC 3049#	0.75	mg/kg	< 0.75	57	< 0.75	< 0.75	< 0.75



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1668122	1668123	1668124	1668125	1668126
Sample ID	PRAIRIE_AUK_TP109	PRAIRIE_AUK_TP110	PRAIRIE_AUK_TP110	PRAIRIE_AUK_TP111	PRAIRIE_AUK_TP112
Depth	1.00	1.00	2.00	1.50	1.50
Other ID	3	3	7	4	4
Sample Type	ES	ES	ES	ES	ES
Sampling Date	21/04/2020	21/04/2020	21/04/2020	22/04/2020	22/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
Petroleum Hydrocarbons								
Aliphatic C5-C6	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C6-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aliphatic C10-C12	DETSC 3072#	1.5	mg/kg	< 1.5	< 1.5	< 1.5	< 1.5	< 1.5
Aliphatic C12-C16	DETSC 3072#	1.2	mg/kg	< 1.2	2.2	< 1.2	< 1.2	< 1.2
Aliphatic C16-C21	DETSC 3072#	1.5	mg/kg	< 1.5	4.4	< 1.5	< 1.5	< 1.5
Aliphatic C21-C35	DETSC 3072#	3.4	mg/kg	< 3.4	35	< 3.4	< 3.4	< 3.4
Aliphatic C5-C35	DETSC 3072*	10	mg/kg	< 10	43	< 10	< 10	< 10
Aromatic C5-C7	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C7-C8	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C8-C10	DETSC 3321*	0.01	mg/kg	< 0.01	< 0.01	< 0.01	< 0.01	< 0.01
Aromatic C10-C12	DETSC 3072#	0.9	mg/kg	< 0.9	< 0.9	< 0.9	< 0.9	< 0.9
Aromatic C12-C16	DETSC 3072#	0.5	mg/kg	< 0.5	1.5	< 0.5	0.8	0.6
Aromatic C16-C21	DETSC 3072#	0.6	mg/kg	< 0.6	8.8	< 0.6	5.2	4.6
Aromatic C21-C35	DETSC 3072#	1.4	mg/kg	< 1.4	73	< 1.4	18	11
Aromatic C5-C35	DETSC 3072*	10	mg/kg	< 10	84	< 10	24	16
TPH Ali/Aro Total C5-C35	DETSC 3072*	10	mg/kg	< 10	130	< 10	24	16
EPH (C10-C40)	DETSC 3311#	10	mg/kg					
PAHs								
Naphthalene	DETSC 3303#	0.03	mg/kg	< 0.03	0.07	< 0.03	0.15	0.07
Acenaphthylene	DETSC 3303#	0.03	mg/kg	< 0.03	0.06	< 0.03	0.31	0.10
Acenaphthene	DETSC 3303#	0.03	mg/kg	< 0.03	1.4	< 0.03	0.13	< 0.03
Fluorene	DETSC 3303	0.03	mg/kg	< 0.03	0.78	< 0.03	0.49	0.09
Phenanthrene	DETSC 3303#	0.03	mg/kg	0.14	3.2	0.12	3.9	1.7
Anthracene	DETSC 3303	0.03	mg/kg	< 0.03	3.1	< 0.03	1.3	0.35
Fluoranthene	DETSC 3303#	0.03	mg/kg	0.29	36	0.52	8.6	3.5
Pyrene	DETSC 3303#	0.03	mg/kg	0.25	37	0.41	6.9	2.6
Benzo(a)anthracene	DETSC 3303#	0.03	mg/kg	0.17	20	0.22	4.2	1.3
Chrysene	DETSC 3303	0.03	mg/kg	0.15	12	0.15	2.6	0.99
Benzo(b)fluoranthene	DETSC 3303#	0.03	mg/kg	0.23	18	0.17	3.6	1.4
Benzo(k)fluoranthene	DETSC 3303#	0.03	mg/kg	0.08	5.6	0.09	1.7	0.61
Benzo(a)pyrene	DETSC 3303#	0.03	mg/kg	0.11	9.4	0.12	2.7	0.86
Indeno(1,2,3-c,d)pyrene	DETSC 3303#	0.03	mg/kg	0.08	3.1	0.06	1.2	0.43
Dibenzo(a,h)anthracene	DETSC 3303#	0.03	mg/kg	< 0.03	1.1	< 0.03	0.25	0.11
Benzo(g,h,i)perylene	DETSC 3303#	0.03	mg/kg	0.10	3.2	0.06	1.2	0.51
PAH - USEPA 16, Total	DETSC 3303	0.1	mg/kg	1.6	150	1.9	39	14



Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1668122	1668123	1668124	1668125	1668126
Sample ID	PRAIRIE_AUK_TP109	PRAIRIE_AUK_TP110	PRAIRIE_AUK_TP110	PRAIRIE_AUK_TP111	PRAIRIE_AUK_TP112
Depth	1.00	1.00	2.00	1.50	1.50
Other ID	3	3	7	4	4
Sample Type	ES	ES	ES	ES	ES
Sampling Date	21/04/2020	21/04/2020	21/04/2020	22/04/2020	22/04/2020
Sampling Time	n/s	n/s	n/s	n/s	n/s

Test	Method	LOD	Units					
PCBs								
PCB 28 + PCB 31	DETSC 3401#	0.01	mg/kg					< 0.01
PCB 52	DETSC 3401#	0.01	mg/kg					< 0.01
PCB 101	DETSC 3401#	0.01	mg/kg					0.01
PCB 118	DETSC 3401#	0.01	mg/kg					< 0.01
PCB 153	DETSC 3401#	0.01	mg/kg					< 0.01
PCB 138	DETSC 3401#	0.01	mg/kg					0.01
PCB 180	DETSC 3401#	0.01	mg/kg					< 0.01
PCB 7 Total	DETSC 3401#	0.01	mg/kg					0.03
Phenols								
Phenol - Monohydric	DETSC 2130#	0.3	mg/kg	0.5	0.6	0.4	0.4	< 0.3

Summary of Chemical Analysis

Soil Samples

Our Ref Combined 4251 Prairie

Client Ref 4251

Contract Title Prairie Site Ground Investigation Works

Lab No	1668127	1668128	1668129	1668130
Sample ID	PRAIRIE_AUK_ TP119	PRAIRIE_AUK_ TP119	PRAIRIE_AUK_ TP133	PRAIRIE_AUK_ TP152
Depth	1.50	2.50	0.50	2.00
Other ID	3	7	2	6
Sample Type	ES	ES	ES	ES
Sampling Date	22/04/2020	22/04/2020	22/04/2020	22/04/2020
Sampling Time	n/s	n/s	n/s	n/s

Test	Method	LOD	Units				
Asbestos Quantification	DETSC 1102	0.001	%				0.002
Metals							
Aluminium	DETSC 2301*	1	mg/kg	37000	14000	21000	15000
Antimony	DETSC 2301*	1	mg/kg	2.5	1.5	6.5	5.0
Arsenic	DETSC 2301#	0.2	mg/kg	11	8.5	35	19
Barium	DETSC 2301#	1.5	mg/kg	380	180	390	230
Beryllium	DETSC 2301#	0.2	mg/kg	4.0	1.1	2.4	1.3
Boron, Water Soluble	DETSC 2311#	0.2	mg/kg	1.8	0.5	1.2	1.8
Cadmium	DETSC 2301#	0.1	mg/kg	0.3	0.2	0.8	1.7
Chromium	DETSC 2301#	0.15	mg/kg	140	33	150	160
Chromium, Hexavalent	DETSC 2204*	1	mg/kg	< 1.0	< 1.0	< 1.0	< 1.0
Copper	DETSC 2301#	0.2	mg/kg	35	31	330	64
Iron	DETSC 2301	25	mg/kg	38000	38000	120000	67000
Lead	DETSC 2301#	0.3	mg/kg	29	28	110	200
Magnesium	DETSC 2301*	1	mg/kg	26000	7300	15000	18000
Manganese	DETSC 2301#	20	mg/kg	6400	660	4800	3300
Mercury	DETSC 2325#	0.05	mg/kg	0.08	< 0.05	0.12	0.30
Molybdenum	DETSC 2301#	0.4	mg/kg	0.8	0.4	3.2	1.9
Nickel	DETSC 2301#	1	mg/kg	11	39	56	34
Silicon	DETSC 2301*	10	mg/kg	58000	160000	94000	120000
Vanadium	DETSC 2301#	0.8	mg/kg	430	40	350	320
Zinc	DETSC 2301#	1	mg/kg	82	96	380	360
Inorganics							
Loss on Ignition at 440oC	DETSC 2003#	0.01	%				
pH	DETSC 2008#		pH	11.1	8.9	11.3	11.0
Calorific Value	DETSC 5008	1	MJ/kg				
Cyanide, Total	DETSC 2130#	0.1	mg/kg	0.1	< 0.1	0.4	0.5
Cyanide, Free	DETSC 2130#	0.1	mg/kg	< 0.1	< 0.1	< 0.1	< 0.1
Thiocyanate	DETSC 2130#	0.6	mg/kg	< 0.6	< 0.6	< 0.6	< 0.6
Organic matter	DETSC 2002#	0.1	%	4.4	2.1	2.2	1.9
Sulphate Aqueous Extract as SO4	DETSC 2076#	10	mg/l	1100	72	170	1700
Sulphur (free)	DETSC 3049#	0.75	mg/kg	< 0.75	< 0.75	8.9	< 0.75